

TK 7874
.A3375
2010
v. 1
Copy 1

PROCEEDINGS OF SPIE

Advances in Resist Materials and Processing Technology XXVII

Robert D. Allen
Mark H. Somervell
Editors

22–24 February 2010
San Jose, California, United States

SPIE 
Advanced Lithography

Volume 7639
Part One of Two Parts



SPIE

Lam Research Ex. 1024 - Page 1
Lam Research Corp. v. Inpria Corp.
IPR2024-00033 - U.S. Patent No. 9,823,564

PROCEEDINGS OF SPIE

Advances in Resist Materials and Processing Technology XXVII

Robert D. Allen
Mark H. Somervell
Editors

22–24 February 2010
San Jose, California, United States

Sponsored by
SPIE

Cooperating Organization
SEMATECH Inc. (United States)

Published by
SPIE

Part One of Two Parts

Volume 7639

Proceedings of SPIE, 0277-786X, v. 7639

SPIE is an international society advancing an interdisciplinary approach to the science and application of light.

The papers included in this volume were part of the technical conference cited on the cover and title page. Papers were selected and subject to review by the editors and conference program committee. Some conference presentations may not be available for publication. The papers published in these proceedings reflect the work and thoughts of the authors and are published herein as submitted. The publisher is not responsible for the validity of the information or for any outcomes resulting from reliance thereon.

Please use the following format to cite material from this book:

Author(s), "Title of Paper," in *Advances in Resist Materials and Processing Technology XXVII*, edited by Robert D. Allen, Mark H. Somervell, Proceedings of SPIE Vol. 7639 (SPIE, Bellingham, WA, 2010) Article CID Number.

ISSN 0277-786X

ISBN 9780819480538

Published by

SPIE

P.O. Box 10, Bellingham, Washington 98227-0010 USA

Telephone +1 360 676 3290 (Pacific Time) · Fax +1 360 647 1445

SPIE.org

Copyright © 2010, Society of Photo-Optical Instrumentation Engineers

Copying of material in this book for internal or personal use, or for the internal or personal use of specific clients, beyond the fair use provisions granted by the U.S. Copyright Law is authorized by SPIE subject to payment of copying fees. The Transactional Reporting Service base fee for this volume is \$18.00 per article (or portion thereof), which should be paid directly to the Copyright Clearance Center (CCC), 222 Rosewood Drive, Danvers, MA 01923. Payment may also be made electronically through CCC Online at copyright.com. Other copying for republication, resale, advertising or promotion, or any form of systematic or multiple reproduction of any material in this book is prohibited except with permission in writing from the publisher. The CCC fee code is 0277-786X/10/\$18.00.

Printed in the United States of America.

Publication of record for individual papers is online in the SPIE Digital Library.


SPIE
Digital Library

SPIDigitalLibrary.org

Paper Numbering: Proceedings of SPIE follow an e-First publication model, with papers published first online and then in print and on CD-ROM. Papers are published as they are submitted and meet publication criteria. A unique, consistent, permanent citation identifier (CID) number is assigned to each article at the time of the first publication. Utilization of CIDs allows articles to be fully citable as soon they are published online, and connects the same identifier to all online, print, and electronic versions of the publication. SPIE uses a six-digit CID article numbering system in which:

- The first four digits correspond to the SPIE volume number.
- The last two digits indicate publication order within the volume using a Base 36 numbering system employing both numerals and letters. These two-number sets start with 00, 01, 02, 03, 04, 05, 06, 07, 08, 09, 0A, 0B ... 0Z, followed by 10-1Z, 20-2Z, etc.

The CID number appears on each page of the manuscript. The complete citation is used on the first page, and an abbreviated version on subsequent pages. Numbers in the index correspond to the last two digits of the six-digit CID number.



Contents

Part One

- xv *Conference Committee*
xvii Immersion BARC for hyper NA applications [7273-92]
W. Tseng, W. L. Huang, B. Lin, B. J. Lu, T. J. Yeh, E. T. Liu, C. C. Yu, United Microelectronics Corp. (Taiwan); S. R. Kim, J. Y. Yu, G. Wayton, S. Lee, S. Wong, C. Lin, M. Ciambra, S. Coley, D. Praseuth, K. O'Connell, G. Barclay, Rohm and Haas Electronic Materials LLC (United States)

INVITED SESSION

- 7639 02 **The evolution of patterning process models in computational lithography (Invited Paper)** [7639-01]
J. L. Sturtevant, Mentor Graphics Corp. (United States)

DOUBLE PATTERNING AND DOUBLE EXPOSURE I

- 7639 04 **Resist material for negative tone development process** [7639-03]
S. Tarutani, S. Kamimura, Y. Enomoto, K. Katou, FUJIFILM Corp. (Japan)
- 7639 05 **Non-reciprocal double-exposure materials for 193nm pitch division** [7639-04]
R. Bristol, J. Roberts, D. Shykind, J. M. Blackwell, Intel Corp. (United States)
- 7639 06 **Photobase generator assisted pitch division** [7639-05]
X. Gu, C. M. Bates, Y. Cho, T. Kawakami, T. Nagai, T. Ogata, The Univ. of Texas at Austin (United States); A. K. Sundaresan, N. J. Turro, Columbia Univ. (United States); R. Bristol, Intel Corp. (United States); P. Zimmerman, SEMATECH Inc. (United States); C. G. Willson, The Univ. of Texas at Austin (United States)
- 7639 07 **The important challenge to extend spacer DP process towards 22nm and beyond** [7639-06]
K. Oyama, Tokyo Electron Ltd. (Japan); E. Nishimura, M. Kushibiki, Tokyo Electron AT Ltd. (Japan); K. Hasebe, S. Nakajima, H. Murakami, Tokyo Electron TOHOKU Ltd. (Japan); A. Hara, S. Yamauchi, S. Natori, K. Yabe, T. Yamaji, R. Nakatsuji, H. Yaegashi, Tokyo Electron Ltd. (Japan)
- 7639 08 **Carbon-rich spin on sidewall material for self-aligned double-patterning technology** [7639-07]
D. S.-H. Hsu, Nanya Technology Corp. (Taiwan); H. Yaguchi, R. Sakamoto, D. Maruyama, Y. Sakaida, Nissan Chemical Industries, Ltd. (Japan); W. Wang, C.-Y. Huang, W.-B. Wu, Nanya Technology Corp. (Taiwan); B.-C. Ho, Nissan Chemical Industries, Ltd. (Japan); C.-L. Shih, Nanya Technology Corp. (Taiwan)

EUVL: JOINT SESSION WITH CONFERENCE 7636

- 7639 09 **Study on approaches for improvement of EUV-resist sensitivity** [7639-08]
S. Tarutani, H. Tsubaki, H. Takahashi, T. Itou, FUJIFILM Corp. (Japan)

- 7639 0A **Polymer photochemistry at the EUV wavelength** [7639-09]
T. H. Fedynyshyn, R. B. Goodman, A. Cabral, Massachusetts Institute of Technology (United States); C. Tarrio, T. B. Lucatorto, National Institute of Standards and Technology (United States)
- 7639 0B **Analysis of trade-off relationships in resist patterns delineated using SFET of Selete** [7639-10]
T. Kozawa, Osaka Univ. (Japan); H. Oizumi, T. Itani, Semiconductor Leading Edge Technologies, Inc. (Japan); S. Tagawa, Osaka Univ. (Japan)

NOVEL RESIST MATERIALS AND PROCESSES I

- 7639 0C **Advanced patterning solutions based on the shrink process assisted by double exposure (SPADE)** [7639-11]
Y. C. Bae, Y. Liu, T. Cardolaccia, R. Bell, K. Spizuoco, G. G. Barclay, Dow Electronic Materials (United States)
- 7639 0D **Design, synthesis, and characterization of fluorine-free PAGs for 193-nm lithography** [7639-12]
S. Liu, M. Glodde, P. R. Varanasi, IBM Systems and Technology Group (United States)
- 7639 0E **Development of an inorganic photoresist for DUV, EUV, and electron beam imaging** [7639-13]
M. Trikeriotis, W. J. Bae, E. Schwartz, M. Krysak, Cornell Univ. (United States); N. Lafferty, P. Xie, B. Smith, Rochester Institute of Technology (United States); P. Zimmerman, SEMATECH Inc. (United States); C. K. Ober, E. P. Giannelis, Cornell Univ. (United States)
- 7639 0F **A silicon-containing resist for immersion lithography** [7639-14]
R. Sooriyakumaran, IBM Almaden Research Ctr. (United States); W.-S. Huang, IBM Systems and Technology Group (United States); S. Swanson, H. Truong, P. Brock, A. Friz, IBM Almaden Research Ctr. (United States); K.-J. Chen, IBM Systems and Technology Group (United States); R. Allen, IBM Almaden Research Ctr. (United States)
- 7639 0G **New self-assembly strategies for next-generation lithography** [7639-15]
E. L. Schwartz, Cornell Univ. (United States); J. K. Bosworth, Hitachi Global Storage Technologies, Inc. (United States); M. Y. Paik, C. K. Ober, Cornell Univ. (United States)
- 7639 0H **Design and development of production-worthy developable BARCs(DBARCs) for implant lithography** [7639-16]
J. Cameron, J. Amara, J. W. Sung, D. Valeri, A. Ware, K. O'Shea, Dow Electronic Materials (United States); Y. Yamamoto, H. Kitaguchi, Dow Electronic Materials (Japan); L. Vyklicky, I. Popova, P. R. Varanasi, IBM Corp. (United States)

NOVEL RESIST MATERIALS AND PROCESSES II

- 7639 0I **Fabrication of dual damascene BEOL structures using a multilevel multiple exposure (MLME) scheme, part 1: lithographic patterning** [7639-17]
D. L. Goldfarb, IBM T.J. Watson Research Ctr. (United States); S. Harrer, J. C. Arnold, IBM Research Division at Albany Nanotech (United States); S. J. Holmes, IBM Systems & Technology Group at Albany Nanotech (United States); R. Chen, IBM Systems & Technology Group (United States); C. Tang, N. Fender, M. Slezak, JSR Micro, Inc. (United States); R. A. Della Guardia, E. A. Joseph, S. U. Engelmann, IBM Thomas J. Watson Research Ctr. (United States); R. P. Varanasi, IBM Systems & Technology Group (United States); M. E. Colburn, IBM Research Division at Albany Nanotech (United States)
- 7639 0J **Multilevel integration of patternable low-k material into advanced Cu BEOL** [7639-18]
Q. Lin, IBM Thomas J. Watson Research Ctr. (United States); S. T. Chen, IBM Systems and Technology Group (United States); A. Nelson, P. Brock, IBM Almaden Research Ctr. (United States); S. Cohen, IBM Thomas J. Watson Research Ctr. (United States); B. Davis, IBM Almaden Research Ctr. (United States); N. Fuller, IBM Thomas J. Watson Research Ctr. (United States); R. Kaplan, R. Kwong, IBM Systems and Technology Group (United States); E. Liniger, D. Neumayer, J. Patel, IBM Thomas J. Watson Research Ctr. (United States); H. Shobha, IBM Systems and Technology Group (United States); R. Sooriyakumaran, IBM Almaden Research Ctr. (United States); S. Purushothaman, IBM Thomas J. Watson Research Ctr. (United States); T. Spooner, IBM Corp. (United States); R. Miller, R. Allen, IBM Almaden Research Ctr. (United States); R. Wisnieff, IBM Thomas J. Watson Research Ctr. (United States)
- 7639 0K **Advantages of BARC and photoresist matching for 193-nm photosensitive BARC applications** [7639-19]
J. Lowes, Brewer Science, Inc. (United States); V. Pham, JSR Micro, Inc. (United States); J. Meador, C. Stroud, Brewer Science, Inc. (United States); F. Rosas, JSR Micro, Inc. (United States); R.-M. L. Mercado, Brewer Science, Inc. (United States); M. Slezak, JSR Micro, Inc. (United States)
- 7639 0L **Sub-millisecond post exposure bake of chemically amplified resists by CO₂ laser heat treatment** [7639-20]
B. Jung, J. Sha, F. Paredes, C. K. Ober, M. O. Thompson, Cornell Univ. (United States); M. Chandhok, T. R. Younkin, Intel Corp. (United States)

NEXT-GENERATION RESIST ARCHITECTURES

- 7639 0M **EUV RLS performance tradeoffs for a polymer bound PAG resist** [7639-21]
R. Gronheid, A. Vaglio Pret, IMEC (Belgium); B. Rathsack, J. Hooge, S. Scheer, Tokyo Electron America, Inc. (United States); K. Nafus, H. Shite, J. Kitano, Tokyo Electron Kyushu Ltd. (Japan)
- 7639 0O **Aqueous and solvent developed negative-tone molecular resists** [7639-23]
R. A. Lawson, J. Cheng, D. E. Noga, Georgia Institute of Technology (United States); T. R. Younkin, Intel Corp. (United States); L. M. Tolbert, C. L. Henderson, Georgia Institute of Technology (United States)
- 7639 0P **Comparison of star and linear ArF resists** [7639-24]
D. C. Forman, Cornell Univ. (United States); F. Wieberger, A. Groeschel, A. H. E. Müller, H.-W. Schmidt, Univ. Bayreuth (Germany); C. K. Ober, Cornell Univ. (United States)

- 7639 OQ **Characteristics of main chain decomposable star shaped polymer on EUV lithography** [7639-25]
T. Hirayama, J. Iwashita, S. Yoshizawa, K. Konno, T. Iwai, Tokyo Ohka Kogyo Co., Ltd. (Japan)
- 7639 OR **Development of EUV resists based on various new materials** [7639-26]
H. Oizumi, K. Matsumaro, J. Santillan, G. Shiraishi, K. Kaneyama, K. Matsunaga, T. Itani, Semiconductor Leading Edge Technologies, Inc. (Japan)
- 7639 OS **High resolution positive-working molecular resist attached with alicyclic acid-leaving group** [7639-27]
A. Yamada, S. Hattori, S. Saito, K. Asakawa, T. Koshiha, T. Nakasugi, Toshiba Corp. (Japan)

NOVEL MATERIALS, PROCESSES, AND APPLICATIONS

- 7639 OU **Negative-tone chemically amplified molecular resist based on novel fullerene derivative for nanolithography** [7639-52]
H. Yamamoto, T. Kozawa, S. Tagawa, Osaka Univ. (Japan); T. Ando, K. Ohmori, M. Sato, J. Onodera, Tokyo Ohka Kogyo Co., Ltd. (Japan)
- 7639 OV **Non-chemically amplified resists for 193-nm immersion lithography: influence of absorbance on performance** [7639-53]
L. Chen, Y.-K. Goh, K. Lawrie, The Univ. of Queensland (Australia); B. Smith, Rochester Institute of Technology (United States); W. Montgomery, P. Zimmerman, SEMATECH Inc. (United States); I. Blakey, A. Whittaker, The Univ. of Queensland (Australia)
- 7639 OW **Photobase generator and photo decomposable quencher for high-resolution photoresist applications** [7639-54]
C. W. Wang, C. Y. Chang, Y. Ku, Taiwan Semiconductor Manufacturing Co. Ltd. (Taiwan)
- 7639 OX **The optimizations of resist shrink process using track-based technology** [7639-55]
Y. Kondo, A. Ookouchi, T. Tsuruda, M. Yamamoto, T. Saito, T. Shibata, S. Shimura, F. Iwao, Tokyo Electron Kyushu Ltd. (Japan); B. Rath sack, M. Carcasi, Tokyo Electron America (United States)
- 7639 OY **Dependence of 20-nm C/H CD windows on critical process parameters** [7639-56]
W.-S. Chen, P.-Y. Gu, M.-J. Tsai, Industrial Technology Research Institute (Taiwan)
- 7639 OZ **Orthogonal lithography for organic electronics** [7639-57]
P. G. Taylor, J.-K. Lee, A. A. Zakhidov, H. S. Hwang, J. A. DeFranco, H. H. Fong, M. Chatzichristidi, E. Murotani, G. G. Malliaras, C. K. Ober, Cornell Univ. (United States)
- 7639 10 **Grayscale lithography process study applied to zero-gap microlenses for sub-2µm CMOS image sensors** [7639-58]
S. Audran, J. Vaillant, V. Farys, F. Hirigoyen, E. Huss, B. Mortini, C. Cowache, L. Berthier, E. Mortini, J. Fantuz, O. Arnaud, L. Depoyan, F. Sundermann, C. Baron, J.-P. Reynard, STMicroelectronics (France)
- 7639 11 **Improved thermal flow characteristic resist optimized for the manufacturing of microlenses** [7639-59]
M. Toukhy, M. Puanescu, S. Meyer, AZ Electronic Materials USA Corp. (United States)

- 7639 12 **Environmentally friendly processing of photoresists in scCO₂ and decamethyltetrasiloxane** [7639-60]
C. Y. Ouyang, J.-K. Lee, J. Sha, C. K. Ober, Cornell Univ. (United States)
- 7639 13 **Gap-fill type HSQ/ZEP520A bilayer resist process-(IV): HSQ-rod and HSQ-tip hardening processes** [7639-61]
W.-S. Chen, M.-J. Tsai, Industrial Technology Research Institute (Taiwan)
- 7639 14 **LWR reduction by novel lithographic and etch techniques** [7639-62]
S. Kobayashi, S. Shimura, T. Kawasaki, K. Nafus, S. Hatakeyama, H. Shite, Tokyo Electron Kyushu Ltd. (Japan); E. Nishimura, M. Kushibiki, A. Hara, Tokyo Electron AT Ltd. (Japan); R. Gronheid, A. Vaglio-Pret, IMEC (Belgium); J. Kitano, Tokyo Electron Kyushu Ltd. (Japan)
- 7639 15 **Alternatives to chemical amplification for 193nm lithography** [7639-63]
B. Baylav, M. Zhao, R. Yin, P. Xie, C. Scholz, B. Smith, T. Smith, Rochester Institute of Technology (United States); P. Zimmerman, SEMATECH Inc. (United States)
- 7639 17 **Further analysis of the effect of point-of-use filtration on microbridging defectivity** [7639-65]
J. Braggin, Entegris, Inc. (United States); R. Gronheid, S. Cheng, D. Van den Heuvel, S. Bernard, P. Foubert, IMEC (Belgium); C. Rosslee, Sokudo Co. Ltd. (United States)
- 7639 18 **Point-of-use filtration methods to reduce defectivity** [7639-66]
J. Braggin, Entegris, Inc. (United States); W. Schoallert, K. Hoshiko, X. Buch, JSR Micro N.V. (Belgium)
- 7639 19 **Fabrication of dual damascene BEOL structures using a multilevel multiple exposure (MLME) scheme, part 2: RIE-based pattern transfer and completion of dual damascene process yielding an electrically functional via chain** [7639-67]
S. Harrer, J. C. Arnold, Albany Nanotech Institute (United States); D. L. Goldfarb, IBM Thomas J. Watson Research Ctr. (United States); S. J. Holmes, Albany Nanotech Institute (United States); R. Chen, IBM Corp. (United States); C. Tang, M. Slezak, N. Fender, JSR Micro, Inc. (United States); R. A. Della Guardia, E. A. Joseph, S. U. Engelmann, IBM Thomas J. Watson Research Ctr. (United States); S.-T. Chen, D. Horak, Y. Yin, Albany Nanotech Institute (United States); R. P. Varanasi, IBM Corp. (United States); M. E. Colburn, Albany Nanotech Institute (United States)
- 7639 1A **Resist residue removal using UV ozone treatment** [7639-68]
S.-F. Chen, C.-Y. Chang, Y.-C. Ku, Taiwan Semiconductor Manufacturing Co. Ltd. (Taiwan)
- 7639 1B **The imaging study of a novel photopolymer used in I-line negative-tone resist** [7639-69]
L. Liu, Y. Zou, Beijing Normal Univ. (China)
- 7639 1C **Development of spin-on hard mask materials under resist in nano imprint lithography** [7639-112]
S. Takei, Nissan Chemical Industries, Ltd. (Japan), The Univ. of Texas at Austin (United States), and Osaka Univ. (Japan); T. Ogawa, R. Deschner, K. Jen, The Univ. of Texas at Austin (United States); M. Hanabata, Nissan Chemical Industries, Ltd. (Japan); C. G. Willson, The Univ. of Texas at Austin (United States)
- 7639 1E **Defect performance of a 2X node resist with a revolutionary point-of-use filter** [7639-116]
J. Braggin, R. Ramirez, A. Wu, W. Choi, Entegris, Inc. (United States); I. Funahshi, K. Yamamoto, Nihon Entegris K.K. (Japan)

- 7639 1F **New filter rating method in practice for sub-30-nm lithography process filter** [7639-117]
T. Umeda, T. Mizuno, S. Tsuzuki, T. Numaguchi, Nihon Pall Ltd. (Japan)
- 7639 1H **The use of surface modifiers to mitigate pattern collapse in thin film lithography** [7639-119]
D. E. Noga, W.-M. Yeh, R. A. Lawson, L. M. Tolbert, C. L. Henderson, Georgia Institute of Technology (United States)
- 7639 1I **Thin film buckling as a method to explore the effect of reactive rinse treatments on the mechanical properties of resist thin films** [7639-120]
W.-M. Yeh, D. E. Noga, R. A. Lawson, L. M. Tolbert, C. L. Henderson, Georgia Institute of Technology (United States)

EUV RESIST MATERIALS AND PROCESSES

- 7639 1J **Highly sensitive EUV-resist based on thiol-ene radical reaction** [7639-70]
M. Shirai, K. Maki, H. Okamura, Osaka Prefecture Univ. (Japan); K. Kaneyama, T. Itani, Semiconductor Leading Edge Technologies, Inc. (Japan)
- 7639 1K **Dynamics of radical cation of poly(4-hydroxystyrene) generated in thin film upon exposure to electron beam** [7639-71]
K. Natsuda, T. Kozawa, K. Okamoto, A. Saeki, S. Tagawa, Osaka Univ. (Japan)
- 7639 1L **Evaluation of hydroxyl derivatives for chemically amplified extreme ultraviolet resist** [7639-72]
K. Furukawa, Y. Arai, Mitsubishi Gas Chemical Co., Inc. (Japan); H. Yamamoto, T. Kozawa, S. Tagawa, Osaka Univ. (Japan)
- 7639 1N **Characterization of the effects of base additives on a fullerene chemically amplified resist** [7639-74]
J. Manyam, M. Manickam, J. A. Preece, R. E. Palmer, A. P. G. Robinson, The Univ. of Birmingham (United Kingdom)

Part Two

- 7639 1O **Study on acid diffusion length effect with PAG-blended system and anion-bounded polymer system** [7639-75]
S. Tarutani, H. Tsubaki, H. Takahashi, T. Itou, FUJIFILM Corp. (Japan); K. Matsunaga, G. Shiraishi, T. Itani, Semiconductor Leading Edge Technologies, Inc. (Japan)
- 7639 1P **Changes in vertical PAG distribution inside photoresist due to the variation of concentration** [7639-115]
J. H. Kim, S. I. Ahn, SAMSUNG Electronics Co., Ltd. (Korea, Republic of); J. G. Yoon, POSTECH (Korea, Republic of); Y.-H. Kim, S.-K. Chae, SAMSUNG Electronics Co., Ltd. (Korea, Republic of); W.-C. Zin, POSTECH (Korea, Republic of)

DOUBLE PATTERNING AND DOUBLE EXPOSURE

- 7639 1Q **Process parameter influence to negative tone development process for double patterning** [7639-76]
S. Tarutani, S. Kamimura, J. Yokoyama, FUJIFILM Corp. (Japan)

- 7639 1R **Bottom anti-reflective coatings (BARC) for LFLE double patterning process** [7639-77]
R. Sakamoto, T. Endo, B.-C. Ho, S. Kimura, T. Ishida, M. Kato, N. Fujitani, R. Onishi, Y. Hiroi, D. Maruyama, Nissan Chemical Industries, Ltd. (Japan)
- 7639 1S **Mesh patterning process for 40nm contact hole** [7639-78]
K. Lee, C. Bok, J. Kim, H. Shim, J. Heo, J. Lee, H.-S. Kim, D. Yim, S.-K. Park, Hynix Semiconductor Inc. (Korea, Republic of)
- 7639 1T **Advanced self-aligned DP process development for 22-nm node and beyond** [7639-79]
A. Hara, Tokyo Electron Ltd. (Japan); E. Nishimura, M. Kushibiki, Tokyo Electron AT Ltd. (Japan); S. Yamauchi, S. Natori, K. Yabe, K. Oyama, H. Yaeasghi, Tokyo Electron Ltd. (Japan)
- 7639 1U **Novel approaches to controlling photo-resist CD in double patterning processes** [7639-80]
K. Yabe, Tokyo Electron Ltd. (Japan); K. Hasebe, S. Nakajima, H. Murakami, Tokyo Electron AT Ltd. (Japan); A. Hara, S. Yamauchi, S. Natori, K. Oyama, H. Yaeasghi, Tokyo Electron Ltd. (Japan)
- 7639 1V **Simplified "Litho-Cluster-Only" solution for double patterning** [7639-81]
H. Tanaka, K. Hoshiko, T. Shimokawa, JSR Corp. (Japan); H. F. Hoefnagels, D. E. Keller, S. Wang, O. Tanriseven, R. Maas, J. Mallman, ASML Netherlands B.V. (Netherlands); K. Shigemori, C. Rosslee, SOKUDO Co., Ltd. (Japan)
- 7639 1W **Process performance of novel resist material and novel coater/developer system for cross-line contact hole process** [7639-82]
T. Nakamura, J. Yokoya, K. Ohmori, Tokyo Ohka Kogyo Co., Ltd. (Japan); H. Nakamura, T. Niwa, H. Kyouda, J. Kitano, Tokyo Electron Kyushu Ltd. (Japan)
- 7639 1X **Improving CD uniformity for thermal cured systems in double patterning** [7639-83]
L. Joesten, K. Spizuoco, Y. Liu, Y. Bae, Dow Electronic Materials (United States)
- 7639 1Y **Reaction kinetics of non-reciprocal photo-base generator (NRPBG) patterning** [7639-85]
D. Shykind, R. Bristol, J. Roberts, J. Blackwell, Y. Borodovsky, Intel Corp. (United States)
- 7639 1Z **Development of reverse materials for double patterning process** [7639-86]
Y. Sakaida, H. Yaguchi, R. Sakamoto, B.-C. Ho, Nissan Chemical Industries, Ltd. (Japan)

IMMERSION MATERIALS AND PROCESSING

- 7639 20 **Study of post develop defect on TC-less immersion resist** [7639-87]
M. Harumoto, S. Suyama, T. Miyagi, A. Hisai, M. Asai, SOKUDO Co., Ltd. (Japan)
- 7639 21 **Novel topcoat materials with improved receding angles and dissolution properties for ArF immersion lithography** [7639-88]
S. G. Yun, J. Y. Lee, Y. S. Yang, S. W. Shin, S. J. Lee, H. Y. Kwon, Y. J. Cho, S. J. Choi, S. J. Choi, J. S. Kim, T. Chang, Cheil Industries Inc. (Korea, Republic of)
- 7639 22 **Evaluation of next generation hardware for lithography processing** [7639-89]
T. Shimoaoki, M. Enomoto, K. Nafus, H. Marumoto, H. Kosugi, Tokyo Electron Kyushu Ltd. (Japan); J. Mallmann, R. Maas, C. Verspaget, E. van der Heijden, S. Wang, ASML Netherlands B.V. (Netherlands)

- 7639 23 **Topcoat-less resist process development for contact layer of 40nm node logic devices** [7639-90]
M. Fujita, T. Uchiyama, NEC Electronics Corp. (Japan); T. Furusho, T. Otsuka, Tokyo Electron Kyushu Ltd. (Japan); K. Tsuchiya, Tokyo Electron Ltd. (Japan)
- 7639 24 **Productivity improvement in the wafer bevel and backside cleaning before exposure** [7639-91]
Y. Tokunaga, S. Nishikido, K. Yoshihara, Tokyo Electron Kyushu Ltd. (Japan); Z. Hong, Tokyo Electron Taiwan Ltd. (Taiwan); M. Strobl, Y. C. Lin, Inotera Memories, Inc. (Taiwan)
- 7639 25 **High contact angle fluorosulfonamide-based materials for immersion lithography** [7639-92]
D. P. Sanders, L. K. Sundberg, IBM Almaden Research Ctr. (United States); M. Fujiwara, Y. Terui, M. Yasumoto, Central Glass International, Inc. (United States)

ARCS AND MULTILAYER PROCESSES

- 7639 26 **Photoresist-induced development behavior in DBARCs** [7639-95]
J. D. Meador, A. Guerrero, J. A. Lowes, C. Stroud, B. Carr, A. Qin, C. Washburn, R-M. L. Mercado, Brewer Science, Inc. (United States)
- 7639 27 **Noble design of Si-SOH in trilayer resist process for sub-30-nm logic device** [7639-96]
T.-H. Oh, Y. Nam, C. Chang, S. Kim, M. Kwak, D. Kim, H. Shin, N.-I. Lee, J. Yoon, SAMSUNG Electronics Co., Ltd. (Korea, Republic of)
- 7639 28 **Process optimization consideration for 193nm developable bottom anti-reflective coatings (DBARCs)** [7639-97]
T. Kudo, S. Chakrapani, A. Diones, E. Ng, C. Antonio, D. Parthasarathy, R. Collett, M. Neisser, M. Padmanaban, AZ Electronic Materials USA Corp. (United States)
- 7639 29 **Improving material-specific dispense processes for low-defect coatings** [7639-98]
B. Smith, Brewer Science, Inc. (United States); R. Ramirez, J. Braggin, A. Wu, K. Anderson, Entegris, Inc. (United States); J. Berron, N. Brakensiek, C. Washburn, Brewer Science, Inc. (United States)
- 7639 2A **Accelerating the dual damascene process time by new filling material** [7639-114]
K.-H. Tsao, Y.-H. Liu, T. Y. Chen, C.-J. Chen, C. C. Huang, United Microelectronics Corp. (Taiwan); Y.-C. Chang, G. Noya, N. Hsiao, S. Chiu, V. Chang, AZ Electronic Materials Taiwan Co., Ltd. (Taiwan); T. Katayama, H. Motobayashi, AZ Electronic Materials K.K. (Japan)

MOLECULAR RESISTS

- 7639 2B **Development of molecular resists based on Phenyl[4]calixarene derivatives.** [7639-99]
M. Echigo, H. Hayashi, Mitsubishi Gas Chemical Co., Inc. (Japan); H. Oizumi, K. Matsumaro, T. Itani, Semiconductor Leading Edge Technologies, Inc. (Japan)
- 7639 2C **All-dry processible and PAG-attached molecular glasses for improved lithographic performance** [7639-100]
M. Krysak, Cornell Univ. (United States); T. Kolb, C. Neuber, H-W. Schmidt, Univ. Bayreuth (Germany); C. K. Ober, Cornell Univ. (United States)

- 7639 2D **Molecular glass positive i-line photoresist materials containing 2,1,4-DNQ and acid labile group** [7639-101]
L. Wang, J. Yu, N. Xu, Beijing Normal Univ. (China)
- 7639 2E **Novel molecular glass photoresist materials for next-generation lithography** [7639-102]
A. Okumura, Y. Funaki, A. Takaragi, K. Okamoto, K. Tsutsumi, K. Inoue, R. Itaya, K. Ikura, Y. Iguchi, Daicel Chemical Industries, Ltd. (Japan)
- 7639 2F **Non-traditional resist designs using molecular resists: positive tone cross-linked and non-chemically amplified molecular resists** [7639-103]
R. A. Lawson, D. E. Noga, J. Cheng, L. M. Tolbert, C. L. Henderson, Georgia Institute of Technology (United States)

SIMULATION OF RESIST PROCESSES

- 7639 2G **Three-dimensional mesoscale model for the simulation of LER in photoresists** [7639-104]
R. A. Lawson, C. L. Henderson, Georgia Institute of Technology (United States)
- 7639 2H **Evolution of resist roughness during development: stochastic simulation and dynamic scaling analysis** [7639-105]
V. Constantoudis, Institute of Microelectronics (Greece); G. P. Patsis, Institute of Microelectronics (Greece) and Technological Educational Institution of Athens (Greece); E. Gogolides, Institute of Microelectronics (Greece)
- 7639 2I **Macroscopic and stochastic modeling approaches to pattern doubling by acid catalyzed cross-linking** [7639-106]
J. Fuhrmann, A. Fiebach, Weierstrass-Institute for Applied Analysis and Stochastics (Germany); G. P. Patsis, Technological Educational Institution of Athens (Greece)
- 7639 2K **Extension of 248-nm Monte Carlo, mesoscale models to 193-nm platforms** [7639-108]
M. Carcasi, M. Somervell, S. Scheer, Tokyo Electron America, Inc. (United States); S. Chauhan, J. Strahan, C. G. Willson, The Univ. of Texas at Austin (United States)
- 7639 2L **Stochastic modeling of photoresist development in 2D and 3D** [7639-109]
C. A. Mack, Lithoguru.com (United States)
- 7639 2M **Simulation study of directed self-assembly for 10-nm pattern formation** [7639-110]
S.-K. Kim, H.-K. Oh, Y.-D. Jung, I. An, Hanyang Univ. (Korea, Republic of)
- 7639 2N **Theoretical analysis of energy dissipation of electron in the resists II** [7639-111]
M. Toriumi, Lab. for Interdisciplinary Science and Technology (Japan)

RESIST FUNDAMENTALS

- 7639 2O **Methods to explore and prevent pattern collapse in thin film lithography** [7639-29]
D. E. Noga, W.-M. Yeh, R. A. Lawson, L. M. Tolbert, C. L. Henderson, Georgia Institute of Technology (United States)

- 7639 2S **A method to characterize pattern density effects: chemical flare and develop loading** [7639-33]
L. K. Sundberg, G. M. Wallraff, A. M. Friz, IBM Almaden Research Ctr. (United States);
A. E. Zweber, Z. Benes, IBM Corp. (United States); R. D. Lovchik, E. Delamarche, IBM Research
Zurich (Switzerland); W. D. Hinsberg, IBM Almaden Research Ctr. (United States)
- 7639 2T **Is the resist sidewall after development isotropic or anisotropic? effects of resist sidewall
morphology on LER reduction and transfer during etching** [7639-34]
V. Constantoudis, G. Kokkoris, E. Gogolides, Institute of Microelectronics (Greece);
E. Pargon, M. Martin, LTM-CNRS (France)

DOUBLE PATTERNING AND DOUBLE EXPOSURE II

- 7639 2U **Inactivation technology for pitch doubling lithography** [7639-35]
J. Hatakeyama, M. Ohashi, Y. Ohsawa, K. Katayama, Y. Kawai, Shin-Etsu Chemical Co., Ltd.
(Japan)
- 7639 2V **Process feasibility investigation of freezing free litho-litho-etch process for below 32nm hp**
[7639-36]
T. Nakamura, M. Takeshita, J. Yokoya, Y. Yoshii, H. Saito, R. Takasu, K. Ohmori, Tokyo Ohka
Kogyo Co., Ltd. (Japan)
- 7639 2W **Evolution of thermal cure resist for double patterning applications** [7639-37]
M. Reilly, Y. C. Bae, V. Vohra, The Dow Chemical Company (United States); C. Koay,
M. Colburn, IBM Corp. (United States)
- 7639 2X **Process characterization of pitch-split resist materials for application at 16nm node**
[7639-38]
S. J. Holmes, Albany Nanotech Institute (United States); C. Tang, JSR Micro, Inc. (United
States); J. C. Arnold, IBM T. J. Watson Research Ctr. (United States); Y. Yin, Albany Nanotech
Institute (United States); R. Chen, IBM Corp. (United States); N. Fender, B. Osborn,
G. Dabbagh, JSR Micro, Inc. (United States); S. Liu, IBM Corp. (United States); M. Colburn,
Albany Nanotech Institute (United States); R. P. Varanasi, IBM Corp. (United States);
M. Slezak, JSR Micro, Inc. (United States)
- 7639 2Y **Simplified double patterning process with non-topcoat self-freezing resist** [7639-39]
T. Fujisawa, Y. Anno, M. Hori, G. Wakamatsu, M. Mita, K. Ito, H. Tanaka, K. Hoshiko, T. Shioya,
K. Goto, JSR Corp. (Japan); Y. Ogawa, H. Takikawa, Y. Kozuma, Hitachi High-Technologies
Corp. (Japan); K. Fujiwara, M. Sugiura, Y. Yamaguchi, T. Shimokawa, JSR Corp. (Japan)
- 7639 2Z **Controlling 2D aspect ratio of elliptical contact level interconnects utilizing spin-on and
reactive ion etch critical dimension shrink for the 22-nm node** [7639-40]
A. Metz, S. Dunn, D. Hetzer, J. Cantone, S. Kawakami, Tokyo Electron Technology Ctr.,
America, LLC (United States); T. Winter, Tokyo Electron America, Inc. (United States);
K. Petrillo, D. Horak, S. Fan, M. Colburn, IBM Corp. (United States)

SIMULATION OF LITHOGRAPHIC PHENOMENA

- 7639 30 **Roughness characterization in the frequency domain and LWR mitigation with post-litho processes** [7639-41]
A. Vaglio Pret, R. Gronheid, P. Foubert, IMEC (Belgium)
- 7639 31 **Line-edge roughness and the ultimate limits of lithography** [7639-42]
C. A. Mack, Lithoguru.com (United States)
- 7639 32 **Meso-scale simulation of the line-edge structure based on polymer chains in the developing and rinse process** [7639-43]
H. Morita, National Institute of Advanced Industrial Science and Technology (Japan);
M. Doi, The Univ. of Tokyo (Japan)
- 7639 33 **Particle generation during photoresist dissolution** [7639-44]
S. Chauhan, The Univ. of Texas at Austin (United States); M. Somervell, M. Carcasi, S. Scheer, Tokyo Electron America, Ltd. (United States); R. T. Bonnacaze, The Univ. of Texas at Austin (United States); C. Mack, Lithoguru.com (United States); C. G. Willson, The Univ. of Texas at Austin (United States)
- 7639 34 **Predictive linewidth roughness and CDU simulation using a calibrated physical stochastic resist model** [7639-45]
S. A. Robertson, J. J. Biafore, M. D. Smith, KLA-Tencor Texas (United States); M. T. Reilly, J. Wandell, Dow Advanced Materials (United States)
- 7639 35 **Reflectivity metrics for optimization of anti-reflection coatings on wafers with topography** [7639-46]
M. D. Smith, T. Graves, J. Biafore, S. Robertson, KLA-Tencor Texas (United States)

RESIST MATERIALS DIGEST

- 7639 37 **Continuous evolution of lithographic films through process steps: an example with 193 chemically amplified resists** [7639-48]
S. Derrough, R. Tiron, CEA, LETI, MINATEC (France); D. Perret, Dow Electronic Materials, MINATEC (France); J. W. Thackeray, Dow Electronic Materials (United States); C. Sourd, CEA, LETI, MINATEC (France); P. Paniez, CNRS, LTM, MINATEC (France)
- 7639 3A **Topcoat-less resist process for 2Xnm node devices** [7639-51]
C. Oh, J. Lee, J. Heo, H. Shim, K. Ban, C. Bok, D. Yim, S. Park, Hynix Semiconductor Inc. (Korea, Republic of)

Author Index

Development of an inorganic photoresist for DUV, EUV, and electron beam imaging

Markos Trikeriotis^a, Woo Jin Bae^a, Evan Schwartz^a, Marie Krysak^a, Neal Lafferty^b, Peng Xie^b,
Bruce Smith^b, Paul Zimmerman^c, Christopher K. Ober^a, Emmanuel P. Giannelis^a

^aDept. of Materials Science and Engineering, Cornell University, Ithaca, New York 14853, USA,

^bMicrosystems Engineering, Rochester Institute of Technology, Rochester, New York 14623, USA,

^cIntel assignee to SEMATECH, Inc.

ABSTRACT

The trend of ever decreasing feature sizes in subsequent lithography generations is paralleled by the need to reduce resist thickness to prevent pattern collapse. Thinner films limit the ability to transfer the pattern to the substrate during etch steps, obviating the need for a hardmask layer and thus increasing processing costs. For the 22 nm node, the critical aspect ratio will be less than 2:1, meaning 40-45 nm thick resists will be commonplace. To address this problem, we have developed new inorganic nanocomposite photoresists with significantly higher etch resistance than the usual polymer-based photoresists. Hafnium oxide nanoparticles are used as a core to build the inorganic nanocomposite into an imageable photoresist. During the sol-gel processing of nanoparticles, a variety of organic ligands can be used to control the surface chemistry of the final product. The different ligands on the surface of the nanoparticles give them unique properties, allowing these films to act as positive or negative tone photoresists for 193 nm or electron beam lithography. The development of such an inorganic resist can provide several advantages to conventional chemically amplified resist (CAR) systems. Beyond the etch resistance of the material, several other advantages exist, including improved depth of focus (DOF) and reduced line edge roughness (LER). This work will show etch data on a material that is ~3 times more etch-resistant than a PHOST standard. The refractive index of the resist at 193 nm is about 2.0, significantly improving the DOF. Imaging data, including cross-sections, will be shown for 60 nm lines/spaces (l/s) for 193 nm and e-beam lithography. Further, images and physical characteristics of the materials will be provided in both positive and negative tones for 193 nm and e-beam lithography.

Keywords: inorganic photoresist, 193 nm lithography, EUV lithography, electron beam lithography, etch resistance

INTRODUCTION

Optical lithography with deep ultraviolet (DUV) wavelengths has been the standard process for patterning in the semiconductor industry, and extensions to sub-45 nm devices are currently being developed. The common trend for such high resolution is the use of a short wavelength laser of 193 nm (ArF), coupled with liquid immersion technology. The introduction of an immersion liquid between the projection optics and the substrate increases the depth of focus (DOF) and allows operation at a higher numerical aperture (NA), which increases resolution. Using water as an immersion fluid, the NA can reach 1.35, which enables patterning at 45 nm half-pitch, while with second generation immersion fluids and an NA of 1.5 or higher, the half-pitch can be reduced to 32 nm or less.¹ Alternative technologies for higher resolution patterning are also under development such as extreme ultraviolet (EUV) lithography. In either case, one of the

challenges for patterning at higher resolutions is the requirement that new photoresists with advanced performance characteristics be compatible with the new lithography tools.

New photoresists must meet two important requirements to be applicable to higher NA lithography: First, they should have a higher refractive index (RI) to match the high NA of the optical setup and second, they should show improved etch resistance during pattern transfer. The latter requirement becomes important as the printed features become smaller, because photoresist films need to be thinner to decrease the aspect ratio of the patterned lines and prevent pattern collapse. These very thin photoresist films must then be highly etch-resistant to allow the pattern to transfer to the substrate. Higher etch resistance is also important for electron beam lithography resists, since the patterning resolution can be as low as 15 nm. To meet these requirements, the approach that is presented in this study is to develop a new inorganic photoresist comprised of hafnium oxide (HfO₂) nanoparticles.

Hafnium oxide is the material of choice for the development of a high refractive index inorganic photoresist.^{2,3} The refractive index of pure HfO₂ at 193 nm is 2.9.⁴ Additionally, a big advantage of an inorganic material like HfO₂ is the higher chemical stability than organic polymers that are commonly used as photoresists. Hafnium oxide cannot be oxidized, it is thermally stable up to very high temperatures, and it does not decompose under exposure to 193 nm light. Moreover, nanoparticles, which are less than 5 nm in diameter, are ideal for the application, since the scattering of light by such small particles is minimized. Additionally, quantum confinement effects result in a blue shift of the absorption peak as the size of the particles gets smaller, resulting in low absorbance of 193 nm light.

The aim of these studies is to develop an inorganic resist made of hafnium oxide nanoparticles that can be used both for optical (DUV or EUV) and electron beam lithography. First, a variety of different synthesis approaches to produce HfO₂ nanoparticles is demonstrated. Second, the characterization of the nanoparticle powders, solutions and thin films is presented. Finally, the photoresist performance is evaluated for both optical and electron beam lithography.

MATERIALS AND METHODS

1.1 Materials

Hafnium oxychloride octahydrate (HfOCl₂·8H₂O) was purchased from Strem Chemicals. Hafnium isopropoxide monoisopropylate, propylene glycol monomethyl ether acetate (PGMEA), and tert-amyl alcohol were purchased from Sigma-Aldrich. All other solvents and chemicals were reagent grade.

1.2 Nanoparticle synthesis

The building blocks for the inorganic photoresist were hafnium oxide nanoparticles stabilized with various carboxylic acids. Two different methods were used to produce nanoparticles that can form stable suspensions in either water or organic solvents:

A) Controlled hydrolysis of hafnium isopropoxide at 65°C for 21 hours results in the formation of a white precipitate. This precipitate was centrifuged at 8,000 g for 10 min and then washed twice with acetone. The final product, a white powder, was obtained after drying at 60°C under vacuum. Photoresist solutions were prepared by adding proper amounts of this powder in PGMEA, followed by stirring and ultrasonication. Any aggregates or dust were removed by filtration using a 0.2 µm filter membrane.

B) A different approach that involves the surface modification of the nanoparticles can be used to synthesize nanoparticles with different properties. The surface ligands are replaced by other carboxylic acids via a direct ligand exchange reaction. In a typical synthesis, 2.0 g of the nanoparticles are dispersed in PGMEA and then the second ligand is added to a small scintillation vial. The solution is then heated at 130°C in an oil bath under stirring until it becomes clear. The product is precipitated by adding water and then is washed repeatedly with acetone to remove any free acid. Finally, the photoresist solutions are prepared by adding proper amounts of the precipitate in PGMEA, followed by stirring and ultrasonication. Any aggregates or dust are removed by filtration using a 0.2 μm filter membrane.

RESULTS AND DISCUSSION

1.3 Nanoparticle powders and suspensions

Hydrolysis and condensation of hafnium isopropoxide lead to the formation of a Hf-O-Hf network similar to hafnium oxide. The yield of the synthesis is about 0.7 g of powder per 1.0 g of hafnium isopropoxide used. The infrared spectrum (Figure 1) shows strong peaks characteristic of a carboxylate group. These are the asymmetric and symmetric stretch of the carboxylate at 1450 cm^{-1} and 1570 cm^{-1} as well as a weak peak at 1710 cm^{-1} , which corresponds to the C = O double bond of a protonated carboxylic acid. The weaker peaks that appear at 1350 cm^{-1} and 1610 cm^{-1} show the existence of mono-dentate acid. These results indicate that both the anionic and the protonated forms of the carboxylic acid are present and that the ligation to Hf ions is either mono- or bi-dentate. Additionally, a broad peak appearing around 3300 cm^{-1} could be attributed either to OH groups that are bridging the Hf atoms or to water that is bound on the nanoparticles. Due to the low synthesis temperature, noncrystalline species with a large number of uncondensed OH groups are expected.

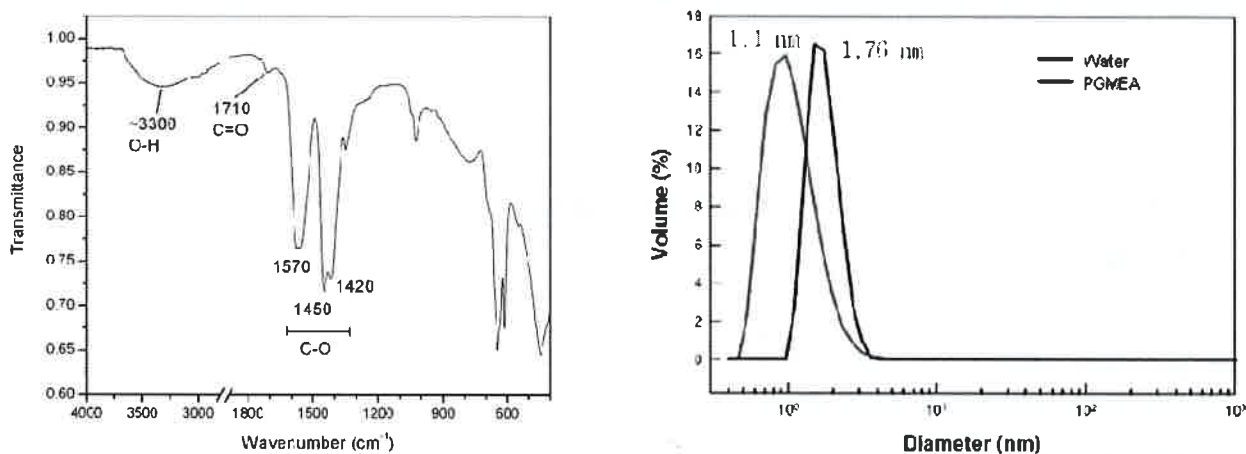


Figure 1. Infrared spectrum of the nanoparticle powder (left) and size distribution of nanoparticle suspensions (right).

The size distribution of the nanoparticles was measured using dynamic light scattering (Figure 1). Depending on the different surface ligands that are used, the nanoparticles can form stable suspensions in either water or organic solvents like PGMEA. In both cases, the size distribution is very narrow with particle diameters ranging from 1–3 nm. Such small sizes are ideal for the application of the nanoparticles as an inorganic photoresist, since the scattering of light by such small particles is minimized and the absorption peak of hafnium oxide is blue shifted due to quantum confinement effects. Additionally, smaller particle sizes are expected to contribute to a lower line edge roughness (LER) value on the relief images of the photoresist.

The composition of the nanoparticle powders was also examined using thermo gravimetric analysis (TGA). As shown in Figure 2, the weight loss occurs in two distinct steps for all the powders that were studied. The first step up to 150°C can be attributed to loss of adsorbed solvent on the nanoparticle surface. The second step, which occurs at 300–450°C, corresponds to the decomposition of the organic acid. The total organic content of the powders varies from 25–35% w/w; this was also confirmed using elemental analysis. The remaining 65–75% is the inorganic core of the nanoparticles. The high inorganic content of the nanoparticles is expected to contribute to the high etch resistance of the photoresist due to the chemical stability of hafnium oxide.

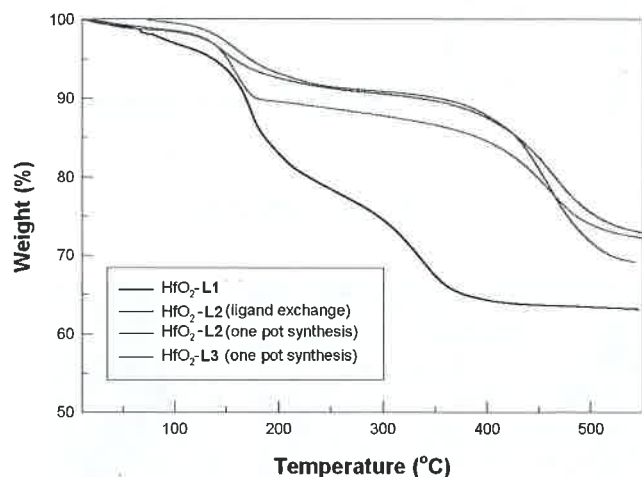


Figure 2. Thermogravimetric analysis of different nanoparticle powders.

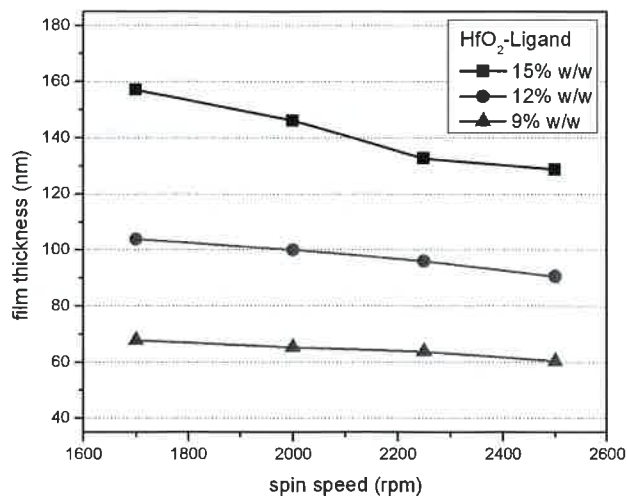


Figure 3. Film thickness versus spin speed at different nanoparticle loadings

1.4 Nanoparticle thin films

Uniform thin films can be spin-coated on Si wafers using either aqueous or PGMEA dispersions of the nanoparticles. Typically, a dispersion containing 5–20% w/w nanoparticles was spin-coated for 60 sec at 1000–3000 rpm. By varying the nanoparticle loading in the dispersion and the spin speed, the film thickness can be controlled. The film thickness was measured with a spectroscopic ellipsometer for different nanoparticle loadings and different spin-coating speeds (Figure 3). In general, film thicknesses ranging from 30 nm to 200 nm can be easily achieved.

The absorbance and the refractive index of the Hf nanoparticle films are important for their application as photoresists. The refractive index of the film, measured using a spectroscopic ellipsometer (Figure 4), was found to be 2.0 at 193 nm. Such a high refractive index can enable patterning up to 1.9 NA. To measure the absorption coefficient of the photoresist, films of a known thickness were spin-coated on quartz slides and their absorbance was measured in the range from 190–400 nm using a spectrophotometer. The absorption coefficient of the films depends on the ligand and the synthesis method that was used. As shown on Figure 4, the absorption coefficient varies from 0.5 to 5.0 μm^{-1} . These measurements show that the absorbance of the nanoparticle films is low enough to allow them to be used as photoresists for optical lithography.

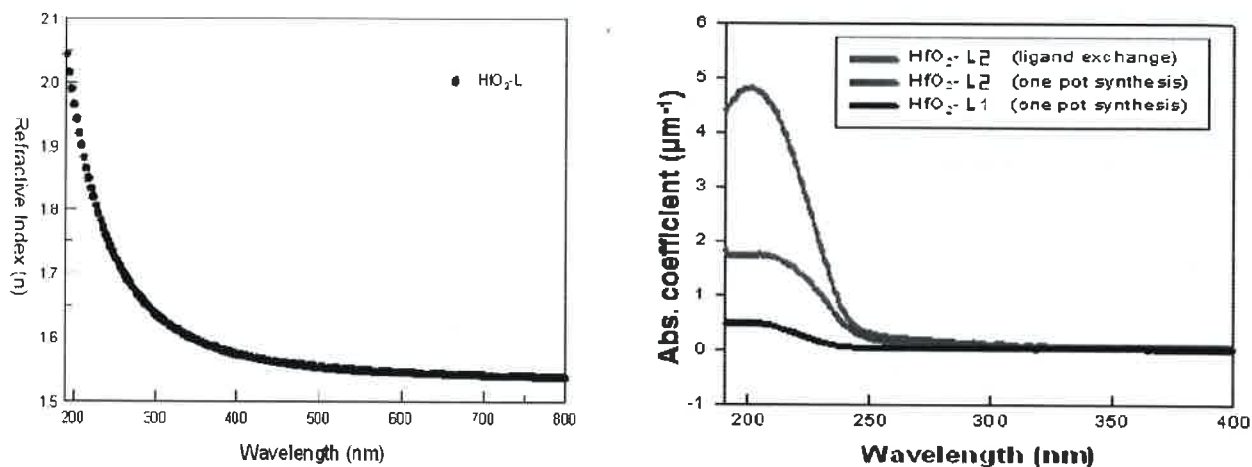


Figure 4. Refractive index (left) and absorption coefficient (right) of the nanoparticle films.

1.5 Optical lithography

The hafnium oxide nanoparticle films are intended for use as inorganic photoresists. To evaluate their potential application in lithography, the Hf nanoparticle films were patterned using DUV light. Various aspects of their performance, such as their patterning resolution capability, their sensitivity, and their etch resistance, were studied.

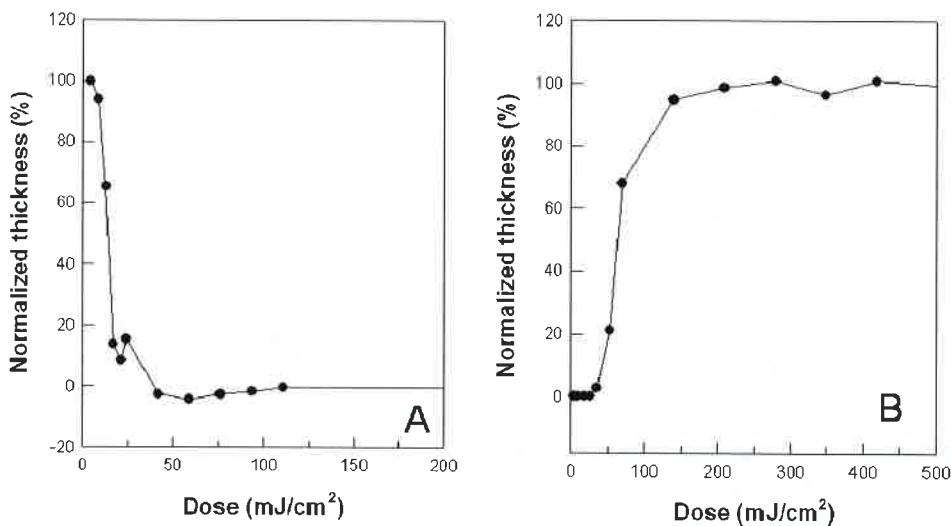


Figure 5. Contrast curves of the nanoparticle films under 254 nm light exposure: positive tone (left) and negative tone (right).

The nanoparticle films with 2,2-dimethoxy-2-phenyl acetophenone (DPAP) as a photoinitiator act both as positive and negative tone photoresists. Films with the desired thickness are prepared and then baked at 130°C for 60 sec on a hot plate. After exposure under DUV light (254 or 193 nm), development in isopropyl alcohol or t-amyl alcohol gives a negative tone image. For the positive tone imaging, the film is baked after exposure (PEB) at 130°C for 3 min and then aqueous tetrametylammonium hydroxide (TMAH) is used for the development.

The contrast curves for the positive and negative tone imaging (Figure 5) were constructed by measuring the thickness of the film after exposure at various doses of 254 nm light and development in 0.26N TMAH for 30 sec (positive tone) or isopropyl alcohol for 2 min (negative tone). Using the same conditions, the films were exposed at 254 nm through a mask to determine the resolution of the positive and negative tone imaging. The optical microscope images of the resulting patterns are presented in Figure 6. For the positive tone image, the resolution is 0.9 μm while for the negative tone it is 0.8 μm .

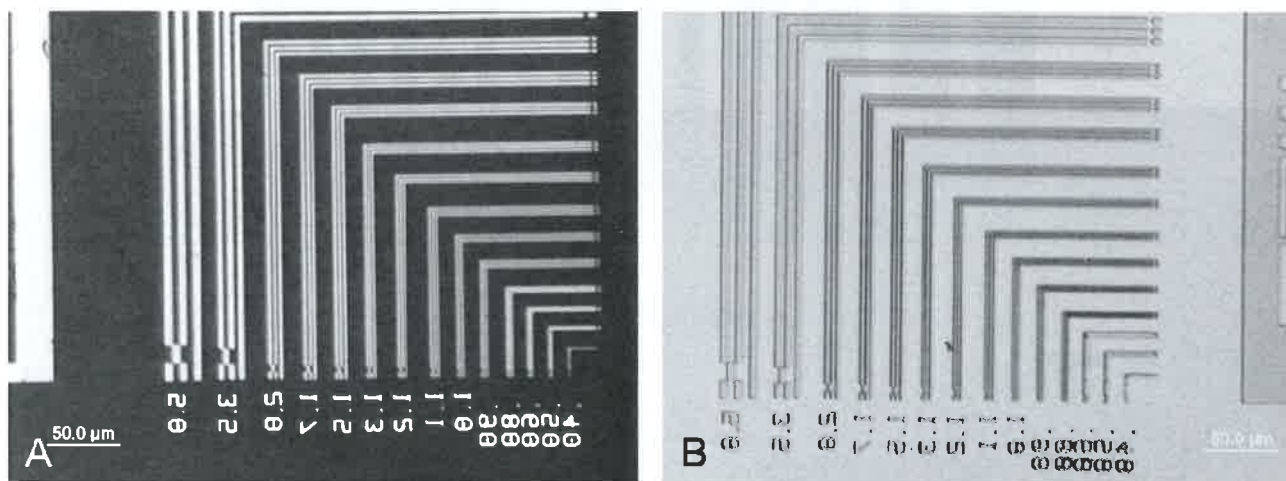


Figure 6. Optical microscope images of patterns printed on the nanoparticle resist using 254 nm light: positive tone (left) and negative tone (right).

Similar films were also exposed at 193 nm light using an Amphibian ArF excimer laser-based interferometric lithography (IL) system. The variable NA system is comprised of a line-narrowed compact excimer laser and projection optics for Talbot interference imaging using a phase grating mask. For the positive tone imaging, a PEB at 130°C for 5 min was applied and the development was done in 0.065N TMAH for 30 sec. For the negative tone, no PEB was required while the images were developed in isopropyl alcohol for 30 sec. Using the IL system with a NA of 0.32, 150 nm lines and spaces were patterned on the Hf nanoparticle films (Figure 7). The scanning electron microscopy (SEM) images show that the negative tone pattern forms well-defined lines and spaces with a square profile. The positive tone image shows a much thinner film than the negative tone, although both films were identical before patterning. This indicates that there is significant dark loss during positive tone imaging.

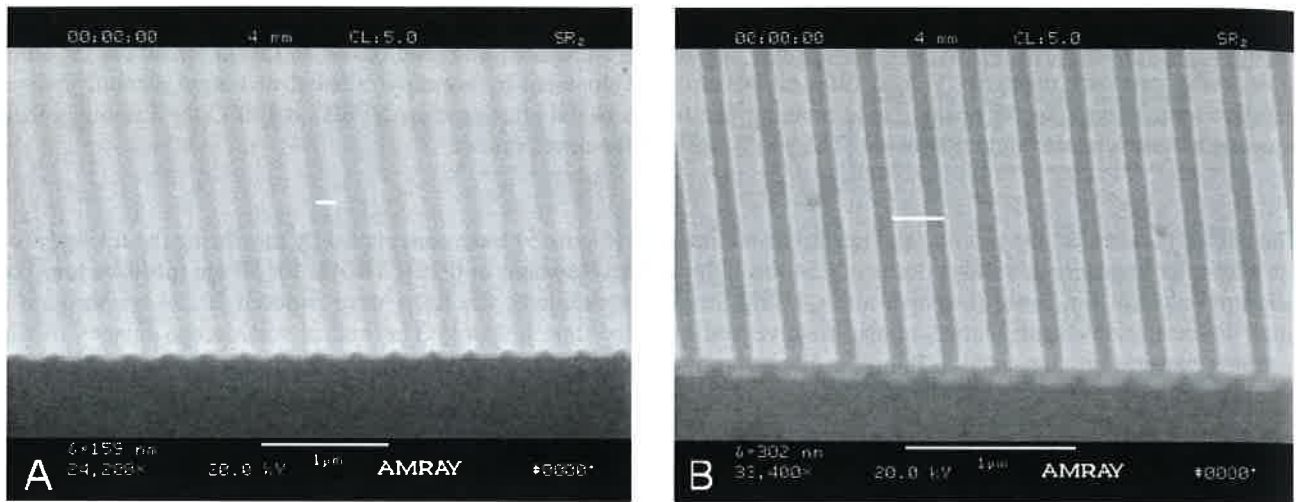


Figure 7. SEM images of patterns printed on the nanoparticle resist using 193 nm light: positive tone (left) and negative tone (right).

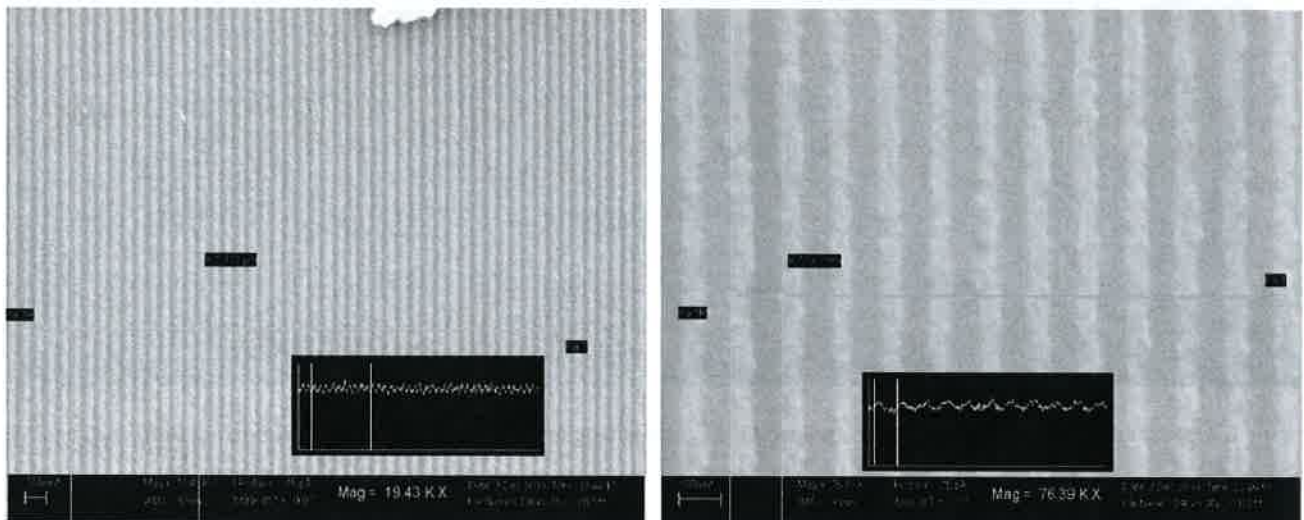


Figure 8. SEM images of 60 nm patterns printed on the nanoparticle resist using 193 nm light.

By changing the optics in the IL system to a NA of 0.80, 60 nm line-space patterns could be imaged to evaluate the negative tone mode of the resist. The films were coated on a bottom anti-reflecting coating (BARC) and tert-amyl alcohol was used as a developer. Figure 8 shows the SEM image of the 60 nm lines and spaces that were printed on the film. The film that was used was only 30 nm thick to minimize the absorbance and reflection of light. Currently, optimization of the photoresist formulation is underway to pattern 60 nm features on thicker films.

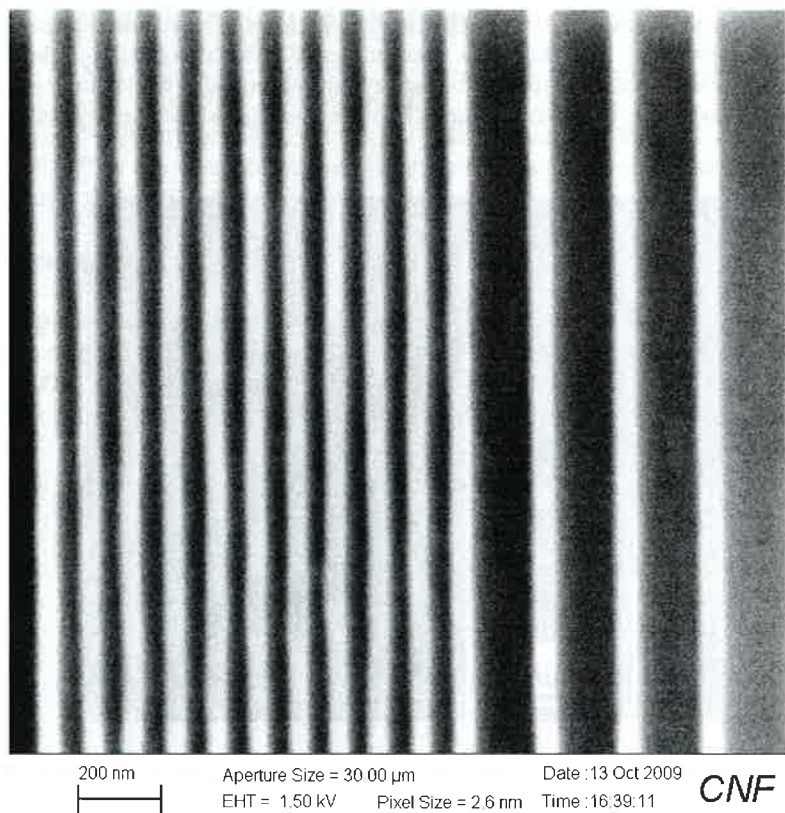


Figure 9. High resolution SEM negative tone images of sub-100 nm patterns.

Etch resistance is an important performance characteristic for photoresist. High resolution patterning in particular requires a very high etch resistance to allow patterns to be transferred from very thin films. The etch resistance of the nanoparticle films was measured and compared to poly-hydroxy styrene (PHOST) films. Both positive and negative tone patterns were etched using SF_6/O_2 plasma for 10s. The results show that the inorganic nanoparticle films are 2–3 times more resistant than PHOST under the same conditions. By reducing the organic content of the Hf nanoparticle films, the etch resistance can be made even higher.

1.6 Electron beam lithography

To determine the ultimate resolution limits of the nanoparticle photoresist, electron beam lithography was used. Just as in optical lithography, both positive tone and negative tone images could be obtained. For the negative tone imaging, the exposed films were developed using either isopropanol for 2 min, or tert-amyl alcohol for 30 sec. The positive tone images required 2 min of baking at 130°C and development in water for 5 min.

The films were exposed using a standard test pattern geometry of regularly repeating lines and spaces of various densities to determine their ability to form well defined high resolution images. An array of these patterns was created with fixed dose increments up to 500 $\mu\text{C}/\text{cm}^2$. The ideal doses were found to be in the range of 100 to 300 $\mu\text{C}/\text{cm}^2$ with the use of the radical photoinitiator DPAP. Without the photoinitiator, the resist still images but the required doses were much higher.

Figure 9 shows high resolution SEM images of the negative tone patterns. The required dose was $103 \mu\text{C}/\text{cm}^2$ and the patterns were developed in isopropanol for 2 min. As seen in Figure 9, both isolated and dense 50 nm lines could be obtained. Even higher resolution is possible for the negative tone photoresist while, in the positive tone case, high resolution imaging was not possible due to the low contrast between the unexposed and exposed areas.

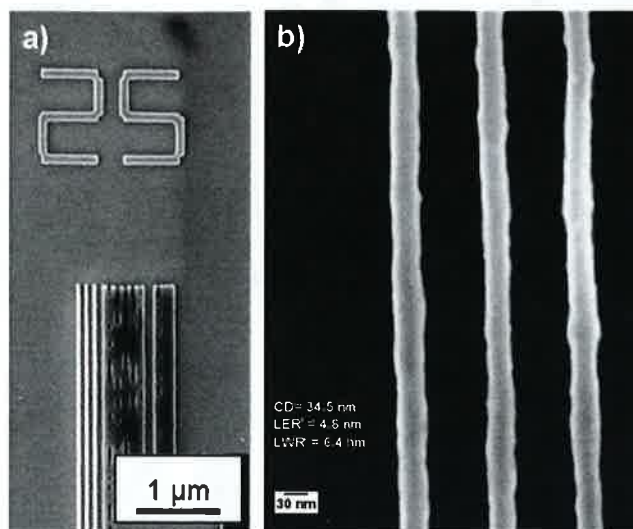


Figure 10. High resolution SEM negative tone images on the nanoparticle film printed at a critical dimension of 35 nm.

Figure 10 shows the highest resolution patterns that were achieved using e-beam lithography on the nanoparticle films. The developer in this case was tert-amyl alcohol, a slightly less polar alcohol than the previously used isopropanol. A less polar solvent was necessary in this case to slow the dissolution of the unexposed film. As shown in Figure 10, SEM analysis of the test patterns at this dose showed 35 nm linewidths without any pattern collapse. The dense lines in this pattern, however, were merged together. Assuming a nanoparticle size of 3 nm (from DLS) and a resist thickness of 60 nm (ellipsometry), a crosslinked stack of about 11 nanoparticles across and 20 nanoparticles high is present. Zooming in on these lines allows a close-up look at the LER and linewidth roughness (LWR). SuMMit software was used for the LER/LWR analysis of these SEM images. The smoothest lines have a 4.8 nm LER and a 6.4 nm LWR. Further optimization of the photoresist formulation could possibly decrease the LER/LWR down to 2.0 nm.

CONCLUSIONS

A new class of photoresist materials, which are mostly inorganic, was developed and tested. The inorganic photoresists are made of hafnium oxide nanoparticles as small as 1.0 nm in diameter. The nanoparticle films have a high refractive index and show low absorbance. Both positive and negative tone imaging is possible using either DUV or e-beam lithography with high resolution. Additionally, the etch resistance of the inorganic photoresists is superior to that of PHOST. Further optimization of the photoresist formulation will lead to higher etch resistance and lower LER/LWR values.

ACKNOWLEDGEMENTS

This work was funded by International SEMATECH. SEMATECH and the SEMATECH logo are registered service marks of SEMATECH, Inc. All other service marks and trademarks are the property of their respective owners.

REFERENCES

- [1] Sewell, H., Mulkens, J., McCafferty, D., Markoya, L., Streefkerk, B. and Graeupner, P., "The next phase for immersion lithography," Proc. SPIE 6154, 615406 (2006).
- [2] Zimmerman, P., A., Rice, B., Rodriguez, R., Zettel, M., F., Trikeriotis, M., Wang, D., Yi, Y., Bae, W., J., Ober, C., K. and Giannelis, E., P., "The use of nanocomposite materials for high refractive index immersion lithography," J. Photopolym. Sci. Technol. 21(5), 621-629 (2008).
- [3] Bae, W. J., Trikeriotis, M., Rodriguez, R., Zettel, M. F., Piscani, E., Ober, C. K., Giannelis, E. P. and Zimmerman, P., "High-index nanocomposite photoresist for 193-nm lithography," Proceedings of SPIE Vol. 7273, 727326 (2009).
- [4] Trikeriotis, M., Rodriguez, R., Zettel, M. F., Bakandritsos, A., Bae, W. J., Zimmerman, P. A., Ober, C. K. and Giannelis, E. P., "High refractive index nanoparticle fluids for 193-nm immersion lithography," Proceedings of SPIE Vol. 7273, 72732A (2009).