



INTEGRATED
OPTICS

TA 1660
.I55275
2006
Copy 1

Integrated Optics: Devices, Materials, and Technologies X

**Yakov Sidorin
Christoph A. Waechter**
Chairs/Editors

**23–25 January 2006
San Jose, California, USA**

Volume 6123



The International Society
for Optical Engineering

PROCEEDINGS OF SPIE




Integrated Optics: Devices, Materials, and Technologies X

Yakov Sidorin
Christoph A. Wächter
Chairs/Editors

23–25 January 2006
San Jose, California, USA

Sponsored and Published by
SPIE—The International Society for Optical Engineering

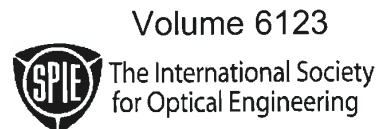

SPIE is an international technical society dedicated to advancing engineering and scientific applications of optical, photonic, imaging, electronic, and optoelectronic technologies.

TA1660
.I55275
2506
Copey1

The papers included in this volume were part of the technical conference cited on the cover and title page. Papers were selected and subject to review by the editors and conference program committee. Some conference presentations may not be available for publication. The papers published in these proceedings reflect the work and thoughts of the authors and are published herein as submitted. The publisher is not responsible for the validity of the information or for any outcomes resulting from reliance thereon.

e-First Publication for Proceedings: As of July 2005, papers in the Proceedings of SPIE are first published electronically in the SPIE Digital Library (www.spiedl.org), and subsequently in print and CD-ROM.

Pagination system: The new citation format uses six-digit article identifier numbers (CIDs). Utilization of article CIDs allows proceedings articles to be fully citable as soon as they are published online, using the same identifier for both online and print versions.

The structure of the six-digit article CID number for Proceedings of SPIE is:

- The first four digits indicate the SPIE volume number.
- The last two digits indicate publication order within the volume using a Base 36 numbering system employing both numerals and letters. The CID number appears on each page, followed by the page number within the actual article.

Please use the following format to cite material from this book:

Author(s), "Title of Paper," in *Integrated Optics: Devices, Materials, and Technologies X*, edited by Yakov Sidorin, Christoph A. Waechter, Proceedings of SPIE Vol. 6123 (SPIE, Bellingham, WA, 2006) Article CID Number.

ISSN 0277-786X
ISBN 0-8194-6165-2

Published by
SPIE—The International Society for Optical Engineering
P.O. Box 10, Bellingham, Washington 98227-0010 USA
Telephone 1 360/676-3290 (Pacific Time) • Fax 1 360/647-1445
<http://www.spie.org>

Copyright © 2006, The Society of Photo-Optical Instrumentation Engineers

Copying of material in this book for internal or personal use, or for the internal or personal use of specific clients, beyond the fair use provisions granted by the U.S. Copyright Law is authorized by SPIE subject to payment of copying fees. The Transactional Reporting Service base fee for this volume is \$15.00 per article (or portion thereof), which should be paid directly to the Copyright Clearance Center (CCC), 222 Rosewood Drive, Danvers, MA 01923. Payment may also be made electronically through CCC Online at <http://www.copyright.com>. Other copying for republication, resale, advertising or promotion, or any form of systematic or multiple reproduction of any material in this book is prohibited except with permission in writing from the publisher. The CCC fee code is 0277-786X/06/\$15.00.

Printed in the United States of America.

LC Control Number



2006

281325

Contents

- ix *Conference Committee*
xi *Symposium Committee*

SESSION 1 MATERIALS, TESTS, AND CHARACTERIZATION

- 612301 **Press-patterned UV-curable high refractive index coatings** [6123-01]
R. Morford, W.-S. Shih, J. Dachsteiner, Brewer Science, Inc. (USA)
- 612302 **Erbium-doped polymer-based materials and waveguides for amplification at 1.55 μm**
[6123-03]
A. Q. Le Quang, Institut d'Alembert, École Normale Supérieure de Cachan (France);
E. Besson, Univ. Montpellier II (France); R. Hierle, Institut d'Alembert, École Normale
Supérieure de Cachan (France); A. Mehdi, C. Reyé, R. Corriu, Univ. Montpellier II (France);
J. Zyss, Institut d'Alembert, École Normale Supérieure de Cachan (France); S. Pietralunga,
CoreCom (Italy); I. Ledoux, Institut d'Alembert, École Normale Supérieure de Cachan
(France)
- 612304 **Fast amplitude and delay measurement for characterization of integrated optic devices**
[6123-05]
M. Thompson, H. Zhu, W. Rivera, M. Solmaz, D. Adams, C. K. Madsen, Texas A&M Univ. (USA)

SESSION 2 MODELLING

- 612306 **Emerging trends in photonics modeling (Invited Paper)** [6123-07]
J. Pond, T. Kleckner, P. Paddon, A. Reid, Lumerical Solutions, Inc. (Canada)
- 612307 **Plasmon-enhanced absorption and transmission in spherical Bragg resonators** [6123-08]
M. Deutsch, K. Hasegawa, C. Rohde, Univ. of Oregon (USA)
- 612308 **Subwavelength plasmonic waveguide structures based on slots in thin metal films** [6123-09]
G. Veronis, S. Fan, Stanford Univ. (USA)
- 612309 **Tunable resonant leaky mode silicon-on-insulator photonic devices** [6123-10]
R. Magnusson, Y. Ding, Univ. of Connecticut (USA)
- 61230A **The modeling of MMI devices** [6123-11]
L. W. Cahill, La Trobe Univ. (Australia)

SESSION 3 IO SENSORS AND MODULATORS

- 61230B **Bimetallic silver-gold film waveguide surface plasmon resonance sensor** [6123-12]
B. H. Ong, X. Yuan, S. C. Tjin, Nanyang Technological Univ. (Singapore)

- 61230C **Some new trends on lithium niobate modulators (Invited Paper)** [6123-13]
N. Courjal, M. P. Bernal, Univ. de Franche Comté (France); J. Hauden, Photline Technologies (France); J. Amet, M. Roussey, Univ. de Franche Comté (France); H. Porte, Photline Technologies (France)
- 61230D **Novel optical-waveguide sensing platform based on input grating coupler** [6123-14]
S. Grego, S. Naskar, A. M. Patel, A. Huffman, C. A. Bower, B. R. Stoner, RTI International (USA)
- 61230E **Novel integrated polarization analyzer sensor made by ion-exchange in glass** [6123-15]
P. Lemaître-Auger, LCIS-INPG (France); K. Djerroud, P. Benech, P. Benech, IMEP, CNRS (France)

SESSION 4 WG ENGINEERING I

- 61230F **Large core single-mode glass-based waveguides for photonic integrated circuits** [6123-16]
D. Zhang, W. Pan, Y. Zhang, A. Loni, P. Sewell, T. M. Benson, C. A. Miller, D. Furniss, A. B. Seddon, Univ. of Nottingham (United Kingdom)
- 61230G **Characterization of highly photorefractive and active silica-germania sputtered thin films** [6123-17]
S. Berneschi, N. Carrara Institute of Applied Physics, IFAC-CNR (Italy) and Bologna Univ. (Italy); M. Brenci, N. Carrara Institute of Applied Physics, IFAC-CNR (Italy); A. Chiasera, M. Ferrari, Institute of Photonics and Nanotechnologies, IFN-CNR (Italy); G. Nunzi Conti, S. Pelli, S. Sebastiani, N. Carrara Institute of Applied Physics, IFAC-CNR (Italy); C. Tosello, Univ. of Trento (Italy); G. C. Righini, N. Carrara Institute of Applied Physics, IFAC-CNR (Italy)
- 61230H **Thick hybrid silica-zirconia sol-gel film for single-step fabrication of channel waveguide** [6123-18]
M. He, J. Bu, Nanyang Technological Univ. (Singapore); X. Yuan, Nanyang Technological Univ. (Singapore) and Shenzhen Univ. (China)
- 61230I **Polymer photonic integrated circuits by DUV-induced modification** [6123-19]
D. G. Rabus, Forschungszentrum Karlsruhe GmbH (Germany) and Univ. of California, Santa Cruz (USA); P. Henzi, M. Bruendel, H. Hein, Y. Ichihashi, T. Rogge, A. Welle, Forschungszentrum Karlsruhe GmbH (Germany)
- 61230J **Highly stable and low loss electro-optic polymer waveguides for high speed microring modulators using photodefinition** [6123-20]
M. Balakrishnan, M. B. J. Diemeer, A. Driessen, M. Faccini, W. Verboom, D. N. Reinhoudt, MESA Institute for Nanotechnology (Netherlands); A. Leinse, Lionix BV (Netherlands)

SESSION 5 NOVEL DEVICES AND APPLICATIONS I

- 61230K **InP-based 1.55 μm waveguide-integrated photodetectors for high-speed applications (Invited Paper)** [6123-21]
A. Beling, Fraunhofer Institute for Telecommunications, Heinrich-Hertz-Institut (Germany)

- 61230L **Infrared single-mode hollow conductive waveguides for stellar interferometry** [6123-22]
P. Labeye, LETI, CEA (France); J.-E. Broquin, IMEP, ENSERG (France); P. Kern, Lab. d'Astrophysique de l'Observatoire de Grenoble (France); P. Noël, LETI, CEA (France); P. Saguet, IMEP, ENSERG (France); L. Labadie, Lab. d'Astrophysique de l'Observatoire de Grenoble (France); C. Ruillier, Alcatel Alenia Space (France); V. Kirshner, ESA-ESTEC, European Space Research and Technology Ctr. (Netherlands)
- 61230M **Manipulation of microparticles with integrated optics (Invited Paper)** [6123-23]
O. G. Hellesø, K. Grujic, Univ. of Tromsø; (Norway); J. P. Hole, Univ. of Southampton (United Kingdom); H. Jaising, Univ. of Tromsø; (Norway) and SINTEF Petroleum Research (Norway); J. S. Wilkinson, Univ. of Southampton (United Kingdom)
- 61230N **Enhanced Cerenkov second-harmonic generation in patterned lithium niobate** [6123-24]
C. Deng, J. W. Haus, A. Sarangan, A. Mahfoud, Univ. of Dayton (USA); C. Sibilia, INFN, Univ. degli Studi di Roma La Sapienza (Italy); M. Scalora, U.S. Army Aviation and Missile Command (USA); A. M. Zheltikov, M.V. Lomonosov Moscow State Univ. (Russia)

SESSION 6 GRATING-BASED DEVICES

- 61230O **Cascaded planar reflective gratings** [6123-25]
S. Bidnyk, M. Pearson, A. Balakrishnan, M. Gao, Enablence Inc. (Canada)
- 61230P **Multilayer integrated nano-optical devices (Invited Paper)** [6123-26]
J. Wang, X. Deng, X. Liu, A. Nikolov, P. Sciortino, F. Liu, L. Chen, NanoOpto Corp. (USA)
- 61230Q **Integration of encoder/decoder for avionic OCDMA by holographic Bragg reflectors** [6123-27]
Y.-K. Huang, I. Glesk, P. R. Prucnal, Princeton Univ. (USA); C. Greiner, D. Iazikov, T. W. Mossberg, LightSmyth Technologies, Inc. (USA)
- 61230R **Compact coding devices using the novel anti-symmetric gratings** [6123-28]
J. M. Castro, The Univ. of Arizona (USA); S. Honkanen, College of Optical Sciences, The Univ. of Arizona (USA); C. M. Greiner, D. Iazikov, T. W. Mossberg, LightSmyth Technologies, Inc. (USA); D. F. Geraghty, The Univ. of Arizona (USA)
- 61230S **Annular Bragg resonators (ABR): the ideal tool for biochemical sensing, nonlinear optics, and cavity QED** [6123-29]
J. Scheuer, W. M. J. Green, A. Yariv, California Institute of Technology (USA)

SESSION 7 WG ENGINEERING II

- 61230T **Study of a pump/signal multiplexer based on a segmented asymmetric Y junction by silver/sodium ion exchange on glass** [6123-30]
D. Bucci, J. Grelin, E. Ghibaudo, J.-E. Broquin, Institut de Microélectronique, Electromagnetisme et Photonique (France)
- 61230V **Active and passive integrated optical devices written in glasses with femtosecond laser systems (Invited Paper)** [6123-32]
R. Osellame, N. Chiodo, G. Della Valle, S. Taccheo, G. Cerullo, R. Ramponi, P. Laporta, Istituto di Fotonica e Nanotecnologie, CNR (Italy); A. Killi, TRUMPF Laser GmbH & Co. (Germany); U. Morgner, Max-Planck-Institut für Kernphysik (Germany)

- 61230W **Fabrication of multifunctional optical waveguides by capillary-electrophoresis doping technique** [6123-33]
T. Yano, J. Taguchi, H. Segawa, S. Shibata, Tokyo Institute of Technology (Japan)
- 61230X **All optical broadband steering by phase angle controlled stationary element (PACSE) mirrors** [6123-34]
D. V. Tsu, R. O. Miller, D. Strand, Energy Conversion Devices (USA)

SESSION 8 NOVEL DEVICES AND APPLICATIONS II

- 61230Y **Photonic crystal waveguide-based dispersion compensators (Invited Paper)** [6123-35]
M. Kamp, J. Zimmermann, Univ. Würzburg (Germany); S. Anand, Kungliga Tekniska Högskolan (Sweden); R. März, Infineon Technologies AG (Germany); A. W. Forchel, Univ. Würzburg (Germany)
- 61230Z **Fabrication and characterization of AlGaAs/GaAs multiquantum well ring lasers** [6123-36]
B. Miao, S. Shi, J. Murakowski, C. Chen, D. W. Prather, Univ. of Delaware (USA)
- 612311 **Net gain demonstration with glass hybrid optical amplifiers made by ion-exchange and wafer bonding** [6123-38]
F. Gardillou, J.-E. Broquin, Institut de Microélectronique, Electromagnétisme et Photonique, ENSERG (France)
- 612312 **Design, fabrication, and characterization of 3D photonic crystals constructed from low-index polymers (Invited Paper)** [6123-39]
D. W. Prather, Univ. of Delaware (USA); A. Sharkawy, P. Yao, S. Shi, E. Kelmelis, EM Photonics Inc. (USA)

SESSION 9 INTEGRATION TECHNOLOGIES

- 612313 **Integration of plastic waveguide lasers on film and its application** [6123-41]
Y. Oki, Y. Ogawa, Kyushu Univ. (Japan); K. Yamashita, National Institute of Advanced Industrial Science and Technology (Japan); H. Watanabe, Kyushu Univ. (Japan); M. Miyazaki, National Institute of Advanced Industrial Science and Technology (Japan); M. Maeda, Kurume National College of Technology (Japan)
- 612314 **From magic to technology: materials integration by wafer bonding (Invited Paper)** [6123-42]
V. Dragoi, EV Group (Austria)
- 612315 **Integrated high-Q reflective cavities** [6123-43]
T. W. Mossberg, C. Greiner, D. Iazikov, LightSmyth Technologies, Inc. (USA)
- 612316 **Wafer bonding between InP and Ce:YIG(CeY₂FeO₁₂) using O₂ plasma surface activation for an integrated optical waveguide isolator** [6123-44]
J. W. Roh, Korea Institute of Science and Technology (South Korea) and Yonsei Univ. (South Korea); J. S. Yang, Yonsei Univ. (South Korea); S. H. Ok, D. H. Woo, Y. T. Byun, Y. M. Jhon, Korea Institute of Science and Technology (South Korea); T. Mizumoto, Tokyo Institute of Technology (Japan); W. Y. Lee, Yonsei Univ. (South Korea); S. Lee, Korea Institute of Science and Technology (South Korea)

POSTER SESSION

- 612318 **Long-term stability of polymeric integrated optical components** [6123-47]
W.-Y. Kwong, Consultant (USA)
- 612319 **Proton exchanged waveguides in LiNbO₃: characterization and design methodology**
[6123-48]
J. M. M. Martins de Almeida, Univ. de Trás-os-Montes e Alto Douro (Portugal);
A. M. P. Pereira Leite, Univ. do Porto (Portugal)
- 61231C **Super slim optical pickup for mobile storage device applications** [6123-51]
S.-D. Suh, E. Cho, H. Kim, Y. Nam, J. Sohn, M. Lee, Samsung Advanced Institute of
Technology (South Korea); Y. Jin, Samsung Electro-Mechanics Co., Ltd. (South Korea)
- 61231D **Designing WDM filter on planar holographic Bragg reflectors with iterative layer-peeling
algorithm** [6123-52]
Y. Ouyang, Chinese Military Academy (Taiwan)
- 61231E **Low loss optical interconnects to silicon waveguides** [6123-53]
A. Donval, R. Oron, M. Oron, KiloLambda Technologies Ltd. (Israel); A. N. M. M. Choudhury,
T. R. Stanczyk, D. Richardson, Molex Inc. (USA)

Author Index

Press-patterned UV-curable high refractive index coatings

Robert Morford, Wu-Sheng Shih, JoElle Dachsteiner
Brewer Science, Inc., 2401 Brewer Dr., Rolla, MO 65401 USA

ABSTRACT

The research and development of organic materials for use in optical components and devices aims to take advantage of several unique properties of these materials, including their stability, tailorability, and flexibility. In this study, by carefully controlling the components, we have developed a material that offers significant advantages over common optical materials. Specifically, the new material has a high refractive index and is curable with ultraviolet (UV) light, solvent free, and transparent over a wide wavelength range. We applied the material to a substrate via spin coating, although other application methods are possible.

The production of optical components through press-patterning has received a large amount of attention. The low cost of replication and high throughput of the process provide the potential for low-cost optical components. Typically a metallic plate is patterned via electroplating or electroforming to produce a negative image on the plate. This plate is then pressed into the patternable material and subsequently treated to form the desired pattern in the organic material. Here we report our initial attempts at press-patterning structures into a UV-curable high refractive index material.

Keywords: High refractive index, UV curable, press-patterning, optoelectronic

1. INTRODUCTION

Recently, great effort has been focused on developing novel and efficient optoelectronic devices [1-4]. These devices will provide the foundation for advanced technologies that will eventually be brought to the marketplace to improve our way of life. Brewer Science, Inc., applies its extensive expertise to developing materials, processes, and machines for the advancement of the microelectronics [5-8] and optoelectronics [9-14] industries by providing full-service solutions to our customers' needs.

Development efforts have focused on the use of organic materials in optoelectronic devices because of the flexibility, toughness, and tailorability of these materials [1-4]. Until recently [11], most organic materials have had reduced refractive indices and have been cured using thermal methods. Increasing the refractive index of the organic materials and utilizing a UV curing mechanism hold several advantages, including minimal shrinkage during curing, the ability to cure at room temperature, no emission of by-products, and more efficient devices.

To fully realize the materials' potential, Brewer Science has been developing processes and machines to provide enabling solutions for device manufacturing. CON-TACT[®] planarization technology has been introduced with thermal- and photo-processing capability [15-17] within a machine. The CON-TACT[®] machine has demonstrated the capability to planarize topographic surfaces using processes that include heat and UV light [15-16]. The versatility of this technology allows the sub-micron patterns to be generated by press-patterning using a thermal process [13] as well as a light process [17]. In contrast to a step-and-repeat process, CON-TACT[®] technology processes the entire substrate surface in one step. It is a wafer-level processing technology.

In the past, we have reported the development of enabling high refractive index materials, processes, and machines useful for the generation of structures in these materials [9-14]. Our efforts have involved three different chemistries, or series of chemistries, which have been briefly summarized elsewhere [14]. Previously, we have reported the generation of patterns in our "B-Series" of materials in another article [13]. Pattern generation in the "A-Series" will be described in a subsequent publication. Here we report the generation of patterns/structures in one of our "C-Series" materials, which are solvent-free, UV-curable, high refractive index materials.

2. EXPERIMENTAL

The photocurable resin solution was prepared by mechanical agitation of the appropriate resin(s), crosslinker(s), and catalyst (photoacid generator, PAG) at room temperature. The resin and crosslinker were selected according to their viscosities, densities, refractive indices, and transmissions. The PAG utilized was selected based on its absorbance curve and corresponding acid strength.

Traditional spin-coating techniques were used to prepare films of varying thicknesses using a CEE® 100CB spinner/hotplate (Brewer Science, Inc.). The films were spun at speeds between 1000 and 5000 rpm, with an acceleration rate of 4500 rpm/s. Substrates used were 100-mm silicon wafers and 76-mm quartz wafers.

Curing was achieved through the exposure of the film on a substrate to broadband UV radiation using a Canon PLA-501F parallel light mask aligner with xenon lamp. The output of the UV source was $\sim 3.7 \text{ mW/cm}^2$, measured at 365 nm. Typical exposure doses were $1\text{--}2 \text{ J/cm}^2$ (6–13 minutes).

Percent transmission data for the films were obtained by coating a film on quartz, curing the film, and analyzing the film on a Varian Cary 500 Scan UV-Vis-NIR dual beam spectrophotometer. The data are presented as percent transmission for wavelengths from 300–3300 nm. The average scan was 0.1 second, and the data interval was 1 nm. A baseline and zero correction were employed.

The refractive indices and thicknesses were measured on a Metricon 2010 prism coupler, which operated at 401 nm, 632.8 nm, and 780 nm using the prism coupling/single film mode.

Optical constant (n and k) data were obtained from thin films using a J.A. Woollam M2000 variable-angle spectroscopic ellipsometer (M2000 VASE®). The thin film was obtained by diluting the resin solution to 20% solids in cyclopentanone and spin coating a film at 2000 rpm, with 4500 rpm/s ramp rate, for 60 seconds. The film was cured with an exposure dose of 1 J/cm^2 . Data were collected from 190 nm to 1000 nm.

The thermal processes for creating a pattern-bearing template and press-patterning high refractive index materials on substrates have been disclosed in a previous paper [13]. Instead of using a thermal process, the CON-TACT® machine equipped with UV capability was used for this work to press-pattern the UV-curable materials. UV radiation was illuminated through the optically transparent plate that bears an optically flat surface as illustrated in earlier publications [13, 15].

A 300-mm SKW 7-2 test wafer (from SKW Associates, Inc.), with various line width and pitch sizes and with a step height of about 900 nm, was used to prepare the pattern-bearing template. The template was installed in the CON TACT® machine for press-patterning processing. This template was used to process all the wafers reported in this work. The material was spin-coated on 100-mm silicon wafers at 5000 rpm for 60 seconds with an acceleration of 4500 rpm/s using a CEE® CB100 spin coater. The wafer was placed into the CON-TACT® machine with pre-determined parameters. Three press-patterning times, 30, 60, and 120 seconds, were used. The press-patterned wafer surface was then cured using UV light. Once the process was completed, the wafer was removed from the machine and characterized.

The SKW 7-2 wafer and the patterned wafer surfaces were characterized using a Dektak 8 stylus profilometer (from Veeco Instruments) for step height measurement. Cross-section scanning electron microscopy (SEM) using a Leo 1560 microscope was performed on the wafer pressed for 120 seconds to verify the step height and film thickness.

3. RESULTS

3.1 Material characterization

3.1.1 Spin speed curves

Once the resin solution was prepared according to the procedure in the experimental section, the material was applied on various substrates using spin coating to create the films. Through variation of the spin speeds and identical curing parameters, different thicknesses of films were obtained as shown in Figure 1.

3.1.2 Refractive index measurements obtained through use of a prism coupler

The films of the material generated by varying the spin speeds during spin coating were measured on a prism coupler to determine the refractive index of each film. Through these measurements, extrapolated refractive index curves were generated, as detailed in Figure 2.

3.1.3 Optical constant data generated through VASE measurements

A portion of the material was diluted as indicated in the experimental section to accommodate VASE measurements. The optical constants for the thinner film are shown in Figure 3.

3.1.4 Transmission data for a film on quartz

A film of the material was generated on a quartz wafer so that the transmission spectrum could be determined. The results from this measurement are shown in Figure 4.

3.1.5 Refractive index data for different irradiation doses

Three films of identical thickness were generated using the same spin speed parameters. The films were subjected to different doses of UV radiation and analyzed on the prism coupler. The extrapolated refractive index curves for the three films are shown in Figure 5.

3.2 Pattern characterization

3.2.1 Step height measurements of the SKW 7-2 and press-patterned wafers

The wafers coated with the "C-Series" material were successfully press-patterned. Step heights at various pitch sizes (20 μm , 30 μm , 50 μm , and 100 μm) and feature density areas (10% and 90%) on the SKW 7-2 test wafer were measured. The different pitch sizes also represent different feature density areas as well. The measured step heights ranged from 940 nm to 960 nm, which is within the vendor's step height variation specification. The step heights measured from press-patterned wafers ranged from 900 nm to 940 nm. The scanned step height profiles for a 100- μm pitch area of the SKW 7-2 test wafer and the wafer press-patterned for 120 seconds are shown in Figures 6 and 7. Table I summarizes the step heights measured from the SKW 7-2 and pressed wafers.

3.2.2 Cross-section SEM characterization

Cross-section SEM study revealed the film thicknesses in three areas with different pitch sizes, 50 μm (Figure 8), 10 μm (Figure 9), and 6 μm (Figure 10), were very comparable. Based on the SEM measurements, these three pitch areas also represented three different feature density areas, 55%, 75%, and 93%, respectively. The feature density is defined as the ratio of line width to pitch. Film thicknesses measured from these three pitch areas, within the lines and trenches, are summarized in Table II.

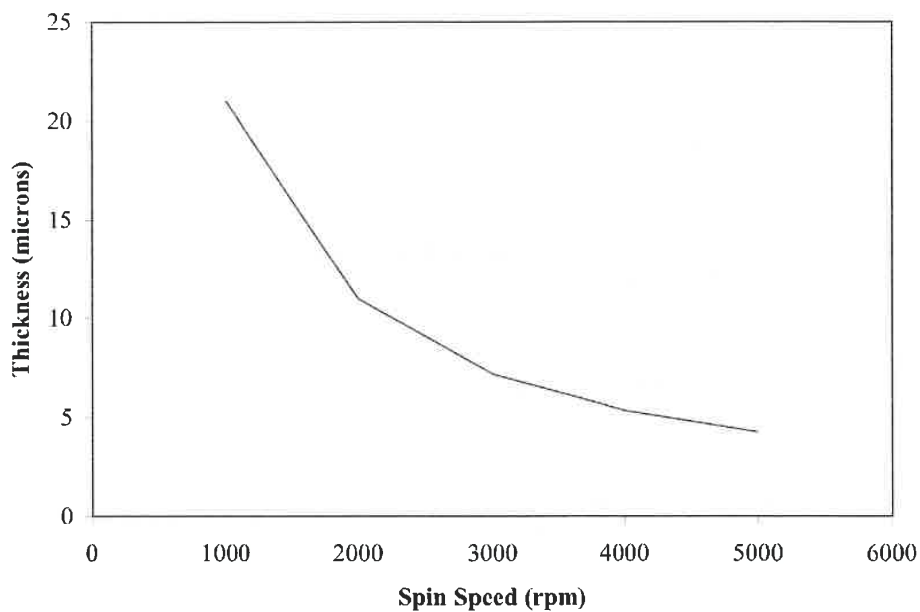


Figure 1. Spin-speed curve for material deposited on silicon wafers.

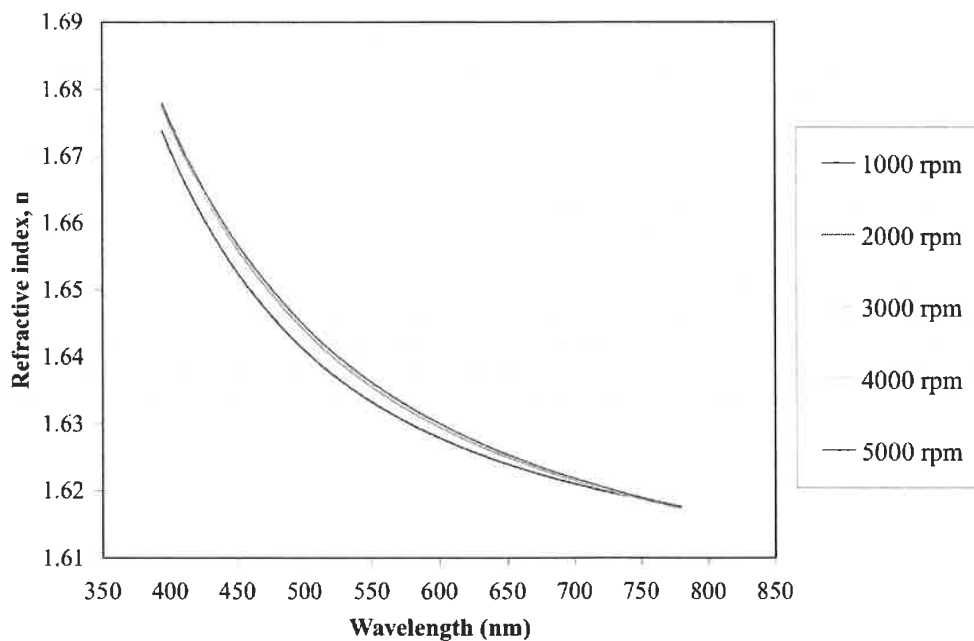


Figure 2. Extrapolated refractive index curves for the cured material coated on silicon wafers at various spin speeds.

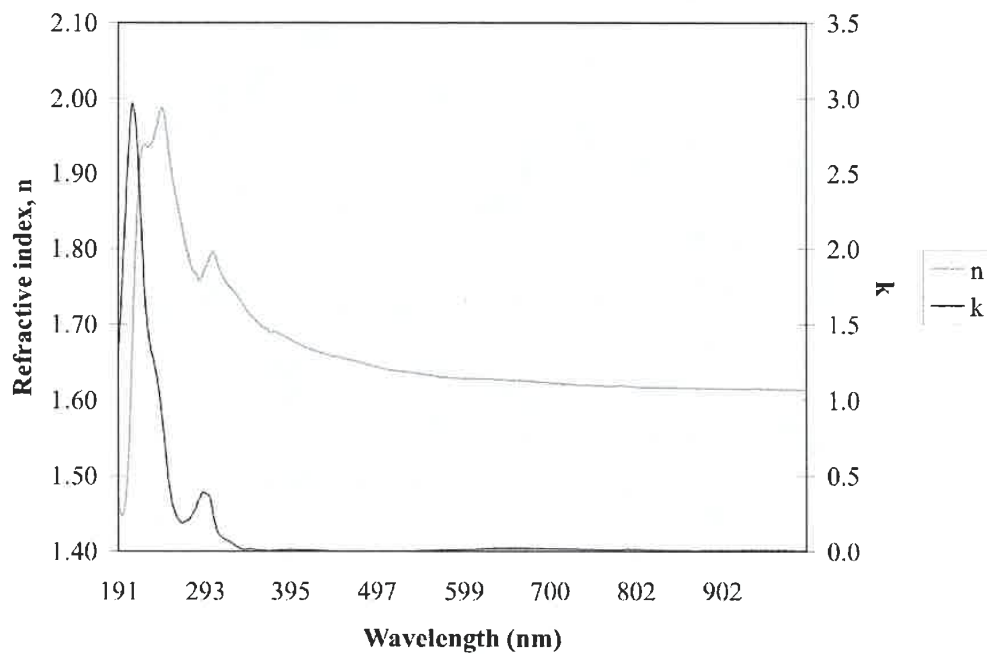


Figure 3. Refractive index and extinction coefficient data for a cured thin film.

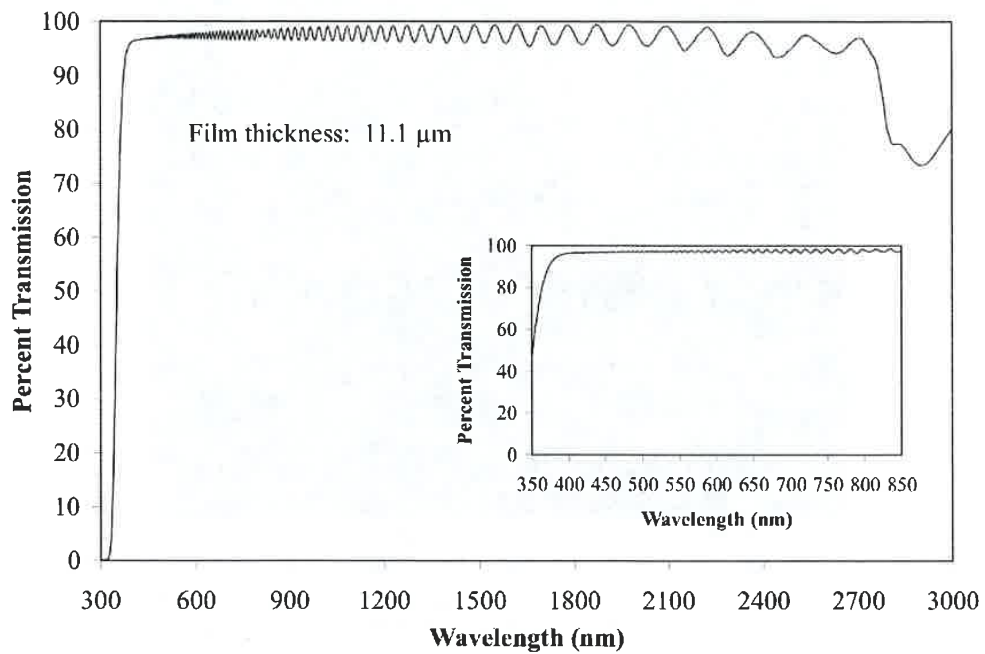


Figure 4. Percent transmission data for a film coated on a quartz wafer.

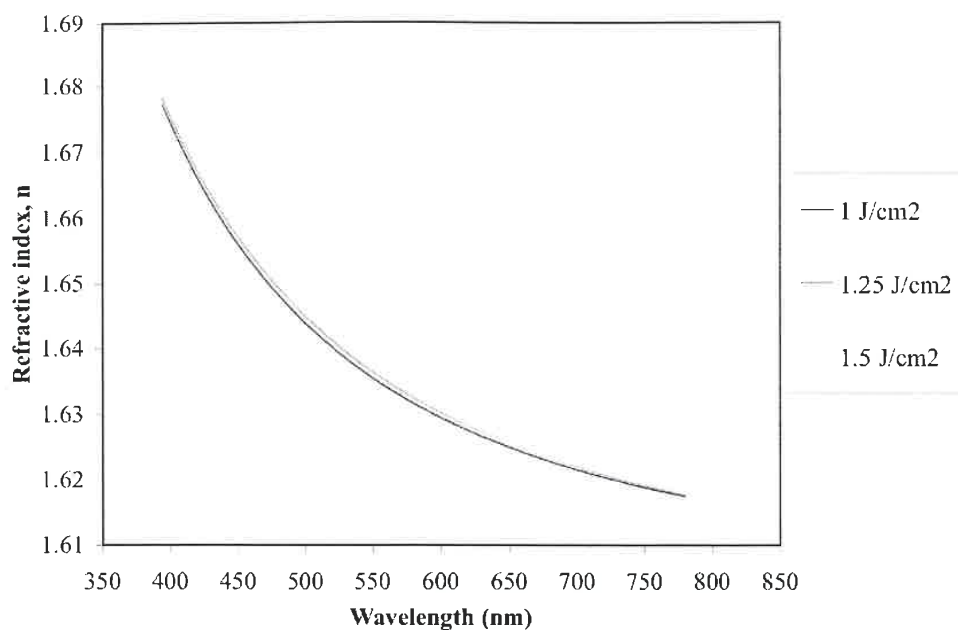


Figure 5. Extrapolated refractive index curves for films coated on silicon wafers cured with different amounts of UV radiation and analyzed on the prism coupler.

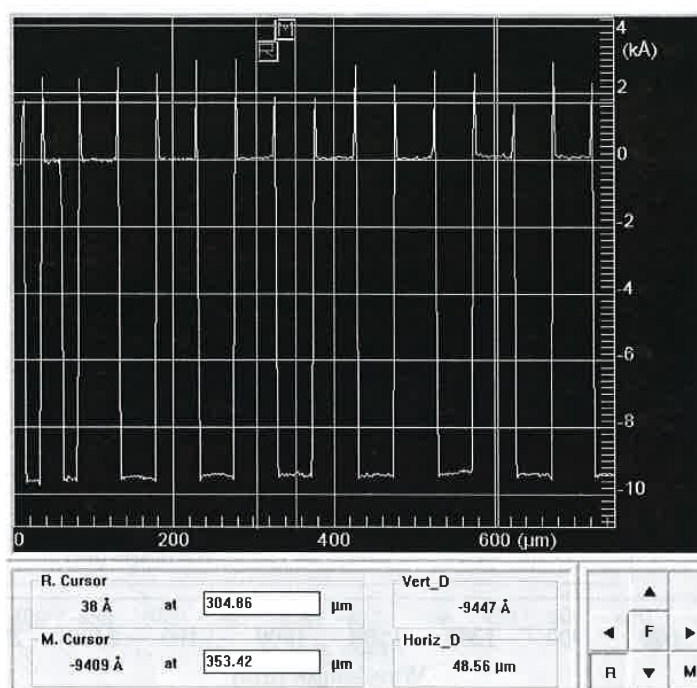


Figure 6. Step height profile of the SKW 7-2 test wafer in a 100-μm pitch size area.

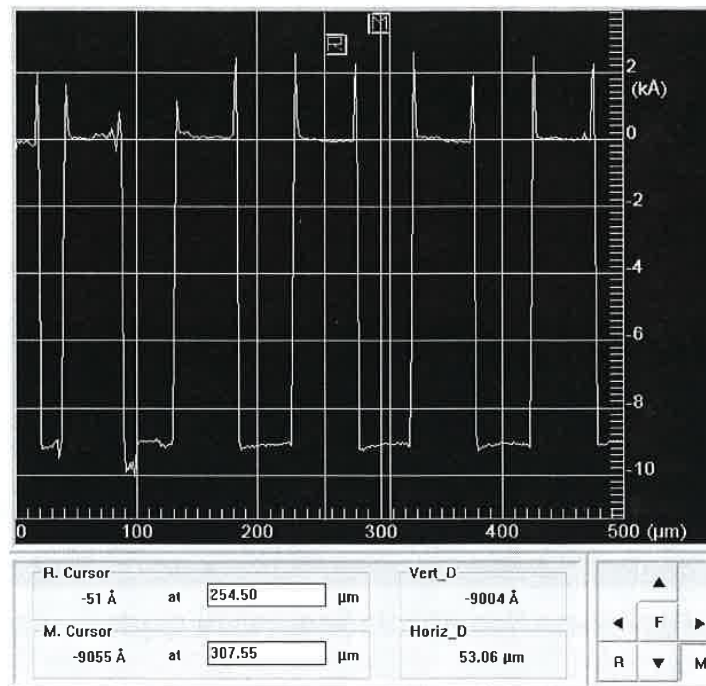


Figure 7. Step height profile of the press-patterned wafer (120 seconds press-patterning time) in a 100- μm pitch size area.

Table I. Step heights of the SKW 7-2 and press-patterned wafers at various pitches and feature density areas.

Pitch/Feature Density Area	SKW 7-2 Wafer Step Height (nm)	Press-Patterned Wafers	
		Press Time (Seconds)	Step Height (nm)
20 μm	956	30	919
		60	928
		120	937
30 μm	950	30	908
		60	910
		120	920
50 μm	947	30	900
		60	897
		120	916
100 μm	945	30	905
		60	902
		120	900
10%	939	30	900
		60	910
		120	926
90%	956	30	924
		60	925
		120	915

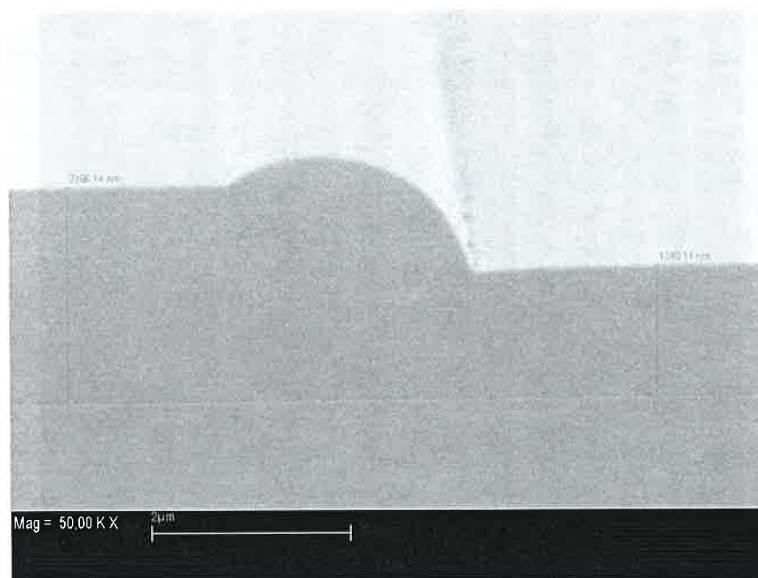


Figure 8. Cross-section SEM micrograph at 50- μ m pitch (~55% feature density) on the wafer press-patterned for 120 seconds.

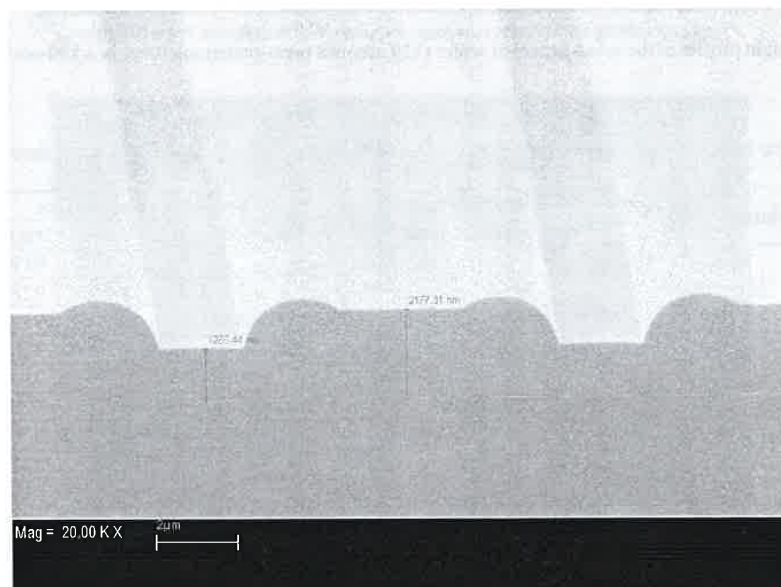


Figure 9. Cross-section SEM micrograph at 10- μ m pitch (~75% feature density) on the wafer press-patterned for 120 seconds.

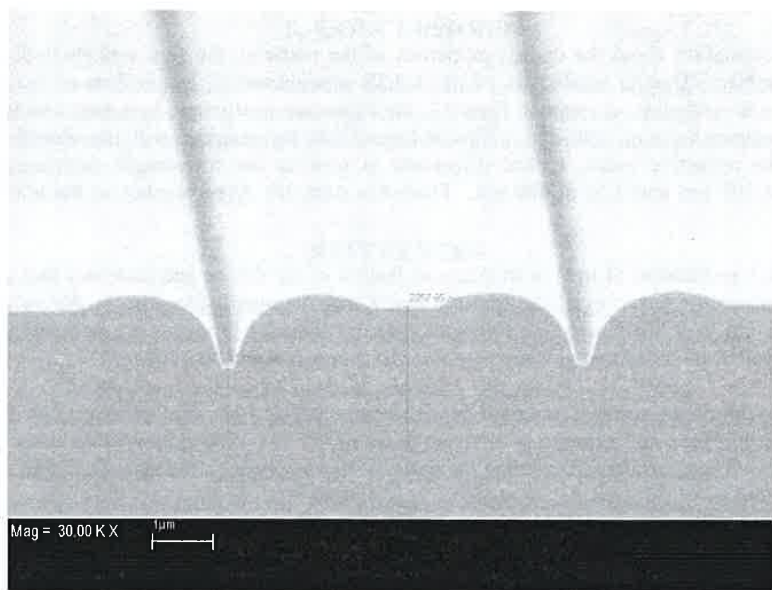


Figure 10. Cross-section SEM micrograph at 6- μ m pitch (~93% feature density) on the wafer press-patterned for 120 seconds.

Table II. Film thickness, within the lines and trenches, at various pitch areas on the wafer press-patterned for 120 seconds.

Pitch	Film Thickness	
	Line	Trench
50 μ m	2.17 μ m	1.31 μ m
10 μ m	2.18 μ m	1.27 μ m
6 μ m	2.26 μ m	1.28 μ m

4. DISCUSSION

4.1 Material characterization

To develop new optoelectronic devices and make current technologies more efficient, high refractive index materials are required. One area that Brewer Science is focusing on is the development of UV-curable, high refractive index materials that have low shrinkage upon curing, can vary in thickness by several orders of magnitude, and are solvent free (or virtually solvent free), free flowing, transparent over a wide wavelength range, fast curing, and physically robust. Through careful selection of the components and their concentrations in the formulations, we can control the viscosity, refractive indices, cure speeds, and thermal properties of the resultant films. Here we detail the properties of a high refractive index, low-viscosity material.

The low-viscosity material used in this study gives significantly thinner films than we reported previously [11]. The spin-speed curve for the current formulation, as shown in Figure 1, displays typical thicknesses in the range of 5-22 μ m.

An issue with UV-curing systems is that too little radiation can cause insufficient curing. This effect can be exacerbated through variation in film thickness. As seen in Figure 2, the extrapolated refractive index curves for the different spin speeds (and thicknesses) are nearly the same, which indicates that the films are sufficiently cured and display similar optical characteristics.

To obtain detailed information about the optical properties of the material, the film was studied using variable-angle spectroscopic ellipsometry. Due to limitations of the VASE measurements, a thin film of material was generated through dilution of the formulation. As seen in Figure 3, the extinction coefficient, k , is very low (near zero) until well below the visible spectrum (around 290 nm). This indicates that the material will not absorb light in the visible spectrum. As for the refractive index, typical dispersion is seen as the wavelength decreases and has values of approximately 1.62 at 800 nm and 1.68 at 400 nm. From this data, the Abbe number of the material was calculated to be 30.

In optical devices, the transmission of light is an essential feature of the device and materials that comprise the device. Accordingly, the transmission spectrum of the film on quartz was measured. As seen in Figure 4, the film is nearly transparent from 400 nm to 2700 nm, which indicates that the material is useful in applications where the visible spectrum is used, as well as the telecommunications spectrum (near infrared, 800-1600 nm).

In UV-cured systems, thorough curing is essential for environmental and physical stability. As detailed in Figure 5, films having the same thickness and exposed to different doses of UV radiation exhibit remarkably similar extrapolated refractive index curves. These results indicate that the material has received sufficient radiation at the lowest dosage to be considered fully cured.

4.2 Pattern characterization

Figures 6 and 7 indicate that the structures of the SKW 7-2 wafer were successfully duplicated on the press-patterned wafers coated with "C-Series" material. Nearly identical results were observed from wafers processed with different press-patterning times. Step height measurements, from different pitch size and feature density areas on all the processed wafers, indicated little ($\leq 6\%$) step height reduction on the pressed-patterned wafer when compared to that of the original step height measured from the SKW 7-2 wafer (Table I). The step height scanned profiles from Figure 6 further indicated that the original SKW 7-2 structures possessed overhang on the line edge, about 0.2 μm in height. This overhang was duplicated onto the press-patterned wafers (Figure 7). Further study using a microscope verified this finding.

It is suspected that the slightly decreased step height, compared to that of the SKW 7-2 wafer, could be due to number of factors, including variation introduced during the pattern generation process in the template and press-patterning and curing the of the "C-Series" material. These factors are influenced by the template material strength and wetting property of the "C-Series" material while it makes contact with the template surface. In addition, material shrinkage during template production and photocuring of the "C-Series" material could also contribute to the variation as well. A more in-depth study is required to verify the causes of step height decrease.

Cross-section SEM characterization shows an important fact that the film thickness stays nearly identical among the pitch size areas characterized (Figures 8 through 10). Film thickness measurements are summarized in Table II. This finding is critical to press-patterning. To press-pattern a low feature density area (fewer and/or thinner line structures), a large amount of material needs to be displaced to higher feature density areas in order to maintain good thickness uniformity. These three pitch areas also represent three feature density areas. A line thickness difference of less than 0.1 μm and a trench thickness difference of less than 0.05 μm were observed among the areas characterized. According to these measurements, a step height of about 900 nm, comparable to those obtained from the Dektak 8 stylus profilometer, was verified using SEM.

Different feature density structures surround these three SEM-characterized pitch areas [18]. The insignificant film thickness variation (Table II) indicates that CON-TACT[®] technology is capable of press-patterning structures with uniform film thickness. More thorough film thickness studies across the die and wafer, and from wafer to wafer, are warranted to better characterize the performance of press-patterning the "C-series" materials using CON-TACT[®] technology.

5. CONCLUSIONS

We have developed a novel transparent, UV-curable, solvent-free composition with a high refractive index. This material may be applied to substrates using spin coating, although other methods are possible. Pattern generation in the film was demonstrated by using a press-patterning technique that indicated reliable, regular structures could be easily replicated from a master film.

REFERENCES

1. J. Wilson and J. Hawkes, *Optoelectronics: An Introduction*, Prentice-Hall, Inc., 1998.
2. D. Wise, G. Wnek, D. Trantolo, T. Cooper, J. Gresser, eds., *Photonic Polymer Systems*, Marcel Dekker: New York, 1998.
3. C. Wong, *Polymers for Electronic & Photonic Application*, Academic Press, 1992.
4. K. Horie, H. Ushiki, F. Winnik, eds., *Molecular Photonics: Fundamentals and Practical Aspects*, Wiley-VCH, 2000.
5. J. Claypool, M. Weimer, V. Krishnamurthy, W. Gehoel, K. van Ingen Schenau, "New advanced BARC materials for ultra-high NA applications," *Proceedings of SPIE: Advances in Resist Technology and Processing XXII*, vol. 5753, 2005, pp. 679-689.
6. K. Ruben, T. Flaim, C. Li, "Polymeric Protective Coatings for MEMS Wet-Etch Processes," *Proceedings of SPIE: Micromachining and Microfabrication Process Technology IX*, vol. 5342, 2004, pp. 212-220.
7. N. Brakensiek, P. Zhang, D. King, C. Ghelli, "Advanced rinse process alternatives for reduction of photolithography development cycle defects," *Proceedings of SPIE: Advances in Resist Technology and Processing XXII*, vol. 5753, 2005, pp. 241-251.
8. <http://www.brewerscience.com/cee/index.html>.
9. T. Flaim, Y. Wang, R. Mercado, "High Refractive Index Polymer Coatings for Optoelectronics Applications," *Proceedings of SPIE: Optical Systems Design 2003*, vol. 5250, 2003, pp. 423-434.
10. R. Mercado, Y. Wang, T. Flaim, W. DiMenna, U. Senapati, "Thin-film polyetherimides with controlled refractive indices," *Proceedings of SPIE: Organic Photonic Materials and Devices VI*, vol. 5351, 2004, pp. 276-283.
11. R. Morford, R. Mercado, C. Planje, T. Flaim, "High refractive index photocurable resins," *Proceedings of SPIE: Organic Photonic Materials and Devices VII*, vol. 5724, 2005, pp. 34-41.
12. Y. Wang, T. Flaim, R. Mercado, S. Fowler, D. Holmes, C. Planje, "Hybrid high refractive index polymer coatings," *Proceedings of SPIE: Organic Photonic Materials and Devices VII*, vol. 5724, 2005, pp. 42-49.
13. R. Mercado, R. Rich, W.-S. Shih, U. Senapati, D. Holmes, "Press-patterned diffraction gratings on high refractive index polyimide films," *Proceedings of SPIE: Integrated Optics: Devices, Materials, and Technologies IX*, vol. 5728, 2005, pp. 227-236.
14. R. Morford, D. Holmes, C. Planje, G. Brand, Z. Zhu, A. Jacobs, "High refractive index polymer coatings," *Proceedings of the 14th International Conference on Polymer Optical Fiber*, Boston, MA: Information Gatekeepers, Inc., 2005, pp. 65-69.
15. W.-S. Shih, M. Daffron, "A Novel Process for Providing Global Planarity for IC Manufacturing," *Proceedings of IMAPS 2003: International Symposium on Microelectronics*, 2003, pp. 813-818.
16. W.-S. Shih, C. Neef, M. Daffron, "A Planarization Process for Multi Layer Lithography Applications," *Proceedings of SPIE: Advances in Resist Technology and Processing XXI*, Vol. 5376, 2004, pp. 664-672.
17. W.-S. Shih, J. Lamb, M. Daffron, "Pattern Structure Reproduction Using Nonsticking Mold," U.S. Patent Application No. 20030071016, April 2003.
18. 300mm SKW7-2 wafer die layout, www.testwafer.com.

ACKNOWLEDGMENT

This work was partially supported by an award from the U.S. Department of Defense Missile Defense Agency under contract number DASG60-01-C-0047.