

Pichler Karl (ITC)

From: Pichler Karl (ITC)
Sent: Thursday, February 08, 2001 4:28 PM
To: Frischknecht Kyle (ITC)
Cc: Proulx George (ITC); Pakbaz Hash (ITC)
Subject: RE: Meeting with Dr. John Affinito

Hi Kyle,

YES, I believe there may be a combination technique with spin-coating that I believe should work (also discussed at FED and I have been considering filing a patent for a long time - lack of time). Spin-, roll- or whatever-coat, cross-link/cure and then sputter the dielectric barrier through a mask over the OLED area only, i.e. leave the contact pads, scribe lines, etc. free from the barrier and then stick the whole thing in, for example, a plasma asher and ash-off the organic where there is no dielectric barrier film. I have a patent from CDT-time (for a completely different purpose) that shows that just a few (say around 10 or more Angstroms) of good sputtered dielectric (e.g. AlOx) act as a perfectly good oxygen plasma ash barrier. Alternatively, I have been thinking if we could deposit the organic liquid layer (via flash-evaporation, spin- or roll-coat or whatever) and then do the UV cross-linking through a mask. The idea is that after this we may be able (don't know if this will work, never tried) to thermally evaporate or somehow spray/wash off the non-cross-linked molecular organic film and then sputter the dielectric also through a mask or alternatively make the contacts first and then sputter the dielectric. In addition, the non-cross-linked organic may be volatile enough so laser ablation becomes perfectly feasible - not sure. This may also have the advantage that the mask-cross-linking should provide a smooth transition from the regions with to those without the organic layer (instead of a sharper step).

These are all just 'undeveloped' ideas without really having thought through them in detail to spot serious bottlenecks and certainly I have not done any practical trials whatsoever (other than the thin oxide as ash barrier).

Just a note: the reason why I was originally thinking of spinning the layer was that this could very easily be added on to e.g. a Satella via a separate spin-chamber without the need to custom-build a flash-evaporator for the organic.

I am looking forward to keep this discussion rolling.
Charlie

-----Original Message-----

From: Frischknecht Kyle (ITC)
Sent: Thursday, February 08, 2001 11:26 PM
To: Pichler Karl (ITC)
Cc: Proulx George (ITC)
Subject: RE: Meeting with Dr. John Affinito

Hi Charlie:

I have also previously considered spin coating the acrylate layer; however, I haven't yet thought up a reasonable method for keeping the electrical pins free of the coating. Performing a subsequent laser ablation seems less than optimum. I anticipate that vapor deposition through a shadow mask will keep the pins free of the coating; therefore, I have been quite partial to the vapor deposition method. Also, I am not too sure if scribing through the multilayer is a good idea; therefore, I anticipate that masking the area for the scribe lines will be a good practice. Obviously, photolithography after cathode deposition (for a "lift-off" technique) doesn't look very promising. Although there will certainly be many equipment issues with PML, it very well may be that vapor deposition through a shadow mask is the easiest method for producing an array of small displays on a large plate of glass. If you are really opposed to the vapor/mask method, I guess we could consider printing techniques (Screen/Inkjet), but when you get down to the details, these methods will have their respective equipment issues as well. Any thoughts on masking for spin coating?

Kyle

-----Original Message-----

From: Pichler Karl (ITC)
Sent: Thursday, February 08, 2001 1:28 AM
To: Proulx George (ITC); 'Guenther Ewald'; Antoniadis Homer (ITC); Pakbaz Hash (ITC); Frischknecht Kyle (ITC); Larson Otto (ITC); Allemand Pierre-Marc (ITC); Cumpston Brian (ITC); 'ZT - Wittmann Georg'; 'ZT - Stoessel Matthias'
Subject: RE: Meeting with Dr. John Affinito

Hi all,

Just a small and CONFIDENTIAL point to be aware of in the future should we need it:

While working with PML encapsulation at FED (eMagin) I and others there discussed and stressed that LML, i.e. spinning in inert conditions a carefully outgassed cross-linkable solution onto the 8" wafers with subsequent cross-linking and barrier layer sputtering should be perfectly feasible and avoid many equipment issues with PML. I do not know if this was actually tried there after I left and/or if a patent was filed. These discussions happened probably from around mid 1999 onwards.

Charlie

-----Original Message-----

INVENTION DISCLOSURE

Page 1 of

Return this completed form,
with any necessary attachments, to:
SIEMENS CORPORATION
Intellectual Property Department (IPD)
4900 Old Ironsides Drive, M/S 503
Santa Clara, CA 95054
phone +1-732-321-3026
fax +1-732-321-3014

PLEASE KEEP A COPY FOR YOUR RECORDS

THIS SE
Receipt Date Stamp

FOR IPD USE ONLY

Division/Dept Code _____

Cost Center Code _____

Docket No. OLE 18483 US

IP Attorney _____

1. Your Div.'s Project # _____; Invention Title Encapsulation of OLED devices
2. INVENTOR

At the time the invention was conceived, this inventor was
☐ an employee of a German legal entity (e.g. Siemens AG)
☒ an employee of a non-German entity (e.g. Siemens
Automotive Corporation or Siemens Canada Limited)
If you are not sure, contact IPD at +1-732-321-3026

Full Name: Karl PICHLERHome Address [REDACTED]
Santa Clara, CA 95050Citizen of [REDACTED]Soc. Sec. # [REDACTED]

COMPANY/LOCATION INFORMATION

Employer Osram Opto-SemiconductorDivision OLED R&DAddress 3870 North 1st StreetSan Jose, CA 95134Work telephone 408 456 4175Fax 408 456 4305Email karl.pichler@osram-os.com

3. CO-INVENTOR (if any)
(use additional forms for more co-inventors)

At the time the invention was conceived, this inventor was
☐ an employee of a German legal entity (e.g. Siemens AG)
☐ an employee of a non-German entity (e.g. Siemens
Automotive Corporation or Siemens Canada Limited)
If you are not sure, contact IPD at +1-732-321-3026

Full Name _____

Home Address _____

Citizen of _____

Soc. Sec. # _____

COMPANY/LOCATION INFORMATION

Employer _____

Division _____

Address _____

Work telephone _____

Fax _____

Email _____

Signature _____

Date _____

Signature _____

Date _____

4. Purpose(s), and likely field(s) of use of this invention Encapsulation of OLED devices

5. Is this invention still secret within Siemens? YES ☒ NO ☐

Do you soon plan to make the invention information available outside of Siemens? YES ☐ NO ☒

Based on your answer to Question #5, explain when and how this invention was/will be made available to someone outside of Siemens (e.g. trade show at location/date, customer presentation at company/location/attendees/date, supplier prototyping by company/date, included in product brochure or advertisement in publication/date, industry technical symposium paper presented place/date, etc) _____

6. Where is this invention described? List all documents containing aspects of this invention (e.g. engineer notebook date/page, internal status report, test logs, physical prototypes, customer presentation, etc) Karl Pichler Laboratory Lab Book # 7; pages 7 & 9.

7. What date do you recall creating this invention? Have been 'carrying around' part of the invention for a long time (>1 year); first written description in internal e-mail dated Feb 8, 2001 to Kyle Frischknecht.

When do you recall first explaining this invention to a witness who is not also a co-inventor? Feb 8, 2001; (only part of the invention)

Who was those witness(es)? Kyle Frischknecht et al. (only part of the invention)

Has this invention been prototyped or tested yet? If so, when, where, by who? What were the results? Not tested yet; internally I am certain and outside our company - I am not aware of anybody who tried it and/or any prior art. Important note: I conceived a significant part of this invention, namely ink-jet printing of the UV-curable liquid prior to the dielectric deposition on August 14, 2001 and did not tell anybody about it. I did some prior art searching to check UV-curable liquid ink-jet printing. Only when I sat down to write this invention disclosure and looked up old e-mails (that to Kyle Frischknecht on Feb 8, 2001), I realized that in fact Kyle was thinking about ink-jet (or screen printing) of the PML UV-curable liquid plus other parts of the invention himself also; see attached e-mail conversation.

8. I have ☒ have not ☐ attached _____ number of additional sheets to better describe this invention.

9. Identify all non-Siemens companies that may in the future benefit from the use of this invention through a license. Potentially a huge range of companies, notably all those working in the field of Organic Light-Emitting Devices (OLEDs); current count well over 100 companies worldwide, essentially almost all display manufacturing companies plus several others entering the display manufacturing field as newcomers (US, Japan, Europe, Taiwan, South Korea, China, etc.); anybody seeking to direct-encapsulate OLEDs (see below for further description).

10. Was this invention developed under, or quoted for, a customer contract? YES ☐ NO ☒

Was it developed under a government contract? YES ☐ NO ☒

If yes to either, please give contract name and number, and further explain the situation N/A

IF THE ANSWERS TO ANY OF THESE QUESTIONS CHANGE BEFORE THIS INVENTION IS FILED AS A PATENT APPLICATION WITH THE GOVERNMENT, MAKE SURE TO SEND AN UPDATE TO SIEMENS IPD.

11. WITNESSED AND UNDERSTOOD BY:

Signature _____

Company Name _____

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES

Pictiva EX2029-p. 2

Samsung v Pictiva

IPR2024-01223

+ added here on 14 Oct 01 or later

INVENTION DISCLOSURE

Page 2 of _____

Name _____
Date _____

Company Address _____

**THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES**

Pictiva EX2029-p. 3
Samsung v Pictiva
IPR2024-01223

INSTRUCTION ON HOW TO USE THIS INVENTION DISCLOSURE

General

- PLEASE TYPE OR PRINT CLEARLY. Answer all questions. Use N/A when not applicable.
- Sign and date each page in ink.
Sign and date all attached additional sheets, diagrams, photographs, etc
Please provide all of your given names in full in sections 2 and 3. When there are more than two inventors, use another form and complete and sign items 1, 2, 3 and 10 on the extra forms.
- Every page of the form and accompanying papers should bear the signature of a witness and the date of his/her signing. The witness should have read the forms and attached papers, and should understand the invention before witnessing. The witness should have a technical background related to the invention, to reduce the chances that someone can later challenge his/her ability to have understood the invention.
- A co-inventor should not be the witness. If you have a choice of several qualified witnesses, choose the witness you believe is most likely to still be a Siemens employee available in this country if a question comes up several years from now. That means you should avoid having a co-op student, contract engineer, or a retiring engineer serve as your witness.

Detailed Description

- The description you provide may serve as the basis for a patent application. Therefore, be as complete and as accurate as possible. Attach pages as necessary, using the following checklist as a guide for content.
 - **Abstract:**
In one or two sentences, briefly describe what your invention does and how it is used, e.g., "A voltage-controlled oscillator (VCO) has its period controlled by a current provided by a current source. The current is proportional to the reciprocal of a control signal so that the VCO frequency is directly proportional to the control signal."
 - **Background Information:**
What is the function of your invention?
What is the problem solved by your invention?
How was the function of your invention performed by any prior systems, either a competitor's or ours?
What are the disadvantages of these prior systems?
What are the advantages of your invention over them?
 - **Details:**
Describe in detail the structural and functional operation of your invention. Use drawings and graphs where they would be helpful. Give specific details, not just general information.
Point out things such as what improvements your invention incorporates, or how and why it achieves superior performance (if you know why).
Are there alternative methods or different structural embodiments of your invention?
Can the general idea or technique of your invention be extended to other related fields? How?
Which features are believed to be new?
Describe how you best envision your invention being put to use.

Related Art

Attach a copy (or bibliographic citation) of all publications, patents, etc. that you know about which relate to your invention, and which you think might be important to consider in understanding how your invention differs from prior work.

Potential Licensing Opportunities

Please identify, in relation to item 9, all companies that are not a part of Siemens and may benefit, in the future, from the use of this invention. This will be helpful in identifying potential licensing opportunities for this invention.

REMEMBER TO UPDATE THE IPD IF ANY OF THE INFORMATION YOU PROVIDED CHANGES.

☐ **Yes, I promise I will update the Siemens Intellectual Property Department (IPD) if any of the information I've provided changes**

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL. THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES

**SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE**

Page ____ of ____

ABSTRACT:

A manufacturing method for the direct encapsulation of OLED devices that encapsulates the sensitive active light-emitting OLED area with at least one encapsulation layer directly over and in contact with the OLED layers but which leaves other, non-light-emitting, areas of the display free of said encapsulation layer.\

BACKGROUND:

Presently, OLEDs are typically developed or fabricated on large sheets of glass with several or tens or even in excess of 100 displays per sheet and, once the OLED fabrication on the sheet of glass is finished, the OLED is encapsulated with a second piece of glass or a metal cap, typically with a cavity between the OLED glass and the encapsulation part; said cavity typically holds a getter materials that absorbs or adsorbs residual oxygen and in particular moisture in the package and oxygen and moisture that penetrate into the display package subsequent to encapsulation, typically done by bonding the two pieces together with an epoxy adhesive. After this process the glass, now encapsulated with getter and a second glass or metal cap, is scribed and broken into the individual displays. This encapsulation process is very difficult to manufacture with high yield and reliability, time-consuming (for example the epoxy glue dispense), is very costly (the getter material and the cover glass or metal cap) and adds to the thickness and weight of the overall display.

To get around these problems, various research groups and companies have been developing so-called 'direct encapsulation' methods. One of these techniques, known as Polymer-Multi-Layer (PML) technology, deposits at least one layer of a UV-curable organic liquid material over the whole display glass, said layer is then UV-cured, followed by the deposition of a barrier layer, e.g. a sputtered metal-oxide or generally a dielectric layer. This process may be repeated, to yield largely impermeable barrier layers and to avoid e.g. external particle/dirt-induced pinholes in said encapsulation layer. The problem with the prior art using these approaches is, that only parts of these displays, essentially the active light-emitting OLED area, must be encapsulated against the ingress of e.g. oxygen and moisture but other parts of the display should be kept exposed, for example the contact pads at which the display is connected to external driver circuitry, power supply, etc. In the PML technology for example, a problem arises with the presence of one or more of the direct-encapsulation layers over areas where encapsulation is not required and/or detrimental, such as over the contact pads.

Alternative techniques known in the prior art are to deposit for example 'Parylene' layer or a polysiloxane layer but these techniques also have the problem as the PML technology described above. Alternatively, a dielectric layer such as SiOx, SiNx, SiOxNy, etc. can be deposited over the OLED for direct encapsulation. This direct dielectric layer encapsulation, in-turn is susceptible to pin-holes and although the deposition (e.g. by sputtering) can be done through masks to block areas over which the encapsulation layer is not desired, this causes additional processing and reliability problems associated with for example the sputter-deposition through masks.

The present invention gets around problems of the prior art by providing processes for an improved direct-encapsulation of OLED devices.

DESCRIPTION OF THE INVENTION:

GENERAL (for all aspects of the invention and embodiments that follow below):

OLED can be typical OLED made on piece of glass with first ITO as first electrode (anode), then OLED layers, then top electrode (cathode); bottom-emitting through glass.

Alternatively, the electrodes can be reversed (cathode at bottom and anode at top).

Alternatively, the OLED can be top-emitting (substrate is opaque, emitting through transparent top electrode); both anode top and cathode bottom and reverse can be used.

Can be used with OLEDs on glass, quartz, metal, plastic foils, metal foils, etc.

Inventor's Signature: _____

Witness' Signature: _____

Date: _____

Date: _____

**THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES**

**SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE**

Page ____ of ____

Can be used for active matrix, passive matrix, segmented, alpha-numeric or backlight OLED displays or any combinations thereof or generally any OLED light source or display.

The organic layers used in the invention are generally known in the prior art, e.g. the PML prior art and the UV-curable monomer and monomer mixes (generally UV-curable compositions); could also be Parylene coatings or other organic coatings that can be deposited in any suitable manner on the OLED without damaging it. Generally organic layers that are carefully outgassed to remove oxygen, moisture and any other reactive mobile species that coat the OLED substrate largely conformally. UV-curable materials are widely known in the prior art (see PML patent literature, see UV-curable printing inks in e.g. www.markem.com or www.vanet.hitachi.co.jp, or D. J. Hayes et al, Journal of the SID, Vol 9/1, 2001 or Hue P. Le, The Society for Imaging Sciences and Technology, Vol 42, No1, Jan/Feb 1998).

Note added on Oct 14, 2001: could also be electron-beam or thermal cure epoxy.

The barrier layer of the invention is typically a dielectric such as a SiOx, AlOx, SiNx, AlNx, SiOxNy, ITO, ZnOx, Al-doped ZnOx, etc. – generally any high barrier dielectrics (or conductive oxides).

In cases in which the fabricated display is bottom-emitting (through the substrate) and the encapsulation does not have to be transparent, metal films or non-transparent or colored dielectric films can be used as the barrier layer.

The deposition of the barrier layer can be any suitable method known in the prior art to deposit dielectric layers, e.g. sputtering or reactive sputtering (DC, AC, pulsed, combinations thereof, etc.). Evaporation of such dielectrics (resistive heating or electron-beam) or metal films is possible also and so are ion-beam assisted deposition methods or other plasma-enhanced deposition methods.

→ DIELEC LAYERS ARE NOT SCREEN OR INK JET PRINTER

CLAIMS (aspects of the invention, embodiments; please note that for all of the below-mentioned it is understood that there can be several sequences (multi-layers) of organic + barrier layer):

1. A process for directly encapsulating a multitude of OLED devices fabricated on an undeviated substrate sheet (can be foil) by putting the encapsulation layer directly (in contact with) on the top-most layer of the to-be encapsulated OLED displays and by using a combination of at least one organic layer and at least one inorganic barrier layer whereby said organic layer is deposited / condensed on the OLED substrate in the form of an unpatterned liquid film; whereby: the unpatterned liquid film is cross-linked in a patterned manner, non-cross-linked areas are subsequently removed, followed by the deposition, in a patterned manner, of a barrier layer over at least part of the layer covered with the cross-linked organic layer.
2. As claim 1 whereby flash evaporation is used to deposit the organic layer (as in PML technology of the prior art).
3. As claim 1 whereby dip-, roll-, blade-coating is used to deposit the organic layer.
4. As claim 1 whereby spin-coating is used to deposit the organic layer.
5. As claim 1 whereby evaporation is used to deposit the organic layer.
6. As claim 1 whereby cross-linking of the organic in a patterned manner is achieved by UV flood-exposure through a mask with the mask being less than 5 and preferably less than 1 and better still less than 0.5 mm away from the OLED substrate.
7. As claim 1 whereby cross-linking of the organic in a patterned manner is achieved by selective UV exposure through an optical patterning system such as a projection exposure system.
8. As claim 1 whereby cross-linking of the organic in a patterned manner is achieved by selective UV exposure with a UV-beam scanning system.
9. As claim 1 whereby the non-exposed areas (non-cross-linked) are removed by thermal evaporation (heating the substrate); can be short higher temperature pulse (e.g. by putting the OLED plate onto hotplate).

Inventor's Signature: _____

Witness' Signature: _____

Date: _____

Date: _____

**THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES**

Fig 4,

Octo,

(INVER CLAIM 4)


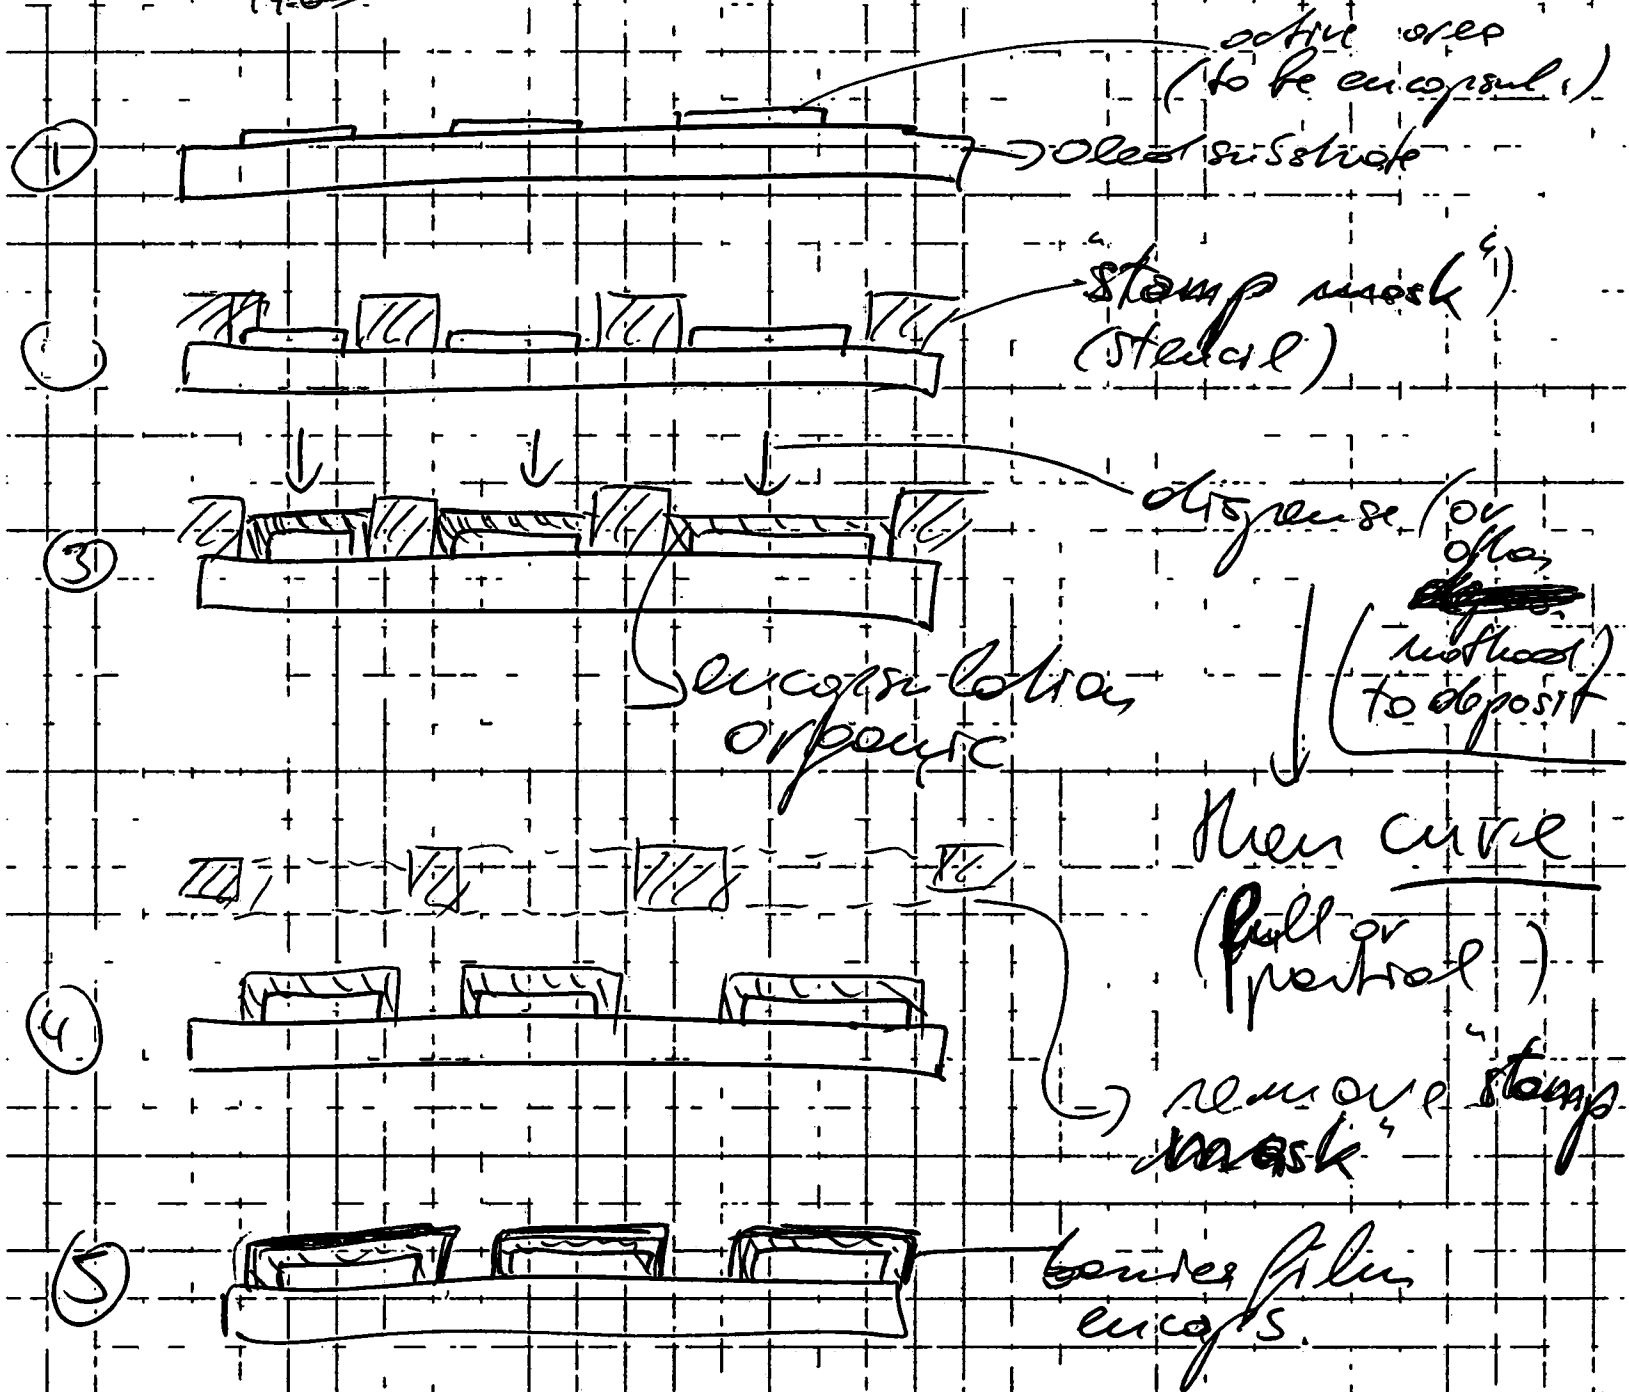


FIG 6 (re CLAIM 4)

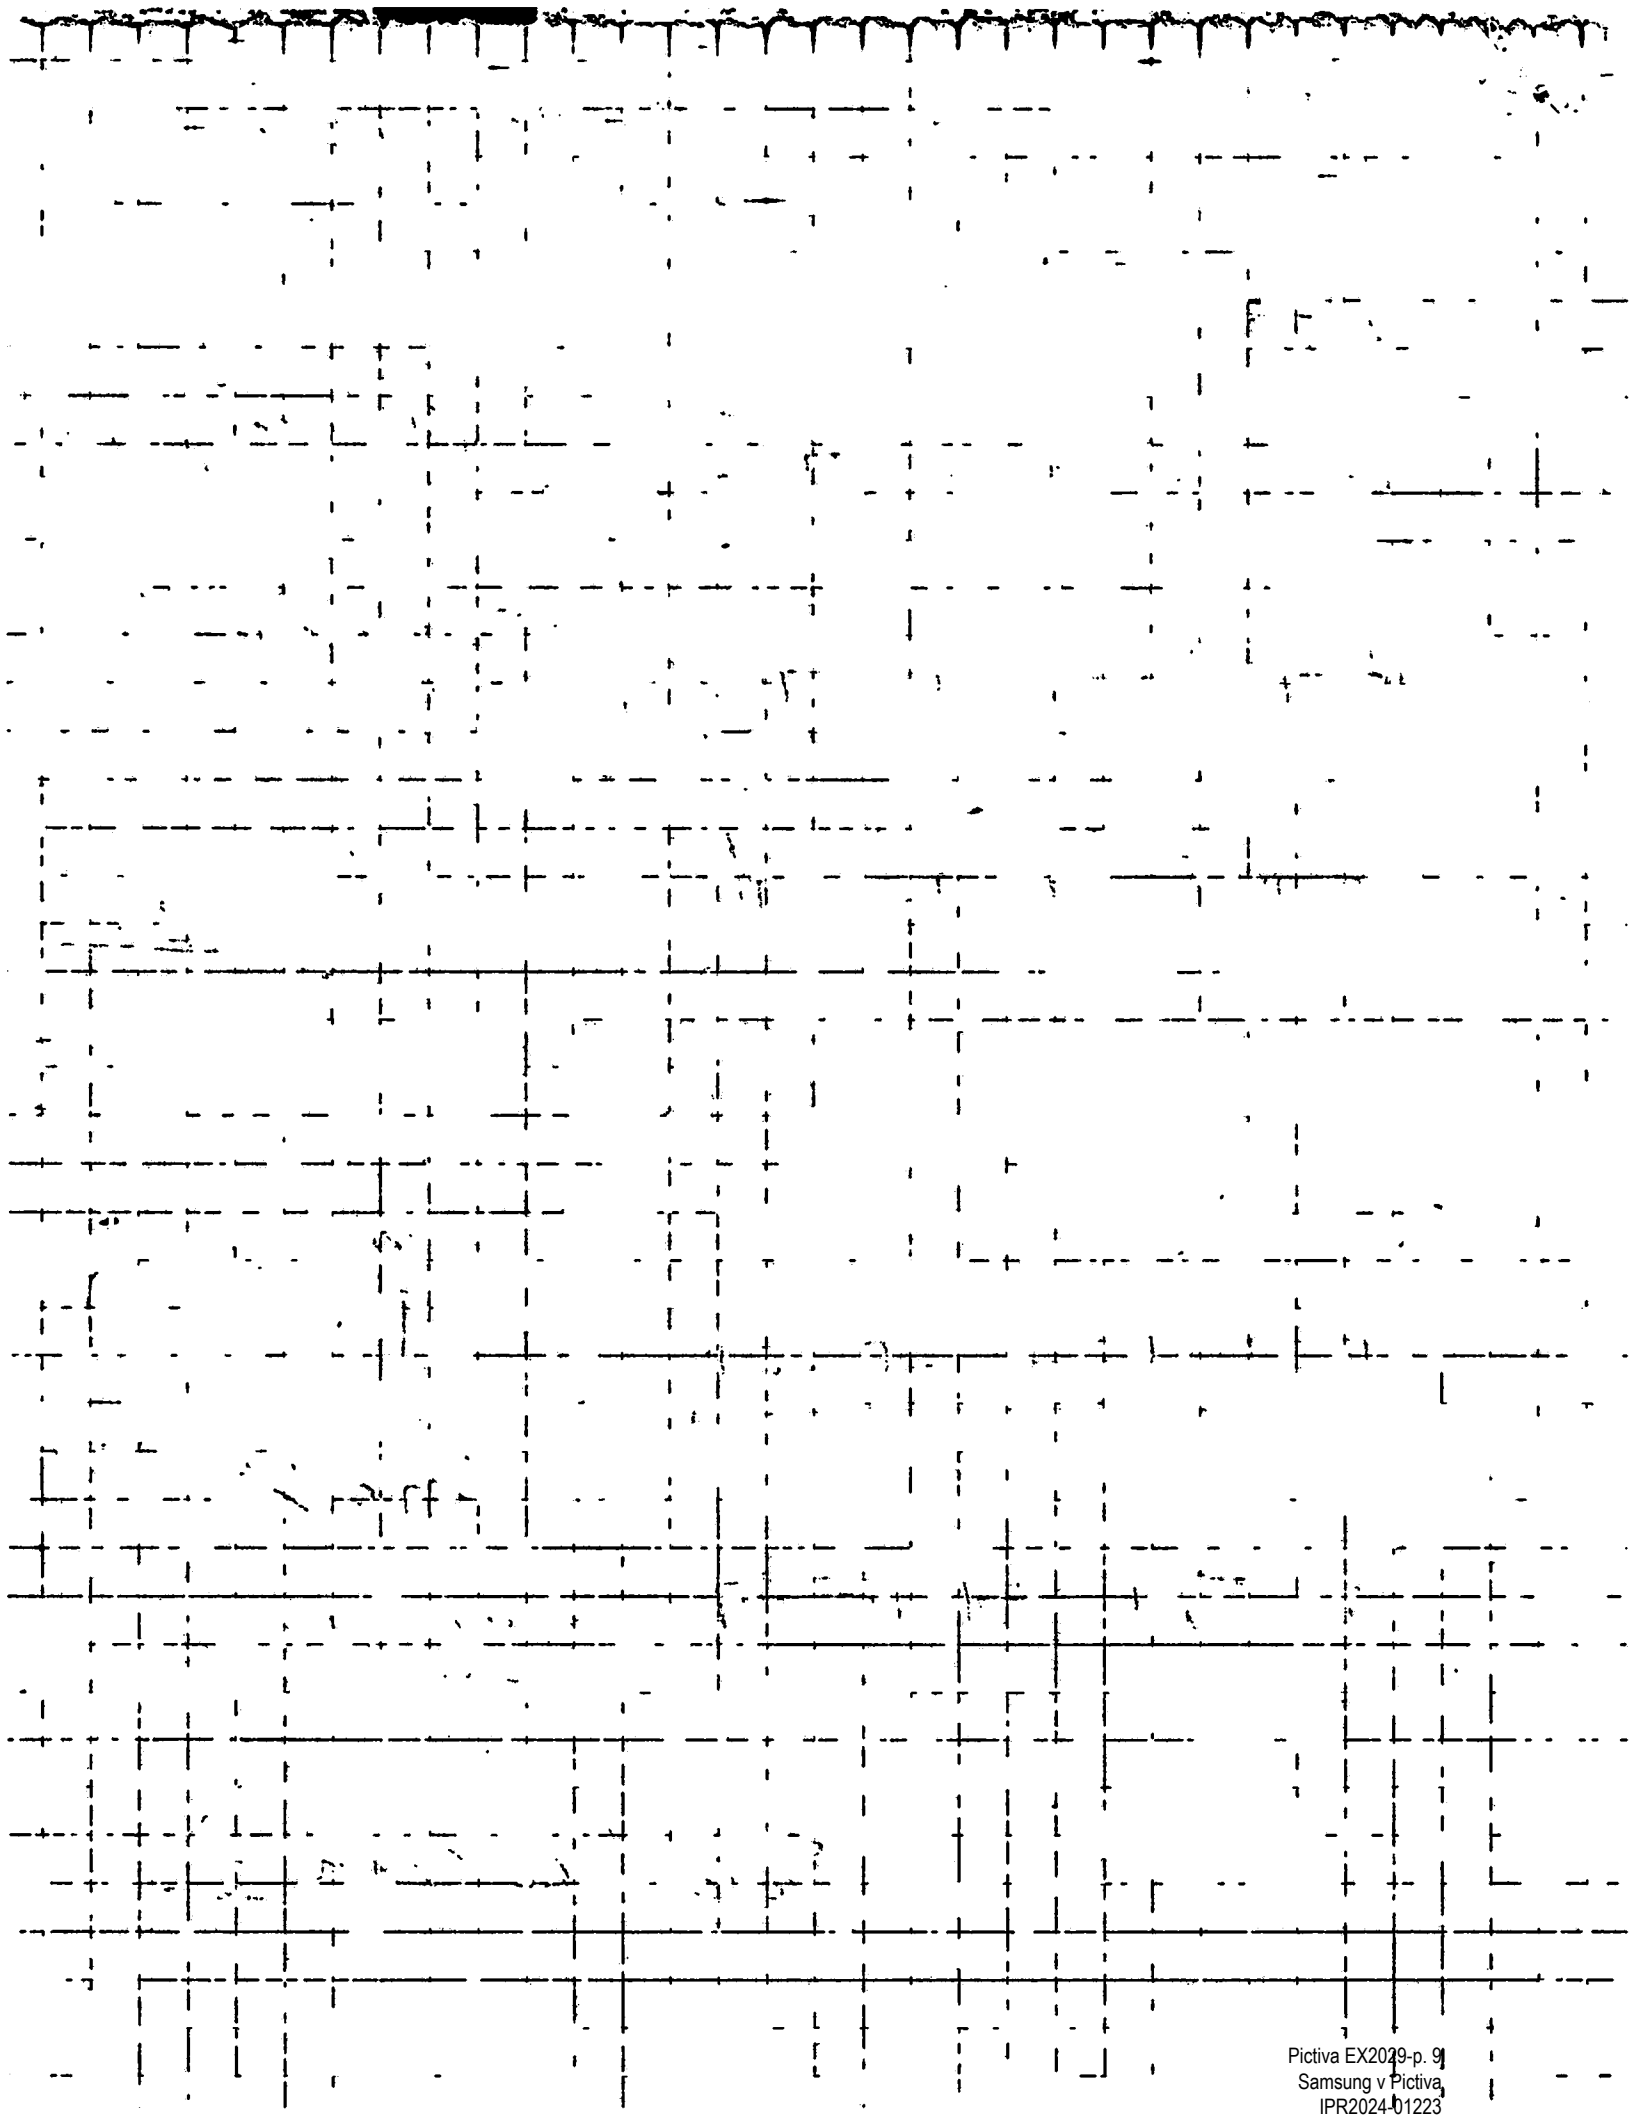

**SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE**

Page ____ of ____

10. As claim 1 whereby the non-exposed areas (non-cross-linked) are removed by pumping in vacuum.
11. Combination of claim 9 and 10.
12. As claim 1 whereby the non-exposed areas (non-cross-linked) are removed by immersion in rinse-tank (washing off), spray-rinsing, ultra-sonicing (dry or wet ultra-sonic), mega-sonic (dry or wet); combination of dry ultra-sonic or mega-sonic in vacuum. Note added on October 14, 2001: should use the word liquid instead of wet.
13. As claim 1 whereby the removal of the non-cross-linked areas of the organic layer is assisted by a plasma process (even if this removes also some of the cross-linked area as long as the rate for the removal of the non-cross-linked material is larger than that for the cross-linked material).
14. As claim 1 whereby the barrier layer (materials and deposition methods see above) is sputtered through a shadow mask over the area of UV-cured organic. Note added on October 14, 2001: maybe we should add: barrier is dielectric; alternative barrier is metal or alloy.
15. As claim 14 whereby the barrier layer is slightly larger in x and y to cover also the edges of the organic layer. Note (for the description of the invention): we should state somewhere that because of optical effects the UV-exposed organic is likely not to have a sharp step (e.g. a round/sloped profile instead) and this is advantageous when depositing the barrier layer on top to assure good side-step coverage.
16. As claim 1 whereby the process is used to encapsulate only the organic light-emissive areas (e.g. pixels) of the display and all contact pads and/or auxiliary encapsulation areas (e.g. for secondary encapsulation) and/or scribe/break areas are left free from the organic layer and the barrier layer.
17. New independent claim: As claim 1 but this time the organic is deposited and cured (if necessary) ALL OVER and only the barrier layer is deposited in a patterned manner, said patterned barrier layer also then acts as an etch stop to remove the organic over unwanted areas (i.e. the areas where the barrier layer is not deposited).
18. For claim 17 we can use all organic layer deposition methods as in claim 1 plus additional ones, namely:
19. As claim 17 whereby evaporation of one or more reactive organic molecules is used to deposit the organic layer, said reactive organic molecules forming a condensed conformal film on the substrate.
20. As claim 17 whereby the methods is as the 'Parylene' coating technology known in the prior art.
21. As claim 17 whereby the organic deposition is a plasma-assisted organic material deposition method.
22. As claim 17 whereby the organic that is subsequently not coated with the barrier is removed by an etching step.
23. As claim 22 whereby the etching is a chemical (dry or wet) etch process suitable to remove the organic.
24. As claim 22 whereby the etching is a plasma-assisted etch process suitable to remove the organic.
25. As claim 22 whereby the etching plasma contains oxygen.
26. As claim 22 whereby reactive ion-etching is used.
27. As claim 22 whereby anisotropic reactive ion-etching is used.
28. New independent claim: As claim 1 and 17 but now the organic itself is already during the deposition (by nature of the deposition process itself) deposited in a patterned manner, then curing of the organic (if necessary as e.g. for the UV-curable organics) then patterned deposition of the barrier, no need to remove e.g. non-UV-cured organic. Note added on October 14, 2001: we need to make sure to write this broad in the sense that any printing technique suitable for printing the organic layer of the invention is used; ink-jet or screen-printing (below) are only preferred.
29. As claim 28 whereby the organic is deposited through a shadow mask using methods as described for claims 1 and 17.

Inventor's Signature: _____

Witness' Signature: _____

Date: _____

Date: _____

**THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES**

**SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE**

Page ____ of ____

30. As claim 28 whereby the organic is printed, in particular using screen-printing or ink-jet printing.
31. Any of the preceeding claims: all encapsulation process steps in inert atmosphere (reduced oxygen, ozone, other reactive gases and in particular moisture.
32. As claim 31 but only the first organic layer + first barrier layer 'dyad' in inert atmosphere.
33. As claim 31 but only the first organic layer in inert atmosphere.
34. Independent claim (?) based on ALL preceeding claims: ... whereby said OLED sheet with the encapsulation of the invention is encapsulated with a secondary encapsulation layer for additional encapsulation and/or mechanical protection.
35. As 34 whereby this is laminating or glueing a plastic or metal or metal+plastic foil or thin glass or thicker (rigid) glass or metal sheet over said OLED display sheet. Note: added on October 1, 2001: with or without a space between the OLED sheet/foil and the cover (= 2nd encapsulation) sheet/foil.
36. Finishing all off by singulation of the display (scribe and break) – may not be necessary.
37. As claims 34 – 36 but where the secondary encapsulation is done after singulation.
- 38.

One such example is shown in figure 1: attach Penang VDOT mask drawing with all layers.

Show barrier over the edge of the display

Material added on October 14, 2001 (see lab book 07, page 12):

This goes on somewhere after the independent claim 28 and its dependent claims and this section could be the basis for another independent claim, namely:

As e.g. claim 28 but instead of directly printing the organic using e.g. screen-printing or ink-jet printing the OLED is covered with a mask which is in direct contact with the OLED and the organic (e.g. the UV cure epoxy) is then dispensed, squashed, rolled, blade coated, dropped into, sprayed onto, etc. the mask openings and then the cure happens; after the cure the mask is removed and the OLED encapsulation (i.e. with the barrier film deposition continues); said mask to confine the organic has openings over the area where the encapsulation on the OLED needs to happen. Said mask could be a film laminated to the OLED or a mask pressed or pushed or clamped etc. to the OLED. The cure of the organic while the mask (to confine the organic) is there could be a multi-step cure, e.g. partial cure, remove the mask and then complete the cure. Said mask could be a multi-use mask or a one-off (e.g. in the case of a lamination) that then gets thrown away. Said mask could be a metal, ceramic or plastic foil or sheet; could in particular be a PTFE (Teflon) or a poly-siloxane-type material (e.g. polydimethylsiloxane such as often used for soft lithography) or generally any material that does not stick to the OLED (too much to cause damage or delaminate OLED material from the OLED glass when the mask is removed) and a material to which the encapsulation organic does not stick to well so that the mask removal after encapsulation organic deposition and cure (complete or partial) does not remove encapsulation organic. but the mask is such that it can be brought in contact with the OLED sufficiently well so that the encapsulation organic is confined over the desired areas and does not seep under the areas where the encapsulation organic is not desired (e.g. contact pads etc.). Said mask is some sort of a 'stamp-mask'. See figure 4 below for a brief description of this concept. This concept is in particular useful for liquid encapsulation organics (see PML).


Inventor's Signature: _____



Witness' Signature: _____

Date: _____

Date: _____

**THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES**

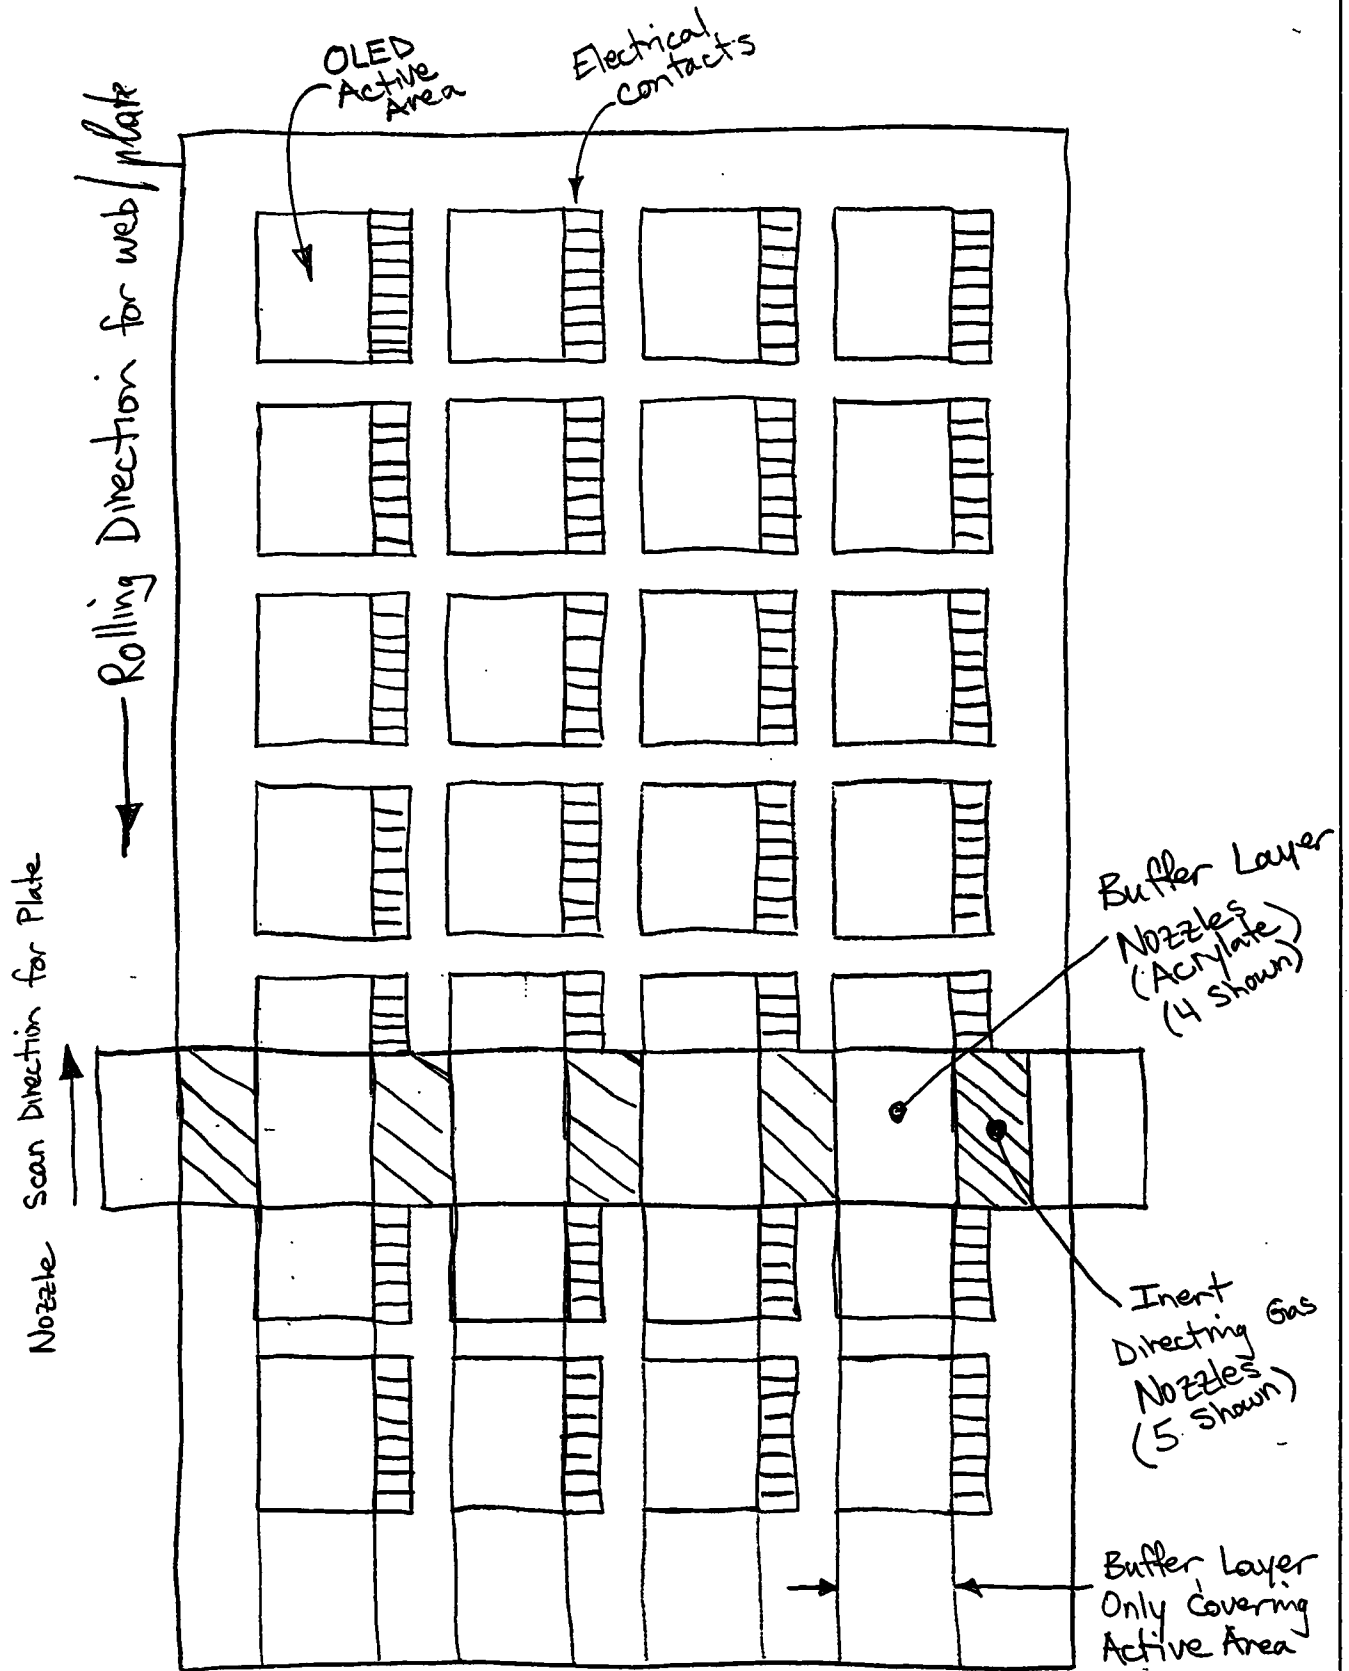

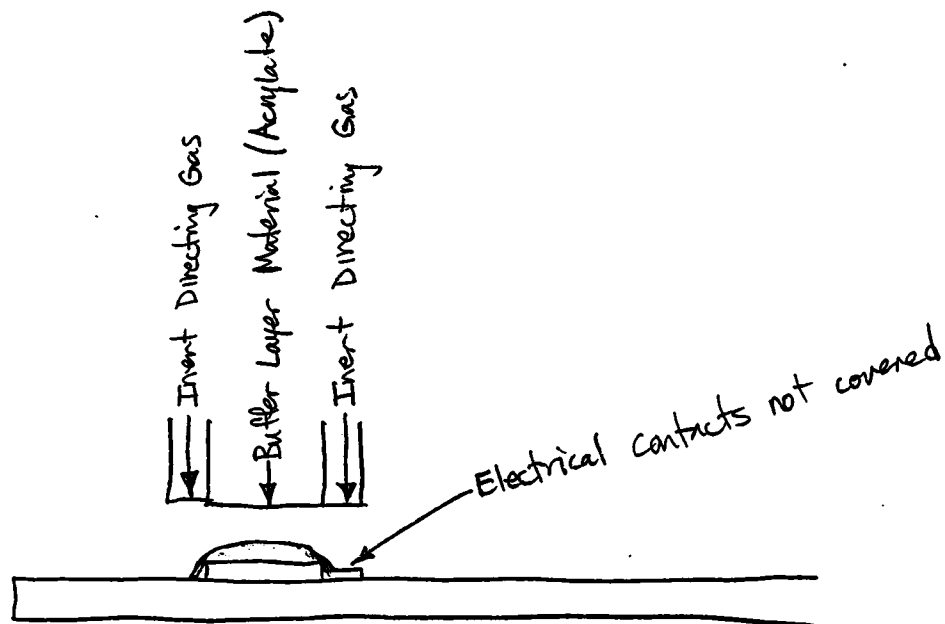

INVENTION DISCLOSURE

Page 1 of 9

Return this completed form, with any necessary attachments, to:
SIEMENS CORPORATION
 Intellectual Property Department (IPD)
 4900 Old Ironsides Drive, M/S 503
 Santa Clara, CA 95054
 phone +1-732-321-3026
 fax +1-732-321-3014
PLEASE KEEP A COPY FOR YOUR RECORDS

THIS SECTION FOR IPD USE ONLY	
Receipt Date Stamp	Division/Dept Code <u>OSRAM Opto Semiconductor</u>
	Cost Center Code <u>8083</u>
RECEIVED	Docket No. <u>2001E1848345</u>
<u>SEP 10 2001</u>	IP Attorney <u>HJG</u>

1. Your Div.'s Project # _____; Invention Title Encapsulation of OLED devices
 2. INVENTOR INTELLECTUAL PROPERTY DEPT WEST COAST

At the time the invention was conceived, this inventor was
☐ an employee of a German legal entity (e.g. Siemens AG)
☒ an employee of a non-German entity (e.g. Siemens Automotive Corporation or Siemens Canada Limited)
 If you are not sure, contact IPD at +1-732-321-3026

Full Name: Karl PICHLER
 Home Address: [REDACTED]
Santa Clara, CA 95050

Citizen of [REDACTED]
 Soc. Sec. # [REDACTED]
COMPANY/LOCATION INFORMATION
 Employer Osram Opto-Semiconductor
 Division OLED R&D
 Address 3870 North 1st Street
San Jose, CA 95134

Work telephone 408 456 4175
 Fax 408 456 4305
 Email karl.pichler@osram-opto.com

Signature [Signature]
 Date 30 Sep 01

At the time the invention was conceived, this inventor was
☐ an employee of a German legal entity (e.g. Siemens AG)
☐ an employee of a non-German entity (e.g. Siemens Automotive Corporation or Siemens Canada Limited)
 If you are not sure, contact IPD at +1-732-321-3026

Full Name _____
 Home Address _____

Citizen of _____
 Soc. Sec. # _____
COMPANY/LOCATION INFORMATION
 Employer _____
 Division _____
 Address _____

Work telephone _____
 Fax _____
 Email _____

Signature _____
 Date _____

4. Purpose(s), and likely field(s) of use of this invention Encapsulation of OLED devices
 5. Is this invention still secret within Siemens? YES ☒ NO ☐
 Do you soon plan to make the invention information available outside of Siemens? YES ☐ NO ☒
 Based on your answer to Question #5, explain when and how this invention was/will be made available to someone outside of Siemens (e.g. trade show at location/date, customer presentation at company/location/attendees/date, supplier prototyping by company/date, included in product brochure or advertisement in publication/date, industry technical symposium paper presented place/date, etc) _____
 6. Where is this invention described? List all documents containing aspects of this invention (e.g. engineer notebook date/page, internal status report, test logs, physical prototypes, customer presentation, etc) Karl Pichler Laboratory Lab Book # 7; pages 7 & 9.
 7. What date do you recall creating this invention? Have been 'carrying around' part of the invention for a long time (>1 year); first written description in internal e-mail dated Feb 8, 2001 to Kyle Frischknecht.
 When do you recall first explaining this invention to a witness who is not also a co-inventor? Feb 8, 2001; (only part of the invention)
 Who was those witness(es)? Kyle Frischknecht et al., (only part of the invention)
 Has this invention been prototyped or tested yet? If so, when, where, by who? What were the results? Not tested yet; internally I am certain and outside our company - I am not aware of anybody who tried it and/or any prior art. Important note: I conceived a significant part of this invention, namely ink-jet printing of the UV-curable liquid prior to the dielectric deposition on August 14, 2001 and did not tell anybody about it. I did some prior art searching to check UV-curable liquid ink-jet printing. Only when I sat down to write this invention disclosure and looked up old e-mails (that to Kyle Frischknecht on Feb 8, 2001), I realized that in fact Kyle was thinking about ink-jet (or screen printing) of the PML UV-curable liquid plus other parts of the invention himself also; see attached e-mail conversation.
 8. I have ☒ have not ☐ attached _____ number of additional sheets to better describe this invention.
 9. Identify all non-Siemens' companies that may in the future benefit from the use of this invention through a license. Potentially a huge range of companies, notably all those working in the field of Organic Light-Emitting Devices (OLEDs); current count well over 100 companies worldwide, essentially almost all display manufacturing companies plus several others entering the display manufacturing field as newcomers (US, Japan, Europe, Taiwan, South Korea, China, etc.); anybody seeking to direct-encapsulate OLEDs (see below for further description).
 10. Was this invention developed under, or quoted for, a customer contract? YES ☐ NO ☒
 Was it developed under a government contract? YES ☐ NO ☒
 If yes to either, please give contract name and number, and further explain the situation N/A

IF THE ANSWERS TO ANY OF THESE QUESTIONS CHANGE BEFORE THIS INVENTION IS FILED AS A PATENT APPLICATION WITH THE GOVERNMENT, MAKE SURE TO SEND AN UPDATE TO SIEMENS IPD.

11. WITNESSED AND UNDERSTOOD BY:

Signature [Signature] Company Name OOS

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL. THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES

*Noted/checked off
 10/1/01*

1005 E U 100

1005 E U 100

INVENTION DISCLOSURE
Name Homer Antelis Company Address _____
Date 10/1/01

Page 2 of 9

U. Picta
30 Sep 01
~~Homer Antelis~~
Oct 1, 2001

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES

Ex. 101-1

Ex. 101-1

INVENTION DISCLOSURE

Page 2 of 1

Name Homer Anto

Company Address _____

Date 10/1/01

U. P. R.
30 Sep 01

Homer
Oct 1, 2001

**THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES**

Pictiva EX2029-p. 18

Samsung v Pictiva

IPR2024-01223

INSTRUCTION ... HOW TO USE THIS INVENTION DISCLOSURE

30/9

General

- PLEASE TYPE OR PRINT CLEARLY. Answer all questions. Use N/A when not applicable.
- Sign and date each page in ink.
Sign and date all attached additional sheets, diagrams, photographs, etc
Please provide all of your given names in full in sections 2 and 3. When there are more than two inventors, use another form and complete and sign items 1, 2, 3 and 10 on the extra forms.
- Every page of the form and accompanying papers should bear the signature of a witness and the date of his/her signing. The witness should have read the forms and attached papers, and should understand the invention before witnessing. The witness should have a technical background related to the invention, to reduce the chances that someone can later challenge his/her ability to have understood the invention.
- A co-inventor should not be the witness. If you have a choice of several qualified witnesses, choose the witness you believe is most likely to still be a Siemens employee available in this country if a question comes up several years from now. That means you should avoid having a co-op student, contract engineer, or a retiring engineer serve as your witness.

Detailed Description

- The description you provide may serve as the basis for a patent application. Therefore, be as complete and as accurate as possible. Attach pages as necessary, using the following checklist as a guide for content.
 - **Abstract:**
In one or two sentences, briefly describe what your invention does and how it is used, e.g., "A voltage-controlled oscillator (VCO) has its period controlled by a current provided by a current source. The current is proportional to the reciprocal of a control signal so that the VCO frequency is directly proportional to the control signal."
 - **Background Information:**
What is the function of your invention?
What is the problem solved by your invention?
How was the function of your invention performed by any prior systems, either a competitor's or ours?
What are the disadvantages of these prior systems?
What are the advantages of your invention over them?
 - **Details:**
Describe in detail the structural and functional operation of your invention. Use drawings and graphs where they would be helpful. Give specific details, not just general information.
Point out things such as what improvements your invention incorporates, or how and why it achieves superior performance (if you know why).
Are there alternative methods or different structural embodiments of your invention?
Can the general idea or technique of your invention be extended to other related fields? How?
Which features are believed to be new?
Describe how you best envision your invention being put to use.

Related Art

Attach a copy (or bibliographic citation) of all publications, patents, etc. that you know about which relate to your invention, and which you think might be important to consider in understanding how your invention differs from prior work.

Potential Licensing Opportunities

Please identify, in relation to item 9, all companies that are not a part of Siemens and may benefit, in the future, from the use of this invention. This will be helpful in identifying potential licensing opportunities for this invention.

REMEMBER TO UPDATE THE IPD IF ANY OF THE INFORMATION YOU PROVIDED CHANGES.

☐ **Yes, I promise I will update the Siemens Intellectual Property Department (IPD) if any of the information I've provided changes**


Oct 1, 2001


30 Sep 01

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL. THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES

Page 4 of 9
U. K. Sch.
30 Sep 01

**SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE**

ABSTRACT:

A manufacturing method for the direct encapsulation of OLED devices that encapsulates the sensitive active light-emitting OLED area with at least one encapsulation layer directly over and in contact with the OLED layers but which leaves other, non-light-emitting, areas of the display free of said encapsulation layer.

BACKGROUND:

Presently, OLEDs are typically developed or fabricated on large sheets of glass with several or tens or even in excess of 100 displays per sheet and, once the OLED fabrication on the sheet of glass is finished, the OLED is encapsulated with a second piece of glass or a metal cap, typically with a cavity between the OLED glass and the encapsulation part; said cavity typically holds a getter materials that absorbs or adsorbs residual oxygen and in particular moisture in the package and oxygen and moisture that penetrate into the display package subsequent to encapsulation, typically done by bonding the two pieces together with an epoxy adhesive. After this process the glass, now encapsulated with getter and a second glass or metal cap, is scribed and broken into the individual displays. This encapsulation process is very difficult to manufacture with high yield and reliability, time-consuming (for example the epoxy glue dispense), is very costly (the getter material and the cover glass or metal cap) and adds to the thickness and weight of the overall display.

To get around these problems, various research groups and companies have been developing so-called 'direct encapsulation' methods. One of these techniques, known as Polymer-Multi-Layer (PML) technology, deposits at least one layer of a UV-curable organic liquid material over the whole display glass, said layer is then UV-cured, followed by the deposition of a barrier layer, e.g. a sputtered metal-oxide or generally a dielectric layer. This process may be repeated, to yield largely impermeable barrier layers and to avoid e.g. external particle/dirt-induced pinholes in said encapsulation layer. The problem with the prior art using these approaches is, that only parts of these displays, essentially the active light-emitting OLED area, must be encapsulated against the ingress of e.g. oxygen and moisture but other parts of the display should be kept exposed, for example the contact pads at which the display is connected to external driver circuitry, power supply, etc. In the PML technology for example, a problem arises with the presence of one or more of the direct-encapsulation layers over areas where encapsulation is not required and/or detrimental, such as over the contact pads. — film damage at scribe lines.

Alternative techniques known in the prior art are to deposit for example 'Parylene' layer or a polysiloxane layer but these techniques also have the problem as the PML technology described above. Alternatively, a dielectric layer such as SiOx, SiNx, SiOxNy, etc. can be deposited over the OLED for direct encapsulation. This direct dielectric layer encapsulation, in-turn is susceptible to pin-holes and although the deposition (e.g. by sputtering) can be done through masks to block areas over which the encapsulation layer is not desired, this causes additional processing and reliability problems associated with for example the sputter-deposition through masks.

The present invention gets around problems of the prior art by providing processes for an improved direct-encapsulation of OLED devices.

DESCRIPTION OF THE INVENTION:

GENERAL (for all aspects of the invention and embodiments that follow below):

OLED can be typical OLED made on piece of glass with first ITO as first electrode (anode), then OLED layers, then top electrode (cathode); bottom-emitting through glass.

Alternatively, the electrodes can be reversed (cathode at bottom and anode at top).

Alternatively, the OLED can be top-emitting (substrate is opaque, emitting through transparent top electrode); both anode top and cathode bottom and reverse can be used.

Can be used with OLEDs on glass, quartz, metal, plastic foils, metal foils, etc. — silicon wafers

Inventor's Signature: *U. K. Sch.*

Date: 30 Sep 01

Witness' Signature: *Thomas Kuntz*

Date: 10/1/01

Et. MW kann das nicht mehr redieren. chiert werden
HEA 20.3.0?
UNIAX Patent
Barrier Layer: Metal (Al, Cr, Cu, Ag), Ceramic (Al₂O₃), Si₃N₄, WC, etc.)
ITO?

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES

**SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE**

Page 5 of 9

Can be used for active matrix, passive matrix, segmented, alpha-numeric or backlight OLED displays or any combinations thereof or generally any OLED light source or display. *General Lighting Applications*

The organic layers used in the invention are generally known in the prior art, e.g. the PML prior art and the UV-curable monomer and monomer mixes (generally UV-curable compositions); could also be Parylene coatings or other organic coatings that can be deposited in any suitable manner on the OLED without damaging it. Generally organic layers that are carefully outgassed to remove oxygen, moisture and any other reactive mobile species that coat the OLED substrate largely conformally. UV-curable materials are widely known in the prior art (see PML patent literature, see UV-curable printing inks in e.g. www.markem.com or www.vanet.hitachi.co.jp, or D. J. Hayes et al, Journal of the SID, Vol 9/1, 2001 or Hue P. Le, The Society for Imaging Sciences and Technology, Vol 42, No1, Jan/Feb 1998).

Fundamental Error: Organic layer is Non conformal but is why the tech works! or thermal cure

NOTE ADDED: can also be a p.e. e-beam cure

The barrier layer of the invention is typically a dielectric such as a SiO_x, AlO_x, SiN_x, AlN_x, SiO_xN_y, ITO, ZnO_x, Al-doped ZnO_x, etc. - generally any high barrier dielectrics (or conductive oxides).

In cases in which the fabricated display is bottom-emitting (through the substrate) and the encapsulation does not have to be transparent, metal films or non-transparent or colored dielectric films can be used as the barrier layer.

The deposition of the barrier layer can be any suitable method known in the prior art to deposit dielectric layers, e.g. sputtering or reactive sputtering (DC, AC, pulsed, combinations thereof, etc.). Evaporation of such dielectrics (resistive heating or electron-beam) or metal films is possible also and so are ion-beam assisted deposition methods or other plasma-enhanced deposition methods. - *Such as PECVD.*

CLAIMS (aspects of the invention, embodiments; please note that for all of the below-mentioned it is understood that there can be several sequences (multi-layers) of organic + barrier layer):

1. A process for directly encapsulating a multitude of OLED devices fabricated on an undeviated substrate sheet (can be foil) by putting the encapsulation layer directly (in contact with) on the top-most layer of the to-be encapsulated OLED displays and by using a combination of at least one organic layer and at least one inorganic barrier layer whereby said organic layer is deposited / condensed on the OLED substrate in the form of an unpatterned liquid film; whereby: the unpatterned liquid film is cross-linked in a patterned manner, non-cross-linked areas are subsequently removed, followed by the deposition, in a patterned manner, of a barrier layer over at least part of the layer covered with the cross-linked organic layer. *or extending beyond*
2. As claim 1 whereby flash evaporation is used to deposit the organic layer (as in PML technology of the prior art).
3. As claim 1 whereby dip-, roll-, blade-coating is used to deposit the organic layer.
4. As claim 1 whereby spin-coating is used to deposit the organic layer.
5. As claim 1 whereby evaporation is used to deposit the organic layer.
6. As claim 1 whereby cross-linking of the organic in a patterned manner is achieved by UV flood-exposure through a mask with the mask being less than 5 and preferably less than 1 and better still less than 0.5 mm away from the OLED substrate.
7. As claim 1 whereby cross-linking of the organic in a patterned manner is achieved by selective UV exposure through an optical patterning system such as a projection exposure system.
8. As claim 1 whereby cross-linking of the organic in a patterned manner is achieved by selective UV exposure with a UV-beam scanning system.
9. As claim 1 whereby the non-exposed areas (non-cross-linked) are removed by thermal evaporation (heating the substrate); can be short higher temperature pulse (e.g. by putting the OLED plate onto hotplate).
10. As claim 1 whereby the non-exposed areas (non-cross-linked) are removed by pumping in vacuum.

Inventor's Signature: [Signature]

Witness' Signature: [Signature]

Date: 30/8/01

Date: 10/11/01

**THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES**

Supplemental Sheet
FOR INVENTION DISCLOSURE

Page 6 of 9

11. Combination of claim 9 and 10.

"MOST LIKELY" - KYLE

12. As claim 1 whereby the non-exposed areas (non-cross-linked) are removed by immersion in rinse-tank (washing off), spray-rinsing, ultra-sonicing (dry or wet ultra-sonic), mega-sonic (dry or wet); combination of dry ultra-sonic or mega-sonic in vacuum.

CHANGE "WET" TO "LIQUID"

13. As claim 1 whereby the removal of the non-cross-linked areas of the organic layer is assisted by a plasma process (even if this removes also some of the cross-linked area as long as the rate for the removal of the non-cross-linked material is larger than that for the cross-linked material).

14. As claim 1 whereby the barrier layer (materials and deposition methods see above) is sputtered through a shadow mask over the area of UV-cured organic.

maybe add: barrier = dielectric barrier = metal alloy

15. As claim 14 whereby the barrier layer is slightly larger in x and y to cover also the edges of the organic layer. Note (for the description of the invention): we should state somewhere that because of optical effects the UV-exposed organic is likely not to have a sharp step (e.g. a round/sloped profile instead) and this is advantageous when depositing the barrier layer on top to assure good side-step coverage.

Show x & y on diagram

16. As claim 1 whereby the process is used to encapsulate only the organic light-emissive areas (e.g. pixels) of the display and all contact pads and/or auxiliary encapsulation areas (e.g. for secondary encapsulation) and/or scribe/break areas are left free from the organic layer and the barrier layer.

17. New independent claim: As claim 1 but this time the organic is deposited and cured (if necessary) ALL OVER and only the barrier layer is deposited in a patterned manner, said patterned barrier layer also then acts as an etch stop to remove the organic over unwanted areas (i.e. the areas where the barrier layer is not deposited).

18. For claim 17 we can use all organic layer deposition methods as in claim 1 plus additional ones, namely:

19. As claim 17 whereby evaporation of one or more reactive organic molecules is used to deposit the organic layer, said reactive organic molecules forming a condensed conformal film on the substrate.

Error!

20. As claim 17 whereby the method is as the 'Parylene' coating technology known in the prior art.

21. As claim 17 whereby the organic deposition is a plasma-assisted organic material deposition method.

22. As claim 17 whereby the organic that is subsequently not coated with the barrier is removed by an etching step.

23. As claim 22 whereby the etching is a chemical (dry or wet) etch process suitable to remove the organic.

24. As claim 22 whereby the etching is a plasma-assisted etch process suitable to remove the organic.

25. As claim 22 whereby the etching plasma contains oxygen.

26. As claim 22 whereby reactive ion-etching is used.

27. As claim 22 whereby anisotropic reactive ion-etching is used.

28. New independent claim: As claim 1 and 17 but now the organic itself is already during the deposition (by nature of the deposition process itself) deposited in a patterned manner, then curing of the organic (if necessary as e.g. for the UV-curable organics) then patterned deposition of the barrier, no need to remove e.g. non-UV-cured organic.

29. As claim 28 whereby the organic is deposited through a shadow mask using methods as described for claims 1 and 17.

30. As claim 28 whereby the organic is printed, in particular using screen-printing or ink-jet printing.

31. Any of the preceding claims: all encapsulation process steps in inert atmosphere (reduced oxygen, ozone, other reactive gases and in particular moisture.)

32. As claim 31 but only the first organic layer + first barrier layer 'dyad' in inert atmosphere.

Inventor's Signature:

Witness' Signature:

Date:

Date:

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL. THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES

33. As claim 28 whereby organic is patterned during evaporation/CVD process using inert gas nozzles to direct and contain condensing/reactive vapor.

SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE

Page 7 of 9

33. As claim 31 but only the first organic layer in inert atmosphere.
34. Independent claim (?) based on ALL preceeding claims: ... whereby said OLED sheet with the encapsulation of the invention is encapsulated with a secondary encapsulation layer for additional encapsulation and/or mechanical protection.
35. As 34 whereby this is laminating or glueing a plastic or metal or metal+plastic foil or thin glass or thicker (rigid) glass or metal sheet over said OLED display sheet.
36. Finishing all off by singulation of the display (scribe and break) – may not be necessary.
37. As claims 34 – 36 but where the secondary encapsulation is done after singulation.
- 38.

One such example is shown in figure 1: attach Penang VDOT mask drawing with all layers.

Show barrier over the edge of the display → Fig 3

Fig 2: concept of the invention

✓ ub: added on
10 Oct 01:

Added also
device structure
claims
~ an OLED ~

with or without
space between the
OLED sheet & the
cover (the 2nd encaps)
sheet.

Ugh → ~~Added~~ SE patent → SFE Technologies
Filed 01/16/86
US Patent 4,682,565 ✓

Inventor's Signature: [Signature]

Date: 30 Sep 01


Witness' Signature: [Signature]

Date: Oct 1, 2001

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES

Cover
with
an caps.
or else
diode
cover metal

Fig 1

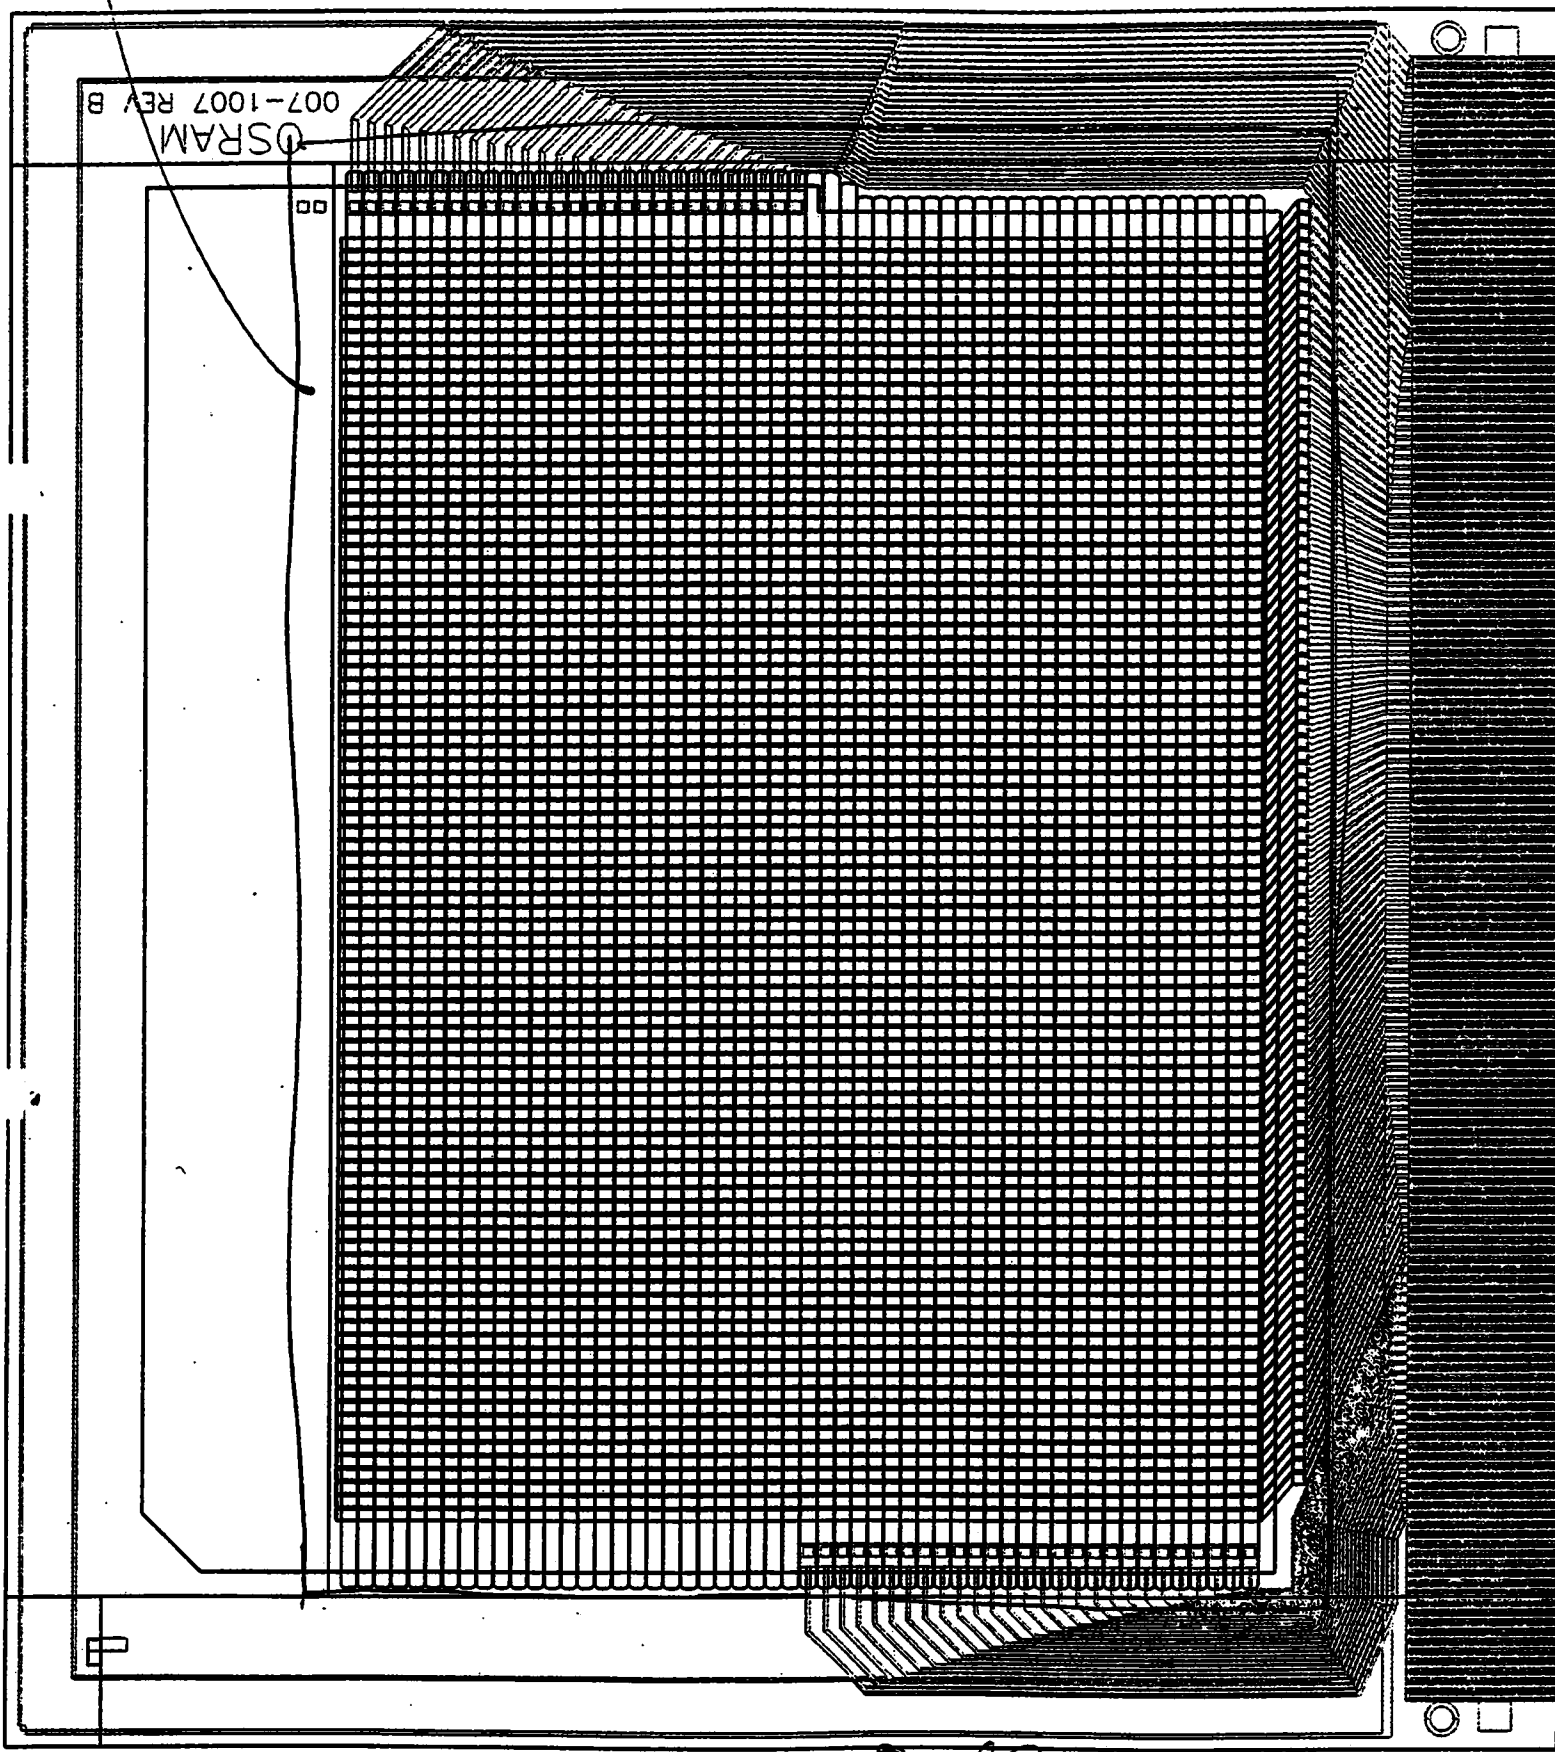

James A. [Signature]
10/1/01

P8 of 9
U. 6282, 308/01
Pictiva EX2029-1. 25
Samsung v Pictiva
IPR2024-01223

production - 1288 sheet
 (e.g. 400x400 mm
 730x920 mm
 etc.)

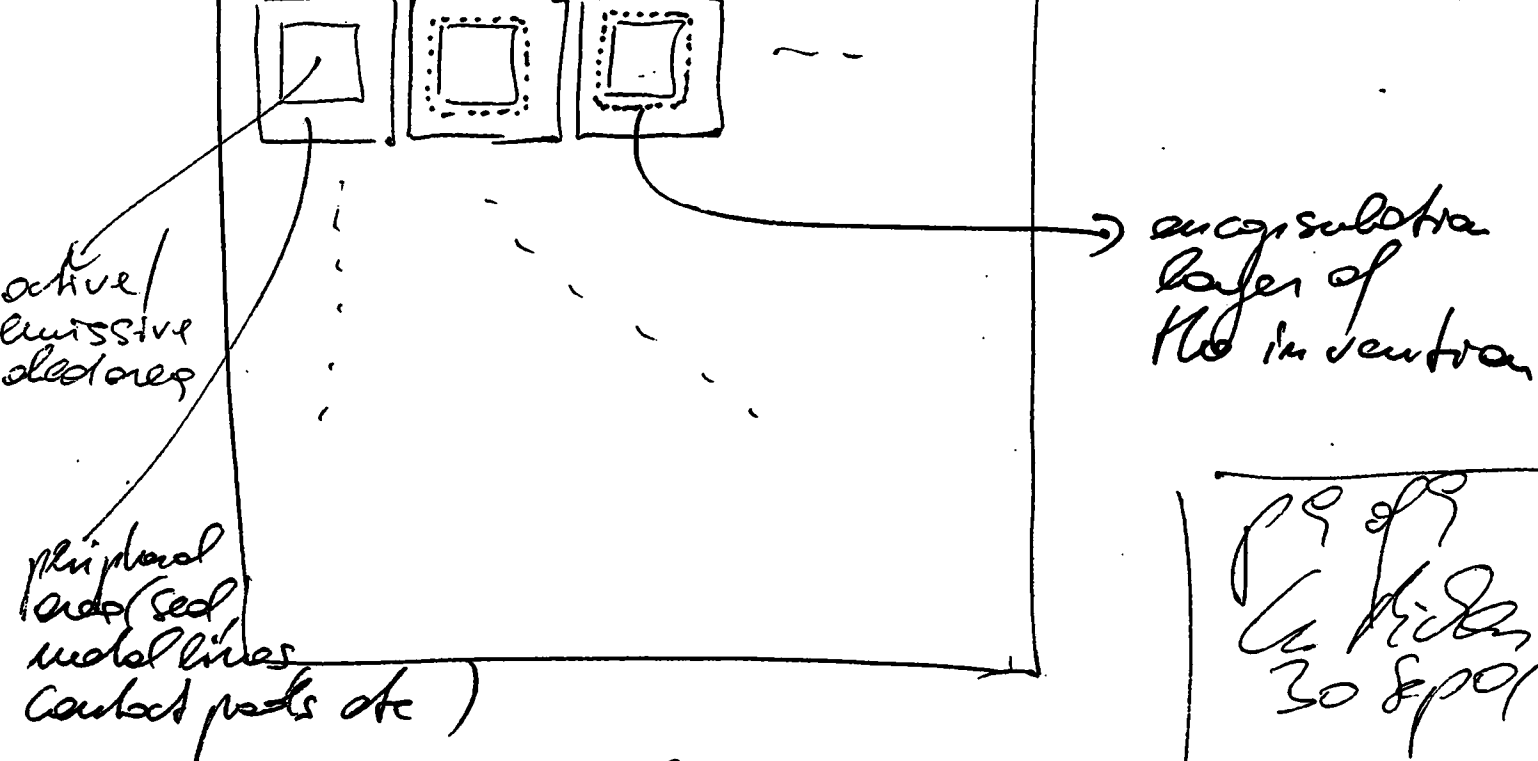


Fig 2

pp of
 6 thick
 30 & 40

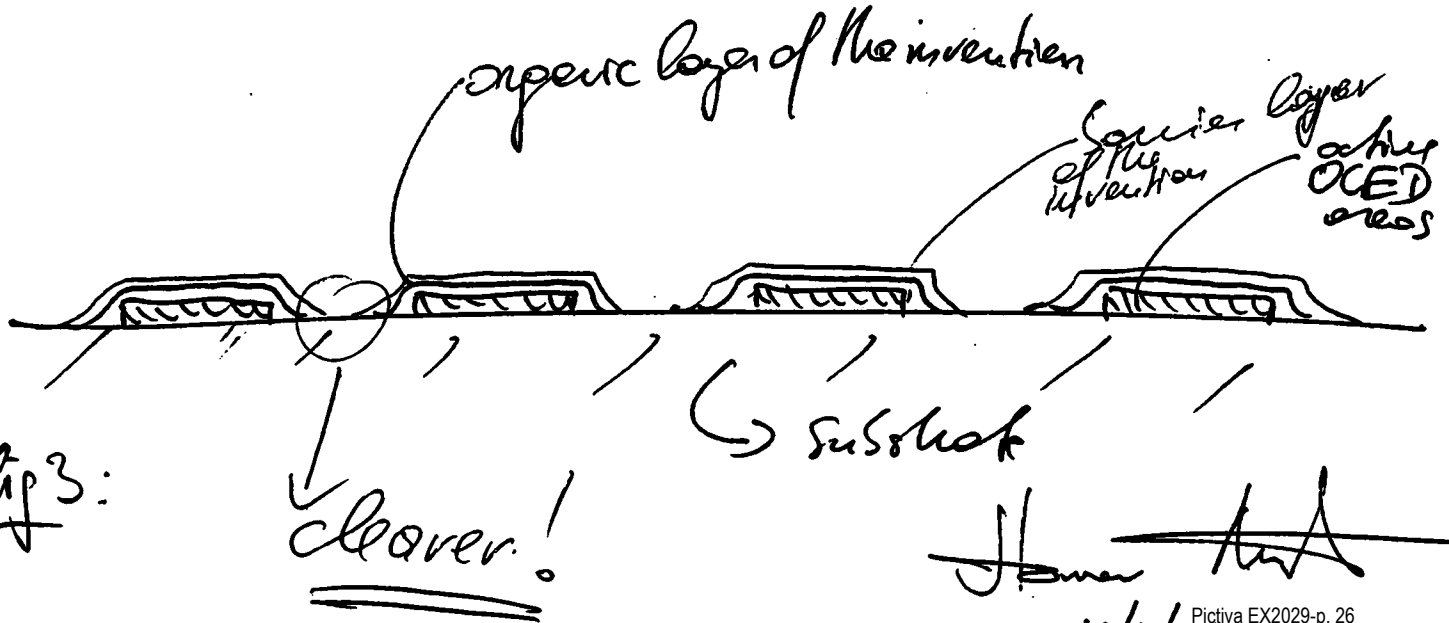


Fig 3:

Handwritten signature

INSTRUCTION ... HOW TO USE THIS INVENTION DISCLOSURE

3 of 9

General

- PLEASE TYPE OR PRINT CLEARLY. Answer all questions. Use N/A when not applicable.
- Sign and date each page in ink.
Sign and date all attached additional sheets, diagrams, photographs, etc
Please provide all of your given names in full in sections 2 and 3. When there are more than two inventors, use another form and complete and sign items 1, 2, 3 and 10 on the extra forms.
- Every page of the form and accompanying papers should bear the signature of a witness and the date of his/her signing. The witness should have read the forms and attached papers, and should understand the invention before witnessing. The witness should have a technical background related to the invention, to reduce the chances that someone can later challenge his/her ability to have understood the invention.
- A co-inventor should not be the witness. If you have a choice of several qualified witnesses, choose the witness you believe is most likely to still be a Siemens employee available in this country if a question comes up several years from now. That means you should avoid having a co-op student, contract engineer, or a retiring engineer serve as your witness.

Detailed Description

- The description you provide may serve as the basis for a patent application. Therefore, be as complete and as accurate as possible. Attach pages as necessary, using the following checklist as a guide for content.
 - **Abstract:**
In one or two sentences, briefly describe what your invention does and how it is used, e.g., "A voltage-controlled oscillator (VCO) has its period controlled by a current provided by a current source. The current is proportional to the reciprocal of a control signal so that the VCO frequency is directly proportional to the control signal."
 - **Background Information:**
What is the function of your invention?
What is the problem solved by your invention?
How was the function of your invention performed by any prior systems, either a competitor's or ours?
What are the disadvantages of these prior systems?
What are the advantages of your invention over them?
 - **Details:**
Describe in detail the structural and functional operation of your invention. Use drawings and graphs where they would be helpful. Give specific details, not just general information.
Point out things such as what improvements your invention incorporates, or how and why it achieves superior performance (if you know why).
Are there alternative methods or different structural embodiments of your invention?
Can the general idea or technique of your invention be extended to other related fields? How?
Which features are believed to be new?
Describe how you best envision your invention being put to use.

Related Art


Attach a copy (or bibliographic citation) of all publications, patents, etc. that you know about which relate to your invention, and which you think might be important to consider in understanding how your invention differs from prior work.

Potential Licensing Opportunities

Please identify, in relation to item 9, all companies that are not a part of Siemens and may benefit, in the future, from the use of this invention. This will be helpful in identifying potential licensing opportunities for this invention.

REMEMBER TO UPDATE THE IPD IF ANY OF THE INFORMATION YOU PROVIDED CHANGES.

☐ **Yes, I promise I will update the Siemens Intellectual Property Department (IPD) if any of the information I've provided changes**


Oct 4, 2001


30 Sep 01

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL. THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES

**SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE**

Page 4 of 9
U. R. S. K.
3-8p01

ABSTRACT:

A manufacturing method for the direct encapsulation of OLED devices that encapsulates the sensitive active light-emitting OLED area with at least one encapsulation layer directly over and in contact with the OLED layers but which leaves other, non-light-emitting, areas of the display free of said encapsulation layer.

BACKGROUND:

Presently, OLEDs are typically developed or fabricated on large sheets of glass with several or tens or even in excess of 100 displays per sheet and, once the OLED fabrication on the sheet of glass is finished, the OLED is encapsulated with a second piece of glass or a metal cap, typically with a cavity between the OLED glass and the encapsulation part; said cavity typically holds a getter materials that absorbs or adsorbs residual oxygen and in particular moisture in the package and oxygen and moisture that penetrate into the display package subsequent to encapsulation, typically done by bonding the two pieces together with an epoxy adhesive. After this process the glass, now encapsulated with getter and a second glass or metal cap, is scribed and broken into the individual displays. This encapsulation process is very difficult to manufacture with high yield and reliability, time-consuming (for example the epoxy glue dispense), is very costly (the getter material and the cover glass or metal cap) and adds to the thickness and weight of the overall display.

To get around these problems, various research groups and companies have been developing so-called 'direct encapsulation' methods. One of these techniques, known as Polymer-Multi-Layer (PML) technology, deposits at least one layer of a UV-curable organic liquid material over the whole display glass, said layer is then UV-cured, followed by the deposition of a barrier layer, e.g. a sputtered metal-oxide or generally a dielectric layer. This process may be repeated, to yield largely impermeable barrier layers and to avoid e.g. external particle/dirt-induced pinholes in said encapsulation layer. The problem with the prior art using these approaches is, that only parts of these displays, essentially the active light-emitting OLED area, must be encapsulated against the ingress of e.g. oxygen and moisture but other parts of the display should be kept exposed, for example the contact pads at which the display is connected to external driver circuitry, power supply, etc. In the PML technology for example, a problem arises with the presence of one or more of the direct-encapsulation layers over areas where encapsulation is not required and/or detrimental, such as over the contact pads.

Alternative techniques known in the prior art are to deposit for example 'Parylene' layer or a polysiloxane layer but these techniques also have the problem as the PML technology described above. Alternatively, a dielectric layer such as SiOx, SiNx, SiOxNy, etc. can be deposited over the OLED for direct encapsulation. This direct dielectric layer encapsulation, in-turn is susceptible to pin-holes and although the deposition (e.g. by sputtering) can be done through masks to block areas over which the encapsulation layer is not desired, this causes additional processing and reliability problems associated with for example the sputter-deposition through masks.

The present invention gets around problems of the prior art by providing processes for an improved direct-encapsulation of OLED devices.

DESCRIPTION OF THE INVENTION:

GENERAL (for all aspects of the invention and embodiments that follow below):

OLED can be typical OLED made on piece of glass with first ITO as first electrode (anode), then OLED layers, then top electrode (cathode); bottom-emitting through glass.

Alternatively, the electrodes can be reversed (cathode at bottom and anode at top).

Alternatively, the OLED can be top-emitting (substrate is opaque, emitting through transparent top electrode); both anode top and cathode bottom and reverse can be used.

Can be used with OLEDs on glass, quartz, metal, plastic foils, metal foils, etc.

Inventor's Signature: *U. R. S. K.*

Date: 30 Sep 01

Witness' Signature: *Harman K. K.*

Date: 10/1/01

**THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES**

**SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE**

Page 5 of 9

Can be used for active matrix, passive matrix, segmented, alpha-numeric or backlight OLED displays or any combinations thereof or generally any OLED light source or display.

The organic layers used in the invention are generally known in the prior art, e.g. the PML prior art and the UV-curable monomer and monomer mixes (generally UV-curable compositions); could also be Parylene coatings or other organic coatings that can be deposited in any suitable manner on the OLED without damaging it. Generally organic layers that are carefully outgassed to remove oxygen, moisture and any other reactive mobile species that coat the OLED substrate largely conformally. UV-curable materials are widely known in the prior art (see PML patent literature, see UV-curable printing inks in e.g. www.markem.com or www.vanet.hitachi.co.jp, or D. J. Hayes et al, Journal of the SID, Vol 9/1, 2001 or Hue P. Le, The Society for Imaging Sciences and Technology, Vol 42, No1, Jan/Feb 1998).

NOTE ADDED: can also be e.g. e-beam cure

The barrier layer of the invention is typically a dielectric such as a SiO_x, AlO_x, SiN_x, AlN_x, SiO_xN_y, ITO, ZnO_x, Al-doped ZnO_x, etc. – generally any high barrier dielectrics (or conductive oxides).

or thermal cure

In cases in which the fabricated display is bottom-emitting (through the substrate) and the encapsulation does not have to be transparent, metal films or non-transparent or colored dielectric films can be used as the barrier layer.

The deposition of the barrier layer can be any suitable method known in the prior art to deposit dielectric layers, e.g. sputtering or reactive sputtering (DC, AC, pulsed, combinations thereof, etc.). Evaporation of such dielectrics (resistive heating or electron-beam) or metal films is possible also and so are ion-beam assisted deposition methods or other plasma-enhanced deposition methods.

CLAIMS (aspects of the invention, embodiments; please note that for all of the below-mentioned it is understood that there can be several sequences (multi-layers) of organic + barrier layer):

1. A process for directly encapsulating a multitude of OLED devices fabricated on an undevided substrate sheet (can be foil) by putting the encapsulation layer directly (in contact with) on the top-most layer of the to-be encapsulated OLED displays and by using a combination of at least one organic layer and at least one inorganic barrier layer whereby said organic layer is deposited / condensed on the OLED substrate in the form of an unpatterned liquid film; whereby: the unpatterned liquid film is cross-linked in a patterned manner, non-cross-linked areas are subsequently removed, followed by the deposition, in a patterned manner, of a barrier layer over at least part of the layer covered with the cross-linked organic layer.
2. As claim 1 whereby flash evaporation is used to deposit the organic layer (as in PML technology of the prior art).
3. As claim 1 whereby dip-, roll-, blade-coating is used to deposit the organic layer.
4. As claim 1 whereby spin-coating is used to deposit the organic layer.
5. As claim 1 whereby evaporation is used to deposit the organic layer.
6. As claim 1 whereby cross-linking of the organic in a patterned manner is achieved by UV flood-exposure through a mask with the mask being less than 5 and preferably less than 1 and better still less than 0.5 mm away from the OLED substrate.
7. As claim 1 whereby cross-linking of the organic in a patterned manner is achieved by selective UV exposure through an optical patterning system such as a projection exposure system.
8. As claim 1 whereby cross-linking of the organic in a patterned manner is achieved by selective UV exposure with a UV-beam scanning system.
9. As claim 1 whereby the non-exposed areas (non-cross-linked) are removed by thermal evaporation (heating the substrate); can be short higher temperature pulse (e.g. by putting the OLED plate onto hotplate).
10. As claim 1 whereby the non-exposed areas (non-cross-linked) are removed by pumping in vacuum.

Inventor's Signature: _____

Date: _____

Witness' Signature: _____


Date: _____

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL. THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES


**SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE**

Page 6 of 9

11. Combination of claim 9 and 10.
12. As claim 1 whereby the non-exposed areas (non-cross-linked) are removed by immersion in rinse-tank (washing off), spray-rinsing, ultra-sonicing (dry or wet ultra-sonic), mega-sonic (dry or wet); combination of dry ultra-sonic or mega-sonic in vacuum. *CLG WET TO LIQUID*
13. As claim 1 whereby the removal of the non-cross-linked areas of the organic layer is assisted by a plasma process (even if this removes also some of the cross-linked area as long as the rate for the removal of the non-cross-linked material is larger than that for the cross-linked material).
14. As claim 1 whereby the barrier layer (materials and deposition methods see above) is sputtered through a shadow mask over the area of UV-cured organic. *maybe add: { barrier = dielectric or metal or alloy }*
15. As claim 14 whereby the barrier layer is slightly larger in x and y to cover also the edges of the organic layer. Note (for the description of the invention): we should state somewhere that because of optical effects the UV-exposed organic is likely not to have a sharp step (e.g. a round/sloped profile instead) and this is advantageous when depositing the barrier layer on top to assure good side-step coverage.
16. As claim 1 whereby the process is used to encapsulate only the organic light-emissive areas (e.g. pixels) of the display and all contact pads and/or auxiliary encapsulation areas (e.g. for secondary encapsulation) and/or scribe/break areas are left free from the organic layer and the barrier layer.
17. New independent claim: As claim 1 but this time the organic is deposited and cured (if necessary) ALL OVER and only the barrier layer is deposited in a patterned manner, said patterned barrier layer also then acts as an etch stop to remove the organic over unwanted areas (i.e. the areas where the barrier layer is not deposited).
18. For claim 17 we can use all organic layer deposition methods as in claim 1 plus additional ones, namely:
19. As claim 17 whereby evaporation of one or more reactive organic molecules is used to deposit the organic layer, said reactive organic molecules forming a condensed conformal film on the substrate.
20. As claim 17 whereby the methods is as the 'Parylene' coating technology known in the prior art.
21. As claim 17 whereby the organic deposition is a plasma-assisted organic material deposition method.
22. As claim 17 whereby the organic that is subsequently not coated with the barrier is removed by an etching step.
23. As claim 22 whereby the etching is a chemical (dry or wet) etch process suitable to remove the organic.
24. As claim 22 whereby the etching is a plasma-assisted etch process suitable to remove the organic.
25. As claim 22 whereby the etching plasma contains oxygen.
26. As claim 22 whereby reactive ion-etching is used.
27. As claim 22 whereby anisotropic reactive ion-etching is used.
28. New independent claim: As claim 1 and 17 but now the organic itself is already during the deposition (by nature of the deposition process itself) deposited in a patterned manner, then curing of the organic (if necessary as e.g. for the UV-curable organics) then patterned deposition of the barrier, no need to remove e.g. non-UV-cured organic.
29. As claim 28 whereby the organic is deposited through a shadow mask using methods as described for claims 1 and 17.
30. As claim 28 whereby the organic is printed, in particular using screen-printing or ink-jet printing.
31. Any of the preceeding claims: all encapsulation process steps in inert atmosphere (reduced oxygen, ozone, other reactive gases and in particular moisture).
32. As claim 31 but only the first organic layer + first barrier layer 'dyad' in inert atmosphere.

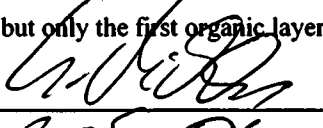Inventor's Signature: 

Date: 30 Sep 01

Witness' Signature: 

Date: 10/1/01

**THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES**

Handwritten text, possibly a signature or date, located in the upper left quadrant of the page.

Handwritten text, possibly a signature or date, located in the lower left quadrant of the page.

**SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE**

Page 7 of 9

33. As claim 31 but only the first organic layer in inert atmosphere.
34. Independent claim (?) based on ALL preceeding claims: ... whereby said OLED sheet with the encapsulation of the invention is encapsulated with a secondary encapsulation layer for additional encapsulation and/or mechanical protection.
35. As 34 whereby this is laminating or glueing a plastic or metal or metal+plastic foil or thin glass or thicker (rigid) glass or metal sheet over said OLED display sheet.
36. Finishing all off by singulation of the display (scribe and break) – may not be necessary.
37. As claims 34 – 36 but where the secondary encapsulation is done after singulation.
- 38.

One such example is shown in figure 1: attach Penang VDOT mask drawing with all layers.

Show barrier over the edge of the display → *Fig 3*

Fig 2: concept of the invention

*✓ub: added on
1 Oct 01:*

*with or without
space between the
OLED sheet & the
cover (the 2nd encaps)
sheet.*

Inventor's Signature: *C. P. [Signature]*

Date: *30 Sep 01*

Witness' Signature: *Home [Signature]*

Date: *Oct 1, 2001*

**THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES**


1944


[illegible]

— 12 —

cover
with
encaps.
or
oxide
coat
(metal)

Fig 1

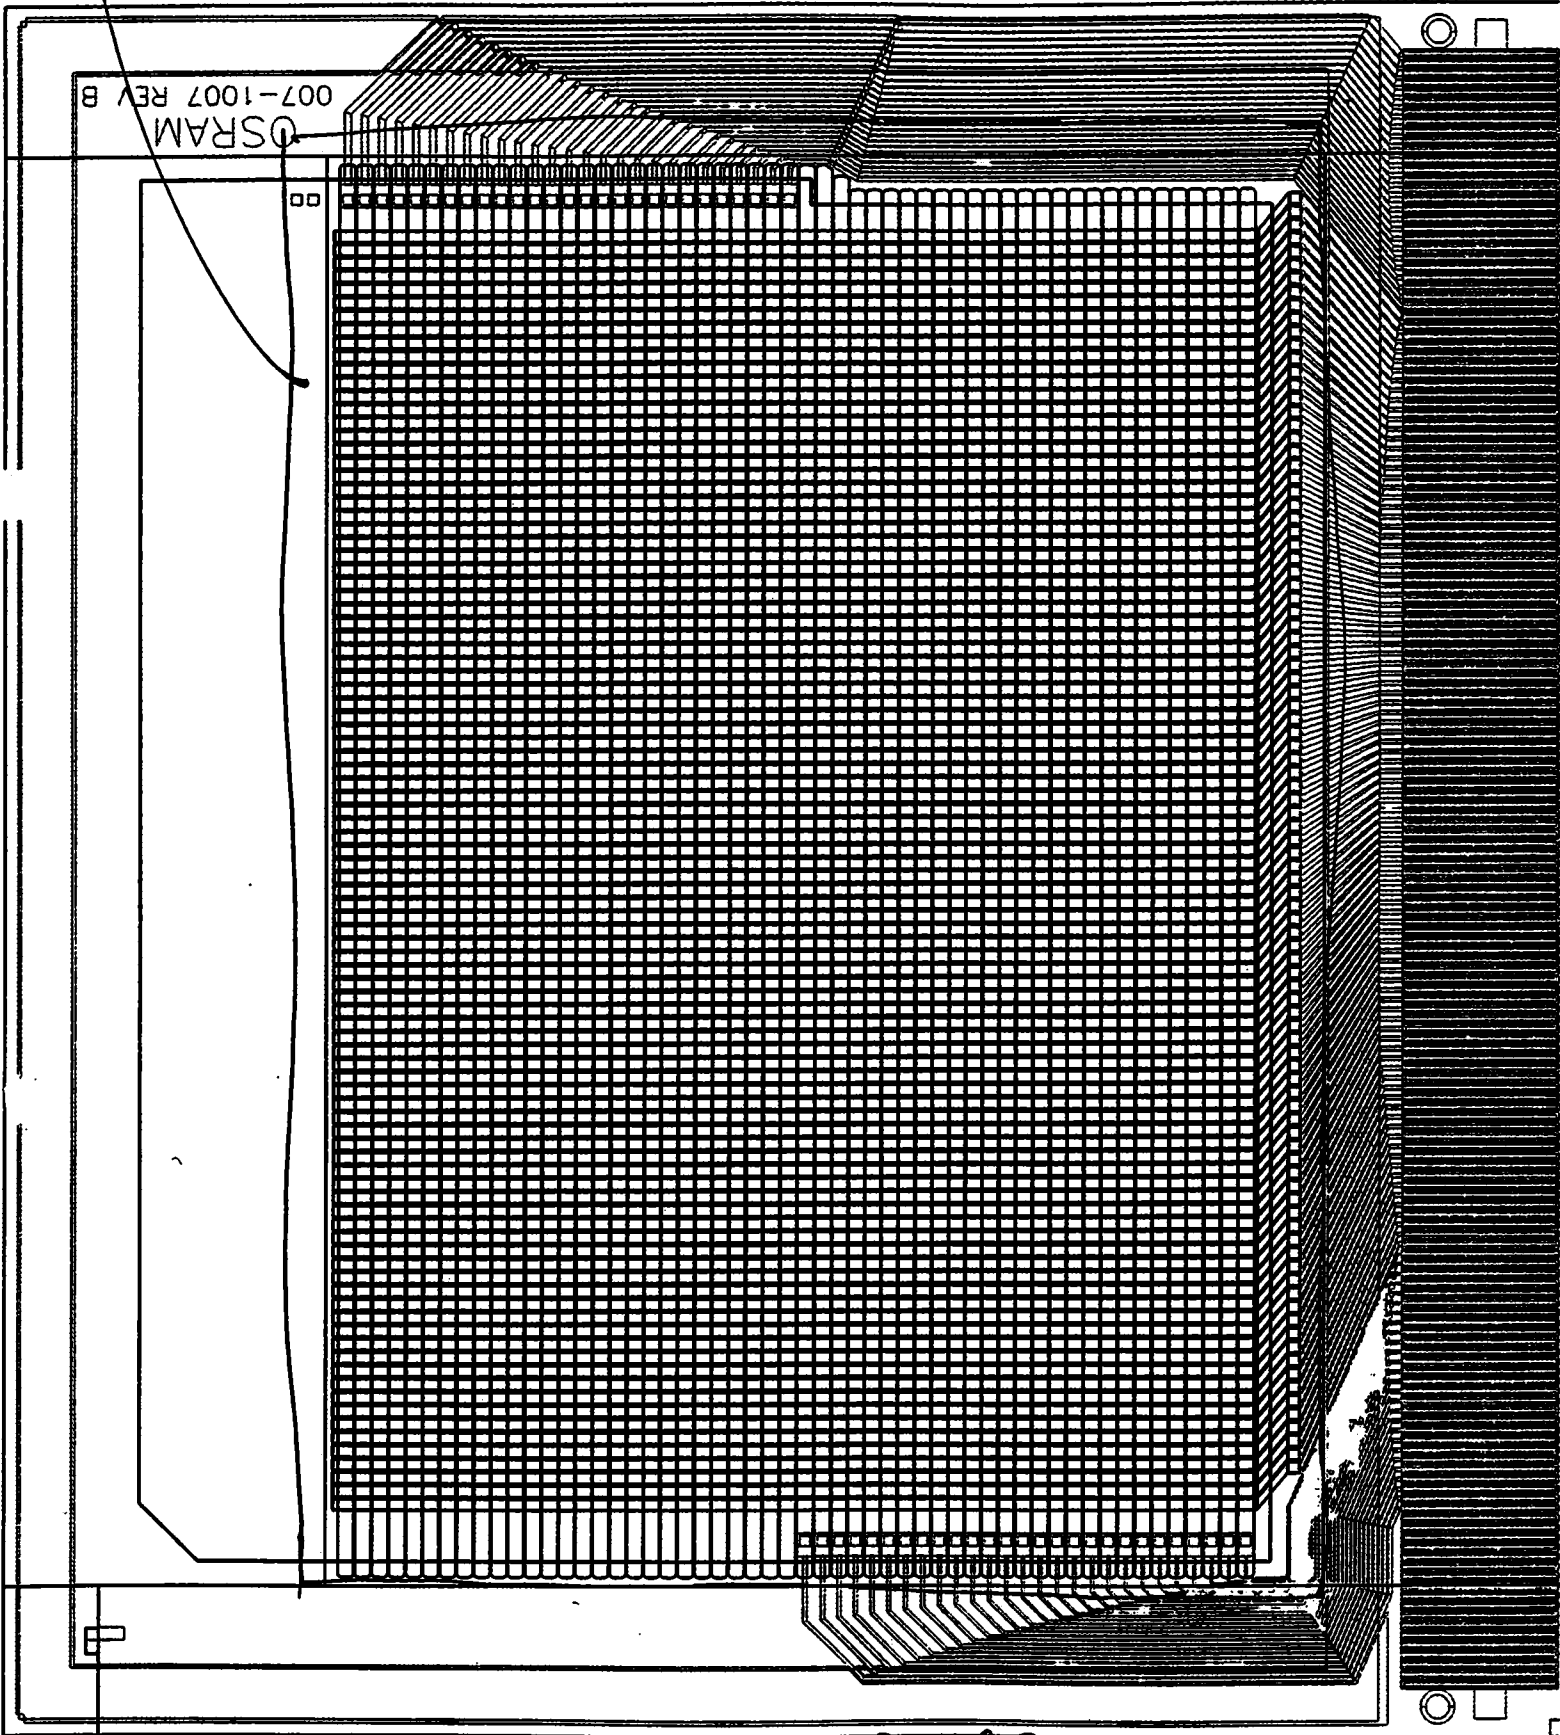

James 
10/1/01

P8 of 9
U. 6222, 308701
Pictiva EX2029, p. 36
Samsung v Pictiva
IPR2024-01223

ss sheet
(e.g. 400x400 mm
730x920 mm
etc.)

production

active/
emissive
devices

organic substrate
layer of
the invention

plurality
of (see
metal lines
contact pads etc)

pp of
the
30 & 40

Fig 2

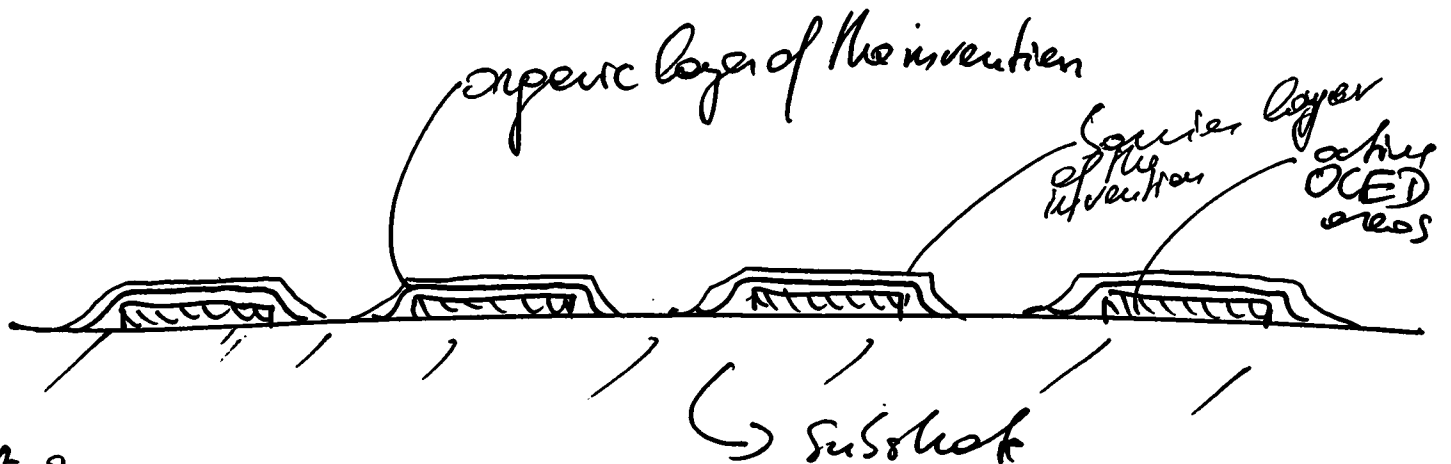


Fig 3:

James [Signature]


10/1/01
Pictiva EX2029-p. 38
Samsung v Pictiva
IPR2024-01223

Pichler Karl (ITC)

From: Cumpston Brian (ITC)
Sent: Thursday, August 16, 2001 9:18 AM
To: Pichler Karl (ITC)
Cc: Antoniadis Homer (ITC)
Subject: RE: defect count and size distribution software

FYI, here are histograms I generated from the spreadsheet you sent (the software doesn't count grown-together spots as individual spots)

Sheet 1:

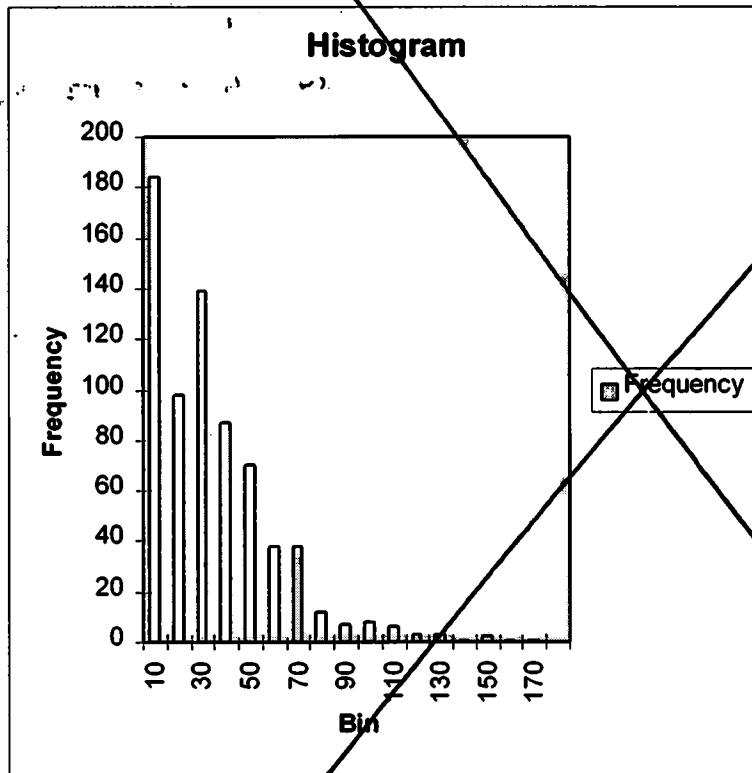

Sheet 3:

IDEA: 14 Aug 01 (during Tenney Pines
for j. rechner)

Problem: cost effective, efficient, simple - Old Encaps.
offer

apparently: simple transport (for) deg. ^{et. MW kann} ^{das nicht mehr} ^{recherchiert} ^{werden} ^{HIA} ^{20.3.09}

acc. to
Tenney
Pines

Industrial rule - get multiple of
liquid monomers that are
UV-cross-linkable is well known
(acc. to Tenney Pines, Heidelberg)
Medicine made use
of machines)

Old photo: encaps. is a big issue

→ one of the solutions → use of ATK

but: ATK NOT simple (vac flash
evap. process)

NOTE: I had this
idea quickly
during the summer
→ NOT discussed
with anyone

→ keep contact problems
→ best for 5000
→ not polymerized (e.g. colors
also of hot parts etc.)

idea / narrative

→ use UV to get liquid monomers
polymerized quickly over active
heat cured → x-ray
polymerized (e.g. super through slabs,
known) dielectric / high dielectric

Read and Understood By

U. Pines

14 Aug 01

M. W.

11/10/01

Date

Signed

Pictiva EX2009-p. 40

Samsung v Pictiva

IPR2024-01223

~~IDEA~~ IDEA: 15 Aug 01

VC → BOI: have been carrying this idea around with me for ~ 2.5 years! (told Cyg, & others)

→ issue: use of PNL to encapsulate OLED → see p. mem (Stefan)

→ problem: liquid monomer (to be x-linked by UV) goes everywhere (also when not wanted, e.g. on contact people's real friend, etc.)

idea/solve: → PNL → coat monomer liquid film (flush away)

UV-cross-link through mask

→ remove liquid film gets evaporated / washed off

→ apply encapsulating film on top also through mask → may repeat.

→ conclude: encaps OLED active area but leave contact pads etc free

Continued on Page

U. P. C. R. N.

15 Aug 01

Date

Read and Understood By

Muller

Signed

01/10/01

INVENTION DISCLOSURE

Page 1 of 9

Return this completed form,
with any necessary attachments, to:
SIEMENS CORPORATION
Intellectual Property Department (IPD)
4900 Old Ironsides Drive, M/S 503
Santa Clara, CA 95054
phone +1-732-321-3026
fax +1-732-321-3014

PLEASE KEEP A COPY FOR YOUR RECORDS

THIS SECTION FOR IPD USE ONLY	
Receipt Date Stamp	Division/Dept Code <u>OSRAM Opto Semicon</u>
	Cost Center Code <u>8083</u>
RECEIVED	Docket No. <u>2001E18483US</u>
<u>2001</u>	IP Attorney <u>HJG</u>

1. Your Div.'s Project # _____; Invention Title Encapsulation of OLED devices
2. INVENTOR

At the time the invention was conceived, this inventor was
☐ an employee of a German legal entity (e.g. Siemens AG)
☒ an employee of a non-German entity (e.g. Siemens
Automotive Corporation or Siemens Canada Limited)
If you are not sure, contact IPD at +1-732-321-3026

Full Name: Karl PICHLER
Home Address: [REDACTED]
Santa Clara, CA 95050

Citizen of [REDACTED]
Soc. Sec. # [REDACTED]
COMPANY/LOCATION INFORMATION

Employer Osram Opto-Semiconductor
Division OLED R&D
Address 3870 North 1st Street
San Jose, CA 95134

Work telephone 408 456 4175
Fax 408 456 4305
Email karl.pichler@osram-opto.com

Signature [Signature]
Date 30 Sep 2001

INTELLECTUAL PROPERTY DEPT
(use additional forms for more co-inventors)

At the time the invention was conceived, this inventor was
☐ an employee of a German legal entity (e.g. Siemens AG)
☐ an employee of a non-German entity (e.g. Siemens
Automotive Corporation or Siemens Canada Limited)
If you are not sure, contact IPD at +1-732-321-3026

Full Name _____
Home Address _____

Citizen of _____
Soc. Sec. # _____
COMPANY/LOCATION INFORMATION

Employer _____
Division _____
Address _____

Work telephone _____
Fax _____
Email _____

Signature _____
Date _____

4. Purpose(s), and likely field(s) of use of this invention Encapsulation of OLED devices
5. Is this invention still secret within Siemens? YES ☒ NO ☐
Do you soon plan to make the invention information available outside of Siemens? YES ☐ NO ☒

Based on your answer to Question #5, explain when and how this invention was/will be made available to someone outside of Siemens (e.g. trade show at location/date, customer presentation at company/location/attendees/date, supplier prototyping by company/date, included in product brochure or advertisement in publication/date, industry technical symposium paper presented place/date, etc) _____

6. Where is this invention described? List all documents containing aspects of this invention (e.g. engineer notebook date/page, internal status report, test logs, physical prototypes, customer presentation, etc) Karl Pichler Laboratory Lab Book # 7, pages 7 & 9.

7. What date do you recall creating this invention? Have been 'carrying around' part of the invention for a long time (>1 year); first written description in internal e-mail dated Feb 8, 2001 to Kyle Frischknecht.

When do you recall first explaining this invention to a witness who is not also a co-inventor? Feb 8, 2001; (only part of the invention)

Who was those witness(es)? Kyle Frischknecht et al. (only part of the invention)

Has this invention been prototyped or tested yet? If so, when, where, by who? What were the results? Not tested yet; internally I am certain and outside our company - I am not aware of anybody who tried it and/or any prior art; Important note: I conceived a significant part of this invention, namely ink-jet printing of the UV-curable liquid prior to the dielectric deposition on August 14, 2001 and did not tell anybody about it; I did some prior art searching to check UV-curable liquid ink-jet printing. Only when I sat down to write this invention disclosure and looked up old e-mails (that to Kyle Frischknecht on Feb 8, 2001), I realized that in fact Kyle was thinking about ink-jet (or screen printing) of the PML UV-curable liquid plus other parts of the invention himself also; see attached e-mail conversation.

8. I have ☒ have not ☐ attached _____ number of additional sheets to better describe this invention.
9. Identify all non-Siemens companies that may in the future benefit from the use of this invention through a license. Potentially a huge range of companies, notably all those working in the field of Organic Light-Emitting Devices (OLEDs); current count well over 100 companies worldwide, essentially almost all display manufacturing companies plus several others entering the display manufacturing field as newcomers (US, Japan, Europe, Taiwan, South Korea, China, etc.); anybody seeking to direct-encapsulate OLEDs (see below for further description).
10. Was this invention developed under, or quoted for, a customer contract? YES ☐ NO ☒
Was it developed under a government contract? YES ☐ NO ☒
If yes to either, please give contract name and number, and further explain the situation N/A

IF THE ANSWERS TO ANY OF THESE QUESTIONS CHANGE BEFORE THIS INVENTION IS FILED AS A PATENT APPLICATION WITH THE GOVERNMENT, MAKE SURE TO SEND AN UPDATE TO SIEMENS IPD.

11. WITNESSED AND UNDERSTOOD BY:

Signature [Signature]

Company Name OOS

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES

INVENTION DISCLOSURE

Name Homer Anton dis Page 2 of 9
Date 10/1/01 Company Address _____

U. Picta
30 Sep 01
Homer Anton
Oct 1, 2001

3 of 9

INSTRUCTION ON HOW TO USE THIS INVENTION DISCLOSURE

General

- PLEASE TYPE OR PRINT CLEARLY. Answer all questions. Use N/A when not applicable.
- Sign and date each page in ink.
Sign and date all attached additional sheets, diagrams, photographs, etc
Please provide all of your given names in full in sections 2 and 3. When there are more than two inventors, use another form and complete and sign items 1, 2, 3 and 10 on the extra forms.
- Every page of the form and accompanying papers should bear the signature of a witness and the date of his/her signing. The witness should have read the forms and attached papers, and should understand the invention before witnessing. The witness should have a technical background related to the invention, to reduce the chances that someone can later challenge his/her ability to have understood the invention.
- A co-inventor should not be the witness. If you have a choice of several qualified witnesses, choose the witness you believe is most likely to still be a Siemens employee available in this country if a question comes up several years from now. That means you should avoid having a co-op student, contract engineer, or a retiring engineer serve as your witness.

Detailed Description

- The description you provide may serve as the basis for a patent application. Therefore, be as complete and as accurate as possible. Attach pages as necessary, using the following checklist as a guide for content.
 - **Abstract:**
In one or two sentences, briefly describe what your invention does and how it is used, e.g., "A voltage-controlled oscillator (VCO) has its period controlled by a current provided by a current source. The current is proportional to the reciprocal of a control signal so that the VCO frequency is directly proportional to the control signal."
 - **Background Information:**
What is the function of your invention?
What is the problem solved by your invention?
How was the function of your invention performed by any prior systems, either a competitor's or ours?
What are the disadvantages of these prior systems?
What are the advantages of your invention over them?
 - **Details:**
Describe in detail the structural and functional operation of your invention. Use drawings and graphs where they would be helpful. Give specific details, not just general information.
Point out things such as what improvements your invention incorporates, or how and why it achieves superior performance (if you know why).
Are there alternative methods or different structural embodiments of your invention?
Can the general idea or technique of your invention be extended to other related fields? How?
Which features are believed to be new?
Describe how you best envision your invention being put to use.

Related Art


Attach a copy (or bibliographic citation) of all publications, patents, etc. that you know about which relate to your invention, and which you think might be important to consider in understanding how your invention differs from prior work.


Potential Licensing Opportunities

Please identify, in relation to item 9, all companies that are not a part of Siemens and may benefit, in the future, from the use of this invention. This will be helpful in identifying potential licensing opportunities for this invention.

REMEMBER TO UPDATE THE IPD IF ANY OF THE INFORMATION YOU PROVIDED CHANGES.

☐ Yes, I promise I will update the Siemens Intellectual Property Department (IPD) if any of the information I've provided changes


Oct 1, 2001

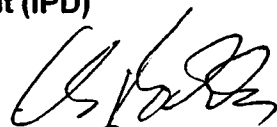
30 Sep 01

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL. THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES

**SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE**

Page 4 of 9
U.S. Patent
378,001

ABSTRACT:

A manufacturing method for the direct encapsulation of OLED devices that encapsulates the sensitive active light-emitting OLED area with at least one encapsulation layer directly over and in contact with the OLED layers but which leaves other, non-light-emitting, areas of the display free of said encapsulation layer.

BACKGROUND:

Presently, OLEDs are typically developed or fabricated on large sheets of glass with several or tens or even in excess of 100 displays per sheet and, once the OLED fabrication on the sheet of glass is finished, the OLED is encapsulated with a second piece of glass or a metal cap, typically with a cavity between the OLED glass and the encapsulation part; said cavity typically holds a getter materials that absorbs or adsorbs residual oxygen and in particular moisture in the package and oxygen and moisture that penetrate into the display package subsequent to encapsulation, typically done by bonding the two pieces together with an epoxy adhesive. After this process the glass, now encapsulated with getter and a second glass or metal cap, is scribed and broken into the individual displays. This encapsulation process is very difficult to manufacture with high yield and reliability, time-consuming (for example the epoxy glue dispense), is very costly (the getter material and the cover glass or metal cap) and adds to the thickness and weight of the overall display.

To get around these problems, various research groups and companies have been developing so-called 'direct encapsulation' methods. One of these techniques, known as Polymer-Multi-Layer (PML) technology, deposits at least one layer of a UV-curable organic liquid material over the whole display glass, said layer is then UV-cured, followed by the deposition of a barrier layer, e.g. a sputtered metal-oxide or generally a dielectric layer. This process may be repeated, to yield largely impermeable barrier layers and to avoid e.g. external particle/dirt-induced pinholes in said encapsulation layer. The problem with the prior art using these approaches is, that only parts of these displays, essentially the active light-emitting OLED area, must be encapsulated against the ingress of e.g. oxygen and moisture but other parts of the display should be kept exposed, for example the contact pads at which the display is connected to external driver circuitry, power supply, etc. In the PML technology for example, a problem arises with the presence of one or more of the direct-encapsulation layers over areas where encapsulation is not required and/or detrimental, such as over the contact pads.

Alternative techniques known in the prior art are to deposit for example 'Parylene' layer or a polysiloxane layer but these techniques also have the problem as the PML technology described above. Alternatively, a dielectric layer such as SiO_x, SiN_x, SiO_xN_y, etc. can be deposited over the OLED for direct encapsulation. This direct dielectric layer encapsulation, in-turn is susceptible to pin-holes and although the deposition (e.g. by sputtering) can be done through masks to block areas over which the encapsulation layer is not desired, this causes additional processing and reliability problems associated with for example the sputter-deposition through masks.

The present invention gets around problems of the prior art by providing processes for an improved direct-encapsulation of OLED devices.

DESCRIPTION OF THE INVENTION:

GENERAL (for all aspects of the invention and embodiments that follow below):

OLED can be typical OLED made on piece of glass with first ITO as first electrode (anode), then OLED layers, then top electrode (cathode); bottom-emitting through glass.

Alternatively, the electrodes can be reversed (cathode at bottom and anode at top).

Alternatively, the OLED can be top-emitting (substrate is opaque, emitting through transparent top electrode); both anode top and cathode bottom and reverse can be used.

Can be used with OLEDs on glass, quartz, metal, plastic foils, metal foils, etc.

Inventor's Signature: *U.S. Patent*

Date: 30 Sep 01

Witness' Signature: *U.S. Patent*

Date: 10/1/01

**THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES**

**SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE**

Page 5 of 9

Can be used for active matrix, passive matrix, segmented, alpha-numeric or backlight OLED displays or any combinations thereof or generally any OLED light source or display.

The organic layers used in the invention are generally known in the prior art, e.g. the PML prior art and the UV-curable monomer and monomer mixes (generally UV-curable compositions); could also be Parylene coatings or other organic coatings that can be deposited in any suitable manner on the OLED without damaging it. Generally organic layers that are carefully outgassed to remove oxygen, moisture and any other reactive mobile species that coat the OLED substrate largely conformally. UV-curable materials are widely known in the prior art (see PML patent literature, see UV-curable printing inks in e.g. www.markem.com or www.vanet.hitachi.co.jp, or D. J. Hayes et al, Journal of the SID, Vol 9/1, 2001 or Hue P. Le, The Society for Imaging Sciences and Technology, Vol 42, No1, Jan/Feb 1998).

NOTE ADDED: can also be e.g. e-beam or thermal cur

The barrier layer of the invention is typically a dielectric such as a SiO_x, AlO_x, SiN_x, AlN_x, SiO_xN_y, ITO, ZnO_x, Al-doped ZnO_x, etc: – generally any high barrier dielectrics (or conductive oxides).

In cases in which the fabricated display is bottom-emitting (through the substrate) and the encapsulation does not have to be transparent, metal films or non-transparent or colored dielectric films can be used as the barrier layer.

The deposition of the barrier layer can be any suitable method known in the prior art to deposit dielectric layers, e.g. sputtering or reactive sputtering (DC, AC; pulsed, combinations thereof, etc.). Evaporation of such dielectrics (resistive heating or electron-beam) or metal films is possible also and so are ion-beam assisted deposition methods or other plasma-enhanced deposition methods.

CLAIMS (aspects of the invention, embodiments; please note that for all of the below-mentioned it is understood that there can be several sequences (multi-layers) of organic + barrier layer):

1. A process for directly encapsulating a multitude of OLED devices fabricated on an undeviated substrate sheet (can be foil) by putting the encapsulation layer directly (in contact with) on the top-most layer of the to-be encapsulated OLED displays and by using a combination of at least one organic layer and at least one inorganic barrier layer whereby said organic layer is deposited / condensed on the OLED substrate in the form of an unpatterned liquid film; whereby: the unpatterned liquid film is cross-linked in a patterned manner, non-cross-linked areas are subsequently removed, followed by the deposition, in a patterned manner, of a barrier layer over at least part of the layer covered with the cross-linked organic layer.
2. As claim 1 whereby flash evaporation is used to deposit the organic layer (as in PML technology of the prior art).
3. As claim 1 whereby dip-, roll-, blade-coating is used to deposit the organic layer.
4. As claim 1 whereby spin-coating is used to deposit the organic layer.
5. As claim 1 whereby evaporation is used to deposit the organic layer.
6. As claim 1 whereby cross-linking of the organic in a patterned manner is achieved by UV flood-exposure through a mask with the mask being less than 5 and preferably less than 1 and better still less than 0.5 mm away from the OLED substrate.
7. As claim 1 whereby cross-linking of the organic in a patterned manner is achieved by selective UV exposure through an optical patterning system such as a projection exposure system.
8. As claim 1 whereby cross-linking of the organic in a patterned manner is achieved by selective UV exposure with a UV-beam scanning system.
9. As claim 1 whereby the non-exposed areas (non-cross-linked) are removed by thermal evaporation (heating the substrate); can be short higher temperature pulse (e.g. by putting the OLED plate onto hotplate).
10. As claim 1 whereby the non-exposed areas (non-cross-linked) are removed by pumping in vacuum.

Inventor's Signature: _____

Witness' Signature: _____

Date: _____

Date: _____

**THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES**

**SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE**

Page 6 of 9

11. Combination of claim 9 and 10.
12. As claim 1 whereby the non-exposed areas (non-cross-linked) are removed by immersion in rinse-tank (washing off), spray-rinsing, ultra-sonicing (dry or wet ultra-sonic), mega-sonic (dry or wet); combination of dry ultra-sonic or mega-sonic in vacuum. *CHG WET TO LIQUID*
13. As claim 1 whereby the removal of the non-cross-linked areas of the organic layer is assisted by a plasma process (even if this removes also some of the cross-linked area as long as the rate for the removal of the non-cross-linked material is larger than that for the cross-linked material).
14. As claim 1 whereby the barrier layer (materials and deposition methods see above) is sputtered through a shadow mask over the area of UV-cured organic. *maybe add: barrier = dielectric barrier = metal add*
15. As claim 14 whereby the barrier layer is slightly larger in x and y to cover also the edges of the organic layer. Note (for the description of the invention): we should state somewhere that because of optical effects the UV-exposed organic is likely not to have a sharp step (e.g. a round/sloped profile instead) and this is advantageous when depositing the barrier layer on top to assure good side-step coverage.
16. As claim 1 whereby the process is used to encapsulate only the organic light-emissive areas (e.g. pixels) of the display and all contact pads and/or auxiliary encapsulation areas (e.g. for secondary encapsulation) and/or scribe/break areas are left free from the organic layer and the barrier layer.
17. New independent claim: As claim 1 but this time the organic is deposited and cured (if necessary) ALL OVER and only the barrier layer is deposited in a patterned manner, said patterned barrier layer also then acts as an etch stop to remove the organic over unwanted areas (i.e. the areas where the barrier layer is not deposited).
18. For claim 17 we can use all organic layer deposition methods as in claim 1 plus additional ones, namely:
19. As claim 17 whereby evaporation of one or more reactive organic molecules is used to deposit the organic layer, said reactive organic molecules forming a condensed conformal film on the substrate.
20. As claim 17 whereby the methods is as the 'Parylene' coating technology known in the prior art.
21. As claim 17 whereby the organic deposition is a plasma-assisted organic material deposition method.
22. As claim 17 whereby the organic that is subsequently not coated with the barrier is removed by an etching step.
23. As claim 22 whereby the etching is a chemical (dry or wet) etch process suitable to remove the organic.
24. As claim 22 whereby the etching is a plasma-assisted etch process suitable to remove the organic.
25. As claim 22 whereby the etching plasma contains oxygen.
26. As claim 22 whereby reactive ion-etching is used.
27. As claim 22 whereby anisotropic reactive ion-etching is used.
28. New independent claim: As claim 1 and 17 but now the organic itself is already during the deposition (by nature of the deposition process itself) deposited in a patterned manner, then curing of the organic (if necessary as e.g. for the UV-curable organics) then patterned deposition of the barrier, no need to remove e.g. non-UV-cured organic.
29. As claim 28 whereby the organic is deposited through a shadow mask using methods as described for claims 1 and 17.
30. As claim 28 whereby the organic is printed, in particular using screen-printing or ink-jet printing.
31. Any of the preceeding claims: all encapsulation process steps in inert atmosphere (reduced oxygen, ozone, other reactive gases and in particular moisture).
32. As claim 31 but only the first organic layer + first barrier layer 'dyad' in inert atmosphere.

Inventor's Signature: *[Signature]*

Date: 30 Sep 01

Witness' Signature: *[Signature]*

Date: 10/1/01

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL. THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES

SUPPLEMENTAL SHEET
FOR INVENTION DISCLOSURE

Page 7 of 9

33. As claim 31 but only the first organic layer in inert atmosphere.
34. Independent claim (?) based on ALL preceeding claims: ... whereby said OLED sheet with the encapsulation of the invention is encapsulated with a secondary encapsulation layer for additional encapsulation and/or mechanical protection.
35. As 34 whereby this is laminating or glueing a plastic or metal or metal+plastic foil or thin glass or thicker (rigid) glass or metal sheet over said OLED display sheet.
36. Finishing all off by singulation of the display (scribe and break) – may not be necessary.
37. As claims 34 – 36 but where the secondary encapsulation is done after singulation.
- 38.

One such example is shown in figure 1: attach Penang VDOT mask drawing with all layers.

Show barrier over the edge of the display → Fig 3.


Fig 2: concept of the invention

✓ ub: added on
1 Oct 01:

with or without
space between the
OLED sheet & the
cover (the 2nd encaps
sheet).

Inventor's Signature: 

Date: 30 Sep 01


Witness' Signature: 

Date: Oct 1, 2001

THIS INVENTION DISCLOSURE IS SIEMENS PROPRIETARY INFORMATION, AND IS CONFIDENTIAL.
THIS DISCLOSURE, AND ITS SUBJECT MATTER, MAY NOT BE DISCLOSED IN WHOLE OR IN PART TO
ANYONE OUTSIDE OF SIEMENS EXCEPT AS APPROVED UNDER SIEMENS CORPORATE PROCEDURES



cover
with
caps.
or
slide
cover
metal,

Fig 1

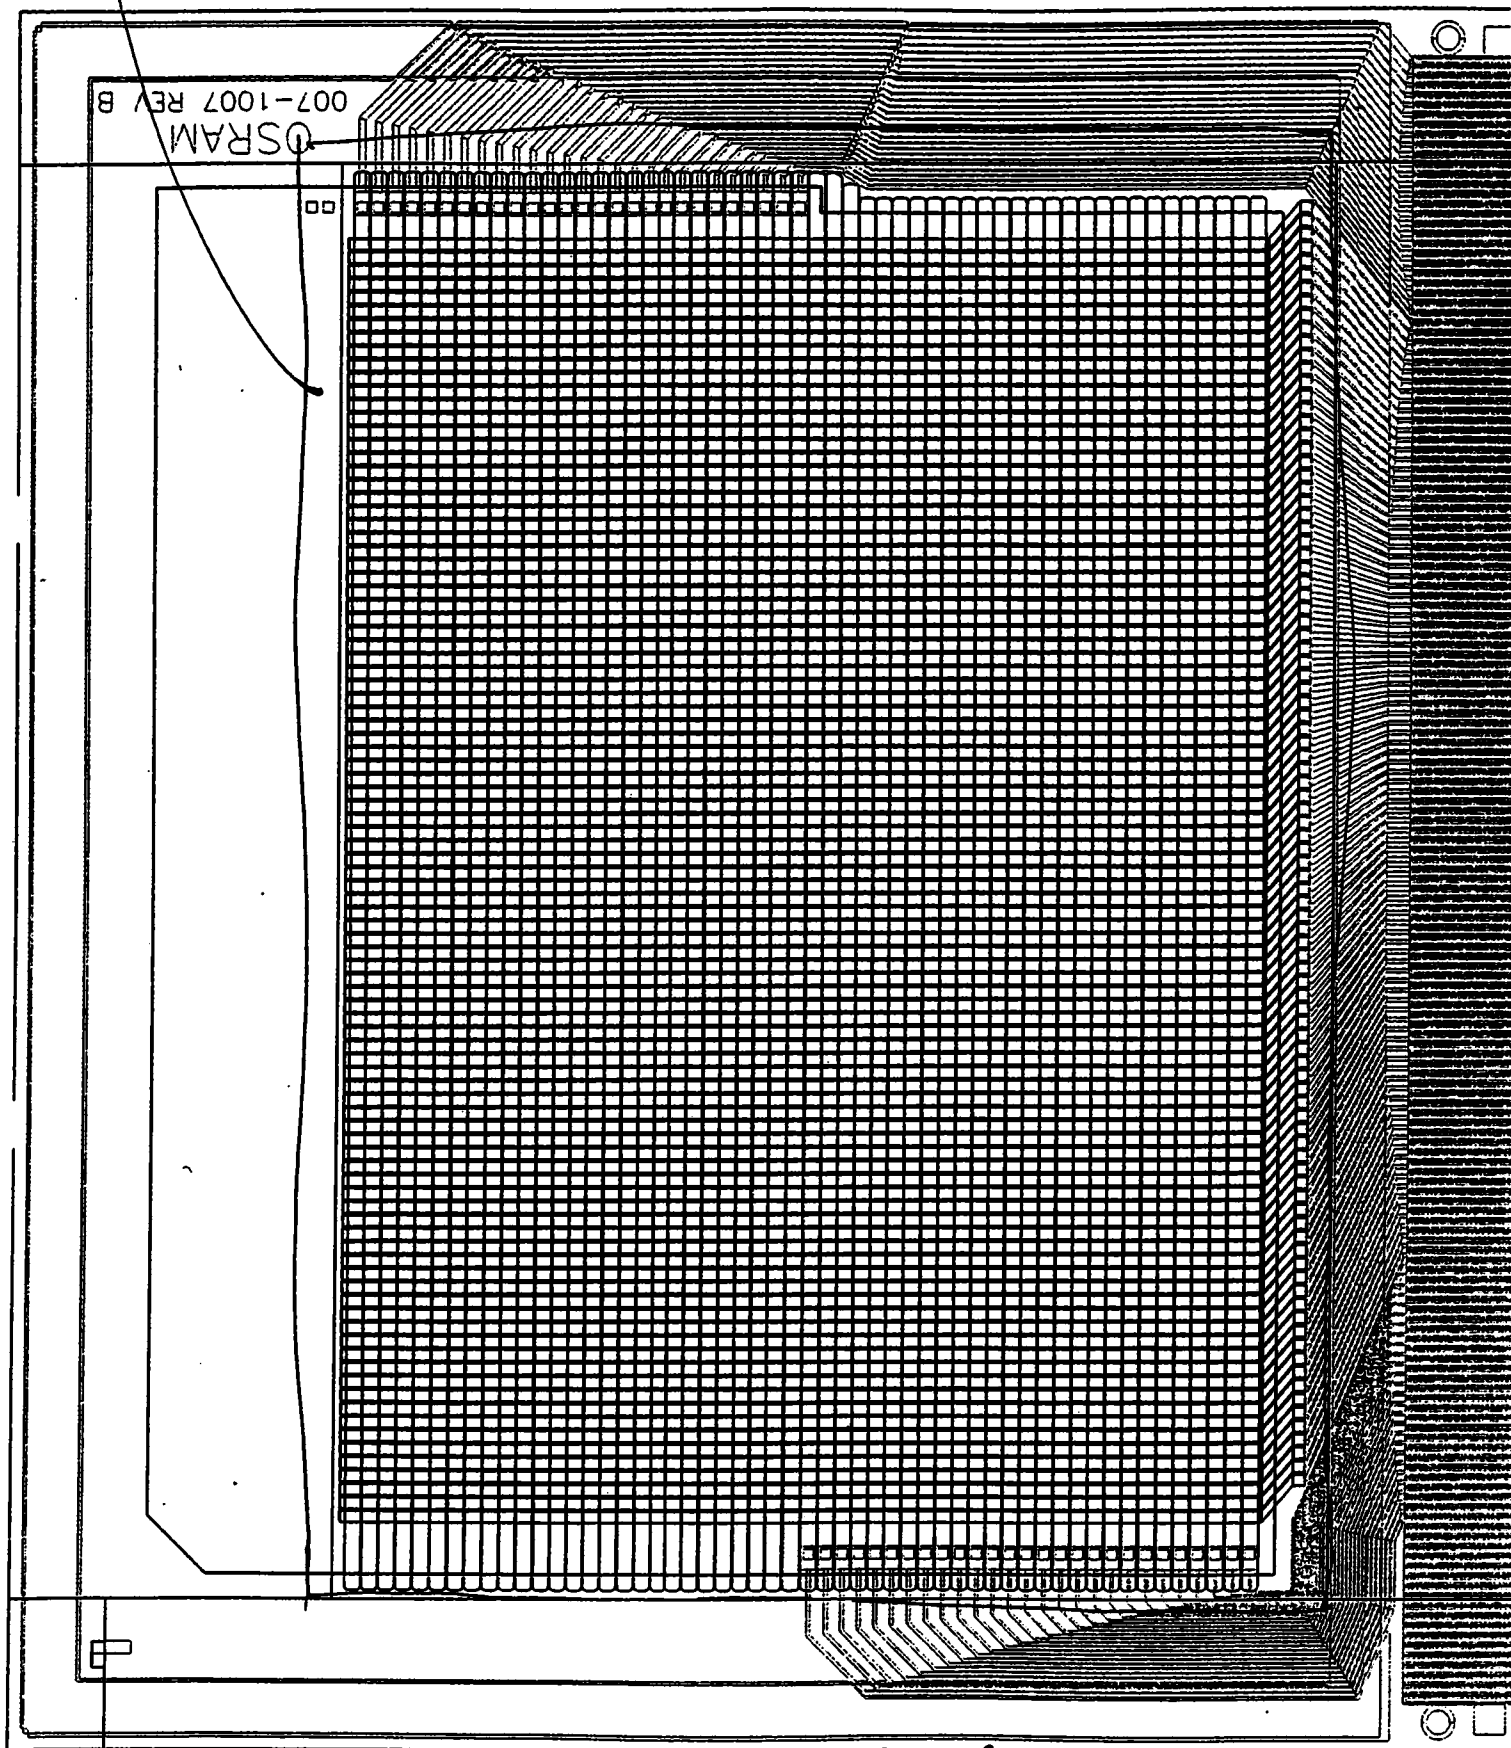

James A. [Signature]
10/1/01

P8 of 9
C. [Signature], 308 p. 01

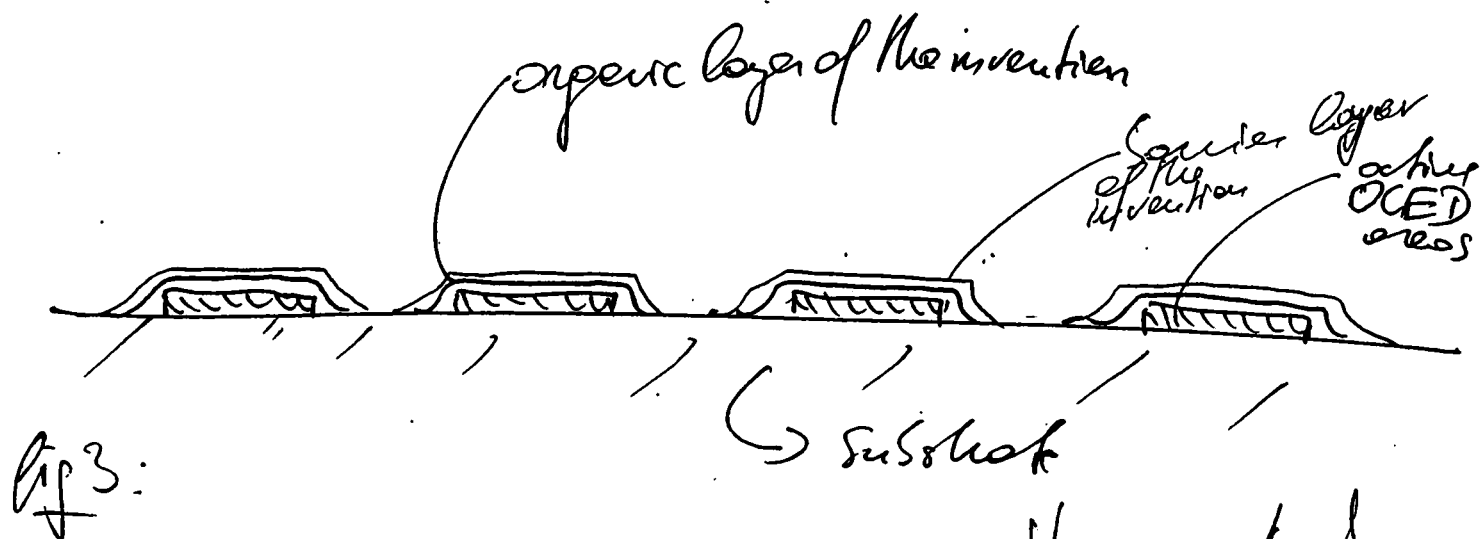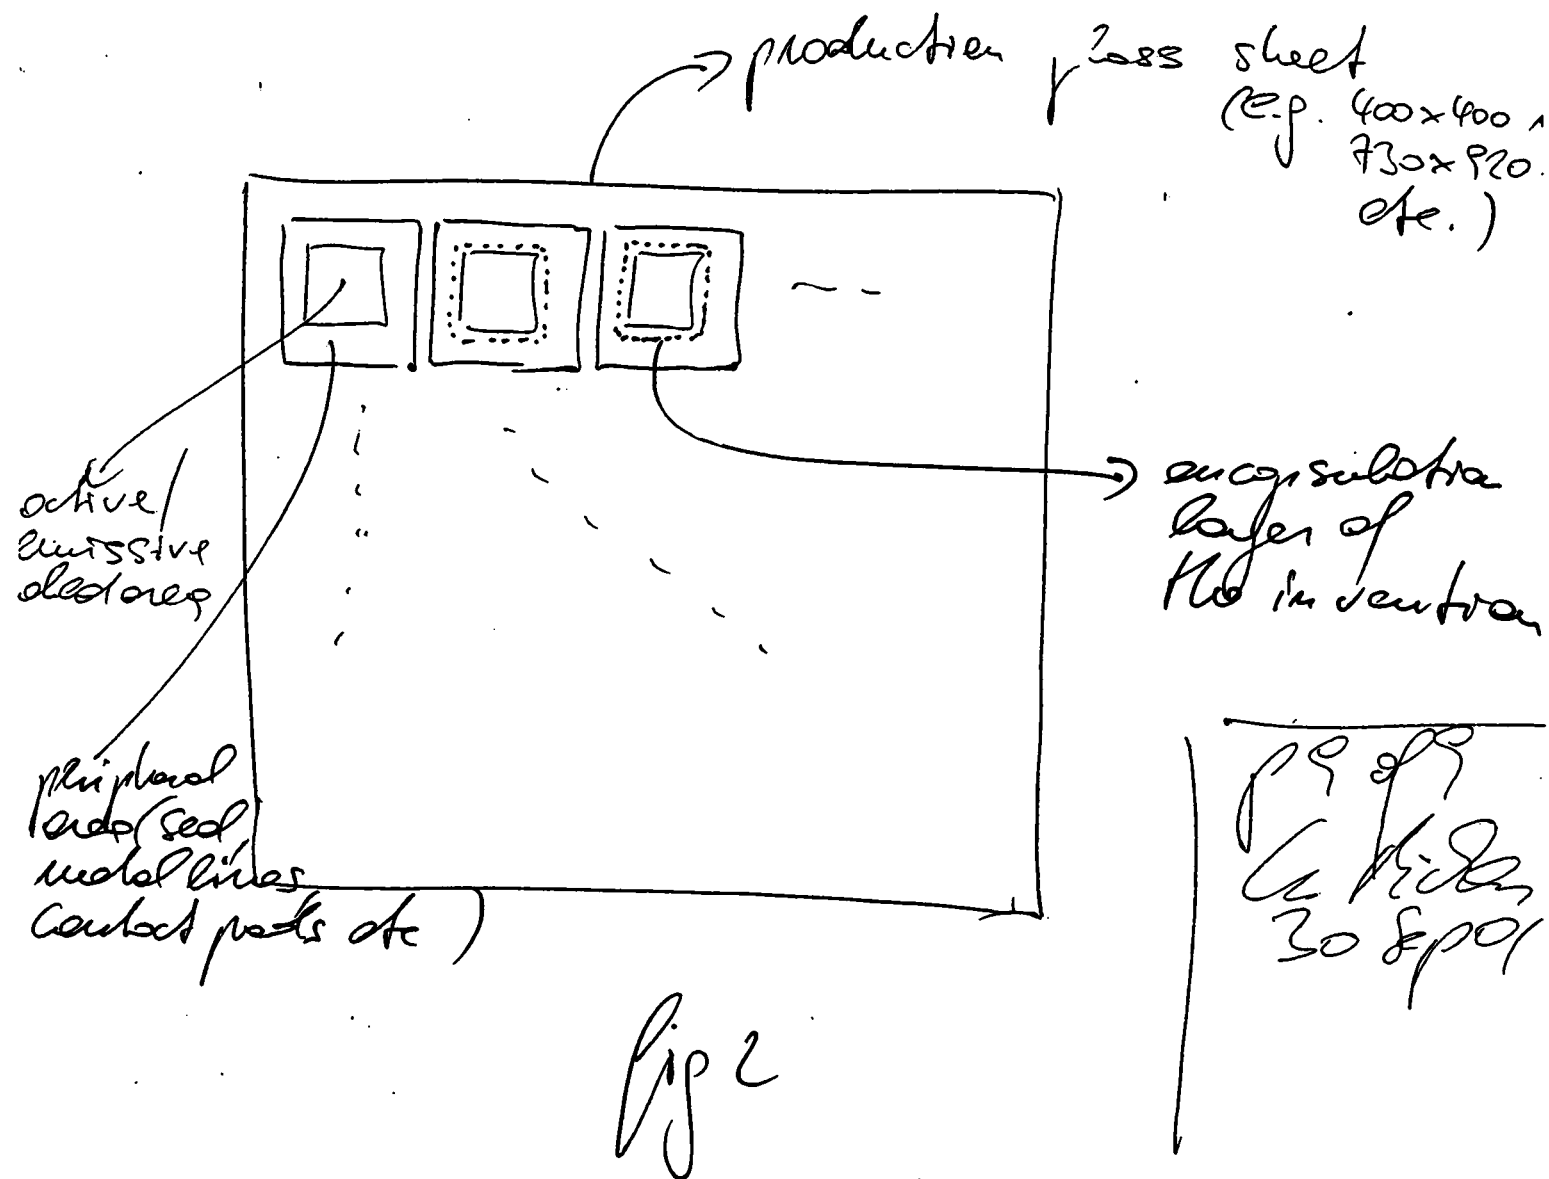

10/1/01

Handwritten signature

IDEA: 14 Aug 01 clump Taney Lines
(J. Reckner)

Problem: cost effective, efficient, simple - dead end

approach: triple transplants / flat / deep
industrial rule - get multiple of
disjoint monomers that are
W-cross-able is well known
(acc. to Taney Lines, Hardscape,
medium scale model /
flat monomers)

Dead end: accs. is big issue

→ one of the solutions → use of ATK
but: ATK NOT simple (acc. to process)

NOTE: I had idea

idea quickly

discuss the idea

→ NOT discussed
with any one

idea / active

→ keep contact problems

→ keep the same

→ not followed (e.g. cores
also contact problems)

→ use to be get lipid now
in permeable fluid active
dead end → 5 - long →
permeable (e.g. water through shell
membrane) discrete fluid step

Read and Understood By

Continued on Page

U. Reckner

14 Aug 01

M. H.

11/10/01

Date

Signed

Date

~~IDEA~~ IDEA: 15 Aug 01

VC → BOT: have been 'convinced'
 this idea around
 with me for ~ 2.5y
 (told by, & others)

→ issue: use of PNL to encapsulate OLED → see e.
 (8th)

→ problem: liquid manure. (to be + liquid by VC
 goes anywhere (also when not
 worked, e.g. on
 contact points seal
 found, etc.)

idea/solve: → PNL → coat manure like
 film (float away)

VC → cross - but through PNL

→ making liquid film gets
 water test / washed off

→ apply encapsulating film on
 top also through work → may
 repeat.

→ conclude: encaps OLED active area
 but leave contact points etc
 free

Continued on Page

Read and Understood By

U. K. P. C. R. A.

15 Aug 01

Date

M. M. A.

Signed

01/10/01

