

IUPAC-NIST Solubility Data Series 70. Solubility of Gases in Glassy Polymers

Volume Editors

Russell Paterson

University of Glasgow, Glasgow, United Kingdom

Yuri Yampol'skii

Topchiev Institute of Petrochemical Synthesis, Moscow, Russia

with the assistance of

Peter G. T. Fogg

University of North London, London, United Kingdom

Contributors

Alexandre Bokarev

Topchiev Institute of Petrochemical Synthesis, Moscow, Russia

Valerii Bondar

North Carolina State University, Raleigh, North Carolina

Oleg Ilinich

Boriskov Institute of Catalysis, Novosibirsk, Russia

Sergey Shishatskii

Topchiev Institute of Petrochemical Synthesis, Moscow, Russia

Contributor and Evaluator

Yuri Yampol'skii

Topchiev Institute of Petrochemical Synthesis, Moscow, Russia

Received December 11, 1998

Solubility of gases in polymers is an important property of polymeric materials relevant to many practical applications. Sorption of small molecules in polymers is a fundamental concern in such areas as food packaging, beverage storage, and polymer processing. However, by far the main interest in the solubility of gases in polymers, and especially in glassy polymers, is related to development of novel advanced materials for gas separation membranes. This is because the concentration gradient of a dissolved gas is the driving force of membrane processes. Development of these novel separation methods resulted in a rapid accumulation, in the recent literature, of thermodynamic data related to the solubility of gases in polymers at different temperatures and pressures. Polymers can be regarded as special cases of media intermediate between liquids and solids. As a consequence, modeling of gas sorption in polymers is very difficult and

©1999 by the U.S. Secretary of Commerce on behalf of the United States.

All rights reserved. This copyright is assigned to the American Institute of Physics and the American Chemical Society.

Reprints available from ACS; see Reprints List at back of issue.

0047-2689/99/28(5)/1255/196/\$95.00

1255

J. Phys. Chem. Ref. Data, Vol. 28, No. 5, 1999

Ningde Amperex Tech. Exhibit No. 2049
Zhuhai CosMX Battery Co. Ltd. v. Ningde Amperex Tech.
IPR2025-00432, U.S. Patent No. 11,575,148
Page 1 of 196

presents a permanent challenge to theoreticians and experimenters. The collection and critical evaluation of solubility data for various gas–polymer systems is relevant to both practical aspects of polymer applications and to fundamental studies of polymer behavior. This volume of the IUPAC-NIST Solubility Data Series summarizes the compilations and critical evaluations of the data on solubility of gases in glassy polymers. It is implied in this edition that “gases” are the components that are either permanent gases (supercritical fluids) or have saturated vapor pressure more than 1 atm at ambient conditions (298 K). The polymeric components of compilations and critical evaluations are primarily high molecular mass, amorphous, linear (noncross-linked) compounds that have the glass transition temperatures above ambient temperature. The data for each gas–polymer system have been evaluated, if the results of at least three independent and reliable studies have been reported. Where the data of sufficient accuracy and reliability are available, values are recommended, and in some cases smoothing equations are given to represent variations of solubility with changes in gas pressure and temperature. Referenced works are presented in the standard IUPAC-NIST Solubility Data Series format. Depending on the gas–polymer system, reported data are given in tabular form or in the form of sorption isotherms. The data included in the volume comprise solubilities of 30 different gases in more than 80 primarily amorphous homo and copolymers. Where available, the compilation or critical evaluation sheets include enthalpies of sorption and parameters for sorption isotherms. Throughout the volume, SI conventions have been employed as the customary units in addition to the units used in original publications.

© 1999 American Institute of Physics and American Chemical Society.

[S0047-2689(99)00305-0]

Contents

1. Preface.	1259	3.18. Polycarbonate—Sulfur Dioxide.	1348
2. Introduction to the Solubility Data Series. The Solubility of Gases in Polymers.	1260	3.19. Polycarbonate—Methane.	1351
3. Critical Evaluations and Compilations of Selected Systems.	1265	3.20. Polycarbonates—Propane and Other Gases.	1352
3.1. Poly(4-Methylpentene-1)—Carbon Dioxide, Methane, Other Gases.	1265	3.21. Poly(Aryl- <i>bis</i> -Isopropylidene Ether Ketone)—Carbon Dioxide and Methane.	1363
3.2. Poly(Vinyl Chloride)—Nitrogen, Carbon Dioxide, Methane.	1267	3.22. Polyarylate—Various Gases.	1364
3.3. Poly(Vinyl Acetate)—Various Gases.	1271	3.23. Polyhydroxyether—Carbon Dioxide, Methane, Nitrogen.	1367
3.4. Poly(Acrylonitrile)—Carbon Dioxide.	1273	3.24. Poly(Phenolphthalein Phthalate)—Various Gases.	1368
3.5. Poly(Methyl Methacrylate)—Carbon Dioxide, Other Gases.	1274	3.25. Polysulfone—Carbon Dioxide.	1371
3.6. Poly(Ethyl Methacrylate)—Carbon Dioxide, Other Gases.	1283	3.26. Polysulfone—Methane and Other Gases.	1373
3.7. Polystyrenes—Various Gases.	1290	3.27. Cellulose—Sulfur Dioxide.	1384
3.8. Poly(Vinyl Cyclohexane Carboxylate)—Carbon Dioxide.	1307	3.28. Nitrocellulose—Various Gases.	1385
3.9. Poly(Vinyl Benzoate)—Various Gases.	1309	3.29. Ethyl Cellulose—Various Gases.	1385
3.10. Poly(Vinyl Butyral)—Carbon Dioxide.	1312	3.30. Cellulose Acetate—Carbon Dioxide.	1389
3.11. Poly(Vinylmethylether)—Propane.	1313	3.31. Poly(γ -Methyl Glutamate)—Carbon Dioxide.	1393
3.12. Poly(Vinyltrimethyl Silane)—Various gases.	1313	3.32. Poly(β -Benzyl- <i>L</i> -Aspartate)—Carbon Dioxide.	1397
3.13. Poly(Trimethylsilyl Propyne)—Various Gases.	1318	3.33. Polyamides (Nylons)—Various Gases.	1398
3.14. Poly(Phenylene Oxides)—Various Gases.	1323	3.34. Polyimide Kapton H—Carbon Dioxide, Methane, Sulfur Dioxide.	1400
3.15. Poly(2,3-Dimethylphenylene Oxide)—Carbon Dioxide, Methane.	1323	3.35. Polyimide Upilex R—Carbon Dioxide.	1406
3.16. Poly(Ethylene Terephthalate)—Carbon Dioxide and Other Gases.	1330	3.36. Other Polyamides—Various Gases.	1409
3.17. Polycarbonate—Carbon Dioxide.	1340	3.37. Polypyrrolone—Various Gases.	1413
		3.38. Block Copolymers and Polymer Blends—Various Gases.	1413
		4. Structural Formulas of Polymers.	1431
		5. Polymer Index.	1441
		6. Gas Index.	1443

7. Registry Number Index.....	1443
8. Author Index.....	1445
9. Solubility Data Series: Published Volumes 66–70.....	1448

List of Figures

1. Sorption isotherms of Ar, N ₂ , CH ₄ (a) and CO ₂ (b) in PVC at 308 K.....	1269
2. Solubility coefficients $S/(\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1})$ for gases in PVA: curves 1: Helium; curves 2: Neon; curves 3: Hydrogen. Continuous curves taken from equilibrium experiments, broken curves from diffusion experiment.....	1271
3. Sorption isotherms for hydrogen in PVA at 268 K and 278 K.....	1272
4a. Temperature dependence of the solubility coefficient $S/(\text{g g atm}^{-1})$	1274
4b. Sorption isotherms of carbon dioxide in PMMA.....	1276
5. Mixed-gas sorption of CO ₂ /C ₂ H ₄ in PMMA at 1.53 ± 0.05 atm CO ₂	1277
6. Mixed gas sorption of CO ₂ and C ₂ H ₄ at 1.53 atm CO ₂ (a) and 3.64 atm CO ₂ (b).....	1278
7. Mixed gas sorption of CO ₂ and C ₂ H ₄ at 3.93 atm C ₂ H ₄ (a) and 2.06 atm C ₂ H ₄ (b).....	1279
8. Sorption isotherms for pure gases in PMMA at 308 K.....	1280
9. High-pressure mixed-gas sorption of CO ₂ /NO ₂ at 5.00 atm N ₂ O.....	1280
10. High-pressure mixed-gas sorption of CO ₂ /C ₂ H ₄ at 5.05 atm CO ₂	1281
11. High-pressure mixed-gas sorption of CO ₂ /C ₂ H ₄ at 4.87 atm C ₂ H ₄	1281
12. Temperature dependence of (a) p_g/MPa and (b) $C_g/(\text{cm}^3(\text{STP})\text{cm}^{-3})$	1283
13. Temperature dependence of the solubility coefficients.....	1284
14. Sorption isotherms of carbon dioxide in PEMA.....	1284
15. Sorption isotherms of carbon dioxide in PEMA at 288, 298, 308, and 318 K.....	1285
16. Temperature dependence of Langmuir adsorption parameter $C'_H/(\text{cm}^3(\text{STP})\text{cm}^{-3})$	1291
17. Temperature dependence of apparent solubility coefficient $S/(\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1})$	1291
18. The solubility of chlorodifluoromethane (Freone 22) in PS was measured only in three papers. ^{1–3} Barrie <i>et al.</i> ³ studied this system using a gravimetric technique in the temperature range 293–333 K. At much higher temperatures, this system was investigated by means of inverse gas chromatography. ² The figure shows the temperature dependence T/K of the solubility coefficient $S/(\text{cm}^3(\text{STP})\text{g}^{-1}\text{atm}^{-1})$	1294
19. Sorption isotherms of carbon dioxide in various monodisperse polystyrenes at 308 K....	1298
20. Effect of temperature on sorption isotherms of carbon dioxide in PS containing 3% by mass of mineral oil (a) and 10% by mass of TCP (b).....	1299
21. Sorption and desorption isotherms of carbon dioxide in PVB. Open and filled symbols represent sorption and desorption, respectively..	1309
22. Sorption and desorption isotherms of carbon dioxide in PVB at 298 K: (□) first sorption run; (○)(●) subsequent sorption and desorption runs.....	1310
23. Sorption and desorption isotherms of carbon dioxide in PVBu at 298 K: (□) first sorption run; (○)(●) subsequent sorption and desorption runs.....	1312
24. Sorption isotherms of various gases in PTMSP at 308 K.....	1318
25. Sorption isotherms of various gases in PTMSP at 298 K.....	1320
26. Sorption isotherms of various gases in PTMSP at 298 K.....	1320
27. Sorption isotherms of various gases in PPO at 298 K.....	1323
28. Mixed gas sorption CO ₂ /CH ₄ in poly(phenylene oxide) at 308 K. (Solid lines) sorption model for mixed gas sorption $C_i = k_{Di}p_i + C'_H b_i p_i / (1 + b_i p_i + b_j p_j)$. (Dotted lines) sorption model for pure gases.....	1324
29. Mixed gas sorption CO ₂ /CH ₄ in CPPO at 308 K and two different pressures. (Solid lines) sorption model for mixed gas sorption $C_i = k_{Di}p_i + C'_H b_i p_i / (1 + b_i p_i + b_j p_j)$. (Dotted lines) sorption model for pure gases.....	1329
30. Temperature dependence of Langmuir adsorption capacity $C'_H/(\text{cm}^3(\text{STP})\text{cm}^{-3})$. (□) Ref. 1; (■) Ref. 2; (●) Ref. 5; (○) Ref. 9 (crystallization by exposure to CO ₂); (◆) Ref. 9 (crystallization by heating).....	1330
31. Sorption isotherms of carbon dioxide in CO ₂ -conditioned crystalline PETP, measured after CO ₂ sorption experiment at 308 K. Open and filled symbols represent sorption and desorption, respectively.....	1334
32. Sorption isotherms of carbon dioxide in amorphous PETP. The dotted arrows show the decreases in concentration accompanying crystallization. Open and filled symbols represent sorption and desorption, respectively..	1334
33. Sorption isotherms of carbon dioxide in c-PETP.....	1335
34. Sorption isotherms of carbon dioxide in h-PETP.....	1335
35. Sorption isotherms of carbon dioxide in PBTP..	1339
36. Effect of temperature on carbon dioxide sorption in PC for “as-received” material conditioned at 20 atm of CO ₂	1343

37. Equilibrium sorption of carbon dioxide in PC samples annealed at 398 K. Sorption measurements were made at 308 K after conditioning at 20 atm of CO₂..... 1343
38. Same as for Fig. 37 except that the annealing temperature was equal to 408 K..... 1343
39. Sorption and desorption isotherms of carbon dioxide in polycarbonate at 308 K. Open and filled symbols represent sorption and desorption, respectively..... 1344
40. Sorption isotherms of CO₂ in PC at 308 K for conditioning pressures of 300, 600, and 900 psia. (○) "as-received," (●) CO₂ conditioned.. 1347
41. Initial CO₂ sorption and desorption in PC at 308 K after conditioning pressures of 300, 600, and 900 psia. (○) "as-received," (●) desorption. 1347
42. Sorption isotherms of CO₂ at 308 K in CO₂-conditioned, "as-received," and annealed PC. The annealed sample was first CO₂ conditioned at 900 psia and then annealed at 408 K for 500 h under vacuum. (○) "as-received," (●) 900 psia conditioned, (□) annealed..... 1347
43. Sorption isotherms of sulfur dioxide in polycarbonate..... 1350
44. Sorption isotherms of methane in polycarbonate for unconditioned, carbon dioxide conditioned and exchange conditioned samples..... 1352
45. Sorption isotherms for propane in PC..... 1353
46. Sorption isotherms of various gases in polycarbonate at 308 K..... 1354
47. Comparison of sorption isotherms of methane at 308 K in TMPC for unconditioned and conditioned films..... 1355
48. Comparison of sorption isotherms of methane at 308 K in TCPC for unconditioned and conditioned films..... 1355
49. Comparison of sorption isotherms of methane at 308 K in TBPC for unconditioned and conditioned films..... 1356
50. Sorption isotherms of carbon dioxide at 308 K in polycarbonates conditioned by prior CO₂ exposure..... 1356
51. Sorption isotherms of methane at 308 K in polycarbonates conditioned by prior CO₂ exposure. (○) PC; (◆) TMPC; (□) TCPC; (●) TBPC. 1356
52. Sorption isotherms of nitrogen at 308 K in polycarbonates without prior CO₂ exposure..... 1356
53. Sorption (open points) and desorption (filled points) isotherms of carbon dioxide in TMPC for maximum conditioning pressures of 37.95 (○), (●) and 62.1 (□), (■) atm. (◆) second desorption. 1358
54. Sorption isotherms of carbon dioxide in PAEK-6H6F (○) and PAEK-6F6H (●)..... 1363
55. Sorption isotherms of sulfur dioxide in polyarylate..... 1366
56. Sorption isotherms of carbon dioxide (□), methane (●), and ethane (○) in the polymer at 308 K..... 1370
57. Sorption isotherms of various gases in Kodar A-150 at 308 K..... 1371
58. (a) $\log S$ vs $1/(T/K)$; (b) $\log k_D$ vs $1/(T/K)$; (c) $\log b$ vs $1/(T/K)$; (d) C'_H vs T/K . [(●) Ref. 1; (○) Ref. 4; (□) Ref. 5; (◆) Ref. 6.]... 1372
59. Sorption isotherms of various gases in "as-received" polysulfone films..... 1375
60. Effects of history of sample treatment on sorption isotherms: CO₂ sorption at 308 K. 1375
61. Effect of temperature on CO₂ sorption isotherms in pure polysulfone..... 1377
62. Effect of the content of DDS (mass %) on CO₂ sorption isotherms for polysulfone at 308 K..... 1377
63. Effect of the content of PNA (mass %) on CO₂ sorption isotherms for polysulfone at 308 K..... 1377
64. Effect of the content of TCP (mass %) on CO₂ sorption isotherms for polysulfone at 308 K..... 1377
65. Sorption isotherms of carbon dioxide in polysulfone..... 1379
66. Sorption isotherms of methane in polysulfone... 1379
67. Temperature dependence of apparent solubility coefficient $S/(\text{cm}^3(\text{STP}) \text{ cm}^{-3} \text{ atm}^{-1})$ 1389
68. Temperature dependence of Henry's law solubility coefficient $k_D/(\text{cm}^3(\text{STP}) \text{ cm}^{-3} \text{ atm}^{-1})$ 1390
69. Sorption isotherms of carbon dioxide. Continuous curves: Gas solubilities calculated from the dual mode sorption model. Dotted curve: Gas solubility at 343 K calculated from the empirical relation $C = 1.4 p \exp(-0.02p)$... 1391
70. Solubility isotherms of methane in cellulose 2,4-acetate (sample I). Solubility=(vol. of gas at STP/cm³)/(mass of unswollen polymer/g).... 1392
71. Reproducibility of solubility isotherms of methane in cellulose 2,4-acetate at 293 K. Solubility=(vol. of gas at STP/cm³)/(mass of unswollen polymer/g). (Solid line) calculated from the dual mode sorption model with sample I, after exposure to CO₂; (○) measurements with sample II prior to CO₂ exposure; (●) measurements with sample II after exposure to high-pressure CO₂..... 1392
72. Sorption isotherms of carbon dioxide in cellulose acetate. 1393
73. Sorption isotherms of carbon dioxide (a) and xenon (b) in PMG. Sorption=(vol. of gas at STP/cm³)/mol of residue. (□) 293 K, (●) 298 K, (○) 303 K, (+) 308 K. Broken line is heat treated sample..... 1393

74. Sorption isotherms of xenon in PELG.
Sorption=(vol. of gas at STP/cm³)/mol of residue.
(□) 293 K, (●) 298 K, (○) 303 K, (+) 308 K. Broken line is heat treated sample..... 1395
75. Sorption isotherms of xenon in
poly(*n*-alkyl-*L*-glutamates) at 298 K.
Sorption=(vol. of gas at STP/cm³)/mol of residue.
(■) Me, (□) Et, (●) Pr, (○) Bu, (+) Amyl.... 1395
76. Fugacity ratio calculated by corresponding
state principle, Refs. 1 and 2. Sorption=(vol.
of gas at STP/cm³)/mole of residue.
Sorption isotherms of carbon dioxide in PBLG.
(■) PBLG cast from benzene at 318 K, (□)
same film heat treated, (●) PBLG cast from
benzene at 333 K, (○) same film heat
treated, (+) cast from ethylene dichloride at
298 K..... 1396
77. Sorption isotherms of carbon dioxide in the α
and ω forms of PBLA.
Sorption=(vol. of gas at STP/cm³)/mol of residue.
(□) 303 K, (●) 308 K, (○) 313 K. Continuous
line: α form; Broken line: ω form..... 1397
78. Sorption isotherms of carbon dioxide in
Kapton H at 333 K. Different symbols
stand for different runs..... 1400
79. Sorption isotherms of methane in Kapton H at
333 K. Different symbols stand for different
runs..... 1401
80. Sorption isotherms in commercial Kapton H
(○) and synthesized samples of polyimide (●)
obtained by reaction of pyromellitic
dianhydride and oxydianiline PMDA-ODA.... 1402
81. Sorption isotherms of sulfur dioxide in
polyimide Kapton H..... 1405
82. Temperature dependence of apparent solubility
coefficient $S/(\text{cm}^3(\text{STP}) \text{ cm}^{-3} \text{ atm}^{-1})$ 1406
83. Temperature dependence of the affinity
parameter $b/(\text{atm}^{-1})$ 1406
84. Temperature dependence of Henry's law
solubility coefficient $k_D/(\text{cm}^3(\text{STP}) \text{ cm}^{-3} \text{ atm}^{-1})$ 1406
85. Sorption isotherms of carbon dioxide in
polyimide Upilex R..... 1408
86. Sorption isotherms of nitrogen and oxygen in
CVC-VA at 298 K for different times of
annealing at 433 K: (a) as cast; (b) 5 h
annealing; (c) 15 h annealing..... 1414
87. Sorption isotherms of carbon dioxide in CVC-
VA at 298 K for different times of annealing
at 433 K: (a) as cast; (b) 1 h; (c) 5 h; (d)
10 h; (e) 15 h..... 1415
88. Sorption (open symbols) and desorption
(closed symbols) isotherms of sulfur dioxide
in block-copolymers with mass % siloxane
content of 13% (circles) and 42% (squares).... 1418
89. Sorption isotherms of sulfur dioxide in
silane-siloxane copolymers with mass %
siloxane content of: 0% (1), 4% (2), 13% (3),
22% (4), 34% (5), 38% (6), 42% (7), 62%
(8), 100% (9)..... 1418
90. Sorption of carbon dioxide was studied in
homogeneous and phase separated blends
PMMA/CPSAN (50/50 by mass). The
composition of CPSAN is 28 mass % of
acrylonitrile. The parameters of dual mode
sorption isotherm for carbon dioxide in the
blends at 308 K are: $k_D=0.89 \text{ cm}^3(\text{STP})/$
 $\text{cm}^3 \text{ atm}$; $C'_H=16.6 \text{ cm}^3(\text{STP})/\text{cm}^3$;
 $b=0.183 \text{ atm}^{-1}$. Sorption isotherm of carbon
dioxide in homogeneous (●) and
phase-separated (○) PMMA/CPSAN blends... 1420
91. Sorption isotherm of carbon dioxide in an
amorphous blend containing 65% PMMA
and 35% PVF₂ at 308 K..... 1420
92. Sorption isotherms of carbon dioxide in
PMMA/PVF₂ blends at 308 K (mass % PVF₂).. 1421
93. Sorption isotherms of carbon dioxide in
PMMA/PVF₂ blends at 308 K for 35 and
50 mass % of PVF₂..... 1421
94. Sorption isotherms of Ar, CH₄ and N₂ in PVF₂
at 308 K..... 1422
95. Sorption isotherms of Ar, CH₄, and N₂ in
PMMA at 308 K..... 1422
96. Sorption isotherms of argon in PMMA/PVF₂
blends at 308 K..... 1423
97. Sorption isotherms of carbon dioxide in
conditioned blends and homopolymers at
308 K..... 1423
98. Sorption isotherms of methane in unconditioned
blends and homopolymers at 308 K..... 1424
99. Sorption isotherms of carbon dioxide in TMPC/
PS blends at 308 K..... 1428
100. Sorption isotherms of methane in TMPC/PS
blends at 308 K..... 1429

1. Preface

The solubility of gases in polymers is an important property of polymeric materials relevant to many practical applications. In addition, information on the solubility of gases, its dependence on temperature, pressure, and pretreatment of polymer are indicative of polymer structure and mechanism of gas sorption and diffusion in polymers. The shape of solubility isotherms can indicate behavior at the molecular level. Sorption of small molecules in polymers is a fundamental concern in such areas as packaging and polymer processing. Dissolution of gases in polymers, especially at high pressure, takes place in many industrial processes and data on the solubility of gases are required in diverse and important applications. Examples include the dissolution of ethene and

other gases in the process of high pressure polymerization of ethene, gas dissolution in injection molding processes, and postreactor polymer processing.

However, the main interest in the solubility of gases in polymers is due to the development of novel advanced materials for gas separation membranes. The driving force in gas transport through such nonporous polymeric membranes is the gradient of concentration of diffusing molecules across the membrane. Therefore, the solubility, the form of sorption, isotherms, and the values of their parameters are of utmost importance for understanding sorption and transport of gases and development of better gas separation processes. An interesting manifestation of this tendency is that 90% of the data available today on gas solubility in polymers and sorption thermodynamics were obtained during the last 10–15 yr, and these years were marked by important advances in the development of membrane gas separation processes.

This volume in the Solubility Data Series contains tabulated collections and critical evaluations of original data for the solubility of gases in glassy polymers. A later volume will contain compiled and evaluated data for the solubility of gases in rubbery and semicrystalline polymers as well as updated data for crystalline polymers. In some cases, the published data include the solubility at temperatures higher than the glass transition temperature of a polymer that is glassy under ambient conditions, for example polystyrene at 373–473 K. In such cases the editors preferred not to split the solubility data between two volumes and included corresponding compilation sheets in this volume.

The chemical structure of the repeat units of polymers was accepted as the basis for organizing the material within this volume. First, carbon-chain polymers are considered followed by heterochain polymers. Each polymer studied in a particular published work has been given a separate compilation sheet. Data from the same published work for the dissolution of different gases in the same polymer have been entered in the same compilation sheet. Gases are considered in sequences of increased complexity from monatomic to diatomic and so on. If several compilation sheets are available for the same polymer–gas system, the material is arranged in chronological order. Enthalpies of solution are also reported where available.

Abundant data that are available in the literature on gas solubility in polymers can be divided into two groups: the data based on direct measurements using volumetric, gravimetric, chromatographic or other methods; and the data acquired via an indirect way using the equation $S = P/D$, where S is the solubility coefficient, and P and D are the gas permeability and diffusion coefficients, respectively. Although in many cases the values obtained using both approaches are in reasonable agreement, the authors of the present volume have not compiled solubility data obtained by an indirect method because these data are less reliable.

Critical evaluations were prepared only in those cases where:

- (1) two or more papers were available for the given gas–polymer system;
- (2) the data corresponded to overlapping ranges of variation of pressure and/or temperature. In only a few cases, however, has there been a sufficient number of detailed studies to enable the evaluator to recommend a set of solubility values.

The data were gathered from a search of the chemical literature from the first years of this century to the first part of 1991.

The editors would like to acknowledge the help and advice from several fellow members of the IUPAC Commission on Solubility Data and in particular Professor Larry Clever (Emory University, USA) and Dr. Peter Fogg (U.K.). Enormous help of S. McFadzean and Marielle Lorusso in the final part of the preparation of the manuscript is also acknowledged and much appreciated. Professor D. R. Paul and Professor W. J. Koros, from The University of Texas at Austin, kindly provided us with the reprints and preprints of their numerous papers. This greatly facilitated our work on compilation and critical evaluation of data.

Russell Paterson
University of Glasgow,
Glasgow, Scotland
Yuri Yampolskii
Institute of Petrochemical Synthesis,
Russian Academy of Sciences, Moscow, Russia.

2. Introduction to the Solubility Data Series. The Solubility of Gases in Polymers

The Solubility Data Project aims to make a comprehensive search of the literature for data on the solubility of gases, liquids, and solids in liquids. Polymers can be regarded as a special case of media intermediate by their properties between liquids and solids. The data for each system are evaluated, and where data of sufficient accuracy and reliability are available, values are recommended and in some cases a smoothing equation is suggested to represent the variation of solubility with gas pressure and/or temperature. In the case of polymers, the correlations of the solubility with some parameters of gases can also be given. A text presenting an evaluation and recommended values and the compiled data sheets are published on consecutive pages.

Definition of Gas Solubility

The distinction between solubilities of gases in liquids (polymers) and vapor–liquid equilibrium is arbitrary. It is generally accepted that the equilibrium set up between a polymer and a typical gas as argon at 298 K, i.e., above its critical temperature, is gas–liquid solubility, where as the equilibrium set up at the same temperature between the same polymer and *n*-butane is an example of vapor–liquid equi-

librium. In this volume, we have taken a fairly liberal view that is in line with the general policy of all the volumes of the Solubility Data Series.

We defined gases as the compounds having vapor pressure more than 1 atm at the temperature 298 K, or having the normal boiling point of 298 K or above. So, e.g., the equilibrium solubility of 2,2-dimethylpropane (neo-pentane) was included whereas the solubility of *n*-pentane was not. The solubility of the vapor of the compounds that are liquid at 298 K will be considered in a subsequent volume of Solubility Data Series.

It is much more difficult to define adequately polymers as solvents. A transition from low molecular mass compounds to high polymers proceeds continuously, and establishing a boundary between these two kinds of chemical objects is always arbitrary. However, help in this essentially tentative choice can come if we bear in mind the fact that studies of solubility in polymers stemmed from many practical applications of high polymers found as construction, barrier, or packaging materials, membranes, etc. In all these cases polymers having molecular mass higher than 20,000–30,000 are used. Another important feature of polymers as solvents is that high molecular mass compounds in a vast majority of cases exist as mixtures of different sorts of molecules having different number of repeat units (polymer homologues), concentration of branchings, cross-links, etc. Additionally, in many cases polymer samples contain some residual solvents, traces of catalysts, curing agents, plasticizers and other additives or impurities. So in contrast to the contents of other volumes, dealing with solubility of gases in liquids, here the data reported characterize solubility in complex, sometimes poorly defined, and by no means pure chemicals. Another problem is related to the fact that glassy polymers are quasiequilibrium objects, since the relaxation processes are too slow at the temperatures below the glass transition temperature T_g . Hence, all the information obtained for solubility of gases in glassy polymers is, strictly speaking, nonequilibrium. Well known manifestations of this phenomenon are prehistory effect on solubility and the parameters of sorption isotherms, the effects of annealing, importance of the protocol of measuring the solubilities of different gases at high pressure, and so on. All this causes the difficulties in comparison of the results of independent studies and hampers the selection of the recommended values in Critical Evaluations.

Units and Quantities

The solubility of gases in polymers is of interest to different fields of polymer science and technology, as well as to other disciplines. The data have been acquired during the last 70 yr in various laboratories by means of diverse instruments. Therefore a variety of ways for reporting gas solubility has been used in the primary literature, and inevitably sometimes, because of insufficient available information, it has been necessary to use several quantities in the compiled tables and plots. Where possible, the gas solubility has been quoted as a quantity of dissolved gas reduced to standard

conditions (pressure 1 atm, temperature 273.2 K) or $\text{cm}^3(\text{STP})$ per 1 cm^3 of polymer. Other quantities of the solubility of gases in polymers, which are in use, will be considered below. The units of pressure used are Pascals, atmospheres, bars, and millimeters or centimeters of mercury. Temperature are reported in Kelvin. Enthalpies of solution data are given in kJ mol^{-1} .

Evaluation and Compilation

The solubility of relatively few systems is known with sufficient accuracy to enable recommended values to be advanced. This is especially true for the solubility in polymers, as polymer samples studied by different authors rarely coincide (different manufacturers of the specimens, variation in molecular mass or molecular mass distribution, etc.). Although a considerable number of systems have been studied by at least two researchers, the range of pressure and/or temperature is often different, thus preventing a meaningful comparison of the data. Occasionally, one has only to guess why several groups of workers sometimes obtain very different results under the same conditions, although all the data reported seem to be flawless or, at least, plausible and internally consistent. In such cases, sometimes an incorrect assessment has been given.

Bearing in mind the mentioned peculiarities of gas–polymer systems, and especially those concerning glassy polymers, Critical Evaluations were prepared mainly for the systems where three or more sources reported solubility data. In contrast to the policy accepted by the evaluators of other volumes of Solubility Data Series, the present authors, in some cases, included the correlations of the solubility coefficients or the parameters of sorption isotherms with different characteristics of gases that allow to estimate the properties for other gas–polymer systems.

Sources and Purity of Materials

The purity of the gases has been quoted in the compiled sheets where given in the original publications. Contrary to what is usually accepted for solubility of gases in liquids, even small impurities of heavier gas components can be a source of error in reported gas solubility values. However, since a purity of gases is adequately reported in most cases, appropriate corrections can be introduced if necessary. It is much more difficult to assess (or define) the purity of polymers. In many cases, the only information available in the papers were the name of producing company and a trademark of the polymer material. The properties more often quoted in the publications are a density and a glass transition temperature. The procedure of the preparation and/or pretreatment of the films is of utmost importance, and, where possible, are also quoted in data sheets.

Apparatus and Procedures

In the compiled data sheets, some key points are made of the instruments for solubility measurement and procedure used. There are several books or papers where the experimental methods of the determination of gas solubility in polymers are considered in more length. They are given in Refs. 1–9.

Methods of Expressing Gas Solubilities

Because gas solubilities have been determined by means of different methods, they have been expressed in a variety of ways. Sometimes solubility is reported as C_{mw} (mol/g) or in number of moles of a gas dissolved in a unit of mass of polymer. When determined using a gravimetric method, solubility is given as C_{ww} (g/g) as a quantity of gas in grams per 1 g of polymer. Volumetric methods of the determination of solubility allow to measure it as C_{vw} (cm³(STP)/g) or as a volume of gas reduced to the standard conditions dissolved in 1 g of polymer. However, the most frequently used unit for the solubility is C_{vv} or the volume of gas reduced to the standard conditions dissolved in 1 cm³ of the polymer.

When a polymer sample is exposed to high pressure gas, its volume is decreased n a fraction determined by its PVT behavior. However, these effects are important only at very high pressure, and in solubility measurements have been introduced very seldom, if ever. Much more relevant are the effects of swelling or dilation of polymer samples in contact with high or even medium pressure gas. Indeed, the dilation isotherms have been reported together with sorption isotherms in many papers. Therefore, the corrections, taking into account the changes in the solubility C_{vv} owing to dilation, can be introduced. However, this was not done in most cases, mainly because a magnitude of such corrections is minor, as a rule, in comparison with the accuracy of the determination of gas solubility. Hence, in majority of the cases the C_{vv} values characterize the solubility of gas in cm³(STP) per cm³ of a pure polymer.

In some very rare cases solubility is expressed as the standard volume of gas per repeat unit of the polymer (expressed in g moles). All these quantities are interrelated.

$$C_{ww} = MC_{mw},$$

where M is the molecular mass of the gas

$$C_{vv} = 22\,146 C_{mw} = 22\,416 M / C_{ww}.$$

If we neglect the swelling of polymer in the process of sorption:

$$C_{vv} = C_{vw} \rho,$$

where ρ is the density of the polymer at the temperature of measurement.

Sorption Isotherms

Contrary to gas solubilities in common liquids, the solubility of gases in polymers is a nonlinear function of pressure if the latter is changed in sufficiently wide range. So a standard way of presenting solubility at a certain temperature is giving, in numerical or, more often, graphical form the dependence of solubility of pressure, or sorption isotherms. It is traditional to distinguish sorption and desorption isotherms. The former are obtained in a regime of growing pressure, the latter when a part of sorbed gas is allowed to desorb from the sample. When sorption is studied under conditions of full equilibrium, i.e., above the glass transition temperature, the sorption and desorption isotherms coincide. If the system is departed from the equilibrium, sorption hysteresis is observed at higher pressures or for highly sorbed gases. Desorption isotherms in glassy polymers lie always above sorption isotherms owing to the conditioning effect caused by high pressure gas. Usually, the model parameters are reported for sorption isotherms.

At sufficiently low pressure the isotherms of all the systems can be reduced to directly proportional dependence

$$C = Sp,$$

where C is the solubility expressed in either way discussed above, p is pressure, and S is the solubility coefficient. S is the reciprocal value of Henry's coefficient H defined by the equation of Henry's law

$$p = HC.$$

If S is expressed in cm³(STP) per cm³ of polymer per atm, it coincides with the Bunsen coefficient defined as the volume of gas reduced to 273.2 K and 1 atm pressure which is dissolved in a unit volume of solvent (at the temperature of measurement). In gas chromatographic determination of solubility, one obtains experimentally the mass fraction Henry's coefficient

$$H_1 = p_1 / (m_1 / m_2),$$

where p_1 is the partial pressure of gas, m_1 is the mass of gas, and m_2 is the mass of polymer, which are in equilibrium. When passing on to the volume of gas and assuming ideal behavior of the gas one obtains

$$S = 1/H_1 = 22\,416 \rho_2 / M_1,$$

where ρ_2 is the density of polymer and M_1 is the molecular mass of the gas. When p and the concentration of dissolved gas are increased, deviations from Henry's law isotherms are observed. Positive deviations, or sorption isotherms convex to the pressure axis, are characteristic for polymers at temperatures above their glass transition temperature. Under such conditions, a satisfactory description of the main part of the systems gas–high molecular weight solvent can be achieved by using Flory–Huggins equation to describe sorption isotherms¹⁰

$$\ln a_1 = \ln f_1 + f_2 + c_{12} f_{22},$$

where a_1 is the activity of gas phase, f is the volume fraction, indices 1 and 2 refer to the dissolved gas and polymer, and c_{12} is the Flory–Huggins parameter characterizing the non-combinatoric contribution into the free energy of the gas–polymer system. For vapors a good approximation of the activity is the ratio p/p_0 , where p is the pressure of the gas and p_0 is its saturated vapor pressure at the temperature of measurement. In the Flory–Huggins equation the f_1 values serve as the measure of gas solubility. The volume fractions f_1 and f_2 are interrelated as $f_1 + f_2 = 1$. An inconvenient feature of this transcendental equation is that it cannot be solved in a straightforward manner to express the solubility f_1 as a function of activity or pressure.

Negative deviations from Henry's law or the isotherms concave to the pressure axis are characteristic for sorption of gases in glassy polymers, and in the vast majority of the cases are described by the dual mode sorption (or Henry+Langmuir) model^{11,12}

$$C = C_D + C_H = k_D p + C'_H b p / (1 + b p),$$

where k_D ($\text{cm}^3(\text{STP})/\text{cm}^3 \text{ atm}$) is Henry's law solubility coefficient, C'_H ($\text{cm}^3(\text{STP})/\text{cm}^3$) is Langmuir's sorption capacity parameter, and b (atm^{-1}) is the affinity parameter. The initial slope of an isotherm is characterized by the equation

$$C = (k_D + C'_H b) p.$$

so the value $k_D + C'_H b$ is often considered as an apparent solubility coefficient in glassy polymers. At higher pressure $p \gg 1/b$ the isotherm approaches the asymptote described by the linear equation

$$C = C'_H + k_D p.$$

A transition from low pressure to high pressure range occurs at $p = 1/b$, where two asymptotes intersect. However, the b value for a certain gas–polymer system is unknown in advance, whereas the experimental range of pressure is often limited. Therefore, graphical determination of three parameters of the dual mode sorption model is quite unreliable. Usually, nonlinear least squares procedures are employed in the simultaneous search for three model parameters or, otherwise, one can be obtained from an independent source, while two others are found by linear least squares method. The dual mode sorption model is not a single way to describe the isotherms concave to the pressure axis. Several other models and equations have been proposed to fit satisfactorily the experimental data. We shall consider here some of them, which contain preferably a minimum number of parameters and do not require for their use knowledge of different properties of pure polymer and the gas–polymer system. A discussion of more sophisticated models and their physical basis can be found in Ref. 13.

Freundlich isotherm might offer an equally acceptable way of analyzing the experimental data. The isotherm can be used in either this

$$C = k p n,$$

or this form

$$C = a p + k p n,$$

where $n < 1$.

Other types of two terms (multiparameter) models have been discussed in the literature, among them the Langmuir1+Langmuir2 type¹⁵

$$C = b_1 C'_{H1} p / (1 + b_1 p) + b_2 C'_{H2} p / (1 + b_2 p).$$

Another model that was proposed to fit this type of sorption isotherms is the so called matrix model¹⁶

$$C = S_0 \exp(-aC)p.$$

The extension of the gas pressure range studied resulted in finding at higher pressures a new form of the isotherm: at a certain pressure (p_g) and solute's concentration (C_g) the isotherm suffers an inflection; above p_g it becomes linear or convex to the pressure axis. This was explained by plasticization induced by sorbed gas and a corresponding decrease in the glass transition temperature T_g from the T_{g0} value characteristic for pure polymer to the experimental temperature T . Several models were proposed to explain this behavior and describe this more complex form of the curve. Mauze–Stern isotherm:¹⁷

$$C = [k_D \exp(sC)]p + C'_H b p / (1 + b p).$$

Paul's *et al.* isotherm:¹⁸

$$C = k_D p + C'_{H0} [(T_g - T)/(T_{g0} - T)] b p / (1 + b p).$$

Here and in subsequent equations, T_g as a function of C can be estimated from the relation of Chow.¹⁹ Kamiya's *et al.* isotherm:²⁰

$$C = C_D + C_H = k_D p + \{C'_{H0} b p / (1 + b p)\} (1 - C^*/C_g),$$

where $C^* = C_D + f C_H$ with $0 < f < 1$. All these models are based on the dual mode sorption model and differ from it by the introduction of various corrections in order to take into account plasticization and a more complex form of an isotherm. However, the same shape of the curve can be described by an entirely different form of equation. Some of the examples will be given below. Stern's *et al.* equation:²¹

$$C = S_0 p \exp[A T_g (T_g - T_{g0}) (T_{g0} - T) / T_{g0}^2],$$

and Laatikainen–Lindstrom's equation:²²

$$C = A a p / \{(1 - b p) [1 + (a + b) p]\}.$$

Several alternative macroscopic and microscopic models having more sound physical basis have been proposed (see e.g., Refs. 23–26). However, much information (usually unavailable) about the polymer, sorbed gas, and gas–polymer interaction is required to use them in fitting or predicting the gas solubility in polymers.

In cases where nonideal behavior of gas phase is significant, all these equations can be expressed in terms of solute fugacity f rather than pressure. However, the model parameters obtained when using the f and p values do not differ dramatically (see, for example, Ref. 27).

References

- ¹R. M. Barrer, *Diffusion in and Through Solids* (Cambridge University Press, Cambridge, 1941).
- ²A. I. Sarakhov, *Balance in Physicochemical Studies* (Nauka, Moscow, 1968).
- ³R. M. Felder and G. S. Huvar, *Methods of Experimental Physics*, edited by R. A. Fava (Academic NY, 1980), Vol. 16C, pp. 315–377.
- ⁴J. L. Lundberg, M. B. Wilk, and M. J. Huyett, *J. Polym. Sci.* **57**, 165, 275.
- ⁵J. L. Lundberg, M. B. Wilk, and M. J. Huyett, *Ind. Eng. Chem., Fundam.* **2**, 37 (1963).
- ⁶W. R. Vieth, P. M. Tam, and A. S. Michaels, *J. Colloid Interface Sci.* **22**, 360 (1966).
- ⁷W. J. Koros and D. R. Paul, *J. Polym. Sci., Polym. Phys. Ed.* **14**, 1903 (1976).
- ⁸E. S. Sanders, W. J. Koros, H. B. Hopfenberg and V. T. Stannett, *J. Membr. Sci.* **13** (1983).
- ⁹J. M. Braun and J. E. Guillet, *Adv. Polym. Sci.* **21**, 107 (1976).
- ¹⁰P. Flory, *Principle Polymer Chemistry* (Cornell University Press, Ithaca, NY, 1953).
- ¹¹R. M. Barrer, J. A. Barrie, and J. Slater, *J. Polym. Sci.* **27**, 177 (1958).
- ¹²D. R. Paul, *Ber. Bunsenges. Phys. Chem.* **83**, 294 (1979).
- ¹³J. H. Petropoulos, *Polymeric Gas Separation Membranes*, edited by D. R. Paul and Yu. P. Yampol'skii (CRC, Boca Raton, 1994) p. 17.
- ¹⁴Z. Grzywna and J. Podkowka, *J. Membr. Sci.* **8**, 23 (1981).
- ¹⁵S. A. Stern and S. S. Kulkarni, *J. Membr. Sci.* **10**, 235 (1982).
- ¹⁶D. Raucher and M. Sefcik, *ACS Symp. Ser.* **223**, 111 (1983).
- ¹⁷G. R. Mause and S. A. Stern, *J. Membr. Sci.* **12**, 51 (1982).
- ¹⁸J. S. Chiou and D. R. Paul, *J. Appl. Polym. Sci.* **32**, 2897 (1986).
- ¹⁹T. S. Chow, *Macromolecules* **13**, 362 (1980).
- ²⁰Y. Kamiya, T. Hirose, K. Mizoguchi, and Y. Naito, *J. Polym. Sci., Polym. Phys. Ed.* **24**, 1525 (1986).
- ²¹Y. Mi, S. Zhou, and S. A. Stern, *Macromolecules* **24**, 2361 (1991).
- ²²M. Laatikainen and M. Lindstrom, *Acta Polytech. Scand., Chem. Techn. Metal. Ser.* **178**, 105 (1987).
- ²³M. A. Krykin, *Vysokomol. Soedin., Ser A* **31**, 1036 (1989).
- ²⁴J. G. A. Bitter, *Transport Mechanism in Membrane Processes* (Plenum, NY, 1990).
- ²⁵J. S. Vrentas and C. M. Vrentas, *Macromolecules* **24**, 2404 (1991).
- ²⁶G. G. Lipscomb, *A. I. Ch. E. J.* **36**, 1505 (1990).
- ²⁷G. K. Fleming and W. J. Koros, *Macromolecules* **23**, 1356 (1990).

3. Critical Evaluations and Compilations of Selected Systems

3.1. Poly(4-methylpentene-1)—Carbon Dioxide; Methane, other gases

Components:	
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]	Evaluator: Yu. P. Yampol'skii; A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994
(2) Poly(4-methylpentene-1) (PMP); [25068-26-2] (1)	

Critical Evaluation:

One two, although detailed, works have been performed on gas solubility in this semicrystalline polyolefin. Tigina¹ studied the solubility of several gases at different temperatures (280–350 K) and up to high pressure, but only for a single sample with a crystallinity of 90%. On the other hand, Puleo *et al.*² investigated the solubility at the narrower pressure range (0–2.0 MPa), but for several samples with crystallinity varying from 21.6% to 66.4%. This enabled the calculation of the contributions to the solubility coefficients characteristic of amorphous and crystalline phases of PMP. The solubility coefficients $S/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$ of PMP with 90% content of crystalline phase at 310 K are compared below.

Gas	Ref. 1	Ref. 2*	
		A	B
CO ₂	0.51	0.346	0.28
CH ₄	0.078	0.12	0.091

*A: crystallinity found by DSC method.
B: crystallinity found by X-ray diffraction.

Bearing in mind an approximate character of the calculations of *S* by an additive scheme,² the agreement can be considered as reasonable. More experimental studies are required at different temperatures and pressures for the samples with varying crystallinity before the properties of this polymer can be properly evaluated and recommended values can be advanced.

References:

- ¹O. N. Tigina, Dissertation, GIAP, State Institute of Nitrogen Industry, USSR, Moscow, USSR 1983.
- ²A. C. Puleo, D. R. Paul, and R. K. Wong, Polymer **30**, 1357 (1989).

Components:	
(1) Helium; He; [7440-59-7] Hydrogen; H ₂ ; [1333-74-0] Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]	Original Measurements: O. N. Tigina, dissertation, GIAP, Moscow, USSR, 1983.
(2) Poly(4-methylpentene-1) (PMP) [25068-26-2] (1)	

Variables:	
<i>T</i> /K=280–350 <i>p</i> /MPa=0.1–15	Prepared By: S. M. Shishatskii

Gas	Experimental Data	
	<i>T</i> /K	Henry's law solubility coefficients <i>S</i> /mol/m ³ Pa
N ₂		Pressure range, MPa
	300	0.1–14
	310	0.1–14
	320	0.1–14
CO ₂	350	0.1–15
	300	0.1–6
	310	0.1–6
	320	0.1–6
CH ₄	290	0.1–7
	300	0.1–10
	320	0.1–12
	330	0.1–14
		<i>S</i> 10 ⁴
		0.395
		0.383
		0.365
		0.325
		2.9
		2.3
		1.8
		0.43
		0.38
		0.32
		0.29

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]		A. C. Puleo, D. R. Paul, and P. K. Wong, <i>Polymer</i> 30 , 1357 (1989).	
(2) Poly(4-methylpentene-1) (PMP); [25068-26-2] (1)			
Variables:		Prepared By:	
T/K=308		Yu. P. Yampol'skii	
p/MPa=0-2.2 (0-22 atm)			
Experimental Data			
Sorption isotherms followed Henry's law, i.e., were linear.			
TABLE 1. Solubility coefficients S/cm ³ (STP)/cm ³ atm*			
Sample	CH ₄	CO ₂	
Q	0.22	0.59	
S	0.20	0.52	
A	0.19	0.49	
H	0.18	0.52	
1.0X	0.24	0.63	
2.5X	0.26	0.69	
10X	0.32	0.83	
2.5R	0.20	0.54	
*Description of samples seen at continuation sheet.			
Within the validity of two-phase model and independence of phase properties of the composition the following local solubility coefficients were found.			
Auxiliary Information			
Method/Apparatus/Procedure	Source and Purity of Materials:		
The apparatus and procedure for sorption measuring were similar to those described in Ref. 1.	PMP samples from Polyscience Co. with different thermal history as well as the copolymers of PMP and 4-(3-butenyl) benzocyclobutane (BBC) were studied. Their properties are given in Table 3. Nothing on gas purity was indicated.		
	Estimated Error: No information given.		
	References: ¹ W. J. Koros, D. R. Paul, and A. A. Rocha, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 14 , 687 (1976).		

Solubility of gases in PMP: $C/(\text{mol}/\text{cm}^3)$ outside the range of Henry's law				
Gas	$T/^\circ\text{K}$	p/MPa	$C/10^3$	
He	293	2	1.8	
		4	4.4	
		6	8.8	
	313	8	15.2	
		10	24.3	
		2	1.0	
		6	4.0	
	333	1	8.8	
		2	0.6	
		6	2.4	
H ₂	280	10	5.3	
		2	4.0	
		4	9.0	
	290	6	14.6	
		8	21.9	
		2	3.7	
		4	8.1	
	300	6	13.4	
		8	20.3	
		2	2.9	
CH ₄	290	4	6.2	
		6	10.2	
		8	15.2	
	320	2	2.2	
		3	1.21	
		4	1.76	
		5	2.30	
	N ₂	290	8	35
			9	40
			10	45
300		12	56	
		14	70	
		11	42	
		13	53	
320		14	60	
		13	43	
		14	47	
CO ₂	290	4	4.4	
		6	6.9	
		8	9.7	
	290	2	8.3	
		4	16.6	
		5	21.0	
		6	25.5	
Auxiliary Information				
Method/Apparatus/Procedure		Source and Purity of Materials:		
The solubility was measured by means of an apparatus of hydrostatic weighing the principle of which had been described in Ref. 1.		PMP of the grade DX-810 had a density of 0.82–0.83 g/cc and crystallinity 90%. All the gases were "chemically pure", according to the Soviet Standard.		
		Estimated Error: $\delta C/C \approx 1.5\%$.		
		References: ¹ I. F. Golubev and O. A. Dobrovolskii, <i>Gaz. Prom.</i> 5 , 43 (1964).		

3.2. Poly(Vinyl Chloride)—Nitrogen, Carbon Dioxide, Methane

Components:	Evaluator:
(1) Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]	Yu. P. Yampol'skii, A. V. Topchev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994
(2) Poly(vinyl chloride) (PVC); [9002-86-2] (II)	

Critical Evaluation:

In spite of the importance of PVC as an industrial polymeric material, only three investigations are available for the solubility of gases (nitrogen [7727-37-9], carbon dioxide [124-38-9], and methane [74-82-8]) in this polymer.¹⁻³ In neither case a molecular mass of the polymer studied has been indicated. The solubility has been measured in PVC containing different amount of stabilizers.^{2,3} Various methods of preparation of PVC have been employed.¹ So the agreement exhibited in the apparent solubility coefficients presented below seems to be quite reasonable. Larger discrepancy is observed between the dual-mode sorption parameters reported by El-Hibri and Paul,² Fried *et al.*,³ and those which can be calculated from the sorption isotherms obtained by Berens.¹ At least partly this can be a result of different pressure ranges used in these studies.

Gas	T/K	k_D	C_H'	b	$S = k_D + C_H'p$	Ref.
CO ₂	298	0.184	40.3	0.0496	2.18	3
	308	0.587	8.9	0.2094	2.45	2
	298	—	—	—	2.7*	1
	298	—	—	—	2.5**	1
N ₂	298	—	Effect of heat treatment			1
	298	—	—	—	1.5*	1
	298	—	—	—	1.7**	1
	308	0.643	4.85	0.361	2.38	2
CH ₄	308	0.0169	0.4505	0.0448	0.037	2
	298	0.105	2.17	0.0491	0.21	3
	308	0.0513	2.305	0.0622	0.19	2

*The sample obtained by emulsion polymerization.

**The sample obtained by suspension polymerization.

Units: k_D /cm³(STP) cm⁻³ atm⁻¹; C_H' /cm³(STP) cm⁻³; b /atm⁻¹.

Further experimental studies are required before this system can be properly evaluated and the parameters of sorption isotherms can be advanced.

References:

- ¹A. R. Berens, *Polym. Eng. Sci.* **20**, 95 (1980).
- ²M. J. El-Hibri and D. R. Paul, *J. Appl. Polym. Sci.* **30**, 3649 (1985).
- ³J. R. Fried, E. Parker, and R. L. Ballard, *Japan-US Polymer Symposium*, 1985, p. 247.

Components:	Original Measurements:
(1) Poly(4-methylpentene-1) (PMP); [25068-26-2] (I)	A. C. Puleo, D. R. Paul, and P. K. Wong, <i>Polymer</i> 30 , 1357 (1989).
(2) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]	

Experimental Data

TABLE 2. Solubility coefficients k_D /cm³(STP)/cm³ atm in amorphous and crystalline phases of PMP

Method of cryst. determination	Amorphous phase		Crystalline phase	
	CH ₄	CO ₂	CH ₄	CO ₂
DSC	0.351	0.93	0.095±0.013	0.28±0.03
X-ray	0.378	0.99	0.060±0.010	0.20±0.02

TABLE 3. Description and characterization of the materials studied

Sample	Description	X-ray cryst. (%)	T_g (K)
Q	Commercial, quenched	53.6	303
S	Commercial, slow cooled	61.2	300
A	Commercial, annealed	66.4	295
H	Homopolymer	62.7	310
1.0X	Cross-linked copolymer with 1% BBC	49.7	310
2.5X	Same with 2.5% BBC	41.8	313
10X	Same with 10% BBC	21.6	326
2.5R	Control: copolymer with 2.5% 4-phenyl-1-butene unable to be cross-linked	55.8	307

Table 3. Concentration isotherms of *n*-butane in emulsion PVC at 303 K; gravimetric data, sorption times >18 h (the original data were represented graphically)

Never-heated			Heat-treated	
Relative Pressure	Concentration (mg/g)	Relative Pressure	Concentration (mg/g)	
0.01	0.91	0.01	0.36	
0.02	1.49	0.04	1.08	
0.04	2.47	0.10	2.27	
0.10	5.96	—	—	

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials
Gravimetric sorption experiments were carried out using a Cahn microbalance and, for highly sorbing gases like butane, a vacuum system described in Ref. 1. For nitrogen and partly for carbon dioxide a volumetric gas sorption method was used by means of Digisorb 2500 automatic surface area analyzer (Micromeritics Instruments Corp.).	Gases: research grade purity. PVC: obtained by suspension and emulsion techniques (in the form of powder), density 1.404±0.014 g/cm ³ . “Never-heated” samples: recovered and dried at temperature not exceeding 273 K. “Heat-treated” samples: heated 1 h at 373 K.
Estimated Error:	No information given.
References:	¹ A. R. Berens, <i>Angew Makromol. Chem.</i> 47 , 97 (1975).

Components:
(1) Nitrogen; N₂; [7727-37-9] Carbon dioxide; CO₂; [124-38-9] *n*-Butane; C₄H₁₀; [106-97-8]
(2) Poly(vinyl chloride) (PVC); [9002-86-2] (II)

Variables:
T/K = 298–303
p/kPa = 0–100

Original Measurements:
A. R. Berens, *Polym. Eng. Sci.* **20**, 95 (1980).

Prepared By:
Yu. P. Yampol'skii

Table 1. Concentration isotherms of CO₂ in emulsion PVC at 298 K (gravimetric data). (The original data were represented graphically)

Never-heated			Heat-treated	
Pressure/kPa	Concentration (mg/g)	Pressure/kPa	Concentration (mg/g)	
7.57	0.36	7.41	0.21	
13.98	0.67	15.03	0.38	
28.37	1.29	28.11	0.73	
41.41	1.76	41.59	1.04	
55.25	2.22	54.68	1.32	
68.51	2.61	68.56	1.58	
81.78	2.98	82.26	1.82	
94.66	3.30	94.77	2.03	

Table 2. Sorption isotherms of CO₂ in suspension PVC (Digisorb data). (The original data were represented graphically)

CO ₂ (<i>T</i> = 298 K)				N ₂ (<i>T</i> = 298 K)			
Never-heated		Heat-treated		Never-heated		Heat-treated	
Pressure /kPa	Concentration (mg/g)	Pressure /kPa	Concentration (mg/g)	Pressure /kPa	Concentration (mg/g)	Pressure /kPa	Concentration (mg/g)
10.79	0.48	10.61	0.33	11.32	0.01	11.13	0.01
15.70	0.69	15.32	0.46	15.02	0.02	15.04	0.01
22.57	0.98	22.39	0.67	22.02	0.02	21.63	0.01
40.64	1.63	40.08	1.14	40.14	0.04	40.17	0.02
49.28	1.91	48.72	1.36	47.96	0.04	48.00	0.03
59.29	2.25	58.94	1.59	58.26	0.05	58.31	0.03
66.76	2.49	66.60	1.80	66.08	0.06	65.74	0.03
73.82	2.82	73.48	1.96	72.88	0.06	72.95	0.03
79.32	2.95	79.57	2.08	78.44	0.06	78.73	0.03
84.24	3.07	83.70	2.19	82.76	0.07	83.05	0.03
88.17	3.16	88.22	2.31	86.88	0.07	86.97	0.04
90.33	3.21	90.18	2.37	89.35	0.07	88.82	0.04
92.88	3.29	92.15	2.42	91.63	0.07	91.51	0.04
95.04	3.35	94.11	2.46	94.72	0.07	93.77	0.04
96.81	3.36	96.67	5.51	96.57	0.07	96.66	0.04
98.39	3.37	98.44	2.54	98.84	0.07	97.90	0.04
100.75	3.38	100.40	2.57	93.47	0.07	98.72	0.04
—	—	—	—	97.81	0.07	99.96	0.04
—	—	—	—	99.66	0.08	—	—


Auxiliary Information	
Method/Apparatus/Procedure	The sorption measurement was carried out using the pressure decay method, Ref. 1.
Source and Purity of Materials:	CH ₄ : purity 99% Other gases: purity 99.7% PVC: B.F. Goodrich Co. (CS 5760); density 1.389 g/cm ³ ; glass transition temperature 344 K. It contained 2% of tin stabilizer.
Estimated Error:	No information given.
References:	¹ W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. 14 , 687 (1976).

Components:	
(1) Argon; Ar; [7440-37-1] Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]	Original Measurements: M. J. El-Hibri and D. R. Paul, J. Appl. Polym. Sci. 31 , 2533 (1986).
(2) Poly(vinyl chloride) (PVC); [9002-86-2] (1)	
Variables:	
T/K=308	Prepared By: Yu. P. Yampol'skii
p/MPa=0–2.5 (0–25 atm)	

Experimental Data			
Dual mode sorption parameters for various gases in PVC at 308 K			
Gas	k_D / cm ³ (STP) cm ⁻³ atm ⁻¹	C'_2 / cm ³ (STP) cm ⁻³	b / atm ⁻¹
Ar	0.0377	1.1320	0.0410
N ₂	0.0169	0.4505	0.0448
CO ₂	0.5870	8.9390	0.2094
CO ₂ *	0.6340	4.8500	0.3610
CO ₂ **	0.5800	5.1600	0.2430
CH ₄	0.0513	2.3050	0.0622

*No drawing, annealing at 358 K.

**Stretching to draw ratio 3 at 358 K.

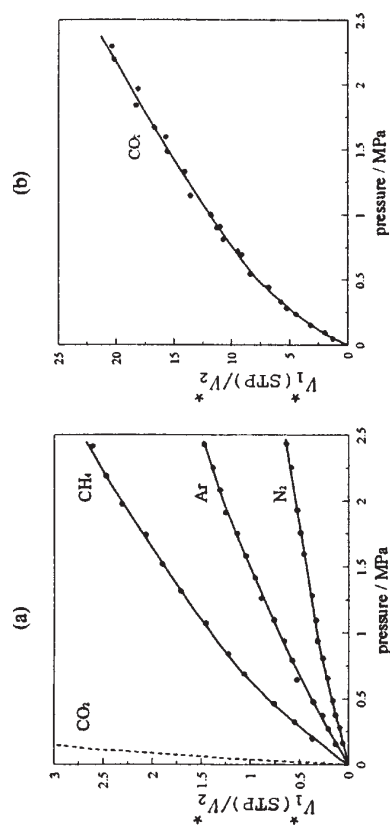FIG. 1. Sorption isotherms of Ar, N₂, CH₄ (a) and CO₂ (b) in PVC at 308 K.

Components: (1) Neon; Ne; [7440-01-9] Hydrogen; H ₂ ; [1330-74-0] (2) Tricresyl phosphate: C ₉ H ₇ O ₄ P; [1330-78-5] (3) Poly(vinyl chloride) (PVC); [9002-86-2] (II)		Original Measurements: R. M. Barrer, R. Mallinder, P.S.-L. Wong, Polymer 8 , 321 (1967).	
Variables: T/K=283–339		Prepared By: Yu. P. Yampol'skii	
Experimental Data			
Smoothed solubility coefficients $S \cdot 10^7 / \text{cm}^3(\text{STP}) / \text{cm}^3 \text{ cm Hg}^*$			
Sample	Temperature/K		
Unplasticized PVC	399	309	319
	4.6	4.4	Hydrogen
	2.2	2.1	4.0
Plasticized PVC	283	291	Neon
	2.8	3.0	2.0
	1.2	1.4	Hydrogen
*Pressure was not indicated; presumably, $p < \text{atm}$.			
Method/Apparatus/Procedure Volumetric method by Meares ¹ was used. The sample was allowed to equilibrate with a gas, then nonsorbed gas was swipped away with mercury. The volume of gas subsequently desorbed from the sample was measured by means of McLeod gauge.		Auxiliary Information	
Source and Purity of Materials: PVC from ICI (99% "pure") in a form of powder was studied. The plasticized sample contained 0.325 mol fraction of tricresylphosphate. Films were prepared by calendering after adding 2 parts of cadmium stearate and 0.2 parts of stearic acid per 100 parts of the polymer.		Estimated Error: No information given.	
References: ¹ p. Meares, Trans. Faraday Soc. 54 , 40 (1958).			

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Poly(vinyl chloride) (PVC); [9002-86-2] (II)		Original Measurements: J. R. Field, B. E. Parker, and R. L. Ballard, Japan-US Polymer Symposium 1985, pp. 247-248.	
Variables: T/K=298 p/MPa=0.16-1.27		Prepared By: Yu. P. Yampol'skii	
Experimental Data			
TABLE 1. Dual mode sorption parameters for methane and carbon dioxide in PVC at 298 K			
Gas	k_D /cm ³ (STP) cm ⁻³ atm ⁻¹	C'_D /cm ³ (STP) cm ⁻³	b /atm ⁻¹
CH ₄	0.105	2.17	0.0491
CO ₂	0.184	40.3	0.0496
TABLE 2. Sorption isotherms of methane and carbon dioxide in PVC at 298 K (The original data were represented graphically)			
CH ₄		CO ₂	
Pressure/Mpa	Sorption ($P_1^{\#}$ (STP)/ $P_2^{\#}$)	Pressure/MPa	Sorption ($P_1^{\#}$ (STP)/ $P_2^{\#}$)
0.17	0.38	0.16	3.48
0.34	0.53	0.27	5.28
0.47	0.85	0.41	7.74
0.55	1.11	0.54	9.71
0.67	1.13	0.64	10.98
0.78	1.42	0.77	12.72
0.88	1.61	0.88	13.99
0.98	1.67	1.00	15.27
1.06	1.83	1.14	16.94
1.16	1.95	1.27	18.01
Auxiliary Information			
Method/Apparatus/Procedure Sorption isotherms were obtained by the pressure decay method. Ref. 1. Conditioning at 23 atm for 60 h and degassing preceded the measurements.		Source and Purity of Materials: PVC: Samples were compression modeled at 450 K from a mixture of low molecular mass PVC resin and 3% of a stabilizer (Cincinnati Milacron (TM-692)).	
		Estimated Error: No information given.	
		References: ¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).	

3.3. Poly(Vinyl Acetate)—Various Gases

Components:	
(1) Helium; He; [7440-59-7] Neon; Ne; [7440-01-9] Hydrogen; H ₂ ; [1333-74-0]	Original Measurements: P. Meures, Trans. Faraday Soc. 54 , 40 (1958).
(2) Poly(vinyl acetate) (PVA); [9003-20-7] (III)	
Variables:	
$T/K=281-313$ $p/kPa=0.6-27$	Prepared By: Yu. P. Yampol'skii

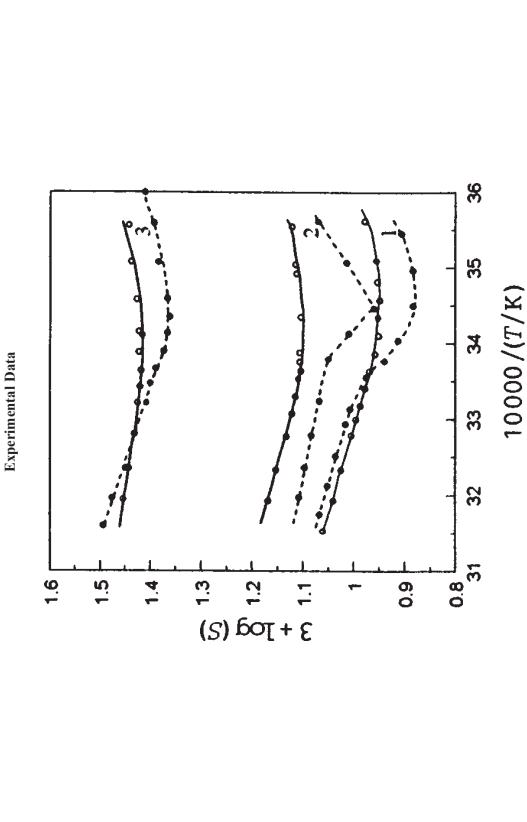


FIG. 2. Solubility coefficients S ($\text{cm}^3(\text{STP})\text{cm}^{-3}\text{am}^{-1}$) for gases in PVA. Curves 1: Helium; curves 2: Neon; curves 3: Hydrogen. Continuous curves taken from equilibrium experiments, broken curves from diffusion experiment.

Auxiliary Information	
Method/Apparatus/Procedure After establishing equilibrium between the sample and the gas, the gas was swept away using mercury. The sorbed gas was then allowed to desorb into a known volume.	Source and Purity of Materials: PVA: Gelva V145, $M_n=450\,000$ (determined from viscosity), $M_w=10\,000$, glass transition temperature 298.6 K.
Estimated Error: No information given.	

Components:	
(1) Chlorine; Cl ₂ ; [7782-50-5]	Original Measurements: S. Wachi, H. Morikawa, and H. Inoue, AIChE J. 34 , 1683 (1988).
(2) Poly(vinyl chloride) (PVC); [9002-86-2] (II)	
Variables:	
$T/K=293-345$ $[Cl_2]=0-35\text{ mol/m}^3$	Prepared By: Yu. P. Yampol'skii

Experimental Data
In the subatmospheric range of pressure the concentration of dissolved chlorine C (mol/m^3) obeyed the following equation:

$$C = S y,$$

where y is the concentration of Cl₂ in gas phase (mol/m^3). Temperature dependence of the solubility coefficient S is given below:

T/K	293	313	323	343
S	20	14	14	11

The following equation was obtained for the temperature dependence of S :

$$S = 0.280 \exp(\Delta H_s / RT),$$

where ΔH_s is the heat of sorption, is 10 480 kJ/mol.

Auxiliary Information	
Method/Apparatus/Procedure Physical sorption of chlorine in PVC was determined using the constant volume cell method. The pressure changes were measured by means of a sensor (Toyoda-Kouki PMS-5.5H).	Source and Purity of Materials: PVC (SC-16, DP-600) supplied by Kaneguchi Chemical Industries Co was prepared by suspension polymerization. No information on the purity of chlorine is given.
Estimated Error: No information given.	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(vinyl acetate), (PVA); [9003-20-7] (III)		Original Measurements: S. Takishima, K. Nakamura, M. Sasaki, and H. Masuoka, Sekiyu Gakkaishi 33, 332 (1990).	
Variables: T/K = 313.2 and 323.2 p/MPa = 0.898–8.755		Prepared By: Yu. P. Yampol'skii	
Experimental Data			
Solubility of carbon dioxide in PVA expressed as mass fractions <i>w</i>			
p/MPa	w	p/MPa	w
313.2 K		323.2 K	
1.258	0.0416	0.898	0.0254
1.449	0.0532	1.819	0.0485
2.650	0.0936	1.906	0.0533
3.467	0.1264	3.309	0.0978
3.846	0.1429	4.698	0.1397
4.583	0.1723	5.655	0.1696
5.659	0.2123	6.519	0.2073
6.885	0.2786	7.861	0.2668
8.755	0.3909		
Auxiliary Information			
Method/Apparatus/Procedure Measurements of the solubility were made using a pressure decay method. The apparatus was similar to one designed by Koros. ¹ Pressure was measured by a semiconductor sensor PX-1A (Tsukasa Sokken). The correction for compressibility of gas phase was introduced.		Source and Purity of Materials: PVA (Aldrich Chemical Co) had "viscosity" average molecular weight 158 000 and glass transition temperature 303 K. The purity of carbon dioxide (Chugoku Teisan) was 99.9%.	
		Estimated Error: No information given.	
		References: ¹ W. J. Koros, Ph.D. dissertation, The University of Texas at Austin, 1977.	

Components: (1) Hydrogen; H ₂ ; [1333-74-0] (2) Poly(vinyl acetate) (PVA); [9003-20-7] (III)		Original Measurements: S. Zhou and S. A. Stern, J. Membr. Sci. 50, 19 (1990).	
Variables: T/K=268 and 278 p/MPa=0.2–2.0		Prepared By: Yu. P. Yampol'skii	
Experimental Data Dual mode sorption parameters for hydrogen in PVA (Compiler). (the value of <i>b</i> seems to be grossly overestimated)			
T/K	k_D / cm ³ (STP) cm ⁻³ atm ⁻¹	C'_D / cm ³ (STP) cm ⁻³	<i>b</i> / atm ⁻¹
268	0.0146	0.096	1.88
278	0.0173	0.027	1.84

FIG. 3. Sorption isotherms for hydrogen in PVA at 268 K and 278 K.

Method/Apparatus/Procedure The solubility was measured by a gravimetric method. The apparatus included a Cahn microbalance, Model C 1100. Pressure was measured by a gauge (Model 901 B, Dresser Industries Inc.).		Source and Purity of Materials: H ₂ : purity >99.99%. PVA: Aldrich Chemical Co.; density 1.191 g/cm ³ , glass transition temperature 296 K (via DSC).	
Estimated Error: Relative precision: solubility <16%, <i>p</i> <0.05%; precision in <i>T</i> : <0.05 K.		Auxiliary Information	

FIG. 3. Sorption isotherms for hydrogen in PVA at 268 K and 278 K.

3.4. Poly(Acrylonitrile)—Carbon Dioxide

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(acrylonitrile) (PAN); [250144-1-9] (IV)		Original Measurements: G. S. Huvard, V. T. Stumett, W. J. Koros, and H. B. Hopfenberg, <i>J. Membr. Sci.</i> 16 , 945 (1972).	
Variables: T/K: 298–338 K P/MPa: 0–3.0		Prepared By: A. K. Bokarev	
Experimental Data			
Dual mode sorption parameters of CO ₂ sorption in PAN			
T/K	$k_D/(\text{cm}^3(\text{STP})/\text{cm}^3 \text{ atm})$	$C'_D/(\text{cm}^3(\text{STP})/\text{cm}^3)$	$b/(\text{atm}^{-1})$
298	0.206	3.615	0.187
328	0.160	3.496	0.139
338	0.134	2.852	0.126
Auxiliary Information			
Method/Apparatus/Procedure The sorption apparatus and procedures used in the sorption experiments are the same as described in Ref. 1.		Source and Purity of Materials: PAN from Standard Oil was used. CO ₂ (Raling Co.) had purity 99.9%.	
Estimated Error: No information given.		References: ¹ W. R. Vieth and J. A. Eilenberg, <i>J. Appl. Polym. Sci.</i> 16 , 945 (1972).	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] Sulfur dioxide; SO ₂ ; [7446-09-5] Ethylene; C ₂ H ₄ ; [74-85-1] Chloromethane; C ₂ H ₆ ; [74-84-0] Methyl chloride; CH ₃ Cl; [74-87-3] (2) Poly(vinyl acetate) (PVA); [9003-20-7] (III)		Original Measurements: D. D. Liu and J. M. Prausnitz, <i>J. Polym. Sci., Polym. Phys. Ed.</i> , 15 , 145 (1977).		
Variables: T/K = 398–473		Prepared By: Yu. P. Yampol'skii		
Experimental Data				
Mass fraction Henry's law constants/atm				
Solute	398	423	448	473
Carbon dioxide	990	1200	1500	1700
Sulfur dioxide	55	87	135	187
Ethylene	2300	2900	3300	3400
Ethane	2700	3000	3400	3700
Methyl chloride	160	220	300	410
Auxiliary Information				
Method/Apparatus/Procedure Inverse gas chromatographic method was used. Two columns were employed; hydrocarbons were studied in Chromosorb-supported column, Fluoropac-80 packed column was used for other solutes. Helium served as a carrier gas. Correction for pressure drop in the column was introduced.			Source and Purity of Materials: PVA (Cellomer Associates) had a molecular mass 83 400. All gases (from Matheson Gas Products) had a purity better than 99%.	
Estimated Error: No information given.				

TABLE 2. Concentrations $C/(\text{cm}^3(\text{STP})\text{cm}^{-3})$ of CO_2 dissolved in PMMA at 308 K

p/atm	References				
	4	5,6	7,8	11	
5	13.5	11.4	14.0	13.2	
10	21.6	18.0	22.4	21.9	
20	34.9	28.7	35.5	36.1	

References:

- ¹P. L. Durrill and R. G. Griskey, A. I. Ch. E. J. **12**, 1147 (1965).
²G. B. Okonishnikov and V. P. Skripov, Vysokomol. Soedin., Ser. B **25**, 890 (1973).
³J. M. H. Fechter, H. B. Hopfenberg, and W. Koros, J. Polym. Eng. Sci. **21**, 925 (1981).
⁴W. J. Koros, G. N. Smith, and V. Stannett, J. Appl. Polym. Sci. **26**, 159 (1981).
⁵E. S. Sanders, W. J. Koros, H. B. Hopfenberg, and V. Stannett, J. Membr. Sci. **13**, 161 (1983).
⁶E. S. Sanders, W. J. Koros, H. B. Hopfenberg, and V. Stannett, J. Membr. Sci. **18**, 53 (1984).
⁷W. J. Koros and E. S. Sanders, J. Polym. Sci., Polym. Symp. **72**, 142 (1985).
⁸E. S. Sanders and W. J. Koros, J. Polym. Sci., Polym. Phys. Ed. **24**, 175 (1986).
⁹T. S. Liu and M. A. McHugh, *Supercritical Fluid Technology*, edited by J. M. L. Penninger *et al.* (Elsevier, New York, 1985), p. 415.
¹⁰R. G. Wissinger and M. E. Paulaitis, J. Polym. Sci., Part B: Polym. Phys. **25**, 2497 (1987).
¹¹P. C. Raymond and D. R. Paul, J. Polym. Sci., Part B: Polym. Phys. **28**, 2103 (1990).

3.5. Poly(Methyl Methacrylate)—Carbon Dioxide, Other Gases

Components:	Original Measurements:
(1) Carbon dioxide; CO_2 ; [124-38-9]	Yu. P. Yampol'skii, A. V. Topchiev, Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994
(2) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)	

Critical Evaluation:

The system PMMA-carbon dioxide has been studied in a large number of papers (Refs. 1-11). However, different temperature and pressure ranges studied and different units of the data reported prevent the comparison of all the results. Figure 4(a) shows the temperature dependence of the solubility coefficient $S/(\text{g g}^{-1}\text{atm}^{-1})$. The values obtained by pressure decay method and expressed in the standard units ($\text{cm}^3(\text{STP})/\text{cm}^3\text{atm}$) were recalculated by evaluator using the density 1.19 g/cm^3 of PMMA.

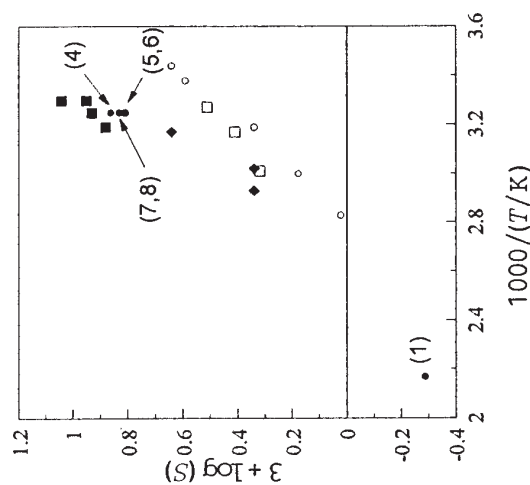


FIG. 4. (a) (●) Ref. (1); (○) Ref. (2); (■) Ref. (3); (◆) Ref. (4); (□) Ref. (5); (○) Ref. (6); (◆) Ref. (7); (□) Ref. (8); (○) Ref. (9); (□) Ref. (10). Reasonable agreement can be seen between the temperature dependences reported by different authors (Refs. 2, 9, and 10). However, a significant and apparently systematic discrepancy (by a factor of 2) is observed between the values obtained at 308 K by pressure decay method (Refs. 3 and 5-8) and gravimetric method (Refs. 2 and 10). Further studies are necessary to explain this result.

TABLE 1. Dual mode sorption parameters for the system PMMA-carbon dioxide at 308 K.

$k_2/(\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1})$	$C_2/(\text{cm}^3(\text{STP})\text{cm}^{-3})$	b/atm^{-1}	Ref.
1.140	14.90	0.218	4
0.916	12.59	0.236	5,6
1.068	18.00	0.186	7,8
1.200	15.60	0.172	11

Critical Evaluation:

They are in reasonable agreement. The predictions of sorption isotherms using them are presented in Table 2.

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)		Original Measurements: G. B. Okonishnikov and V. P. Skripov, <i>Vysokomol. Soedin.</i> Ser. B, 25 , 890 (1973).			
Variables: T/K=291–353 p/MPa=0.4–6.0		Prepared By: S. M. Shishatskii			
Experimental Data: Linear sorption isotherms were found in the pressure range shown. Solubility coefficients, S, for carbon dioxide in PMMA					
T/K	291	295.7	313	333	353
10 ³ S'/(g/g atm)	4.4	3.9	2.4	1.5	1.05
Method/Apparatus/Procedure Sorption measurements were made using a McBain spring balance described in Ref. 1. A correction for buoyancy and for sample's swelling were introduced.		Auxiliary Information		Source and Purity of Materials: ST-1-110 grade PMMA studied did not contain any plasticizers. No data are given on the purity of CO ₂ taken from a cylinder.	
		Estimated Error: No information given.		References: A. I. Sakharov, <i>Balance in Physicochemical Studies</i> (Russian), (Nauka, Moscow, 1968).	

Components: P. L. Durrill, Ph.D. dissertation, Virginia Polytech. Inst., 1965. P. L. Durrill, R. G. Griskey, <i>AIChE J.</i> 12 , 1147 (1965).		Original Measurements: P. L. Durrill, Ph.D. dissertation, Virginia Polytech. Inst., 1965. P. L. Durrill, R. G. Griskey, <i>AIChE J.</i> 12 , 1147 (1965).	
Variables: T/K: 461 p/MPa: 0.26–1.9 (2.6–19 atm)		Prepared By: A. K. Bokarev	
Experimental Data Henry's law solubility constants S for gases in PMMA			
Gas	Pressure/atm	S'/(cm ³ (STP)/g atm)	
He	3.8–7.2	0.066	
Ne	2.7	0.126	
Ar	3.2–7.4	0.105±0.063	
Kr	2.6–4.6	0.122	
N ₂	5.7–15.0	0.045±0.028	
CO ₂	4.0–19.0	0.260±0.024	
Method/Apparatus/Procedure The equipment and a manometrical procedure for solubility measurements were similar to those of Lundberg <i>et al.</i> ¹		Auxiliary Information	
		Source and Purity of Materials: PMMA (Lucite) used is a product of du Pont de Nemours Co.; $\rho=1.20 \text{ g/cm}^3$. Gases from Air Reduction Co., had a minimum purity: CO ₂ -99.5%, N ₂ -99.90%, Ar-99.997%, He-99.99%. Gases (Matheson Co.), included as impurities: Ne-14 ppm He, Kr-12 ppm N ₂ and 23 ppm Xe.	
Estimated Error: $\delta C/C \approx 8\%$.		References: J. L. Lundberg, M. B. Wilk, and M. J. Hugett, <i>Appl. Phys.</i> 31 , 1131 (1960).	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)		Original Measurements: G. B. Okonishnikov and V. P. Skripov, Vysokomol. Soedin, Ser. B. 25 , 890 (1973).			
Variables: T/K = 291–353 p/MPa = 0.4–6.0		Prepared By: S. M. Shishatskii			
Experimental Data: Linear sorption isotherms were found in the pressure range shown.					
Solubility coefficients, <i>S</i> , for carbon dioxide in PMMA					
T/K	291	295.7	313	333	353
10 ³ <i>S</i> /(g/g atm)	4.4	3.9	2.4	1.5	1.05
Auxiliary Information					
Method/Apparatus/Procedure Sorption measurements were made using a McBain spring balance described in Ref. 1. A correction for buoyancy and for sample's swelling were introduced.			Source and Purity of Materials: ST-1-10 grade PMMA studied did not contain any plasticizers. No data are given on the purity of CO ₂ taken from a cylinder.		
Estimated Error: No information given.			References: A. I. Sakharov, <i>Balance in Physicochemical Studies</i> (in Russian), (Nauka, Moscow, 1968).		

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)		W. J. Koros, G. N. Smith, and V. Stannett, <i>J. Appl. Polym. Sci.</i> 26 , 159 (1981).	
Variables:		Prepared By:	
T/K = 308–353 p/MPa = 0–2.2		Yu. P. Yampol'skii	

Experimental Data			
Dual mode sorption parameters for carbon dioxide in PMMA at various temperatures			
T/K	k_D / cm ³ (STP)cm ⁻³ atm ⁻¹	C'_D / cm ³ (STP) cm ⁻³	b /atm ⁻¹
308	1.14	14.9	0.218
328	0.74	12.0	0.116
353	0.505	7.13	0.0683

Sorption enthalpies: $\Delta H_D = -3.9$ kcal mol⁻¹; -16.3 kJ mol⁻¹
 $\Delta H_b = -5.6$ kcal mol⁻¹; -23.4 kJ mol⁻¹

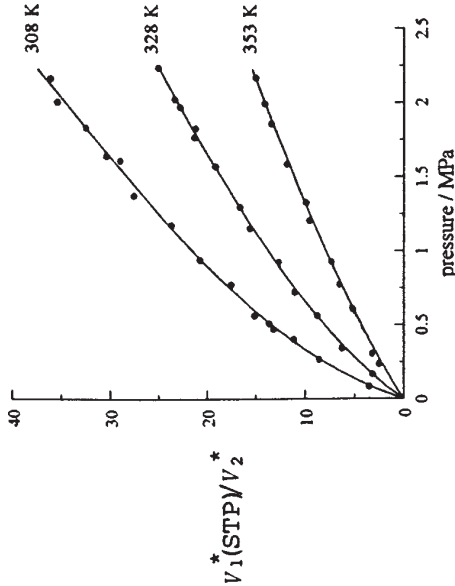


FIG. 4. (b) Sorption isotherms of carbon dioxide in PMMA.

Method/Apparatus/Procedure		Auxiliary Information	
The sorption equipment described in Refs. 1 and 2 was used. The procedure involved "interval" sorption measurement and standard pretreatment: equilibration with carbon dioxide at 20 atm for 6 h before measurement.		Source and Purity of Materials CO ₂ : Air Products, purity >99.9% PMMA: Aldrich Chemical Co., $M_w = 599\,000$.	
Estimated Error:		No information given.	

References:
¹W. J. Koros, A. H. Chan, and D. R. Paul, *J. Membr. Sci.* **2**, 165 (1977).
²W. J. Koros and D. R. Paul, *J. Polym. Sci., Polym. Phys. Ed.* **14**, 1903 (1976).

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)		J. M. H. Fechter, H. B. Hopfenberg, and W. J. Koros, <i>Polym. Eng. Sci.</i> 21 , 925 (1981).	
Variables:		Prepared By:	
T/K = 293–313 p/kPa = 13–93		Yu. P. Yampol'skii	

Experimental Data			
Sorption isotherms of carbon dioxide in: (I) "as received" PMMA microspheres with 14530 Å diameter at 303, 308, and 313 K, (II) preswollen PMMA microspheres with 5436 Å diameter at 303 K. (The original data were represented graphically)			
T = 303 K		T = 313 K	
Pressure/kPa	Sorption (g [*] /100 g [*]) ₂	Pressure/kPa	Sorption (g [*] /100 g [*]) ₂
(I)			
13.02	0.15	13.22	0.09
26.23	0.27	26.80	0.19
39.81	0.36	39.67	0.26
52.85	0.45	52.90	0.33
66.07	0.54	66.31	0.39
79.65	0.62	79.72	0.46
92.88	0.71	93.13	0.52
(II)			
13.17	0.17		
26.17	0.29		
39.71	0.41		
53.09	0.51		
66.46	0.60		
79.83	0.70		
93.02	0.80		

Method/Apparatus/Procedure		Auxiliary Information	
Measurements were made on a Cahn RG Electrobalance. Samples of the polymer had been preswollen by exposure of methanol vapours ($p/p_s = 0.98$). After quick removal of methanol gas sorption isotherms of carbon dioxide were obtained.		Source and Purity of Materials: CO ₂ : purity 99.99% PMMA: microspheres of diameters 1453 Å (I) and 5436 Å (II). $M_w(I) = 206\,000$, $M_w(II) = 137\,000$, glass transition temperature (II) 393 K.	
Estimated Error:		No information given.	

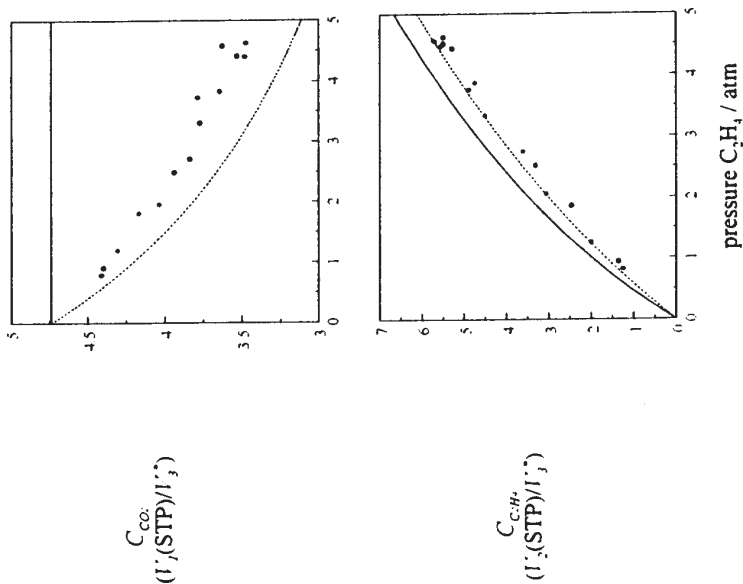


FIG. 5. Mixed gas sorption of CO₂/C₂H₄ in PMMA at 1.53 ± 0.05 atm CO₂.

Auxiliary Information	
Method/Apparatus/Procedure	A novel apparatus to measure precisely both pure and mixed gas sorption in glassy polymers is described. A method for accurate calibration and operation of the equipment is discussed, based upon complete closure of the material balance of all gaseous components in all phases. The overall scheme of the sorption apparatus is illustrated and the details of the sorption cell are presented.
Source and Purity of Materials	CO ₂ : Air Products, purity 99.99% (Coleman grade). C ₂ H ₄ : Airco Research Triangle Park, purity 99.5% (2.5 grade). PMMA: Aldrich Chemical Co., M _w = 600 000.
Estimated Error:	No information given.

Components:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]	Original Measurements: E. S. Sanders, W. J. Koros, H. B. Hopfenberg, and V. Stannett, J. Membr. Sci. 13 , 161 (1983)
(2) Ethylene; C ₂ H ₄ ; [74-85-1]	
(3) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)	
Variables:	
T/K = 308	Prepared By: A. K. Bokarev
p/MPa = 0–0.8	

Experimental Data				
C ₂ H ₄			CO ₂	
Pressure/MPa	Sorption (P ₁ [*] (STP)/P ₂ [*])	Pressure/MPa	Sorption (P ₁ [*] (STP)/P ₂ [*])	Sorption (P ₁ [*] (STP)/P ₂ [*])
0.09	2.03	0.06	2.37	11.90
0.16	2.92	0.11	3.58	12.13
0.19	3.36	0.12	4.03	12.30
0.22	3.81	0.15	4.64	12.46
0.27	4.29	0.20	5.85	13.25
0.32	4.90	0.21	5.97	13.56
0.34	5.13	0.24	6.79	13.72
0.39	5.62	0.27	7.39	14.05
0.43	5.99	0.30	8.05	14.19
0.47	6.46	0.34	8.80	—
0.53	6.92	0.39	9.66	—
0.56	7.04	0.42	9.92	—
0.64	7.83	0.45	10.45	—
0.73	8.29	0.45	10.64	—
0.75	8.85	0.48	10.92	—
0.80	9.06	0.50	11.34	—

TABLE 2. Dual mode sorption parameters for pure component sorption of CO₂ and C₂H₄ in PMMA at 308 K

Gas	k_D /cm ³ (STP) cm ⁻³ atm ⁻¹	C_H /cm ³ (STP) cm ⁻³	b /atm ⁻¹
CO ₂	0.916	12.59	0.236
C ₂ H ₄	0.531	7.09	0.259

The following figure concerns mixed gas sorption of CO₂ and C₂H₄. Points are experimental data, solid lines are predictions of DMS equation and dashed lines are prediction of DMS equation for mixed penetrants:

$$C_1 = k_{D1}P_1 + C_{H1}P_1 / (1 + b_1P_1 + b_2P_2)$$
$$C_2 = k_{D2}P_2 + C_{H2}P_2 / (1 + b_1P_1 + b_2P_2)$$

All the parameters for gases (1) and (2) are pure components sorption parameters from Table 2.

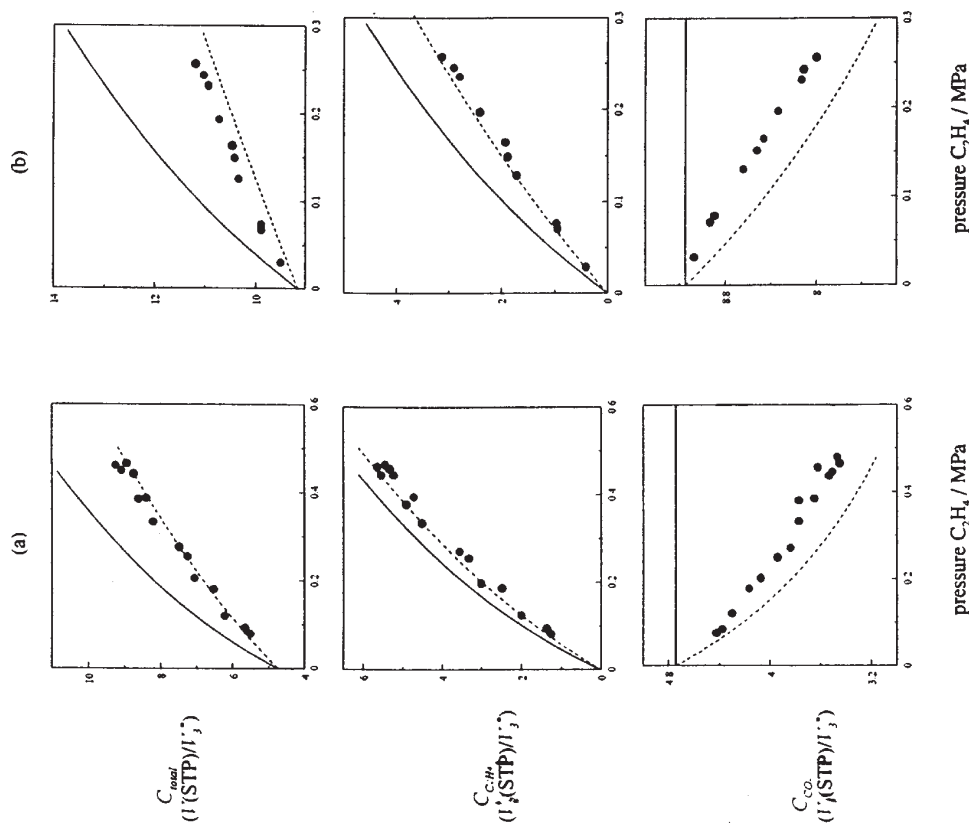


Fig. 6. Mixed gas sorption of CO₂ and C₂H₄ at 1.53 atm CO₂ (a) and 3.64 atm CO₂ (b).

Components:		Original Measurements:				
(1) Carbon dioxide; CO ₂ ; [124-38-9]		E. S. Sanders and W. J. Koros, J. Membr. Sci. 18 , 53 (1984).				
(2) Ethylene; C ₂ H ₄ ; [74-85-1]						
(3) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)						
Variables:		Prepared By:				
T/K=308		Yu. P. Yampol'skii				
p/MPa=0-0.81						
Experimental Data						
TABLE 1. Sorption isotherms of pure carbon dioxide and ethylene in PMMA at 308 K (The original data were represented graphically)						
	Pressure/MPa	Sorption (l [*] (STP)/l [*])	Pressure/MPa	Sorption (l [*] (STP)/l [*])	Pressure/MPa	Sorption (l [*] (STP)/l [*])
CO ₂	0.07	2.40	0.43	9.86	0.64	13.09
	0.13	4.09	0.46	10.51	0.66	13.61
	0.20	5.92	0.46	10.70	0.68	13.80
	0.22	6.25	0.49	10.84	0.70	14.22
	0.27	7.28	0.51	11.31	0.71	14.36
	0.31	8.08	0.56	12.16	—	—
C ₂ H ₄	0.35	8.87	0.57	12.44	—	—
	0.10	2.16	0.35	5.20	0.65	7.82
	0.16	3.00	0.39	5.67	0.73	8.29
	0.20	3.47	0.44	6.00	0.80	9.08
	0.23	3.80	0.47	6.47	0.81	9.13
	0.27	4.31	0.54	6.93	—	—
0.33	4.97	0.56	7.00	—	—	
TABLE 2. Dual mode sorption parameters for pure carbon dioxide and ethylene in PMMA at 308 K						
Gas	k _D /cm ³ (STP) cm ⁻³ atm ⁻¹	C' _H /cm ³ (STP) cm ⁻³	b/atm ⁻¹			
Pressure based parameters						
CO ₂	0.916	12.59	0.236			
C ₂ H ₄	0.531	7.09	0.259			
Fugacity based parameters						
CO ₂	1.015	11.86	0.243			
C ₂ H ₄	0.490	8.32	0.217			

The two following figures (Fig. 6 and 7) deal with mixed gas sorption of CO₂ and C₂H₄. Points are experimental data, solid lines are predictions of DMS equation and dashed lines are prediction of equation:

$$C_1 = K_D p_1 + C'_H p_1 / (1 + b_1 p_1 + b_2 p_2),$$
$$C_2 = K_D p_2 + C'_H p_2 / (1 + b_1 p_1 + b_2 p_2).$$

All the parameters for gases (1) and (2) are pure components sorption parameters from Table 2.

Auxiliary Information

Method/Apparatus/Procedure

Apparatus specifically designed to measure mixed gas sorption was described in Ref. 1. It consisted of four chambers: one chamber contained the polymer, three others were used to meter gases accurately (individual or mixtures) into the first one or for sampling gases directly into a gas chromatograph. All chambers were provided with pressure transducers (Gould Model PA 822). The method is based on the concept of maintaining material balance. For both pure gases and mixtures, PVT behavior was taken into account.

Source and Purity of Materials:

CO₂: Air Products, purity 99.99%
C₂H₄: Airco, purity 99.5%
PMMA: Aldrich Chemical Co., $M_n = 600\,000$, glass transition temperature 393 K.

Estimated Error:

Relative precision of pressures: $\pm 0.3\%$
Precision in T : ± 0.01 K.

References:

¹E. S. Sanders, W. J. Koros, H. B. Hopfenberg, and V. T. Stannett, *J. Membr. Sci.* **13**, 161 (1983).

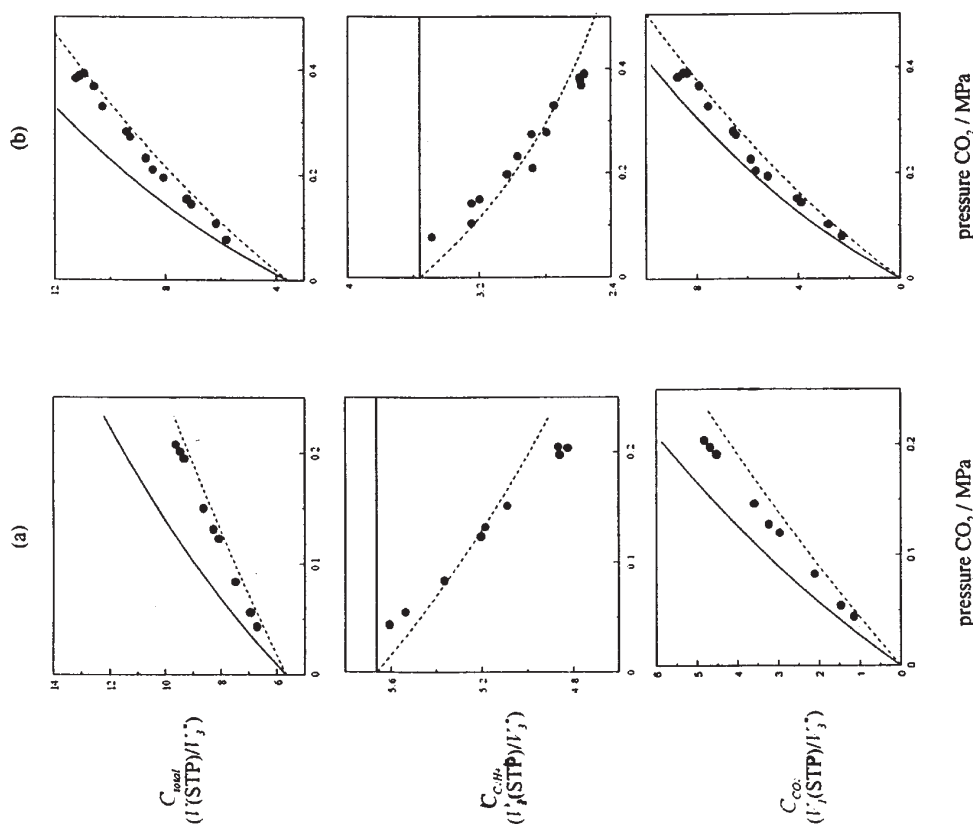


FIG. 7. Mixed gas sorption of CO₂ and C₂H₄ at 3.93 atm C₂H₄ (a) and 2.06 atm C₂H₄ (b).

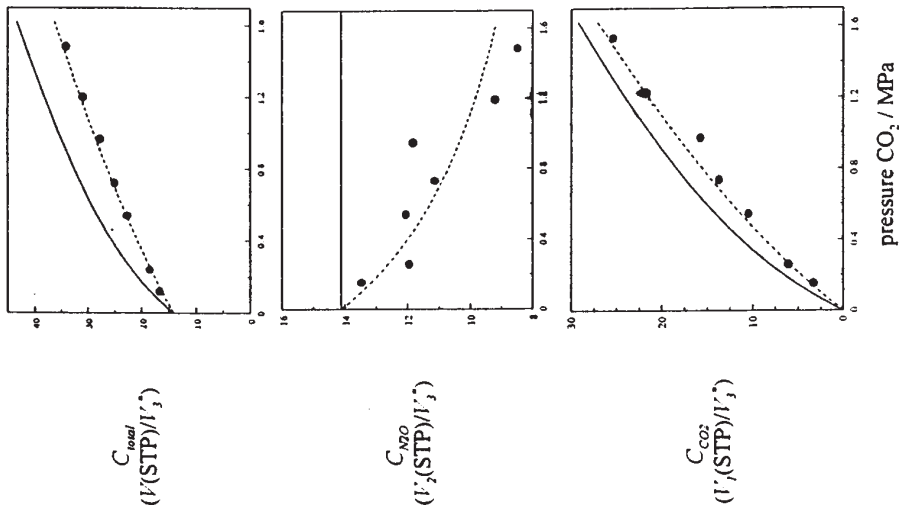


FIG. 9. High-pressure mixed-gas sorption of CO₂/NO₂ at 5.00 atm N₂O.

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]		W. J. Koros and E. S. Sanders, J. Polym. Sci. Polym. Symp. 72, 142 (1985).	
(2) Ethylene; C ₂ H ₄ ; [74-85-1] Nitrous oxide; N ₂ O; [10024-97-2]		E. S. Sanders and W. J. Koros, J. Polym. Sci., Polym. Phys. Ed. 24, 175 (1986).	
(3) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)			
Variables:		Prepared By:	
T/K= 308		A. K. Bokarev	
p/MPa=0-2.0			

Experimental Data			
Dual mode sorption parameters for pure component sorption of CO ₂ , C ₂ H ₄ , and N ₂ O in PMMA			
Gas	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
CO ₂	0.944	19.68	0.158
C ₂ H ₄	0.461	12.40	0.189
N ₂ O	1.068	18.00	0.186

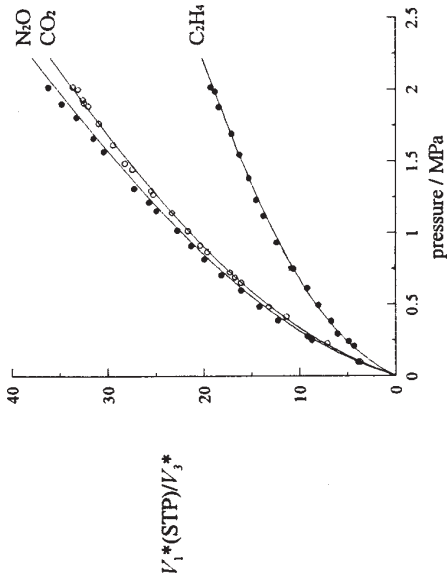


FIG. 8. Sorption isotherms for pure gases in PMMA at 308 K.

The following figures (Figs. 9–11) refer to mixed gas sorption of CO₂/C₂H₄ and CO₂/N₂O. Points are experimental data, solid lines are predictions of DMS equation and dashed lines are prediction of equation:

$$C_1 = k_{D1}p_1 + C_H'p_1/(1 + b_1p_1 + b_2p_2)$$
$$C_2 = k_{D2}p_2 + C_H'p_2/(1 + b_1p_1 + b_2p_2)$$

All the parameters for gases (1) and (2) are pure components sorption parameters from Table 1.

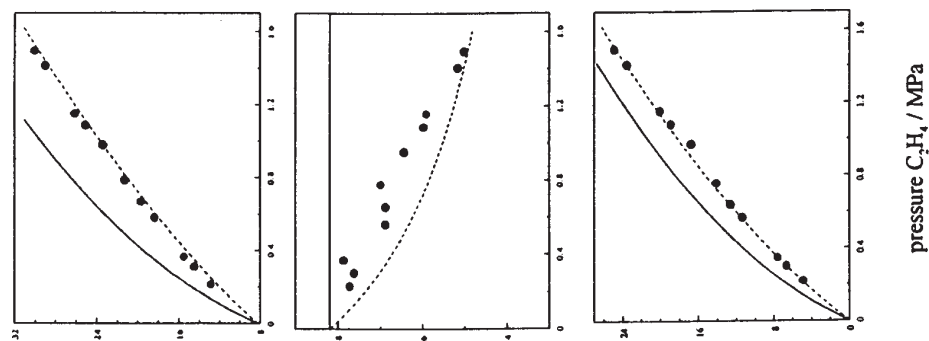


FIG. 11. High-pressure mixed-gas sorption of $\text{CO}_2/\text{C}_2\text{H}_4$ at 4.87 atm C_2H_4 .

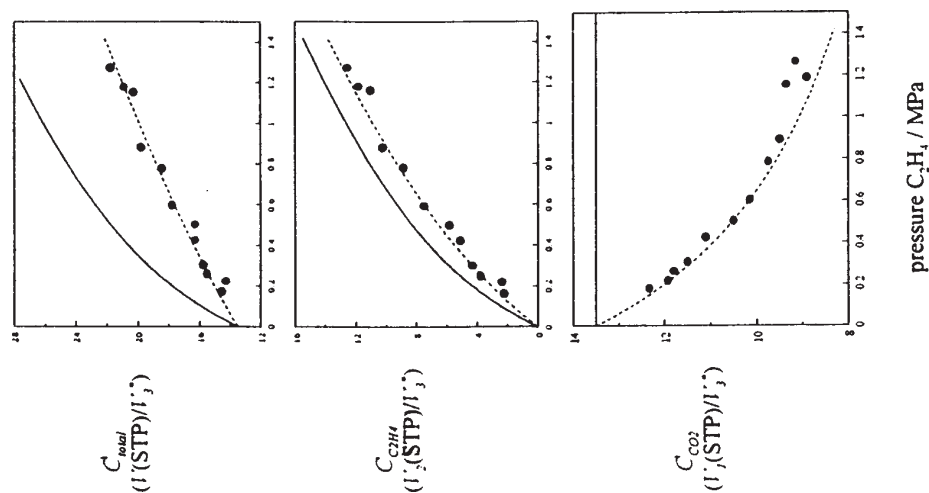


FIG. 10. High-pressure mixed-gas sorption of $\text{CO}_2/\text{C}_2\text{H}_4$ at 5.05 atm CO_2 .

Auxiliary Information	
Method/Apparatus/Procedure An apparatus for precise measurement of both pure and mixed gas sorption in glassy polymers was used. Details in Ref 1.	Source and Purity of Materials: CO ₂ : Air Products; purity 99.99% (Coleman grade). C ₃ H ₈ : Airco Research Triangle Park; purity 99.5% (2.5 grade). N ₂ O: Airco Research Triangle Park; purity 99.5% (4.5 grade). PMMA: Aldrich Chemical Co.; $M_w = 600\,000$. Estimated Error: No information given.
Method/Apparatus/Procedure An apparatus similar to that described in Ref. 1 was used for pressure equilibrium sorption of supercritical fluid solvent into solid polymers up to 300 atm. Experimental apparatus included: gas/liquid compressor (Suprapressure Inc., Model 46-14025-1), pressure gauges (Dresser Industries, Models Z15R, Z15T), holding tank (316 stainless steel, volume of 123.33 ± 0.28 cm ³), and high pressure view cell. The temperature was measured using a platinum resistance element (Degussa, Inc.).	Source and Purity of Materials: CO ₂ : Linde Co. PMMA: $M_w = 60\,600$, $M_n = 33\,200$, glass transition temperature 378 K. Estimated Error: Relative precision of solubilities <3%. Precision in T : ±0.2 K.
References: ¹ E. S. Sanders, W. J. Koros, B. Hopfenberg, and V. Stannett, <i>J. Membr. Sci.</i> 13 , 161 (1983). ² W. J. Koros, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 18 , 981 (1980).	
Components:	
(1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)	
Original Measurements:	
I. S. Liao and M. A. McHugh, <i>Supercritical Fluid Technology</i> , edited by J. M. L. Penninger, M. Radosz, M. A. McHugh, and V. J. Krukonis (Elsevier, Amsterdam, 1985), pp. 415-434.	
Variables:	
$T/K = 315 - 341.2$ $p/\text{MPa} = 0 - 26.2$	
Prepared By:	
A. K. Bokarev	
Experimental Data	
Sorption isotherms of carbon dioxide in poly(methyl methacrylate).	
T = 315 K	
Weight fraction	Pressure/MPa
2.78	0.67
4.52	1.23
5.52	1.66
7.71	2.38
9.16	3.10
10.21	4.71
14.74	5.78
17.57	6.89
17.73	7.30
19.13	8.87
23.77	11.63
25.03	13.41
25.94	14.86
26.89	15.91
27.45	17.97
27.94	21.74
28.40	23.48
28.77	25.95
T = 331.2 K	
Weight fraction	Pressure/MPa
2.94	1.36
8.67	4.12
12.51	6.12
12.67	7.13
18.29	9.28
18.81	11.59
22.01	14.28
23.98	17.83
24.30	19.57
25.41	21.88
26.78	24.91
—	—
—	—
—	—
—	—
—	—
—	—
—	—
—	—
—	—
T = 341.2 K	
Weight fraction	Pressure/MPa
3.99	1.96
14.06	7.40
15.50	8.12
18.11	11.23
20.76	12.79
24.30	15.36
26.51	17.86
30.16	20.67
30.62	22.37
32.74	26.16
—	—
—	—
—	—
—	—
—	—
—	—
—	—
—	—
—	—

3.6. Poly(Ethyl Methacrylate)—Carbon Dioxide, Other Gases

Components:		Evaluator:
(1) Carbon dioxide; CO ₂ ; [124-38-9]		Yu. P. Y. Yampol'skii, A. V. Topchiev Institute of Petro-
(2) Poly(ethyl methacrylate) (PEMA); [9003-42-3] (VII)		chemical Synthesis, Russian Academy of Sciences, April, 1994

Critical Evaluation:

Three independent studies¹⁻³ have been reported on sorption of carbon dioxide in PEMA. In all three cases, a high molecular weight polymer was used. Koros *et al.*¹ observed, in the pressure range 0–2 MPa, a dual mode sorption shapes of the isotherms concave to the pressure axis. However, at higher pressures, the isotherms change to linear or even nonlinear form convex to the pressure axis.^{2,3} that was explained in terms of the effect of plasticization exerted by carbon dioxide.

Figure 12 shows the temperature dependence of the pressure P_g at which the glass transition in the polymer takes place, as well as the corresponding concentration C_g of carbon dioxide. It is seen that the data of Refs. 2 and 3 are in a good agreement. The both curves reach the temperature axis as it can be anticipated, in the vicinity of the glass transition temperature for the pure PEMA.

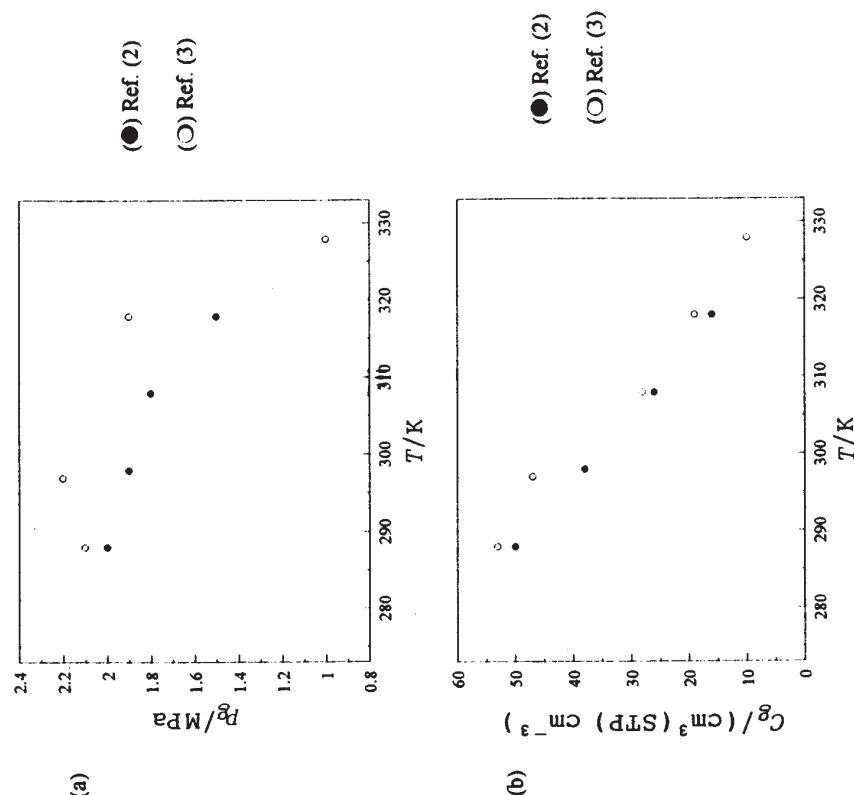


Fig. 12. Temperature dependence of (a) P_g /MPa and (b) C_g / (cm³ (STP) cm⁻³).

Components:		Original Measurements:
(1) Carbon dioxide; CO ₂ ; [124-38-9]		R. G. Wissinger and M. E. Paulaitis, J. Polym. Sci., Part B: Polym. Phys. 25 , 2497 (1987).
(2) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)		
Variables:		Prepared By:
T /K = 305.9–332.0		Yu. P. Yampol'skii
p /MPa = 0–10.4		

Experimental Data

Sorption isotherms of carbon dioxide in PMMA at elevated pressures. Sorption=vol. of gas at STP/mass of unswollen polymer (cm³ (STP) g⁻¹). (The original data were represented graphically)

$T = 305.9$ K			$T = 315.2$ K			$T = 332.0$ K		
Pressure/MPa	Sorption (V_1^* (STP)/g ₂ [#])		Pressure/MPa	Sorption (V_1^* (STP)/g ₂ [#])		Pressure/MPa	Sorption (V_1^* (STP)/g ₂ [#])	
0.60	11.13		0.64	7.79		1.30	13.78	
1.30	21.51		1.34	18.42		2.12	22.88	
2.10	33.43		2.16	28.55		3.00	29.40	
2.92	46.65		2.92	36.86		3.83	37.99	
3.76	58.32		3.74	47.25		4.69	44.25	
4.61	70.00		4.50	54.53		5.57	50.78	
5.49	83.73		5.38	65.70		6.28	58.06	
6.47	103.41		6.23	77.37		7.31	70.27	
7.41	119.47		7.25	93.18		8.08	83.22	
8.35	119.56		8.12	107.44		8.88	94.89	
9.39	119.67		8.89	113.18		9.67	105.79	
10.40	121.57		9.66	120.21		10.37	113.33	
—	—		10.38	135.99		—	—	

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials:
A gravimetric method was used. The polymer samples were suspended from a quartz spring. Correction for buoyancy were introduced using CO ₂ densities up to higher pressures.	CO ₂ : Linde Co., purity 99.99% PMMA: Scientific Polymer Products, M_w =90 000, glass transition temp. 378 K.
Estimated Error:	No information given.

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(ethyl methacrylate) (PEMA); [9003-42-3] (VII)	Original Measurements: W. J. Koros, G. N. Smith, and V. Stannett, <i>J. Appl. Polym. Sci.</i> , 26 , 159 (1981).	
	Prepared By: Yu. P. Yampol'skii	

Variables: $T/K=303-328$ $p/\text{MPa}=0-2.1$
--

Experimental Data			
Dual mode sorption parameters for carbon dioxide in PEMA			
T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_2/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
303	1.28	8.14	0.193
313	1.14	3.78	0.204
328	0.932	0.996	0.246

Sorption enthalpies: $\Delta H_D = -2.6\text{ kcal mol}^{-1}$; -10.9 kJ mol^{-1} ; $\Delta H_b = +2.0\text{ kcal mol}^{-1}$; $+8.4\text{ kJ mol}^{-1}$

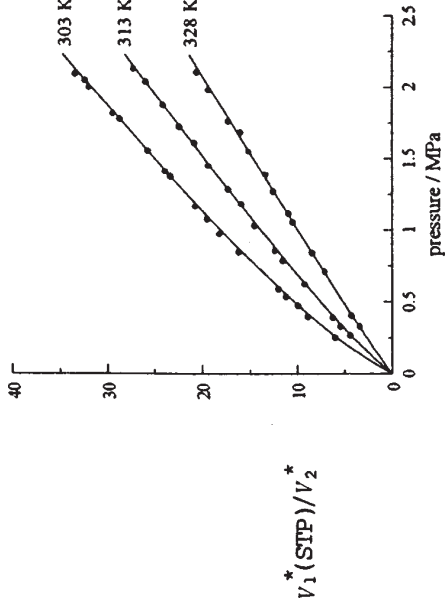


Fig. 14. Sorption isotherms of carbon dioxide in PEMA.

Auxiliary Information	
Method/Apparatus/Procedure The sorption equipment described in Refs. 1 and 2 was used. The procedure involved "interval" sorption measurement and standard pretreatment: equilibration with carbon dioxide at 20 atm for 6 h before measurement.	Source and Purity of Materials: CO ₂ : Air Products; purity >99.9% PEMA: Aldrich Chemical Co., $M_w=309\,000$.
Estimated Error: No information given.	References ¹ W. J. Koros, A. H. Chan, and D. R. Paul, <i>J. Membr. Sci.</i> , 2 , 165 (1977). ² W. J. Koros, and D. R. Paul, <i>J. Polym. Sci., Polym. Phys. Ed.</i> , 14 , 1903 (1976).

Figure 13 shows Van't Hoff plot for the solubility coefficients taken from the graphs^{2,3} or calculated by the dual mode sorption parameters. The values reported in all three works are in good agreement.

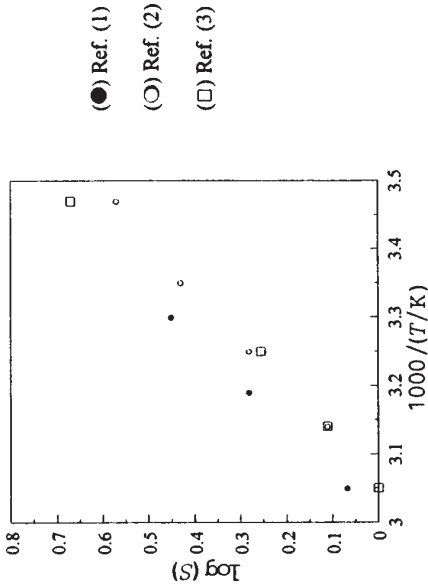


Fig. 13. Temperature dependence of the solubility coefficients.

The least squares treatment of the data gave the following equation:

$$\log(S/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}) = -4.353 + 1.433/(T/K).$$

The corresponding enthalpy of sorption $\Delta H_s = -27.5\text{ kJ/mol}$.
It can be recommended for the prediction of the initial slope of the isotherms. For the pressure of carbon dioxide up to 2 MPa the dual mode sorption parameters reported by Koros *et al.*¹ can be used. For the higher pressure, the works of Chou and Paul² and Kamiya *et al.*³ give rather close values of solubility, but the sorption isotherm obtained in Ref. 3 should be, tentatively, recommended since they cover the wider range of pressure and temperature.

- References:**
¹W. J. Koros, G. N. Smith, and V. Stannett, *J. Appl. Polym. Sci.*, **26**, 159 (1981).
²J. S. Chou and D. R. Paul, *J. Membr. Sci.*, **45**, 167 (1989).
³Y. Kamiya, K. Mizoguchi, T. Hirose, and Y. Naito, *J. Polym. Sci., Part B: Polym. Phys.*, **27**, 879 (1989).

TABLE 3. Sorption isotherms of various gases in PEMA at 308 K (The original data were represented graphically)

	Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Sorption ($V_1^*(\text{STP})/V_2^*$)
Ar	0.27	0.33	1.40	1.68	3.21
	0.39	0.48	1.61	1.94	3.21
	0.50	0.61	1.75	2.05	3.29
	0.77	0.94	1.98	2.25	3.82
	0.85	1.07	2.04	2.42	4.08
	1.04	1.22	2.27	2.66	—
	1.26	1.51	2.45	2.77	—
CH ₄	0.25	0.70	1.52	3.44	6.01
	0.51	1.29	1.82	4.15	6.42
	0.75	1.89	2.14	4.63	6.71
	1.02	2.44	2.23	5.00	7.34
	1.34	3.20	2.60	5.57	—
CH ₄ (films conditioned in 30 atm of CO ₂)	0.33	0.90	1.03	2.70	4.69
	0.52	1.38	1.28	3.09	5.2
	0.61	1.62	1.42	3.47	5.28
	0.77	2.02	1.62	3.75	5.66
	0.92	2.30	2.00	4.47	5.90
N ₂	0.28	0.17	1.56	0.95	1.62
	0.34	0.26	1.62	0.95	1.73
	0.62	0.41	1.89	1.10	1.86
	0.68	0.46	2.11	1.23	2.03
	0.90	0.59	2.25	1.34	1.99
	1.05	0.61	2.32	1.39	2.21
	1.45	0.87	2.63	1.54	2.21

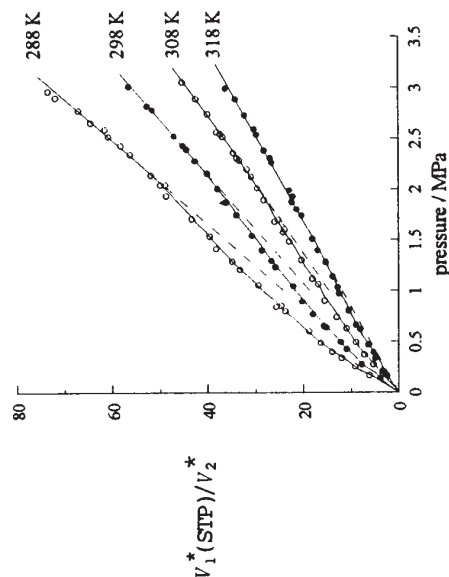


FIG. 1.5. Sorption isotherms of carbon dioxide in PEMA at 288, 298, 308, and 318 K.

Components:

(1) Argon; Ar; [7440-37-1] Nitrogen; N₂; [7727-37-9] Carbon dioxide; CO₂; [124-38-9] Methane; CH₄; [74-82-8] (2) Poly(ethyl methacrylate) (PEMA); [9003-42-3] (VII)

Original Measurements:

J. S. Chou and D. R. Paul, J. Membr. Sci. **45**, 167 (1989).

Variables:

$T/K = 298-318$
 $p/\text{MPa} = 0-3.8$

Prepared by:
Yu. P. Yampol'skii

Experimental Data

TABLE 1. Dual mode sorption parameters for methane and argon in PEMA

Gas	T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_D/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
CH ₄	298	0.183	2.87	0.0677
	308	0.165	2.24	0.0536
	313	0.144	1.87	0.0422
Ar	308	0.0902	1.20	0.0405

Solubility coefficient for N₂ at 308 K: $0.058\text{ cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$ (calculated by compiler).

TABLE 2. Sorption isotherms of methane in PEMA at 298 K (a) and 318 K (b) (The original data were represented graphically)

	Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)
(a)	0.20	0.73	1.43	4.11	2.71	6.85
	0.42	1.41	1.63	4.50	2.90	7.18
	0.64	2.02	1.85	5.05	3.33	8.10
	0.82	2.55	2.06	5.62	3.39	8.27
	1.02	3.03	2.28	5.95	—	—
	1.25	3.62	2.47	6.19	—	—
	0.26	0.55	1.37	2.65	2.67	4.89
	0.27	0.59	1.43	2.81	2.76	4.99
	0.55	1.12	1.74	3.29	3.00	5.39
	0.66	1.40	1.96	3.62	3.29	5.83
(b)	0.81	1.60	2.19	4.16	3.30	5.89
	0.97	1.91	2.29	4.14	3.37	6.42
	1.24	2.45	2.50	4.51	3.67	6.42

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
Sorption isotherms were measured by the pressure decay method using a dual-volume sorption cell.	PEMA: DuPont Co. (Elvacite 2042), $M_v=438\,000$, glass transition temp. 342 K (DSC method).
	Estimated Error:
	No information given.

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124:38:9]		Y. Kamiya, K. Mizoguchi, T. Hirose, and Y. Naito, <i>J. Polym. Sci., Part B: Polym. Phys.</i> 27 , 879 (1989).	
(2) Poly(ethyl methacrylate) (PEMA); [9003:42:3] (VII)			
Variables:		Prepared By:	
$T/K=288$		A. K. Bokarev	
$p/\text{MPa}=0-5.1\,(50\text{ atm})$			

Experimental Data	
The isotherms were treated by the equation:	
$C=C_D+C_H=[k_D\exp(sC^*)]p+C_H^0bp/[1-C^*(C_g)/(1+bp)],$	
where the parameters k_D , C_H^0 , and b have the usual meaning; s is the parameter characterizing the concentration dependence of the ordinary dissolution, that is, $s=0$ and $s>0$ correspond to Henry's law and Flory-Huggins dissolution, respectively, C_g is the solute concentration corresponding to the glass transition and	
$C^*=C_D+fC_H=[k_Dp+fC_H^0bp/(1+bp)]/[1+C_H^0bp/C_g(1+bp)],$	
where f is the ratio of the plasticizing ability of a Langmuir species (H) to that of an ordinary dissolved species (D).	

TABLE 1. Parameters for ordinary dissolution (Flory-Huggins s) and for Langmuir isotherms					
T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H^0/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}	$10^3\,S/\text{cm}^3(\text{STP})\text{cm}^{-3}$	$C_g/\text{cm}^3(\text{STP})\text{cm}^{-3}$
288	2.11	28.9	0.097	3.0	-0.17
297	1.90	22.5	0.065	2.3	-0.34
308	1.42	15.8	0.055	2.6	-0.28
318	1.15	9.5	0.045	2.8	-0.27
328	0.97	3.5	0.022	3.1	-0.22
338(T_g)	0.84	0	0	2.4	-0.40
348	0.76	0	0	1.9	-0.51
358	0.67	0	0	3.1	-0.19

TABLE 3. Sorption and desorption isotherms of carbon dioxide in PEMA at (a) 328 K, (b) 338 K, (c) 348 K, and (d) 358 K (The original data were represented graphically)

	Pressure/MPa	Solubility (V_1^* (STP)/ V_2^*)	Pressure/MPa	Solubility (V_1^* (STP)/ V_2^*)	Pressure/MPa	Solubility (V_1^* (STP)/ V_2^*)
(a) Sorption	0.30	3.59	1.49	14.38	4.03	43.88
	0.70	7.00	2.26	23.27	4.98	55.79
	1.08	10.97	3.01	31.59	—	—
	0.14	2.08	1.28	12.49	4.40	48.42
Desorption	0.51	5.30	2.05	21.19	—	—
	0.90	8.89	3.21	34.24	—	—
	1.23	10.04	3.43	30.29	—	—
	2.23	19.50	5.01	46.56	—	—
(b) Sorption	0.31	2.65	1.75	15.34	4.26	38.99
	0.70	5.68	2.84	25.37	—	—
	0.37	2.65	2.08	16.10	4.02	32.20
	1.09	8.34	2.57	19.70	4.16	33.34
(c) Sorption	1.58	11.37	3.06	23.68	5.01	41.29
	1.83	13.64	3.53	28.22	—	—
	0.15	1.51	1.58	10.43	3.27	22.94
	0.60	3.61	2.08	14.22	3.77	26.54
(d) Sorption	0.62	4.55	2.56	17.63	4.26	30.14
	1.10	7.02	3.04	21.23	5.02	36.20

Auxiliary Information

Method/Apparatus/Procedure
Sorption and desorption isotherms were measured with an electronic microbalance (Cahn model 2000) placed in a high-pressure chamber in Ref. 1

Source and Purity of Materials
CO₂: purity 99.99%
PEMA: prepared by radical polymerization; density 1.120 g/cm³ at 298 K (floatation method), glass transition temperature of pentamethylene PEMA 334 K.

Estimated Error
No information given.

References:

1. Y. Kamiya, K. Mizoguchi, T. Hirose, and Y. Naito, J. Polym. Sci., Polym. Phys. Ed. **24**, 535 (1986).

TABLE 2. Sorption and desorption isotherms of carbon dioxide in PEMA at (a) 288 K, (b) 297 K, (c) 308 K, and (d) 318 K (The original data were represented graphically)

	Pressure/MPa	Solubility (V_1^* (STP)/ V_2^*)	Pressure/MPa	Solubility (V_1^* (STP)/ V_2^*)	Pressure/MPa	Solubility (V_1^* (STP)/ V_2^*)
(a) Sorption	0.11	3.96	1.58	42.26	3.04	79.99
	0.21	7.92	2.06	50.19	3.54	99.79
	0.61	19.99	2.23	54.91	3.77	109.59
	1.10	30.75	2.56	64.90	—	—
Desorption	0.21	9.24	1.08	32.07	2.82	71.88
	0.36	13.76	1.34	36.97	3.29	90.17
	0.61	21.12	1.82	46.79	—	—
	0.82	26.97	2.32	59.05	—	—
(b) Sorption	0.21	6.04	2.23	46.62	5.02	122.46
	0.69	16.79	4.21	99.07	—	—
	1.47	31.33	4.90	129.61	—	—
	0.11	3.40	1.10	26.23	2.60	54.55
Desorption	0.29	9.24	1.29	27.37	3.46	77.19
	0.49	13.58	1.71	35.67	3.98	88.89
	0.91	20.76	2.03	44.73	—	—
(c) Sorption	0.21	4.34	1.29	20.21	3.21	50.24
	0.50	9.06	1.68	25.69	3.67	59.68
	0.71	10.58	1.88	28.52	4.92	87.61
	0.89	14.54	2.64	40.80	4.97	88.56
Desorption	0.31	6.23	1.47	22.86	3.38	55.34
	0.43	7.18	2.05	31.36	4.03	66.85
	0.71	12.65	2.36	35.89	4.38	75.34
	1.06	17.56	2.93	45.52	—	—
(d) Sorption	0.36	5.10	1.58	18.91	3.55	45.74
	0.86	10.21	2.56	31.76	5.02	69.54
Desorption	0.61	8.31	2.07	25.33	4.27	57.26
	1.09	13.42	3.06	38.56	—	—

Components: (1) Argon; Ar; [7440-37-1] (2) Poly(ethyl methacrylate) (PEMA); [9003-42-3] (VII)		Original Measurements: Y. Kamiya, K. Mizoguchi, Y. Naito, and D. Bourbon, Int. Congress on Membranes (ICOM-90), Chicago, 1990, pp. 1382–1384.
Variables: $T/K=278.2-358.2$ $p/\text{MPa}=0-5.0$ (0–50 atm)		Prepared By: Yu. P. Yampol'skii

Experimental Data			
TABLE 1. Dual mode sorption parameters for argon in PEMA			
T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
278.4	—	5.23	0.024
283.2	—	4.21	0.023
288.2	—	3.55	0.023
298.2	—	2.75	0.020
308.2	—	2.23	0.019
318.2	—	2.36	0.014
328.2	0.104	3.49	0.006
338.2	0.094	1.40	0.006
343.2	0.091	0.21	0.020
348.2	0.088	—	—
353.2	0.089	—	—

Components: (1) Propane; C_3H_8 ; [74-98-6] (2) Poly(ethyl methacrylate) (PEMA); [9003-42-3] (VII)		Original Measurements: U. B. Goradia and H. G. Spencer, J. Appl. Polym. Sci. 33 , 1525 (1987).
Variables: $T/K: 288-353$ $p/\text{kPa}: 0-79.74$		Prepared By: A. K. Bokarev

Experimental Data	
TABLE 1. Apparent Henry's law solubility coefficient	
T/K	$k_D\ 10^2/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{cm Hg}^{-1}$
333	2.10(+3%)
333*	2.06(+3%)
342	2.44(+6%)
348	2.27(+7%)
353	1.96(+9%)

* Sorption experiment with annealed samples.

TABLE 2. Dual mode sorption model parameters		
T/K	$k_D 10^2/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{cm Hg}^{-1}$	$b\ 10^2/\text{cm Hg}^{-1}$
288	3.02(±7%)	4.83(±10%)
303	2.73(±10%)	3.10(±14%)
318	2.24(±9%)	1.77(±15%)

Auxiliary Information	
Method/Apparatus/Procedure A low pressure, finite volume, sorption apparatus previously described ¹ was used at pressures up to 60 cm Hg.	Source and Purity of Materials: Atactic PEMA obtained from Polyscience, Inc., as a primary standard, had an M_w of 350 000 with $M_w/M_n=2.2$; $T_g=338\text{ K}$.
Estimated Error:	
References: ¹ J. A. Yavorsky and H. G. Spencer, J. Appl. Polym. Sci. 31 , 501 (1986).	

TABLE 2. Sorption isotherms of argon in PEMA (The original data were represented graphically)

T = 278.4 K		T = 298.2 K		T = 328.2 K		T = 358.2 K	
Pressure/MPa	Sorption ($V^s(\text{STP})/V_2^s$)	Pressure/MPa	Sorption ($V^s(\text{STP})/V_2^s$)	Pressure/MPa	Sorption ($V^s(\text{STP})/V_2^s$)	Pressure/MPa	Sorption ($V^s(\text{STP})/V_2^s$)
0.51	1.01	0.34	0.28	0.51	0.54	0.51	0.74
0.54	0.99	0.39	0.33	0.52	0.49	0.52	0.67
0.56	1.05	0.85	0.76	0.10	1.07	1.00	1.43
0.99	1.86	1.10	0.92	1.01	1.05	1.01	1.35
1.02	1.81	1.10	0.99	1.50	1.58	1.29	1.29
1.04	1.85	2.08	1.81	1.49	1.54	1.50	2.08
1.51	2.61	2.08	1.85	1.99	2.10	1.50	1.92
2.01	3.47	3.07	2.67	2.00	2.06	1.99	2.75
2.01	3.39	3.07	2.71	2.96	3.12	2.00	2.69
2.01	3.37	3.32	2.91	2.96	3.05	1.98	2.60
2.51	4.16	4.05	3.49	3.95	4.06	1.99	2.52
3.01	4.78	4.11	3.56	3.97	4.02	2.48	3.23
3.02	4.70	5.04	4.33	4.95	5.07	2.48	3.08
3.98	6.01	5.03	4.39	4.95	5.02	2.99	3.85
3.98	5.94	—	—	—	—	3.02	3.85
3.98	5.89	—	—	—	—	2.98	3.74
4.90	7.13	—	—	—	—	2.99	3.67
4.90	7.10	—	—	—	—	2.97	3.61
—	—	—	—	—	—	3.47	4.33
—	—	—	—	—	—	3.49	4.17
—	—	—	—	—	—	3.95	4.90
—	—	—	—	—	—	3.96	4.81
—	—	—	—	—	—	3.97	4.69
—	—	—	—	—	—	4.37	5.28
—	—	—	—	—	—	4.49	5.22
—	—	—	—	—	—	4.90	5.84
—	—	—	—	—	—	4.96	5.87
—	—	—	—	—	—	4.95	5.72

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials
Sorption isotherms were determined gravimetrically with an electronic microbalance Cahn 2000.	Ar: purity 99.999%.
	PEMA: glass transition temperature 334 K.
	Estimated Error: No information given.

Components:

- (1) Ethane; C_2H_6 ; [7484-0] *n*-butane; C_4H_{10} ; [106-97-8]
 (2) Poly(*n*-butyl methacrylate) (PBMA); [9003-63-8] (VIII)

Original Measurements:

- S. A. Stern, U. M. Vakili, and G. R. Mauze, J. Polym. Sci., Part B: Polym. Phys. **27**, 405 (1989).

Variables:

T/K: 259.4–315.4
 p/kPa: 0–67

Prepared By:

A. K. Bokarev

Experimental Data

Sorption isotherms of ethane are linear in the range 259–315 K. Solubility coefficients can be described by van't Hoff equation

$$S = 5.25 \times 10^{-5} - \exp(-\Delta H_s/RT) \text{ cm}^3(\text{STP})/\text{cm}^3 \text{ cm Hg},$$

where $\Delta H_s = -14.9 \text{ kJ/mol}$.

Sorption isotherms of butane are linear in the range 283–313 K; at lower temperatures they are convex to the pressure axis. The isotherms were represented by exponential relation

$$C = S(0)p - \exp(\sigma c),$$

where $S(0)$ is the Henry's law solubility coefficient and σ is a constant which depends on temperature. The parameters of this equation are given below:

T/K	$S(0)/\text{cm}^3(\text{STP})/\text{cm}^3 \text{ cm Hg}^{-1}$	$\sigma/\text{cm}^3 \text{ cm}^{-3}(\text{STP})$
273	0.432	0.0128
283	0.336	0.0051
293	0.252	0
303	0.176	0
313	0.179	0

$S(0)$ can be described by the van't Hoff equation

$$S(0) = 5.24 \times 10^{-4} \exp(-\Delta H_s/RT) \text{ cm}^{-3}(\text{STP}) \text{ cm Hg}^{-1}, \text{ where } \Delta H_s = -20.6 \text{ kJ/mol}.$$

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials
The solubility was measured by a gravimetric method. The apparatus included a Cahn microbalance, Model 2000 RG.	PBMA (Scientific Polymer Products of Ontario, NY) had a density of 1.06 g/cm^3 at 299 K and glass transition temperature (DSC) in the temperature range from 295 to 308 K.
	The minimum purity of ethane and <i>n</i> -butane (Linde Division of Union Carbide Corp.) were 99.0%.
	Estimated Error: No information given.

3.7. Polystyrene—Various Gases

Components:		Evaluator:
(1) Nitrogen; N ₂ ; [7727-37-9]		Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994
(2) Polystyrene (PS); [9003-53-6] (IX)		

Critical Evaluation:	
Four investigations ¹⁻⁴ have been reported for the solubility of nitrogen in PS. The work by Scultz and Gerrrens ² seems to be unreliable: the pressure of the measurement is not indicated, besides there is some inconsistency among the solubility coefficients for various gases (N ₂ , He, H ₂). The only paper reported the solubility for the ambient temperature is the paper of Vieth <i>et al.</i> , ⁴ and its results can be, tentatively, recommended for this most important range of temperature.	
Two papers ^{1,3} deal with solubility at higher temperature above <i>T</i> _g of PS and at higher pressure. The results of them are in disagreement. Tentatively, one can give the preference to the results of Durrill. ⁵ Further careful work is needed before really reliable values can be advanced as recommended for this system.	
The values of solubility at different pressures and 298 K given below are based on dual mode sorption parameters reported in Ref. 4.	
<i>p</i> /MPa	<i>C</i> /cm ³ (STP) cm ⁻³
0.5	0.6
1.0	1.2
1.5	1.7
2.0	2.3

Components:		Evaluator:
(1) Argon; Ar; [7440-37-1]		Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994
(2) Polystyrene (PS); [9003-53-6] (IX)		

Critical Evaluation:	
Only three papers ¹⁻³ have been published for the system PS-argon. The work of Schulz and Gerrrens ¹ is inconsistent and should be excluded from further consideration. Vieth <i>et al.</i> ³ reported sorption isotherms and dual mode sorption parameters for the solubility in oriented and unoriented PS at the ambient temperature, whereas Durrill ² studied the solubility in PS above its glass transition temperature. Pressure dependence of solubility is given below based on the parameters of sorption isotherms obtained by Vieth <i>et al.</i> ³	
<i>p</i> /MPa	<i>C</i> /cm ³ (STP) cm ⁻³
0.5	1.2
1.0	2.2
1.5	3.2
2.0	4.0

Combined consideration of the results from Refs. 2 and 3 results in the enthalpy of sorption of argon in PS equal to -7.1 kJ/mol.	
---	--

References:	
¹ G. V. Schulz and H. Gerrens, <i>Z. Phys. Chem.</i> 7 , 182 (1956).	
² P. L. Durrill, dissertation, Virginia Polytechnic Institute, 1965.	
³ W. R. Vieth, P. M. Tam, and A. S. Michaels, <i>J. Colloid Interface Sci.</i> 22 , 360 (1996).	
⁴ W. R. Vieth, P. M. Tam, and A. S. Michaels, <i>J. Colloid Interface Sci.</i> 22 , 360 (1996).	
⁵ P. L. Durrill, dissertation, Virginia Polytechnic Institute, 1965.	

Components:		Evaluator:
(1) Nitrogen; N ₂ ; [7727-37-9]		Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994
(2) Polystyrene (PS); [9003-53-6] (IX)		
Critical Evaluation:		
Four investigations¹⁻⁴ have been reported for the solubility of nitrogen in PS. The work by Scultz and Gerrens² seems to be unreliable: the pressure of the measurement is not indicated, besides there is some inconsistency among the solubility coefficients for various gases (N₂, He, H₂). The only paper reported the solubility for the ambient temperature is the paper of Vieth <i>et al.</i>,⁴ and its results can be, tentatively, recommended for this most important range of temperature. Two papers^{1,3} deal with solubility at higher temperature above <i>T_g</i> of PS and at higher pressure. The results of them are in disagreement. Tentatively, one can give the preference to the results of Durrill.³ Further careful work is needed before really reliable values can be advanced as recommended for this system. The values of solubility at different pressures and 298 K given below are based on dual mode sorption parameters reported in Ref. 4.		
<i>p</i> /MPa	<i>C</i> /cm ³ (STP) cm ⁻³	
0.5	0.6	
1.0	1.2	
1.5	1.7	
2.0	2.3	
References:		
¹ D. M. Newitt and K. E. Weale, <i>J. Chem. Soc.</i> 1541 (1948).		
² V. Schulz and H. Gerrens, <i>Z. Phys. Chem.</i> 7 , 182 (1956).		
³ P. L. Durrill, dissertation, Virginia Polytechnic Institute, 1965.		
⁴ W. R. Vieth, P. M. Tam, and A. S. Michaels, <i>J. Colloid Interface Sci.</i> 22 , 360 (1966).		

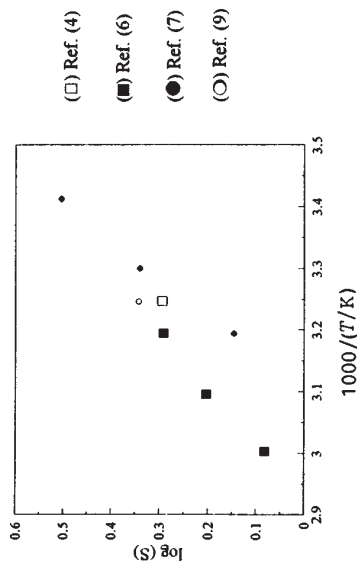


FIG. 17. Temperature dependence of apparent solubility coefficient $S'/(cm^3(STP) cm^{-3} atm^{-1})$.

Temperature dependence of C'_H intersects the horizontal axis at about 360 K, i.e., somewhat lower than accepted glass transition temperature of PS (about 373 K).

Temperature dependence of the apparent solubility coefficient can be given by the equation

$$\log(S'/(cm^3(STP) cm^{-3} atm^{-1})) = -2.840 + 970.0/(T/K).$$

Enthalpy of sorption is equal to -18.6 kJ/mol.

The interval of higher pressures has been investigated by Wissinger and Paulaitis.⁸ They found nearly linear sorption isotherms, probably, owing to the plasticization effects. The solubilities found in Ref. 6 and 8 for 3.0 MPa, where the pressure ranges of two works overlap, are in good agreement. So for higher pressure the results of Ref. 8 may be recommended.

All the results considered above concern high molecular mass PS (M_w about 105). Toi and Paul¹ studied the effects of the molecular mass of PS on the solubility and the parameters of the dual mode sorption isotherms. The increase in molecular mass from 3 600 to 850 000 results in the increase in the solubility at any given pressure as well as in the values of C'_H , while two other parameters remain intact.

The solubility in PS stretched or biaxially oriented was studied by Vieth *et al.*³ and Carfagna *et al.*⁶ It was shown that the deformation tends to decrease the solubility. Meanwhile, no quantitative recommendation can be made basing on the results of these papers.

The range of rubbery state of PS was investigated much less thoroughly.^{1,2} The results of Newitt and Weale¹ and of Durnil² do not agree with each other. The results of Ref. 2 may be preferred at least tentatively. Further studies are needed to resolve this range of conditions.

References:

- ¹D. M. Newitt and K. E. Weale, *J. Chem. Soc.* 1541 (1948).
- ²P. L. Durnil, dissertation, Virginia Polytechnic Institute, 1965.
- ³W. R. Vieth, P. M. Tam, and A. S. Michaels, *J. Colloid Interface Sci.* **22**, 360 (1966).
- ⁴K. Toi and D. R. Paul, *Macromolecules* **15**, 1104 (1982).
- ⁵J. S. Chou, Y. Maeda, and D. R. Paul, *J. Appl. Polym. Sci.* **30**, 4019 (1985).
- ⁶C. Carfagna, L. Nicolais, and G. Campanile, *J. Polym. Sci., Part B: Polym. Phys.* **24**, 1805 (1986).
- ⁷E. Sada, H. Kumazawa, H. Yashiji, Y. Bamba, K. Sakata, and S-T. Wang, *Ind. Eng. Chem., Res.* **26**, 433 (1987).
- ⁸G. Wissinger and M. E. Paulaitis, *J. Polym. Sci., Part B: Polym. Phys.* **25**, 2497 (1987).
- ⁹P. C. Raymond and D. R. Paul, *J. Polym. Sci., Part B: Polym. Phys.* **28**, 2079 (1990).

Components:	
Evaluator:	
Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994.	

Critical Evaluation:

Nine experimental studies are available for the solubility of carbon dioxide in PS. In several papers this system was studied in the range of glassy state of this polymer and at pressures as high as 7.0 MPa.^{3,4,6-9} Newitt *et al.*¹ and Durnil² have studied the solubility at higher temperatures and pressures. Chou, Maeda, and Paul⁵ have investigated sorption in plasticized PS.

Different samples of PS having molecular mass in the range 36 000–850 000 were studied in the range of temperature 293–393 K. Up to 333 K sorption isotherms are concave to the pressure axis, i.e., agree with the dual mode sorption model, above this temperature they are linear possibly due to the plasticization effect exerted by carbon dioxide on PS.

A summary of the dual mode sorption parameters as well as the apparent solubility coefficients S are given in Table 1.

TABLE 1. The dual mode sorption parameters at different temperatures

T/K	k_D	C'_H	b	$S = k_D + C'_H b$	Ref.
293	0.801	13.0	0.184	3.19	7
303	0.713	11.0	0.134	2.19	7
308	0.535	8.6	0.194	2.20	9
308	0.50	9.2	0.16	1.97	4
313	0.586	8.8	0.092	1.40	7
313	0.80	8.3	0.14	1.96	6
323	0.70	6.0	0.15	1.60	6
333	0.66	5.0	0.11	1.21	6

Units: k_D and $S/(cm^3(STP) cm^{-3} atm^{-1})$; $C'_H/(cm^3(STP) cm^{-3} atm^{-1})$; b/atm^{-1} .

The parameters k_D and b decrease with temperature but do not form an overall smooth dependence. Accordingly, it is not included into this critical evaluation and, for the temperatures 293–313 K, the results of Sada *et al.*⁷ and, for the range 313–333 K, the results of Carfagna *et al.*⁶ should be recommended.

The values of C'_H and S found by different authors^{4,6,7,9} are in good agreement and form, within experimental scatter, a smooth temperature dependence (Figs. 16 and 17). The results of Vieth *et al.*³ reveal a deflection from these and were excluded from the group of recommended values.

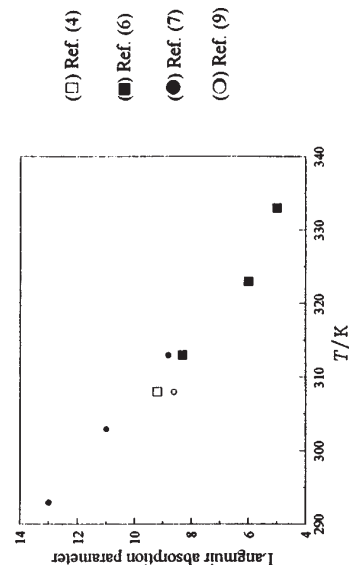


FIG. 16. Temperature dependence of Langmuir adsorption parameter $C'_H/(cm^3(STP) cm^{-3} atm^{-1})$.

TABLE 3. Solubility of methane in PS at high pressure and temperature

p/atm	$C/\text{cm}^3(\text{STP})\text{g}^{-1}$	p/atm	$C/\text{cm}^3(\text{STP})\text{g}^{-1}$
$T=398.6\text{ K}$			
100	8.3	100	$T=428.6\text{ K}$
200	16	200	
300	20		
$T=461.6\text{ K}$			
400	24	100	12
500	26	200	21
600	28	300	30

References:

¹J. L. Lundberg, B. M. Wilk, M. J. Hugett, *J. Polym. Sci.* **57**, 165, 275 (1962).
²J. L. Lundberg, B. M. Wilk, and M. J. Hugett, *Ind. Eng. Chem., Fundam.* **2**, 37 (1963).
³W. R. Vieth, P. M. Tam, and A. S. Michaels, *J. Colloid Interface Sci.* **22**, 360 (1966).
⁴W. R. Vieth, C. S. Frangoulis, and J. A. Rionda, *J. Colloid Interface Sci.* **22**, 454 (1966).
⁵J. L. Lundberg, E. J. Mooney, and C. E. Rogers, *J. Polym. Sci.: Part A* **7**, 947 (1969).
⁶J. A. Barrie, M. J. L. Williams, and K. Mundy, *Polym. Eng. Sci.* **20**, 21 (1980).
⁷E. Sada, H. Kumazawa, H. Yakushiji, Y. Bamba, K. Sakata, and S.-T. Wang, *Ind. Eng. Chem., Res.* **26**, 433 (1987).
⁸P. C. Raymond and D. R. Paul, *J. Polym. Sci., Part B: Polym. Phys.* **28**, 2079 (1990).

Components:	Evaluator:
(1) Methane, CH ₄ ; [74-82-8]	Yu. P. Yampol'skii, A. V. Topchiev, Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994
(2) Polystyrene (PS); [9003-53-6] (IX)	

Critical Evaluation:

A number of studies¹⁻⁸ have been published for the system PS-methane. Sorption isotherms in the range of pressure 0–3 MPa at the temperatures 293–323 K, i.e., in the glassy state have been reported by several authors.^{3,4,6-8} Lundberg *et al.*^{1,2} have studied this system at much higher pressures and at temperatures above the glass transition of this polymer. These two sets of data should be considered separately.

A summary of the parameters of the dual mode sorption model for this system are presented in Table 1 at different temperatures. The apparent solubility coefficients *S* are shown as well. It is seen that the *C'_H* and *S* values decrease with temperature monotonously while temperature dependence for two other parameters *k_D* and *b* is not evident. The linear extrapolation of the temperature dependence of *C'_H* indicates that Langmuir capacity parameter vanishes at the temperature somewhat lower than the glass transition temperature of PS.

TABLE 1. Dual mode sorption parameters at different temperatures

<i>T</i> /K	<i>k_D</i>	<i>C'_H</i>	<i>b</i>	<i>S</i> = <i>k_D</i> + <i>C'_H</i> / <i>b</i>	Ref.
293	0.305	5.00	0.0811	0.7105	7
298	0.193	3.25	0.164	0.726	4
298	0.16	7.4	0.108	0.9592	3
303	0.277	4.93	0.0623	0.584	7
303	—	—	—	0.5244	6
308	0.175	2.53	0.146	0.5444	4
308	0.135	3.28	0.061	0.335	8
313	0.244	3.63	0.0439	0.4034	7
318	0.165	1.98	0.112	0.3868	4
323	—	—	—	0.3344	6

Units: *k_D* and *S*/cm³(STP) cm⁻³ atm⁻¹; *C'_H*/cm³(STP) cm⁻³; *b*/atm⁻¹.

Smoothed concentration of methane dissolved at different temperatures and pressures are shown in Table 2. The solubility coefficients obtained in high pressure (0–3.0 MPa)^{4,7,8} and low pressure (up to 7 kPa)⁶ ranges are in reasonable agreement.

TABLE 2. Smoothed data for solubility *C*/(cm³(STP)cm⁻³) of methane in PS

<i>T</i> /K	Pressure/MPa			Ref.
	1.0	2.0	3.0	
293	5.3	9.2	12.7	7
298	3.9	6.3	8.5	4
308	3.0	5.0	6.8	4, 8
318	2.7	4.7	6.5	4

The results of Vieth *et al.*³ show that biaxial orientation leads to the decrease in solubility. All three model parameters (*k_D*, *C'_H*, *b*) go down as well.
For the range of higher pressures and temperatures the earlier results^{1,2} have been proved later⁵ to be somewhat erroneous. Recalculated data are presented in Ref. 5 and can be recommended.
Smoothed values of solubility are presented below for different pressures and temperatures.

Components:	Evaluator:
(1) 2-Methylpropane; C ₄ H ₁₀ ; [75-28-5] (2) Polystyrene (PS); [9003-53-6] (IX)	Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994

Critical Evaluation:

Three experimental studies¹⁻³ are available for the solubility of 2-methylpropane in PS. The results have been obtained by means of inverse gas chromatography.

Solubility coefficients $S/(\text{cm}^3(\text{STP}) \text{ g}^{-1} \text{ atm}^{-1})$ from these papers are compared below:

	T/K			
Ref.	423	448	473	498
1	1.20	0.86	0.65	0.52
2, 3	0.77	0.66	0.58	0.50

It is evident that there is a reasonable agreement between the data at higher temperatures, but at the lower temperature the discrepancy becomes significant. Further research is desirable to resolve this system.

References:

- ¹L. I. Stiel and D. F. Harnish, *AIChE. J.* **22**, 117 (1976).
²M. Ohzono, Y. Iwai, and Y. Arai, *Kagaku Kogaku Ronbunshu* **10**, 536 (1984).
³Y. Iwai, M. Ohzono, and Y. Arai, *Chem. Eng. Commun.* **34**, 225 (1985).

Components:	Evaluator:
(1) Propane; C ₃ H ₈ ; [74-98-6] (2) Polystyrene (PS); [9003-53-6] (IX)	Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994

Critical Evaluation:

The papers where solubility data have been reported for the system PS-propane can be partitioned into two groups. Barrie *et al.*² Yavorsky,⁴ and Stewart *et al.*⁶ have studied sorption isotherms by gravimetric or volumetric methods at the temperatures 293–353 K and in the pressure range 0–5 kPa. Inverse gas chromatography was employed in measurement solubility at higher temperatures.^{4–6} So these two groups of works cover the different intervals of conditions and should be considered separately.

In the lower temperature range, the dual mode sorption parameters for the sorption in glass PS have been reported only in Refs. 2 and 4. Barrie *et al.* found much higher values of b and the smaller C'_H values than those reported by Yavorsky.⁴ There are some regular discrepancies in the apparent solubility coefficients $S = k_D + C'_H b$. On the other hand, the data of Barrie *et al.*² agree reasonably with the sorption isotherms reported in Ref. 6. Bearing in mind this, and the greater scatter of the points in the sorption isotherms obtained by Yavorsky,⁴ the results of Barrie *et al.* should be tentatively recommended for the temperature range 293–333 K.

The values of Langmuir capacity constant C'_H reported in Ref. 2 go down with temperature and vanish at about 360 K, i.e., below the glass transition temperature of PS.

In the high temperature range, the data of Iwai *et al.*^{3,5} and Stiel and Harnish¹ agree quite reasonably. Average solubility coefficients $S/(\text{g Mpa}^{-1} \text{ g}^{-1})$ based on these results are given below:

T/K	408	423	448	473	498
$S/10^2$	1.56	1.33	1.06	0.88	0.76

References:

- ¹L. I. Stiel and D. F. Harnish, *AIChE J.* **22**, 117 (1976).
²J. A. Barrie, M. J. L. Williams, and K. Munday, *Polym. Eng. Sci.* **20**, 21 (1980).
³M. Ohzono, Y. Iwai, and Y. Arai, *Kagaku Kogaku Ronbunshu* **10**, 536 (1984).
⁴J. A. Yavorsky, dissertation, Clemson University, 1984.
⁵Y. Iwai, M. Ohzono, and Y. Arai, *Chem. Eng. Commun.* **34**, 225 (1985).
⁶M. E. Stewart, H. B. Hopfenberg, W. J. Koros, and N. R. McCoy, *J. Appl. Polym. Sci.* **34**, 721 (1987).

Components:	Original Measurements:
(1) Nitrogen N ₂ ; [7727-37-9] Ethylene C ₂ H ₄ ; [74-86-2] Hydrogen; H ₂ ; [1333-74-0] Carbon dioxide; CO ₂ ; [124-38-9] (2) Polystyrene; (PS); [9003-53-6] (IX)	D. M. Newitt and K. E. Weale, J. Chem. Soc. 1541 (1948).
Variables:	Prepared By:
T/K; 347-464 p/MPa; 8.0-30.0	A. K. Bokarev

Experimental Data				
TABLE 1. Solubility $C(\text{cm}^3(\text{STP})/\text{cm}^3$ of gases in PS at 443 K				
Gas	p/atm	C	Gas	C
H ₂	80	2.89	N ₂	118
	142	5.35		182
	224.5	8.48		5.02
	233	9.42		187
	243	9.66		232
CO ₂	306.5	11.95		282.5
				287
				7.77
	50	3.04	C ₂ H ₂	49
	51	2.82		77.55
				8.05
				9.75

TABLE 2. Temperature dependence of solubility coefficient $S(\text{cm}^3(\text{STP})/\text{cm}^3 \text{ atm})$				
Gas	T/K	S	Gas	T/K
N ₂	347	0.035	H ₂	290
	409	0.033		322
	422	0.031		345
	443	0.0275		399
	464	0.026		415
				443
				459.5

The data fitted the following van't Hoff equations:
 $\log(S/\text{cm}^3(\text{STP})/\text{cm}^3 \text{ atm}) = -2.4 + 1900/4.58 (T/\text{K})$ for H₂;
 $\log(S/\text{cm}^3(\text{STP})/\text{cm}^3 \text{ atm}) = -2.4 + 1700/4.58 (T/\text{K})$ for N₂.

Method/Apparatus/Procedure	Auxiliary Information	Source and Purity of Materials
Manometric method of measurement of solubility was used.		PS from B. X. Plastics Ltd. was studied. No characteristics of the polymer given.
		Estimated Error: Nothing specified.

Components:	Evaluator:
(1) Chlorodifluoromethane; CHClF ₂ ; [75-45-6] (2) Polystyrene (PS); [9003-53-6] (IX)	Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994

Critical Evaluation:
The solubility coefficients measured at higher temperatures² were recalculated to convert them into the same units as in Ref. 3, i.e., (cm³(STP)/cm³ atm). Volumetric thermal expansion coefficients³ $2 \times 10^{-4} \text{ K}^{-1}$ at $T < T_g$ (●) and $6 \times 10^{-4} \text{ K}^{-1}$ at $T > T_g$ (○) were used in the calculation. It is seen that the slopes of the linear dependences and, hence, the enthalpies of sorption change when passing from glassy to rubbery state of PS. The point reported by Durrill and Griskey was not included, tentatively, into the calculation. The enthalpies of sorption corresponding the glassy and rubbery states are equal to -34.2 and -15.4 kJ/mol, respectively.

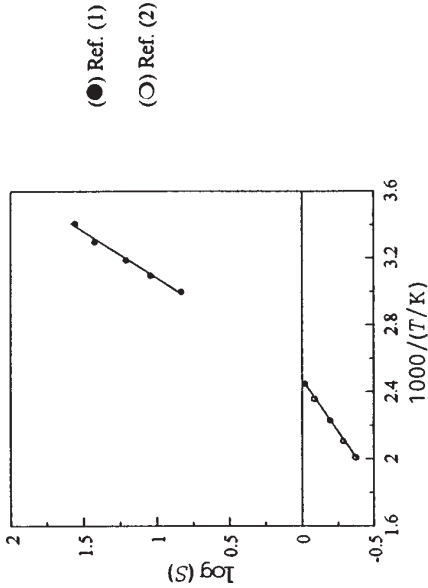


FIG. 18. The solubility of chlorodifluoromethane (Freon-22) in PS was measured only in three papers.¹⁻³ Barrie *et al.*³ studied this system using a gravimetric technique in the temperature range 293-333 K. At much higher temperatures, this system was investigated by means of inverse gas chromatography.² The figure shows the temperature dependence T/K of the solubility coefficient $S/(\text{cm}^3(\text{STP}) \text{ g}^{-1} \text{ atm}^{-1})$.

- References:**
¹P. L. Durrill and R. G. Griskey, *AIChE J.* **12**, 1147 (1966).
²L. I. Stiel and D. F. Hamish, *AIChE J.* **22**, 117 (1976).
³J. A. Barrie, M. J. L. Williams, and K. Munday, *Polym. Eng. Sci.* **20**, 21 (1980).
⁴*Polymer Encyclopaedia* (in Russian) (Sov. Enycl. Publishers, Moscow, 1977), Vol. 3, p. 534.

Components:	
(1) Argon; Ar; [7440-37-1] Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Polystyrene (PS); [9003-53-6] (IX)	
Original Measurements:	
W. R. Vieth, P. M. Tam, and A. S. Michaels, J. Colloid Interface Sci. 22 , 360 (1966).	
Variables:	
<i>T</i> /K=298	
<i>p</i> /MPa=0–2.1 (0–20 atm)	
Prepared By:	
A. K. Bokarev	

Experimental Data				
TABLE 1. Dual mode sorption parameters for various gases in polystyrene at 298 K				
Gas	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$		$C'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	
	Oriented	Unoriented	Oriented	Unoriented
N ₂	0.02	0.025	6.65	8.3
Ar	0.06	0.065	7.55	9.1
CH ₄	0.13	0.160	5.58	7.4
CO ₂	0.57	0.650	6.05	7.7
				0.370

Components:	
(1) Helium; He; [7440-59-7] Nitrogen; N ₂ ; [7727-37-9] Argon; Ar; [7440-37-1] Carbon dioxide; CO ₂ ; [124-38-9] Chlorodifluoromethane (R22); CHFC1 ₂ ; [75-45-6] (2) Polystyrene (PS); [9003-53-6] (IX)	
Original Measurements:	
P. L. Durrill, Ph.D. dissertation, Virginia Polytech. Inst., 1965; P. L. Durrill and R. G. Griskey, <i>AIChE J.</i> 12 , 1147 (1965).	
Variables:	
<i>T</i> /K= 461	
<i>p</i> /MPa= 0.3–1.9 (3–19 atm)	
Prepared By:	
A. K. Bokarev	

Experimental Data	
Henry's law solubility coefficients <i>S'</i> of gases in PS	
Gas	Pressure/atm
He	2–13.6
N ₂	3.1–7.0
Ar	3.3–7.4
CO ₂	7.4–19.1
CHFC1 ₂	5.8–8.1
	<i>S'</i> /(cm ³ (STP)/(g atm)
	0.029±0.020
	0.0488
	0.093±0.004
	0.223±0.015
	0.388

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
The equipment and a manometrical procedure for solubility measurements were similar to those of Lundberg <i>et al.</i> ¹	PS used is a product of Monsanto Co. $M_w=450\,000$; $T_g=354\text{ K}$; $\rho=1.05\text{ g/cm}^3$.
	Gases from Air Reduction Co., had a minimum purity:
	CO ₂ -99.5%;
	N ₂ -99.90%;
	Ar-99.997%;
	He-99.99%;
	R22 (Allied Chemical Co.)-99.9%.
	Estimated Error:
	$\delta C/C=8\%$.
	References:
	¹ J. L. Lundberg, M. B. Wilk, and M. J. Huyett, <i>Appl. Phys.</i> 31 , 1131 (1960).

TABLE 2. Solubility isotherms of various gases in polystyrene at 298 K (The original data were represented graphically)

First runs				Second runs			
Oriented		Unoriented		Oriented		Unoriented	
Pressure/MPa	Sorption ($V^*_1(\text{STP})/V^*_2$)	Pressure/MPa	Sorption ($V^*_1(\text{STP})/V^*_2$)	Pressure/MPa	Sorption ($V^*_1(\text{STP})/V^*_2$)	Pressure/MPa	Sorption ($V^*_1(\text{STP})/V^*_2$)
Ar							
0.42	0.98	0.54	1.23	0.56	1.60	0.43	1.23
0.79	1.68	0.99	1.97	1.05	2.42	1.01	2.34
1.12	2.17	1.50	2.71	1.42	3.20	1.70	3.57
1.43	2.75	1.84	3.20	1.77	3.73	2.09	4.10
1.78	3.25	2.06	3.48	2.10	4.30	—	—
2.04	3.32	—	—	—	—	—	—
CO ₂							
0.14	3.07	0.17	3.36	0.35	6.35	0.29	5.82
0.27	4.63	0.34	5.57	0.69	9.88	0.83	11.39
0.41	6.19	0.51	7.42	1.04	13.12	1.39	15.70
0.55	7.54	0.68	8.89	1.35	15.04	1.89	18.89
0.69	8.77	0.88	10.29	1.75	18.40	—	—
0.86	9.84	1.08	11.56	1.98	19.88	—	—
1.02	10.86	1.32	12.91	—	—	—	—
1.17	11.97	1.54	14.47	—	—	—	—
1.37	13.12	1.77	15.53	—	—	—	—
1.55	14.39	—	—	—	—	—	—
1.73	15.33	—	—	—	—	—	—
CH ₄							
0.34	1.80	0.43	2.38	0.48	3.40	0.48	3.40
0.51	2.54	0.85	3.57	0.93	5.16	0.97	5.25
0.78	3.36	1.26	4.67	1.36	6.60	1.59	7.21
1.05	4.14	1.77	5.78	1.79	7.87	2.03	8.24
1.34	4.88	2.02	6.27	2.06	8.44	—	—
1.63	5.49	—	—	—	—	—	—
1.90	6.19	—	—	—	—	—	—
N ₂							
0.47	0.66	0.60	0.82	0.58	0.98	0.49	0.78
0.99	1.07	1.08	1.15	1.09	1.48	0.86	1.19
1.53	1.56	1.57	1.64	1.55	1.89	1.33	1.64
1.99	1.93	2.06	1.97	2.09	2.42	1.85	2.21

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials
A direct measurement of the solubility was made with a volumetric apparatus. With the film sample placed in the sorption bomb, the sorption system is evacuated and flushed with gas several times. The system is then evacuated to 0.02 mm Hg. Gas is then introduced rapidly, and the initial pressure recorded. Sorption takes place instantaneously and proceeds until the equilibrium pressure is established.	Gases: minimum purity 99.99%. Biaxially oriented PS film: Dow Chemical Co., density 1.0490 g/cm ³ . Cast annealed PS film: prepared from a solution of about 2.0% by weight of oriented PS in methylene dichloride, density 1.0474 g/cm ³ .
Estimated Error:	Relative precision of solubilities: CO ₂ 8.1%; CH ₄ 6.3%; Ar 10.5%; N ₂ 15%.

Components:
(1) Various gases (He, Ar, Kr, Xe, N₂)
(2) Polystyrene (PS); [9003-53-6] (IX)

Original Measurements:
H. Odani, K. Taira, N. Nemoto, and M. Kurata, Bull. Inst. Chem. Res., Kyoto Univ. **57**, 4, 226 (1979).

Variables:
T/K: 298–348
p/kPa: 0–26
Prepared By:
A. K. Bokarev

Experimental Data
Equilibrium solubility coefficient at 298 K and heats of solution of gases in polystyrene

Gas	$S \cdot 10^3/\text{cm}^3(\text{STP}) \text{ cm}^{-3} \text{ cm Hg}^{-1}$	$\Delta H_f / \text{kJ mol}^{-1}$
Helium; He; [7440-59-7]	0.17	—
Argon; Ar; [7440-37-1]	5.03	−13.6
Krypton; Kr; [7439-90-9]	17.8	−17.5
Xenon; Xe; [7440-63-3]	89.0	−23.2
Nitrogen; N ₂ ; [7727-37-9]	2.29	−13.8

Auxiliary Information

Method/Apparatus/Procedure
The solubility has been measured by a volumetric method. Measurements were performed using an apparatus similar to that employed by Meares.¹

Source and Purity of Materials:
Anionically polymerized PS sample having $M_w = 106\,000$ was used.
He, Ar, Kr, Xe and N₂ were obtained from Takachiho Kagaku Kogyo, Co. Ltd., and the purity of each gas exceeded 99.995% by volume.

Estimated Error:
No information.

References:
¹ P. Meares, Trans. Faraday Soc. **54**, 40 (1958).

Components:		Original Measurements:	
(1) Methane, CH ₄ ; [74-82-8]		(1) Carbon dioxide, CO ₂ ; [124-38-9]	
(2) Polystyrene (PS); [9003-53-6] (IX)		(2) Polystyrene (PS); [9003-53-6] (IX)	
Variables:		Prepared By:	
$T/K = 373-461$		Yu. P. Yampol'skii	
$p/\text{MPa} = 4.9-67$		$T/K = 308-328$	
		$p/\text{MPa} = 0-2.3$ (0-22 atm)	
		$M_w = 3600-850\ 000$	

Experimental Data			
TABLE 1. Molecular masses and polydispersity of PS studied			
Type	MM	M_w/M_n	
PS-I	$M_w = 3600$	M_w/M_n	<1.06
PS-I	$M_w = 9100$	M_w/M_n	<1.06
PS-I	$M_w = 17\ 400$	M_w/M_n	<1.06
PS-I	$M_w = 850\ 000$	M_w/M_n	<1.06
PS-II	$M_w = 90\ 000$	M_w/M_n	2.8

TABLE 2. Dual mode sorption parameters for carbon dioxide at 308 K (Read off the plots by the compiler)				
MM	T_g/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_2'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
3600	345	0.38	5.0	0.17
9100	359	0.46	7.5	0.20
17 400	371	0.45	8.0	0.17
850 000	374	0.50	9.2	0.16
90 000	374	0.51	9.5	0.17

Components:		Original Measurements:	
(1) Methane, CH ₄ ; [74-82-8]		J. L. Lundberg, B. M. Wilk, and M. J. Huyett, Ind. Eng. Chem., Fundam. 2 , 37 (1963).	
(2) Polystyrene (PS); [9003-53-6] (IX)		J. L. Lundberg, E. J. Mooney, and C. E. Rogers, J. Polym. Sci. Part A-2 7 , 947 (1969).	
Variables:		Prepared By:	
$T/K = 373-461$		Yu. P. Yampol'skii	
$p/\text{MPa} = 4.9-67$			

Experimental Data		
Solubility of methane in PS		
T/K	p/atm	$C/\text{cm}^3(\text{STP})\text{cm}^{-3}$
373.35	320	22.5
398.55	50	4.5
	217	16.5
	300	22
	333	21
	347	24
	433	24
	467	25
	537	27
	590	28
	667	29
428.57	50	5
	163	14
	243	23
461.55	67	8
	120	14
	200	21
	250	25
	313	30

Digitized by the compiler from the original figure.

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
The method of "interval" sorption was used. Pressure decrease due to sorption in a closed system of known volume was measured with a pressure transducer. Polymer samples were put between two disks of sintered glass. No correction for the swelling of the sample was introduced.	PS had $M_w = 500\ 000$. Purity of methane was >99.0%.
	Estimated Error:
	$\delta T = \pm 0.02\ \text{K}$
	$\delta p = \pm 0.5\ \text{atm}$
	$\delta C/C < 5\%$

TABLE 3. Effect of temperature on sorption of CO₂ in monodisperse polystyrenes with $M_w = 3600$ (The original data were represented graphically)

$T = 308\text{ K}$			$T = 318\text{ K}$			$T = 328\text{ K}$		
Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)		Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)		Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	
0.08	0.92		0.08	0.63		0.10	0.42	
0.13	1.42		0.13	0.92		0.14	0.71	
0.17	1.72		0.18	1.17		0.24	1.13	
0.22	2.18		0.20	1.38		0.31	1.43	
0.28	2.76		0.33	2.14		0.38	1.60	
0.36	3.18		0.37	2.27		0.43	1.85	
0.40	3.56		0.41	2.48		0.52	2.40	
0.52	4.27		0.46	2.94		0.63	2.73	
0.60	4.73		0.53	3.31		0.74	3.16	
0.72	5.45		0.63	3.65		0.82	3.45	
0.80	5.78		0.73	3.90		1.01	4.25	
0.89	6.70		0.81	4.37		1.21	5.01	
0.99	7.17		0.91	4.91		1.40	5.64	
1.18	7.92		1.01	5.54		1.60	6.44	
1.36	8.89		1.22	6.26		1.75	7.07	
1.55	9.56		1.41	7.06		1.93	7.75	
1.76	10.74		1.56	7.73		2.02	8.21	
1.91	11.41		1.76	8.53		2.11	8.67	
2.01	11.75		1.96	9.25		2.18	8.80	
2.09	12.21		2.03	9.79		—	—	
2.17	12.51		2.13	10.09		—	—	
2.29	13.01		2.20	10.34		—	—	
—	—		2.29	10.93		—	—	

Method/Apparatus/Procedure
The method of sorptions measurement was the same as described in Refs. ¹ and ². Prior to determination of the sorption isotherms the films cast from trichloroethylene solution and free from the solvent were conditioned for 1 d at 24 atm of CO₂.

Source and Purity of Materials
Monodispersed PS-I: Pressure Chemical Co., Polydispersed PS-II: Cosden Oil and Chemical Co.
Their viscosity molecular masses, M_w/M_n ratios and T_g values are given above.

Estimated Error:
No information given.

References:
¹W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. **14**, 687 (1976).
²W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. **14**, 1903 (1976).

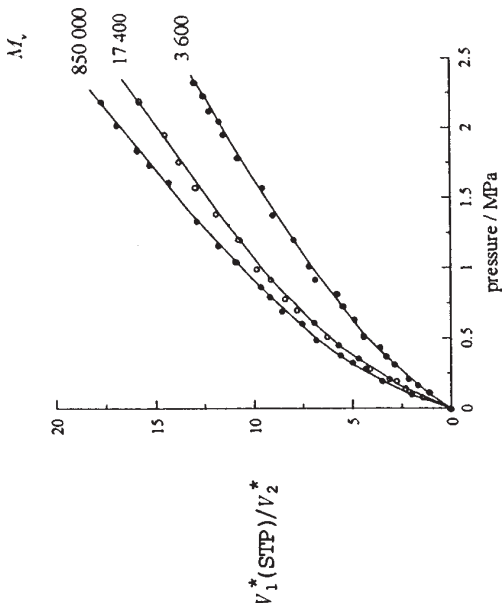


FIG. 19. Sorption isotherms of carbon dioxide in various monodisperse polystyrenes at 308 K.

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]		R. G. Wissinger and M. E. Paulaitis, J. Polym. Sci., Part B: Polym. Phys. 25 , 2497 (1987).	
(2) Polystyrene (PS); [9003-53-6] (IX)			
Variables:		Prepared By:	
$T/K = 308.2 - 338.2$		Yu. P. Yampol'skii	
$p/\text{MPa} = 0 - 7.3$ (0–70 atm)			
Experimental Data			
Sorption isotherms of carbon dioxide in polystyrene at different temperatures. (The original data were represented graphically)			
$T = 308.2 \text{ K}$		$T = 323.2 \text{ K}$	
Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)
0.51	6.04	0.52	4.86
1.02	9.38	1.05	6.94
1.57	13.31	1.57	10.03
2.06	15.98	2.17	14.88
2.92	23.44	2.68	17.46
3.78	31.73	3.19	20.89
4.55	36.32	3.68	23.64
5.52	42.67	4.22	25.64
6.38	48.36	4.71	29.23
7.29	57.32	5.17	31.31
—	—	5.57	35.67
$T = 338.2 \text{ K}$		$T = 338.2 \text{ K}$	
Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)
0.42	4.19	0.42	4.19
0.80	5.94	0.80	5.94
1.24	7.60	1.24	7.60
1.65	10.61	1.65	10.61
2.04	11.35	2.04	11.35
2.47	14.53	2.47	14.53
2.87	16.44	2.87	16.44
3.33	18.01	3.33	18.01
3.69	19.51	3.69	19.51
4.01	21.68	4.01	21.68
4.32	24.11	4.32	24.11
Auxiliary Information			
Method/Apparatus/Procedure		Source and Purity of Materials:	
A gravimetric method was used. The polymer samples were suspended from a quartz spring. A correction for buoyancy was introduced using the densities of carbon dioxide up to high pressures.		CO ₂ : Linde, purity 99.99%.	
		Polystyrene: Scientific Polymer Products, $M_w = 250\,000$, glass transition temp. 373 K.	
Estimated Error:		Estimated Error:	
No information given.		No information given.	

Components:

(1) Carbon dioxide; CO₂; [124-38-9]
 (2) Polystyrene (PS); [9003-53-6] (IX)
 (3) Mineral oil Phosphate acid, tri(methyl phenyl) ester (tricresyl phosphate, TCP); (CH₃C₆H₄)₃PO; [1330-78-5]

Variables:

$$T/K = 298 - 338$$

$$p/\text{MPa} = 0 - 3.0$$

Original Measurements:

J. S. Chion, Y. Maeda, and D. R. Paul, J. Appl. Polym. Sci. **30**, 4019 (1985).

Prepared By:

Yu. P. Yampol'skii

Experimental Data

Figure 20 consists of two graphs, (a) and (b), showing the effect of temperature on the sorption isotherms of carbon dioxide in polystyrene (PS) containing 3% by mass of mineral oil (a) and 10% by mass of TCP (b). The y-axis for both graphs is $V_1^*(\text{STP})/V_2^*$ and the x-axis is pressure / atm.

Graph (a) shows three curves for temperatures 318 K, 328 K, and 338 K. The y-axis ranges from 0 to 20, and the x-axis ranges from 0 to 30. The curves show a non-linear increase in sorption with pressure, with higher temperatures resulting in higher sorption values.

Graph (b) shows three curves for temperatures 298 K, 308 K, and 318 K. The y-axis ranges from 0 to 30, and the x-axis ranges from 0 to 30. The curves show a non-linear increase in sorption with pressure, with higher temperatures resulting in higher sorption values.

Fig. 20. Effect of temperature on sorption isotherms of carbon dioxide in PS containing 3% by mass of mineral oil (a) and 10% by mass of TCP (b).

Auxiliary Information

Method/Apparatus/Procedure

Sorption isotherms were obtained using dual-volume dual-transducer cell design based on the pressure decay principle.

Source and Purity of Materials:

PS: $M_w = 90\,000$, $M_w/M_n = 2.8$.
 PS containing 3% of mineral oil: $T_g = 360 \text{ K}$.
 PS containing 10% of TCP: $T_g = 343 \text{ K}$.
 The samples were conditioned at the highest CO₂ pressure before measurement.

Estimated Error:

No information given.

FIG. 20. Effect of temperature on sorption isotherms of carbon dioxide in PS containing 3% by mass of mineral oil (a) and 10% by mass of TCP (b).

Table 2. Sorption isotherms of carbon dioxide in oriented PS films at various temperatures (The original data were represented graphically)

Pressure/MPa		Sorption ($V_1^*/(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*/(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*/(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*/(\text{STP})/V_2^*$)
<i>T</i> = 300.8 K								
0.04	1.44	13.63	0.96	1.43	16.08	2.28	22.04	
0.31	6.10	13.85	1.02	1.84	19.72	2.37	23.60	
0.46	7.84	15.62	1.20	1.93	20.56	2.92	26.67	
0.45	8.70	16.59	1.37	2.16	21.61	—	—	
<i>T</i> = 313 K								
0.13	2.06	5.54	0.43	1.15	10.88	2.15	15.59	
0.17	2.87	6.38	0.49	1.23	11.27	2.34	16.51	
0.30	4.29	7.31	0.61	1.61	13.29	2.89	18.49	
0.33	4.78	9.04	0.82	1.80	13.71	—	—	
0.39	5.18	9.83	0.93	2.06	15.29	—	—	
<i>T</i> = 323 K								
0.11	1.29	7.01	1.01	1.82	9.54	2.33	10.90	
0.28	2.62	7.16	1.22	1.92	9.43	2.55	11.22	
0.33	3.06	8.17	1.37	2.03	10.23	2.64	11.79	
0.55	4.29	8.64	1.51	2.14	9.84	2.89	12.61	
0.71	5.48	8.79	1.74	2.22	10.65	—	—	
<i>T</i> = 333 K								
0.10	0.57	2.97	0.58	1.15	4.50	2.02	7.78	
0.16	0.79	3.50	0.67	1.23	5.44	2.34	8.68	
0.21	1.19	3.57	0.80	1.35	6.05	2.53	9.23	
0.31	1.62	4.54	0.95	1.43	6.13	2.93	10.25	
0.40	2.24	4.79	1.04	1.53	6.38	—	—	
0.48	2.63	4.65	1.10	1.72	6.93	—	—	
<i>T</i> = 353 K								
0.13	0.34	4.68	1.15	1.80	6.78	2.74	11.59	
0.27	1.31	5.54	1.41	1.88	8.08	—	—	
0.59	2.34	6.09	1.62	2.01	8.19	—	—	
0.82	3.25	6.69	1.56	2.31	9.32	—	—	
<i>T</i> = 373 K								
0.30	0.99	2.54	0.72	0.88	3.19	2.43	9.39	
0.41	1.29	3.16	0.79	1.70	6.57	—	—	

Table 1. Dual mode sorption parameters for CO₂ in polystyrene at various temperatures

<i>T</i> /K		$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_D/\text{cm}^3(\text{STP})\text{cm}^{-3}$	<i>b</i> /atm ^{−1}
Oriented film				
300.8	0.698	8.132	—	0.388
313	0.463	6.839	—	0.298
323	0.296	5.273	—	0.227
333	0.307	2.956	—	0.157
352	0.453	—	—	—
373	0.425	—	—	—
Unoriented film				
313	0.744	8.341	—	0.131
323	0.712	5.990	—	0.151
333	0.659	5.004	—	0.112
353	0.577	—	—	—
373	0.477	—	—	—
393	0.417	—	—	—

TABLE 3. Sorption isotherms of carbon dioxide in unoriented PS films at various temperatures (The original data were represented graphically)

Pressure/MPa	Sorption ($V^*_g(\text{STP})/V^*_g$)	Pressure/MPa	Sorption ($V^*_g(\text{STP})/V^*_g$)	Pressure/MPa	Sorption ($V^*_g(\text{STP})/V^*_g$)	Pressure/MPa	Sorption ($V^*_g(\text{STP})/V^*_g$)
$T = 313 \text{ K}$							
0.15	2.78	1.00	12.46	1.96	19.72	3.01	26.35
0.30	4.02	1.27	14.49	2.19	22.44	—	—
0.60	8.10	1.52	16.06	2.30	22.14	—	—
0.76	9.34	1.78	19.46	2.89	26.59	—	—
$T = 323 \text{ K}$							
0.29	3.40	0.893	10.13	1.52	14.46	2.63	22.73
0.40	5.10	1.204	11.92	1.78	16.66	2.87	23.56
0.61	6.73	1.386	13.50	2.40	20.19	—	—
$T = 333 \text{ K}$							
0.17	1.81	0.47	4.86	1.10	10.05	2.16	17.41
0.23	2.15	0.71	6.72	1.36	12.48	2.51	20.23
0.31	2.94	0.70	7.35	1.48	13.15	3.03	23.26
0.44	4.24	0.89	8.01	1.78	14.77	—	—
$T = 353 \text{ K}$							
0.18	1.18	1.17	7.07	2.24	13.41	2.85	16.54
0.61	3.70	1.48	9.09	2.30	13.11	—	—
0.89	5.56	1.82	10.88	2.65	15.19	—	—
$T = 373 \text{ K}$							
0.17	0.78	0.90	4.36	1.44	7.15	2.24	10.49
0.29	1.17	0.99	4.35	1.56	7.48	2.47	11.15
0.60	2.79	1.08	5.19	1.85	8.19	2.92	13.39
0.83	3.74	1.10	5.02	2.15	9.76	3.07	14.05
$T = 393 \text{ K}$							
0.22	0.60	0.46	1.49	1.50	6.23	2.38	9.45
0.27	0.83	0.60	2.28	1.91	7.39	2.93	11.73
0.30	0.94	0.91	3.78	2.17	9.07	3.05	12.40

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials
The sorption apparatus used was similar to that described in Ref. 1. Experiments were performed on uniaxially drawn samples. Unoriented samples were obtained by annealing the extruded film at 453 K for 20 min.	PS atactic: Montedison Co., $M_w = 290\ 000$, glass transition temperature 371 K.
	Estimated Error: No information given.
	References: 1W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).

Components:

(1) Carbon dioxide; CO₂; [124-38-9] Methane; CH₄; [74-82-8]
 (2) Polystyrene (PS); [9003-53-6] (IX)

Variables:

$T/\text{K} = 293 - 313$
 $p/\text{MPa} = 0.2 - 3.0$

Original Measurements:

E. Sada, H. Kumazawa, H. Yakushiji, Y. Bamba, K. Sakata, and S.-T. Wang, Ind. Eng. Chem., Res. **26**, 433 (1987).

Prepared By:

Yu. P. Yampol'skii

Experimental Data

Dual mode sorption parameters

Gas	T/K	$k_D/\text{cm}^3(\text{STP})/\text{cm}^3 \text{ atm}$	$C'_D/\text{cm}^3(\text{STP})/\text{cm}^3$	b/atm^{-1}
CO ₂	293	0.801	13.0	0.184
	303	0.713	11.0	0.134
	313	0.586	8.81	0.0918
CH ₄	293	0.305	5.00	0.0811
	303	0.277	4.93	0.0623
	313	0.244	3.63	0.0439

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials	Estimated Error	References
Equilibrium sorption was measured by the pressure decay method in the cell similar to that described in Ref. 1. The pressure in the cell was continuously measured by a pressure transducer.	PS films provided by Mirzabishi-Monsanto Chemical Co were studied.	No information given.	1W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed., 14 , 687 (1976).

Components: (1) Propane; C ₃ H ₈ ; [74-98-6] (2) Polystyrene (PS); [9003-53-6] (IX)		Original Measurements: H. G. Spencer and J. A. Yavorsky, <i>J. Appl. Polym. Sci.</i> 28 , 2937 (1983).	
Variables: T/K=345–370 p/kPa=0–40		Prepared By: A. K. Bokarev	
Experimental Data			
Temperature dependence for the solubility coefficient <i>S</i> of propane in polystyrene is given by the equation: $S = S_0 \exp(-\Delta H/RT)$.			
At 353 K, the parameters are:			
$\Delta H/\text{kJ mol}^{-1}$	$\ln(S_0/(\text{cm}^3(\text{STP})/\text{cm}^3 \text{ Hg}))$	$\ln(S/\text{cm}^3(\text{STP})/(\text{cm}^3 \text{ cm Hg}))$	
–8	–7.15	–4.49	
Temperature dependence for solubility coefficient <i>S</i> of propane in polystyrene.			
T/K	$\ln(S/\text{cm}^3(\text{STP})/(\text{cm}^3 \text{ cm Hg}))$		
343.6	–4.44		
348.4	–4.52		
357.1	–4.48		
370.3	–4.59		
Auxiliary Information			
Method/Apparatus/Procedure		Source and Purity of Materials: C ₃ H ₈ : Matheson, purity 99.999%. PS: Polysciences Inc., $M_w = 23\,000$, glass transition temperature 334 K, density (303 K) 1.06 g/cm ³ .	
		Estimated Error: No information given.	
		References: 1. J. A. Yavorsky and H. G. Spencer, <i>J. Appl. Polym. Sci.</i> 25 , 2109 (1980).	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Polystyrene (PS); [9003-53-6] (IX)		Original Measurements: P. C. Raymond and D. R. Paul, <i>J. Polym. Sci., Part B: Polym. Phys.</i> 28 , 2079 (1990).	
Variables: T/K=308 p/MPa=0–2.5 (0–25 atm)		Prepared By: Yu. P. Yampol'skii	
Experimental Data			
TABLE 1. Sorption $C/(\text{cm}^3(\text{STP})/\text{cm}^3)$ of methane and carbon dioxide in PS*			
p/atm		CH ₄	CO ₂
5		1.5	6.7
10		2.6	11.1
15		3.6	14.6
20		4.4	17.6
25		5.3	20.0
*Smoothed data taken from the plot by the compiler.			
TABLE 2. Dual mode sorption parameters			
Gas	$k_D/\text{cm}^3(\text{STP})/\text{cm}^3 \text{ atm}$	$C'_D/\text{cm}^3(\text{STP})/\text{cm}^3$	b/atm^{-1}
CH ₄	0.135	3.28	0.061
CO ₂	0.535	8.63	0.194
Auxiliary Information			
Method/Apparatus/Procedure Gas sorption measurement was performed using the same equipment and procedure as in Ref. 1. Sorption isotherm for methane were obtained using polymer samples which had never been exposed to CO ₂ . The CO ₂ isotherm was obtained using the sample that had been conditioned in CO ₂ at 25 atm for 24 h.		Source and Purity of Materials: PS (Corden Oil 550) had a density 1.052 g/cc and the glass transition temperature 373 K. No information on gas purity given.	
		Estimated Error: No information given.	
		References: 1Y. Maeda and D. R. Paul, <i>Polymer</i> 26 , 2055 (1985).	

Components:		Original Measurements:	
(1) Propane; C ₃ H ₈ ; [74-98-6]		M. E. Stewart, H. B. Hopfenberg, W. J. Koros, and N. R. McCoy, <i>J. Appl. Polym. Sci.</i> 34 , 721 (1987).	
(2) Polystyrene (PS); [9003-53-6] (IX)			
Variables:		Prepared By:	
<i>T</i> /K: 303		Yu. P. Yampol'skii	
<i>p</i> /kPa: 6.1–93.1			

Experimental Data				
Solubility <i>C</i> (g per 100 g polymer) of propane in PS*				
Sample	<i>p</i> /mm Hg	<i>C</i>	Sample	<i>C</i>
PS as received	46	0.20	PS preswollen	46
	149	0.38	in C ₃ H ₈	144
	357	0.56	(700 mm Hg, 30 min)	448
	558	0.79		0.85
	700	1.05		

*Taken from the graph by compiler.

Method/Apparatus/Procedure		Source and Purity of Materials:	
Gas sorption measurements were performed using a Cahn RG microbalance. The sorption apparatus and procedure are discussed in Ref. 1		Emulsion polymerized PS (B.F. Goodrich Co R/D center) had $M_w = 440\,000$ and glass transition temperature 381 K.	
		Instrument grade propane was 99.99% pure.	
Estimated Error:		References:	
No information given.		J. M. H. Fechter, H. B. Hopfenberger, and W. J. Koros, <i>Polym. Eng. Sci.</i> 21 , 925 (1981).	

Components:		Original Measurements:	
(1) Propane; C ₃ H ₈ ; [74-98-6]		J. A. Yavovsky, Ph.D. dissertation, Department of Chemistry and Geology, Clemson University, 1984.	
(2) Polystyrene (PS); [9003-53-6] (IX)			
Variables:		Prepared By:	
<i>T</i> /K=313–353		A. K. Bokarev	
<i>p</i> /kPa=0–580			

Experimental Data			
TABLE 1. Dual mode sorption parameters for propane in polystyrene			
<i>T</i> /K	$10^2 k_D / \text{cm}^3 (\text{STP}) \text{cm}^{-3} \text{cm Hg}^{-1}$	$C'_H / \text{cm}^3 (\text{STP}) \text{cm}^{-3}$	$10^2 b / \text{cm Hg}^{-1}$
313	2.49	3.7	1.33
333	1.98	4.2	0.25
353	1.62	3.7	0.06

TABLE 2. Sorption isotherms of propane in polystyrene (The original data were represented graphically)

<i>T</i> = 313 K			
Pressure/kPa	Sorption ($(P/P^s)(\text{STP})/P^s$)	Pressure/kPa	Sorption ($(P/P^s)(\text{STP})/P^s$)
32.64	1.32	36.97	0.40
41.20	1.74	36.44	0.69
51.07	2.03	131.88	2.73
238.32	7.02	141.62	2.78
—	—	144.81	3.51
—	—	248.83	6.02
—	—	313.34	6.08
—	—	493.11	11.34
—	—	550.73	10.27

Auxiliary Information	
Method/Apparatus/Procedure	
The equilibrium solubility of gases in the polymer was measured by a manometric technique. High pressure apparatus (up to 930 kPa) with pressure transducers was employed.	
Source and Purity of Materials:	
C ₃ H ₈ ; Matheson, minimum purity 99.98%.	
PS; Polyscience, Inc., $M_w = 190\,000$.	
Estimated Error:	
Relative precision of DMS parameters: $k_D \pm 21\%$; $C'_H \pm 29\%$; $b \pm 55\%$.	

Components: (1) Various organic gases (2) Polystyrene (PS); [9003-53-6] (IX)		Original Measurements: L. I. Stiel and D. F. Harnish, <i>AIChE J.</i> 22 , 117 (1976).				
Variables: $T/K=408-503$		Prepared By: Yu. P. Yampol'skii				
		Experimental Data Infinite dilution solubility coefficients $S/(\text{cm}^3(\text{STP})/\text{g atm})$				
		Temperature				
Gas		408	423	448	473	498
Trichlorofluoromethane; CCl_3F [75-69-4]		3.85	3.02	2.09	1.55	1.17
Dichlorodifluoromethane; CCl_2F_2 [75-71-8]		1.12	0.94	0.70	0.56	0.45
Chlorodifluoromethane; CHClF_2 [75-45-6]		0.94	0.81	0.64	0.53	0.44
Chlorofluoromethane; CH_2ClF [593-70-4]		2.01	1.65	1.20	—	—
Chloromethane; CH_3Cl [74-87-3]		—	1.70	1.30	—	—
Propane; C_3H_8 [74-98-6]		0.90	0.78	0.62	0.51	0.43
2-Methylpropane; C_4H_{10} [75-28-5]		—	1.20	0.86	0.65	0.52
Auxiliary Information						
Method/Apparatus/Procedure Solubility in the limit of infinite dilution ($p \rightarrow 0$) was determined by means of inverse gas chromatography PS was coated on Fluoropak-80 support. Polymer content was in the range 4.8%–13.1% in the columns having the length 24–71 m. The correction for pressure drop in a column was introduced.						
Source and Purity of Materials: Molecular mass, M_n , of PS = 110 000–115 000.						
Estimated Error: $\delta T = 1\text{ K}$ $\delta S/S = 10\%$						

Components: (1) <i>n</i> -Butane; C ₄ H ₁₀ ; [106-97-8] 2-Methylpropane; C ₄ H ₁₀ ; [75-28-5] Propane; C ₃ H ₈ ; [74-98-6] (2) Polystyrene (PS); [9003-53-6] (IX)		Original Measurements: Y. Iwai, M. Ohzono, and Y. Arai, Chem. Eng. Commun. 34 , 225 (1985).	
Variables: T/K=423–498		Prepared By: Yu. P. Yampol'skii	
Experimental Data Values of weight fraction Henry's constants/MPa for hydrocarbons in molten polystyrene. The experienced data follow the curves calculated by the UNIFAC-FV model. (The original data were represented graphically)			
T/K		2-Methylpropane	Propane
<i>n</i> -Butane			
423.2	35.96	47.49	78.79
448.2	42.33	56.46	100.53
473.2	51.81	62.58	123.04
498.2	61.53	74.33	137.76
Auxiliary Information			
Method/Apparatus/Procedure A gas chromatographic method used for the determination of weight fraction Henry's constants and was similar to those described in Refs. 1 and 2. PS was coated on Chromosorb W (AW DMSC 60/80). Helium was used as a carrier gas.		Source and Purity of Materials: Estimated Error: No information given.	
References: ¹ D. D. Liu and J. M. Prausnitz, Ind. Eng. Chem. Fundam. 15 , 330 (1976). ² M. Ohzono, Y. Iwai, and Y. Arai, Kagaku Kogaku Ronbunshu 10 , 536 (1984).			

TABLE 2. Sorption isotherms of chlorodifluoromethane in polystyrene powder

Pressure/kPa	Sorption (P/P^*)(STP)/ P^*)	Sorption (P/P^*)(STP)/ P^*)		Sorption (P/P^*)(STP)/ P^*)		Sorption (P/P^*)(STP)/ P^*)	
		Pressure/kPa	(P/P^*)(STP)/ P^*)	Pressure/kPa	(P/P^*)(STP)/ P^*)	Pressure/kPa	(P/P^*)(STP)/ P^*)
$T=293\text{ K}$							
2.10	0.61	12.93	2.03	28.67	3.30	46.78	4.51
4.89	1.13	16.80	2.49	32.64	3.65	54.80	5.02
6.38	1.30	20.66	2.70	36.89	3.82	—	—
8.57	1.65	25.01	3.08	39.76	4.07	—	—
$T=303\text{ K}$							
2.00	0.41	12.61	1.63	29.43	2.75	49.50	3.69
4.08	0.75	16.77	1.90	33.88	2.89	56.81	3.99
6.17	1.02	20.73	2.20	37.24	3.15	—	—
8.55	1.23	25.87	2.47	40.90	3.28	—	—
$T=313\text{ K}$							
2.19	0.28	13.28	1.22	29.10	2.07	49.55	2.90
4.77	0.60	17.13	1.41	33.64	2.26	55.97	3.15
6.75	0.77	21.19	1.66	36.91	2.43	—	—
8.82	0.91	25.04	1.83	40.76	2.56	—	—
$T=323\text{ K}$							
2.48	0.23	12.87	0.92	29.66	1.63	48.83	2.32
4.16	0.36	18.80	1.21	33.02	1.78	56.24	2.58
7.73	0.64	21.37	1.29	37.17	1.92	—	—
9.41	0.73	25.72	1.53	41.91	2.11	—	—
$T=333\text{ K}$							
2.37	0.15	12.75	0.65	28.85	1.19	49.98	1.80
4.65	0.28	17.10	0.80	32.90	1.34	58.18	2.04
6.43	0.37	21.74	0.94	37.04	1.40	—	—
8.70	0.48	25.49	1.09	41.59	1.55	—	—

TABLE 3. Sorption isotherms of methane and propane in polystyrene film

CH ₄				C ₃ H ₈			
$T=303\text{ K}$		$T=323\text{ K}$		$T=303\text{ K}$		$T=323\text{ K}$	
Pressure/kPa	$(P/P^*)_{(STP)/P^*}$	Pressure/kPa	$(P/P^*)_{(STP)/P^*}$	Pressure/kPa	$(P/P^*)_{(STP)/P^*}$	Pressure/kPa	$(P/P^*)_{(STP)/P^*}$
5.53	0.03	3.50	0.01	2.43	0.33	2.65	0.15
7.87	0.04	8.72	0.03	3.37	0.44	3.75	0.20
9.89	0.05	11.53	0.04	5.72	0.67	7.26	0.36
10.52	0.06	13.47	0.04	7.43	0.77	10.22	0.44
11.92	0.06	21.10	0.07	15.63	1.22	14.12	0.62
15.43	0.08	28.81	0.10	23.20	1.58	19.89	0.84
18.00	0.10	30.45	0.11	28.34	1.81	26.74	1.01
24.31	0.13	45.17	0.15	44.80	2.49	38.04	1.32
28.05	0.15	—	—	—	—	48.25	1.57
33.97	0.18	—	—	—	—	—	—
38.80	0.20	—	—	—	—	—	—
46.66	0.24	—	—	—	—	—	—

Components:
(1) Methane; CH₄; [74-82-8] Propane; C₃H₈; [74-98-6]
Chlorodifluoromethane; CHClF₂; [75-45-6]
(2) Polystyrene (PS); [9003-53-6] (IX)

Original Measurements:

J. A. Barrie, M. J. L. Williams, and K. Munday, Polym. Eng. Sci.
20, 21 (1980).

Prepared by:

Yu. P. Yampol'skii

Experimental Data

TABLE 1. Dual mode sorption parameters and solubility coefficients ($S=k_D+C_{FH}$)

Gas	T/K	$k_D/10^2/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{cmHg}^{-1}$	$C_F/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/cmHg^{-1}	$S/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{cmHg}^{-1}$
CH ₄	303	—	—	—	0.0069
	323	—	—	—	0.0044
	303*	4.69	1.01	0.18	0.229
C ₃ H ₈	323*	2.82	0.735	0.071	0.0804
	293	4.39(±5%)	1.32(±9%)	0.208(±18%)	0.32(±9%)
	303	3.30(±11%)	1.36(±17%)	0.136(±28%)	0.218(±11%)
CHClF ₂	313	2.93(±6%)	0.90(±12%)	0.127(±20%)	0.143(±8%)
	323	2.46(±6%)	0.70(±16%)	0.106(±23%)	0.0984(±7%)
	333	2.29(±14%)	0.51(±45%)	0.108(±62%)	0.0776(±17%)
303*	293*	7.34(±8%)	2.16(±15%)	0.18(±28%)	0.471(±13%)
	303*	5.42(±9%)	1.95(±14%)	0.15(±25%)	0.347(±11%)
	313	4.49(±7%)	1.50(±13%)	0.11(±20%)	0.210(±7%)
323	323	3.81(±7%)	1.20(±15%)	0.089(±20%)	0.145(±6%)
	333	3.18(±18%)	0.80(±59%)	0.071(±63%)	0.089(±9%)

*PS films, other data refer to PS powder.

(For Tables 2, 3, and 4, the original data were represented graphically.)

TABLE 4. Sorption isotherms of propane in polystyrene powder

Pressure/kPa	Sorption (V^g (STP)/ V^g_0)	Pressure/kPa	Sorption (V^g (STP)/ V^g_0)	Pressure/kPa	Sorption (V^g (STP)/ V^g_0)
$T=293\text{ K}$					
1.37	0.32	6.59	0.88	16.78	1.48
2.54	0.49	8.51	0.98	24.75	1.88
4.37	0.64	12.36	1.29	33.20	2.19
$T=303\text{ K}$					
1.36	0.24	6.66	0.68	17.43	1.26
2.62	0.36	8.88	0.84	24.82	1.59
4.35	0.51	12.63	1.04	32.97	1.87
$T=313\text{ K}$					
1.64	0.19	6.64	0.48	16.72	0.90
2.99	0.26	8.37	0.58	24.97	1.17
4.34	0.35	12.88	0.76	33.21	1.41
$T=323\text{ K}$					
1.45	0.13	6.82	0.35	16.7	0.70
2.79	0.19	8.45	0.43	24.94	0.90
4.33	0.27	12.39	0.55	33.08	1.10
$T=333\text{ K}$					
1.44	0.10	6.53	0.28	16.78	0.56
2.50	0.16	8.45	0.35	25.60	0.78
4.49	0.22	12.47	0.47	33.26	0.93

Method/Apparatus/Procedure	Auxiliary Information	Source and Purity of Materials
Sorption isotherms were measured using an electronic vacuum microbalance (Sartorius, Model 4102) as described in Ref. 1.		CHClF ₂ ; purity >99.5%. Hydrocarbon gases: purity >99.9 mol %. Emulsion polymerized PS: B. F. Goodrich Research Center; dispersed form (particles size 0.53 μm) or film cast from methylene chloride. PS: glass transition temperature 374 K.
Estimated Error: Indicated in Table 1.		
References: J. A. Barrie and D. Machin, J. Macromol. Sci.-Phys. B, 3 , 645 (1969).		

Components:	Original Measurements:
(1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(<i>p</i> -methoxystyrene); [24936-44-5] (X)	A. C. Puleo, N. Mungundam, and D. R. Paul, J. Polym. Sci., Part B: Polym. Phys. 27 , 2385 (1989).

Variables:	Prepared By:
$T/\text{K}=308$ $p/\text{MPa}=0.2-2.0$	Yu. P. Yampol'skii

Experimental Data		
TABLE 1. Dual mode sorption parameters for carbon dioxide at 308 K		
	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H/\text{cm}^3(\text{STP})\text{cm}^{-3}$
1st cycle	0.873	3.03
2nd cycle	0.536	14.08

TABLE 2. Sorption isotherms of carbon dioxide at 308 K (The original data were represented graphically)			
1st cycle		2nd cycle	
Pressure/MPa	Sorption (V^g_1 (STP)/ V^g_0)	Pressure/MPa	Sorption (V^g_1 (STP)/ V^g_0)
0.27	4.09	0.21	3.96
0.54	7.04	0.66	9.55
0.87	9.95	1.06	13.53
1.28	13.61	1.44	16.56
1.63	16.63	1.79	19.02
1.96	19.41	1.96	20.54

Method/Apparatus/Procedure	Auxiliary Information	Source and Purity of Materials
The apparatus and procedure in sorption measurements were the same as those described in Ref. 1.		Polymer: prepared according to Ref. 2; glass transition temperature 378 K; $M_w=980\,000$, density 1.118 g/cm ³ .
Estimated Error: No information given.		
References: ¹ W. J. Koros, A. H. Chan, and D. R. Paul, J. Membr. Sci. 2 , 165 (1977). ² H. K. Hall and M. A. Howey, Polym. Bull. 12 , 427 (1984).		

3.8. Poly(Vinyl Cyclohexane Carboxylate)—Carbon Dioxide

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(vinyl cyclohexane carboxylate) (PVCH); [29316-32-3] (XI)	Original Measurements: T. Hinse, K. Mizoguchi, and Y. Kamiya, J. Appl. Polym. Sci. 34 , 1657 (1987).	
	Prepared By: Yu. P. Yampol'skii	
Variables: T/K=278–358 p/kPa=0–100		

Experimental Data			
TABLE 1. Dual mode sorption parameters for carbon dioxide in PVCH			
T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
278	2.19	1.150	1.87
283	1.97	0.830	2.11
288	1.77	0.684	1.85
293	1.60	0.559	1.57
298	1.46	0.373	1.69
303	1.32	0.230	1.57
308	1.22	0.227	1.04

TABLE 2. Henry's law parameters for carbon dioxide in rubbery PVCH	
T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$
318	1.020
328	0.866
338	0.752
348	0.653
358	0.560

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(<i>p</i> -acetoxystyrene); [24979-78-0] (XI)	Original Measurements: A. C. Puleo, N. Muruganandam, and D. R. Paul, J. Polym. Sci., Part B: Polym. Phys. 27 , 2385 (1989).	
	Prepared By: Yu. P. Yampol'skii	
Variables: T/K=308 p/MPa=0.2–2.0		

Experimental Data		
TABLE 1. Dual mode sorption parameters for carbon dioxide at 308 K		
	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	b/atm^{-1}
1st cycle	1.24	0.431
2nd cycle	0.769	0.221

TABLE 2. Sorption isotherms of carbon dioxide at 308 K (The original data were represented graphically)		
Pressure/MPa	1st cycle	2nd cycle
	Sorption ($(P^*(\text{STP})/P^*)^2$)	Sorption ($(P^*(\text{STP})/P^*)^2$)
0.35	7.15	5.38
0.67	11.15	9.20
0.95	14.71	13.13
1.19	18.03	16.82
1.41	20.92	20.07
1.56	22.89	23.08
1.94	27.00	26.19

Auxiliary Information	
Method/Apparatus/Procedure The apparatus and procedure in sorption measurements were the same as those described in Ref. 1.	Source and Purity of Materials: Polymer: Celanese Chemical Co., glass transition temperature 399 K, $M_w=250\,000$, density 1.168 g/cm ³ .
Estimated Error: No information given.	References: ¹ W. J. Koros, A. H. Chan, and D. R. Paul, J. Membr. Sci. 2 , 165 (1977).

TABLE 3. Sorption isotherms of carbon dioxide in PVCH in the range 278–358 K (The original data were represented graphically)

Pressure/kPa	Sorption ($(P/P^*_1)(\text{STP})/P^*_2$)	Pressure/kPa	Sorption ($(P/P^*_1)(\text{STP})/P^*_2$)	Pressure/kPa	Sorption ($(P/P^*_1)(\text{STP})/P^*_2$)
$T=278\text{ K}$					
6.89	0.24	$T=293\text{ K}$		$T=318\text{ K}$	
13.77	0.50	54.69	1.14	13.44	0.13
20.19	0.73	64.22	1.30	26.88	0.27
26.61	0.97	79.69	1.59	40.81	0.42
38.03	1.34	93.12	1.80	54.23	0.53
38.81	1.31	$T=298\text{ K}$		66.12	0.68
53.04	1.78	6.72	0.12	79.24	0.81
65.71	2.11	13.91	0.26	92.68	0.95
76.18	2.38	22.97	0.43	$T=328\text{ K}$	
77.90	2.36	32.97	0.62	14.20	0.10
85.24	2.54	45.62	0.82	27.32	0.21
93.22	2.73	53.12	0.96	41.56	0.37
$T=283\text{ K}$					
6.73	0.22	66.39	1.16	54.49	0.44
13.14	0.42	81.07	1.40	67.32	0.60
20.18	0.63	93.72	1.57	79.48	0.69
26.59	0.81	$T=303\text{ K}$		92.44	0.82
39.57	1.17	4.84	0.09	$T=338\text{ K}$	
43.95	1.26	13.59	0.21	26.52	0.20
53.48	1.49	20.62	0.31	40.75	0.32
66.14	1.76	26.87	0.46	53.84	0.40
75.21	2.01	33.26	0.49	67.89	0.51
85.68	2.20	41.08	0.64	79.74	0.61
97.71	2.46	46.54	0.70	93.48	0.72
$T=288\text{ K}$					
7.19	0.20	54.19	0.84	$T=348\text{ K}$	
13.45	0.37	59.97	0.92	14.07	0.06
27.52	0.73	66.84	1.01	27.28	0.15
41.11	1.01	72.47	1.10	40.72	0.28
52.99	1.26	79.49	1.17	53.97	0.36
67.53	1.59	89.95	1.30	66.61	0.46
79.24	1.80	96.98	1.40	79.52	0.50
92.68	2.06	$T=308\text{ K}$		93.11	0.62
$T=293\text{ K}$					
8.75	0.19	5.46	0.05	$T=358\text{ K}$	
15.32	0.34	13.59	0.18	20.18	0.10
22.04	0.48	27.02	0.38	34.07	0.19
34.23	0.75	39.82	0.56	40.86	0.25
40.95	0.89	54.81	0.75	53.96	0.33
		67.15	0.92	67.96	0.36
		84.63	1.12	79.96	0.46
		93.53	1.24	93.04	0.50
		—	—	—	—

Method/Apparatus/Procedure	Source and Purity of Materials
Cahn RG electromicrobalance was used. The procedure is described in Refs. 1 and 2. Two types of experiments were performed: sorption in fully preevacuated sample and "interval" sorption experiments. No difference between the data obtained is observed.	CO ₂ : purity 99.99%. PVCH: prepared from polyvinyl alcohol (polymerization degree <i>n</i> = 2000) and cyclohexane carboxylic acid chloride in anhydrous pyridine. Degree of esterification >97%, <i>M_w</i> = 270 000 (GPC), density 1.119 g/cm ³ , <i>T_g</i> = 328 K.
Estimated Error:	No information given.
References:	¹ Y. Kamiya, K. Mizoguchi, Y. Naito, and J. Hirose, <i>J. Polym. Sci., Part B: Polym. Phys.</i> 24 , 535 (1986). ² Y. Kamiya, T. Hirose, K. Mizoguchi, and Y. Naito, <i>J. Polym. Sci.: Part B: Polym. Phys.</i> 24 , 1525 (1986).

3.9. Poly(Vinyl Benzoate)—Various Gases

Components:		Original Measurements:	
(1) Argon; Ar; [7440-37-1] Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9]	Carbon	Y. Kamiya, K. Mizoguchi, Y. Naito, and T. Hirose, <i>J. Pol. Sci., Polym. Phys. Ed.</i> 24 , 535 (1986).	
(2) Poly(vinyl benzoate) (PVB); [24991-32-0] (XIII)			
Variables:		Prepared By:	
<i>T</i> /K = 298–343		A. K. Bokarev	
<i>p</i> /MPa = 0–5.0			

Experimental Data

TABLE 1. Sorption and desorption isotherms of nitrogen in PVB (The original data were represented graphically)

	$T = 308.2\text{ K}$			$T = 323.2\text{ K}$			$T = 338.2\text{ K}$		
	Pressure/MPa	Solubility ($V_1^*(\text{STP})/V_2^*$)	Pressure/MPa	Solubility ($V_1^*(\text{STP})/V_2^*$)	Pressure/MPa	Solubility ($V_1^*(\text{STP})/V_2^*$)	Pressure/MPa	Solubility ($V_1^*(\text{STP})/V_2^*$)	
Sorption									
0.20	0.09	0.22	0.05	0.05	0.22	0.02			
0.61	0.26	0.61	0.17	0.17	0.61	0.10			
1.10	0.44	1.09	0.31	0.31	1.09	0.21			
2.08	0.79	2.07	0.58	0.58	2.07	0.42			
3.05	1.11	3.06	0.82	0.82	3.05	0.62			
4.03	1.39	4.04	1.07	1.07	4.04	0.81			
5.01	1.68	5.02	1.29	1.29	5.02	0.99			
Desorption									
0.36	0.15	0.36	0.10	0.10	0.35	0.07			
0.85	0.37	0.85	0.25	0.25	0.84	0.19			
1.33	0.55	1.59	0.47	0.47	1.35	0.30			
2.56	0.98	2.57	0.73	0.73	2.32	0.50			
3.54	1.26	3.31	0.92	0.92	3.31	0.70			
4.52	1.58	4.28	1.14	1.14	4.29	0.87			

TABLE 2. Sorption and desorption isotherms of argon in PVB (The original data were represented graphically)

	<i>T</i> = 298.2 K			<i>T</i> = 308.2 K			<i>T</i> = 338.2 K			<i>T</i> = 343.2 K		
	Pressure/MPa	Solubility (<i>V</i> ₁ [*] (STP)/ <i>V</i> ₂ [*])	Pressure/MPa	Solubility (<i>V</i> ₁ [*] (STP)/ <i>V</i> ₂ [*])	Pressure/MPa	Solubility (<i>V</i> ₁ [*] (STP)/ <i>V</i> ₂ [*])	Pressure/MPa	Solubility (<i>V</i> ₁ [*] (STP)/ <i>V</i> ₂ [*])	Pressure/MPa	Solubility (<i>V</i> ₁ [*] (STP)/ <i>V</i> ₂ [*])	Pressure/MPa	Solubility (<i>V</i> ₁ [*] (STP)/ <i>V</i> ₂ [*])
Sorption												
0.11	0.15	0.07	0.06	0.15	0.22	0.15	0.11	0.09				
0.60	0.77	0.60	0.63	0.60	0.60	0.41	0.36	0.18				
1.09	1.29	1.08	1.09	1.09	1.09	0.70	1.08	0.50				
2.12	2.25	2.07	1.92	2.07	2.07	1.29	2.06	0.92				
3.09	3.09	3.04	2.71	3.09	3.09	1.83	3.05	1.34				
4.13	3.87	4.04	3.33	4.03	4.03	2.32	4.27	1.80				
4.52	4.14	5.02	3.96	5.01	5.01	2.82	5.02	2.10				
5.02	4.47	—	—	—	—	—	—	—				
Desorption												
0.35	0.49	0.22	0.24	0.35	0.26	0.26	0.60	0.27				
0.85	1.01	0.86	0.89	0.84	0.60	0.60	1.82	0.84				
1.58	1.80	1.58	1.54	1.57	1.05	1.05	3.78	1.65				
2.55	2.71	2.57	2.34	2.55	1.63	1.63	—	—				
3.78	3.68	3.54	3.03	3.54	2.13	2.13	—	—				
—	—	4.23	3.47	4.52	2.61	2.61	—	—				

J. Phys. Chem. Ref. Data, Vol. 28, No. 5, 1999

TABLE 3. Dual mode sorption parameters of gases in PVB at various temperatures

Gas	<i>T</i> /K	<i>k</i> _D /cm ³ (STP) cm ⁻³ atm ⁻¹	<i>C</i> _H [*] /cm ³ (STP) cm ⁻³	<i>b</i> /atm ⁻¹
N ₂	308	0.0230	1.07	0.0222
	323	0.0217	0.44	0.0222
	338	0.0207	—	—
	298	0.0597	2.30	0.0398
Ar	308	0.0563	1.80	0.0387
	318	0.0510	1.30	0.0382
	328	0.0458	0.91	0.0358
	338	0.0510	—	—
	343	0.0444	—	—

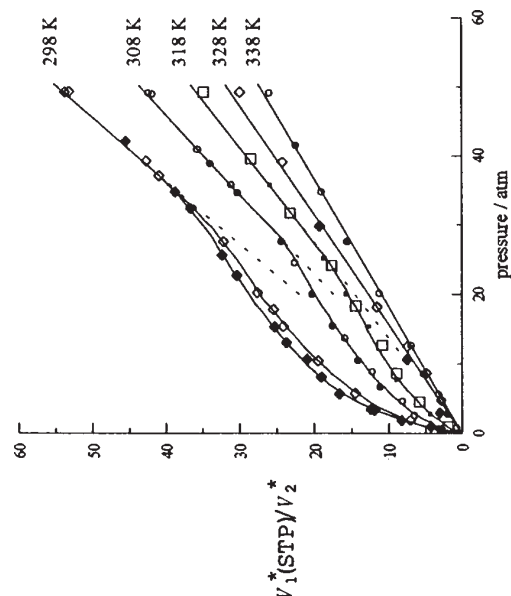


FIG. 21. Sorption and desorption isotherms of carbon dioxide in PVB. Open and filled symbols represent sorption and desorption, respectively.

Method/Apparatus/Procedure	Auxiliary Information
Sorption isotherms were measured gravimetrically with a Cahn model 2000 electrobalance.	Source and Purity of Materials: Ar: purity 99.999% N ₂ : purity 99.999% CO ₂ : purity 99.99% PVB: reaction of poly(vinyl alcohol) and benzoyl chloride (see Ref. 1).
	Estimated Error: No information given.
References:	T. Hirose, K. Mizoguchi, and Y. Kamiya, <i>J. Appl. Polym. Sci.</i> 30 , 401 (1985).

Components:		Original Measurements:
(1) Carbon dioxide; CO ₂ ; [124-38-9]		T. Hirose, K. Mizoguchi, Y. Naito, and Y. Kamiya, J. Appl. Polym. Sci. 35 , 1715 (1988).
(2) Poly(vinyl benzoate) (PVB); [24991-32-0] (XIII)		
Variables:		Prepared By:
T/K=278–358		A. K. Bokarev
p/kPa=0–100		

Experimental Data			
TABLE 3. Dual mode sorption parameters for carbon dioxide in PVB			
T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_{H'}/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
278	1.78	4.69	1.60
288	1.45	3.59	1.35
298	1.18	3.52	0.821
308	1.00	3.05	0.623
318	0.851	1.78	0.547
328	0.730	0.666	0.760
338	0.641	—	—
343	0.577	—	—
348	0.545	—	—
353	0.511	—	—
358	0.472	—	—

TABLE 2. Dual mode sorption parameters for carbon dioxide in PVB after annealing at 358 K			
T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_{H'}/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
288	1.45	1.71	1.338
298	1.55	1.73	0.739
308	1.00	0.890	0.828
318	0.851	0.477	0.760

Components:		Original Measurements:
(1) Carbon dioxide; CO ₂ ; [124-38-9]		Y. Kamiya, T. Hirose, K. Mizoguchi, and K. Terada, J. Polym. Sci., Part B: Polym. Phys. 26 , 1409 (1988).
(2) Poly(vinyl benzoate) (PVB); [24991-32-0] (XIII)		
Variables:		Prepared By:
T/K=298		A. K. Bokarev
p/MPa=0–5.0		

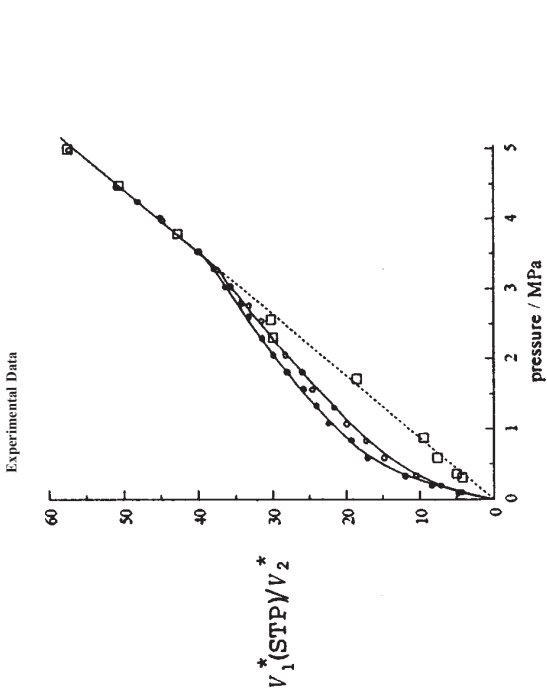


FIG. 22. Sorption and desorption isotherms of carbon dioxide in PVB at 298 K: (□) first sorption run; (○) subsequent sorption and desorption runs.
The isotherm was treated by the Kamiya's *et al.* equation. The following values of the parameters were found at 298 K:
 $k_D = 1.15 \text{ cm}^3(\text{STP})/\text{cm}^3 \text{ atm}$, $b = 0.167 \text{ atm}^{-1}$
 $C'_{H'} = 22.0 \text{ cm}^3(\text{STP})/\text{cm}^3(\text{sorption})$; $C'_{H'} = 30.2 \text{ cm}^3(\text{STP})/\text{cm}^3(\text{desorption})$
 $C_g = 38.5 \text{ cm}^3(\text{STP})/\text{cm}^3$, $f = 0.8$ (dimensionless)

Auxiliary Information	
Method/Apparatus/Procedure	Sorption isotherms were measured gravimetrically with a Cahn model 2000 electrobalance. A correction for the buoyancy was introduced.
Source and Purity of Materials:	CO ₂ : purity 99.99%. PVB: reaction of poly(vinyl alcohol) and benzoyl chloride (see Ref. 1). Density (298 K)=1.214 g/cm ³ .
Estimated Error:	No information given.
References:	¹ T. Hirose, K. Mizoguchi, and Y. Kamiya, J. Appl. Polym. Sci. 30 , 401 (1985).

TABLE 3. Sorption isotherms of carbon dioxide in PVB. Sorption isotherms are linear above 338 K. (The original data were represented graphically)

Pressure/kPa	Sorption ($V_1^*/(STP)/V_2^*$)	Pressure/kPa	Sorption ($V_1^*/(STP)/V_2^*$)	Pressure/kPa	Sorption ($V_1^*/(STP)/V_2^*$)
<i>T</i> = 278 K					
6.72	0.51	40.08	2.53	79.84	4.03
16.17	1.27	53.44	3.05	94.13	4.46
26.85	1.86	66.96	3.59	—	—
<i>T</i> = 288 K					
6.70	0.40	41.07	1.83	80.78	3.02
13.55	0.74	54.11	2.28	93.63	3.29
27.09	1.34	67.13	2.63	—	—
<i>T</i> = 298 K					
6.84	0.26	40.84	1.34	82.26	2.35
13.36	0.51	54.17	1.67	94.95	2.63
26.23	0.94	67.03	2.00	—	—
<i>T</i> = 308 K					
10.48	0.27	43.64	1.07	80.11	1.78
19.53	0.52	54.27	1.28	89.78	1.91
33.97	0.87	66.96	1.59	94.23	2.07
<i>T</i> = 318 K					
6.66	0.11	40.89	0.67	80.97	1.21
13.47	0.23	54.99	0.85	99.03	1.44
26.63	0.46	68.14	1.06	—	—
<i>T</i> = 328 K					
10.93	0.12	42.60	0.47	78.86	0.81
12.66	0.10	47.04	0.55	86.77	0.89
20.59	0.24	60.96	0.63	98.48	0.98
24.70	0.24	63.34	0.67	99.59	0.98
32.78	0.38	73.63	0.76	—	—
<i>T</i> = 338 K					
14.39	0.07	53.72	0.35	79.64	0.51
26.40	0.14	66.84	0.43	93.38	0.59
34.13	0.21	66.67	0.44	97.65	0.61
40.76	0.26	66.99	0.44	—	—
<i>T</i> = 348 K					
20.09	0.07	54.69	0.31	80.46	0.43
41.57	0.23	68.13	0.37	93.74	0.49
<i>T</i> = 358 K					
33.68	0.16	62.45	0.29	81.27	0.38
38.42	0.17	68.62	0.32	89.02	0.42
53.13	0.24	68.94	0.32	95.03	0.44
54.23	0.27	78.58	0.37	98.67	0.45

TABLE 4. Sorption isotherms of carbon dioxide in PVB after annealing at 358 K. (The original data were represented graphically)

Pressure/kPa	Sorption ($V_1^*/(STP)/V_2^*$)	Pressure/kPa	Sorption ($V_1^*/(STP)/V_2^*$)	Pressure/kPa	Sorption ($V_1^*/(STP)/V_2^*$)
<i>T</i> = 288 K					
7.04	0.21	34.24	1.04	80.89	2.02
13.77	0.44	41.41	1.20	89.18	2.21
20.65	0.64	54.47	1.48	99.66	2.39
27.20	0.82	65.95	1.76	—	—
<i>T</i> = 298 K					
6.83	0.11	40.13	0.85	93.35	1.76
13.70	0.30	53.47	1.08	98.78	1.90
27.07	0.57	66.68	1.35	99.52	1.82
28.04	0.62	80.04	1.60	—	—
<i>T</i> = 308 K					
13.49	0.20	53.33	0.81	82.82	1.19
26.82	0.40	67.44	0.98	90.58	1.27
41.12	0.64	75.85	1.11	98.66	1.36
<i>T</i> = 318 K					
13.77	0.13	53.85	0.61	89.45	0.93
27.40	0.30	66.85	0.76	98.79	1.01
41.01	0.44	80.44	0.86	—	—

TABLE 5. Dual mode sorption parameters for CO₂ in PVB at 298 K after exposure to 50 atm of CO₂

	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
Just after exposure	1.18	6.88	0.889
Next day	1.18	5.74	0.990
7 days later	1.18	5.00	0.942
11 months later	1.18	3.54	1.008
After measurements at 298 K in Table 3	1.18	3.52	0.827
After annealing at 358 K	1.18	1.73	0.739

Auxiliary Information

Method/Apparatus/Procedure

Sorption measurements were made using facilities and procedures described in Ref. 1.

Source and Purity of Materials:

CO₂: purity >99.99%
 PVB films: preparation and its properties reported in Ref. 2. The sample films were exposed to CO₂ of 50 atm at 308 K before measurements.

Estimated Error:

No information given.

References:

- ¹T. Hirose, K. Mizoguchi, and Y. Kamiya, *J. Appl. Polym. Sci.* **34**, 1657 (1987).
- ²T. Hirose, K. Mizoguchi, and Y. Kamiya, *ibid.* **30**, 401 (1985).

3.10. Poly(Vinyl Butyral)—Carbon Dioxide

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(vinyl butyral) (PVBu) (XIV)		Original Measurements: Y. Kamiya, T. Hirose, K. Mizoguchi, and K. Terada, <i>J. Polym. Sci., Part B: Polym. Phys.</i> 26 , 1409 (1988).
Variables: $T/K = 298$ $p/\text{MPa} = 0-5.0$		
Prepared By: A. K. Bokarev		

Experimental Data

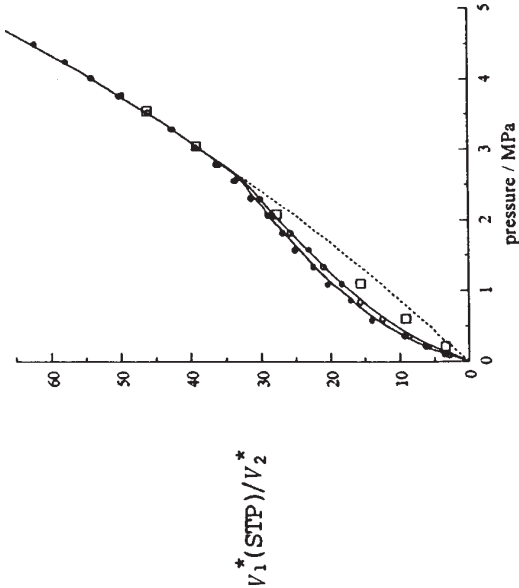


FIG. 23. Sorption and desorption isotherms of carbon dioxide in PVBu at 298 K: (□) first sorption run; (○) (●) subsequent sorption and desorption runs.

The isotherm was treated by the equation:

$$C = C_D + C_{H'} = [k_D \exp(sC^*)]p + C'_{H0}bp / (-C^*C_g)/(1 + bp),$$

where the parameters k_D , C'_{H0} , and b have the usual meaning, C_g is the solute concentration corresponding to the glass transition and

$$C^* = C_D + fC_H = [k_Dp + fC'_{H0}bp/(1 + bp)]/[1 + fC'_{H0}bp/C_g(1 + bp)],$$

where f is an adjustable parameter, characterizing the plasticizing ability of a solute.

Parameters for ordinary dissolution (Flory–Huggins's) and for Langmuir isotherms at 298 K.

f	$k_D / \text{cm}^3(\text{STP}) \text{cm}^{-3} \text{atm}^{-1}$	$C'_{H0} / \text{cm}^3(\text{STP}) \text{cm}^{-3}$	b / atm^{-1}	$10^3 S / \text{cm}^3(\text{STP}) \text{cm}^{-3}$	$C_g / \text{cm}^3(\text{STP}) \text{cm}^{-3}$
0.8	1.13	20.7 (sorption) 28.6 (desorption)	0.096	3.5	34.0

Auxiliary Information	
Method/Apparatus/Procedure Sorption isotherms were measured gravimetrically with a Cahn model 2000 electrobalance. A correction for the buoyancy was introduced.	Source and Purity of Materials: CO ₂ : purity 99.99% PVBu Mitsubishi Monsanto Chemical Co., density at 308 K 1.087 g/cm ³ , M_n between 34 000 and 38 000, butyral content 88%.
	Estimated Error: No information given.
	References: †T. Hirose, K. Mizoguchi, and Y. Kamiya, <i>J. Appl. Polym. Sci.</i> , 30 , 401 (1985).

3.12. Poly(Vinyltrimethyl Silane)—Various Gases

Components:	Evaluator:		
(1) Hydrocarbon gases C ₁ –C ₄	Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994		
(2) Poly(vinyltrimethyl silane) (PVTMS); [25036-32-2] (XV)			
Critical Evaluation:			
The solubility of gaseous hydrocarbons in PVTMS has been measured using three different techniques: volumetric, ¹ gravimetric, ^{2–4} and inverse gas chromatography. ^{5–8} The data for the following gases are available: methane [74-82-8], ¹ acetylene [74-86-2], ^{2–4,8,9} ethylene [74-85-1], ^{2–5,7–9} ethane [74-84-0], ^{2–5,7–9} propadiene [463-49-0], ^{2–4,8,9} propyne [74-99-7], ^{2–4,8,9} propene [115-07-1], ^{2–5,7–9} propane [74-98-6], ^{2,9} <i>n</i> -butane [106-97-8]. ^{5,7} Except propane and butane for which the dual mode sorption isotherms have been obtained, ^{4,6} the solubility of all other gases was measured in the range of pressure corresponding to the linear part of the sorption isotherm, i.e., the solubility coefficients have been reported. There is a general tendency for the solubility to increase with the critical temperature of gases, the variation of solubility with critical temperature is shown below. Values of critical temperature were taken from Ref. 10.			
Correlation of the solubility coefficients <i>S</i> with critical temperature <i>T_c</i> /K of hydrocarbons			
Hydrocarbons	<i>T_c</i> /K	log(<i>S</i> /cm ³ (STP) cm ^{–3} atm ^{–1})	Ref.
CH ₄	190.5	–1.86	1
C ₂ H ₂	309	–1.48	2–4
	309	–1.6	7, 8
C ₂ H ₄	282.6	–1.33	2–4
	282.6	–1.44	5, 6
	282.6	–1.44	7, 8
C ₂ H ₆	305.4	–1.15	2–4
	305.4	–1.14	5, 6
	305.4	–1.14	7, 8
CH ₃ CCH ₃	393	–0.5	7, 8
	393	–0.5	2–4
CH ₃ CCH	401	–0.5	7, 8
	401	–0.5	2–4
C ₃ H ₆	364.9	–0.5	2–4
	364.9	–0.6	7, 8
	364.9	–0.6	5, 6
C ₃ H ₈	379.9	–0.6	5, 6
	379.9	–0.4	7, 8
	379.9	–0.4	2–4
<i>n</i> -C ₄ H ₁₀	427.1	–0.05	5, 6

3.11. Poly(Vinylmethylether)—Propane

Components:	Original Measurements:
(1) Propane; C ₃ H ₈ ; [74-82-8]	H. G. Spencer and J. A. Yavorsky, J. Appl. Polym. Sci., 28 , 2937 (1983).
(2) Poly(vinylmethylether) (PVME); [9003-09-2]	
Variables:	Prepared By:
<i>T</i> /K: 317–357	A. K. Bokarev
<i>p</i> /kPa: 0–40	
Experimental Data	
In the pressure range indicated above, solubility obeys Henry's law. Temperature dependence for solubility coefficient, <i>S</i> , is given by equation: $S = S_0 \exp(-\Delta H/RT)$	
Parameter	Data
ΔH /(kJ/mol)	–10.0
ln(<i>S</i> ₀ /cm ³ (STP)/cm ³ cm Hg)	–7.57
ln(<i>S</i> (353 K)/cm ³ (STP)/cm ³ cm Hg)	–4.05
Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials: The polymer investigated was supplied by Polysciences, Inc. It had <i>M_w</i> = 34 000; <i>T_g</i> = 247 K. A density at 303 K was 1.04 g/cm ³ . Propane of 99.99% purity (Matheson) was used.
Sorption measurements were carried out in a low pressure, constant-volume cell previously described. ¹ The correction for the buoyancy was introduced.	Estimated Error: No estimates.
	References: ¹ J. A. Yavorsky and H. G. Spencer, J. Appl. Polym. Sci. 25 , 2109 (1980).

The solubility coefficients obtained by means of a gravimetric method (McBain balance) are, in majority of cases, higher than those measured using inverse gas chromatography method. However, the differences are well within the limits of scatter.

Critical Evaluation:

References:

¹V. V. Volkov, S. G. Durgaryan, E. G. Novitskii, and N. S. Nameikin, Dokl. Akad. Nauk SSSR **232**, 838 (1977).
²V. V. Volkov, N. S. Nameikin, E. G. Novitskii, and S. G. Durgaryan, Vysokomol. Soedin. Ser. A **21**, 920 (1979).
³V. V. Volkov, N. S. Nameikin, E. G. Novitskii, and S. G. Durgaryan, Vysokomol. Soedin. Ser. A **21**, 927 (1979).
⁴V. V. Volkov, dissertation, Moscow, TIPI, 1979.
⁵N. E. Kaluzhnyi, Yu. P. Yampol'skii, S. G. Durgaryan, and N. S. Nameikin, Dokl. Akad. Nauk SSSR **265**, 1170 (1982).
⁶V. V. Volkov, A. K. Bokarev, S. G. Durgaryan, and N. S. Nameikin, Dokl. Akad. Nauk SSSR **282**, 641 (1985).
⁷Yu. P. Yampol'skii, N. E. Kaluzhnyi, and S. G. Durgaryan, Macromolecules **19**, 846 (1986).
⁸M. B. Davydova, Yu. P. Yampol'skii, N. K. Gladkova, and S. G. Durgaryan, Vysokomol. Soedin. Ser. A **30**, 554 (1988).
⁹M. B. Davydova, Yu. P. Yampol'skii, and S. G. Durgaryan, Vysokomol. Soedin. Ser. A **30**, 1430 (1988).
¹⁰D. R. Stull, E. F. Westrum, and G. C. Sinke, *The Chemical Thermodynamics of Organic Compounds* (Wiley, New York, 1969).

Components:	Original Measurements:
(1) Different gases	V. V. Volkov, S. G. Durgaryan, E. G. Novitskii, and N. S. Nameikin, Dokl. Akad. Nauk SSSR 232 , 838 (1977); Vysokomol. Soedin., Ser. A 21 , 927 (1979).
(2) Poly(vinyltrimethyl silane) (PVTMS); [25036-32-2] (XV)	

Variables:	Prepared By:
$T/K=283-323$	Yu. P. Yampol'skii
$p/\text{kPa}=0-93$	

Experimental Data	
Solubility coefficients $S/\text{cm}^3(\text{STP})/\text{cm}^3$ atm at 298 K and enthalpies of sorption ΔH kcal/mol	
Gas	$S/10^2$ $-\Delta H$
Helium; He; [7440-59-7]	0.11 1.45
Argon; Ar; [7440-37-1]	0.63 2.83
Hydrogen; H ₂ ; [1333-74-0]	0.12 1.66
Nitrogen; N ₂ ; [7727-37-9]	0.40 2.62
Oxygen; O ₂ ; [7782-44-7]	0.56 2.69
Methane; CH ₄ ; [74-82-8]	1.37 3.82
Carbon dioxide; CO ₂ ; [124-38-9]	3.52 4.93

Method/Apparatus/Procedure	Auxiliary Information
A McBain quartz spring microbalance and a volumetric apparatus were used for sorption measurements.	
Source and Purity of Materials: PVTMS synthesized by BuLi initiated anionic polymerization had: $M_w=608\,000$, $M_n=416\,000$. All the gases were "chromatographically" pure.	
Estimated Error: $\delta S/S=10\%$, $\delta(\Delta H)/\Delta H=20\%$.	

Components:		Original Measurements:	
(1) Various hydrocarbons C ₂ -C ₄		N. E. Kaluzhnyi, Yu. P. Yampol'skii, S. G. Durgaryan, and N. S. Nemetkin, Dokl. Akad. Nauk SSSR 265 , 1170 (1982).	
(2) Poly(vinyltrimethyl silane) (PVTMS); [25036-32-2] (XV)			
Variables:		Prepared By:	
T/K = 298-383		Yu. P. Yampol'skii	
Experimental Data			
Solubility coefficients S/cm ³ (STP)/cm ³ atm of hydrocarbons			
Gas	S (at 298 K)	Gas	S
Ethylene; C ₂ H ₄ ; [74-85-1]	3.6	Propane; C ₃ H ₈ ; [74-98-6]	27
Ethane; C ₂ H ₆ ; [74-84-0]	7.2	n-Butane; C ₄ H ₁₀ ; [106-97-8]	90
Propene; C ₃ H ₆ ; [115-07-1]	23		5.62
Enthalpies of sorption ΔH/kcal/mol			
Gas			ΔH
C ₂ H ₆			5.4
C ₃ H ₈			6.42±0.15
C ₄ H ₁₀			8.02±0.06
Method/Apparatus/Procedure		Auxiliary Information	
Inverse gas chromatography was used for the determination of solubility coefficients. By the measurements correction for the pressure drop in a column was introduced.		Source and Purity of Materials: PVTMS was prepared by anionic polymerization (sec. BuLi as a catalyst) and had molecular mass about 500 000 and a density 0.898 g/cc.	

Components:		Original Measurements:	
(1) Xenon; Xe; [7440-63-3] and hydrocarbons		V. V. Volkov, N. S. Nemetkin, E. G. Novitskii, and S. G. Durgaryan, Vysokomol. Soedin, Ser. A. 21 , 920 (1979).	
(2) Poly(vinyltrimethyl silane) (PVTMS); [25036-32-2] (XV)			
Variables:		Prepared By:	
T/K = 293–313 p/kPa = 0–93		Yu. P. Yampol'skii	
Experimental Data			
Solubility coefficients $S/\text{cm}^3(\text{STP})/\text{cm}^3$ atm at 298 K and enthalpies of sorption $\Delta H/\text{kcal/mol}$		$S/10^2$	$-\Delta H$
Gas			
Xenon		7.1	4.20
Acetylene; C_2H_2 ; [74-86-2]		3.3	—
Ethylene; C_2H_4 ; [74-85-1]		4.7	4.02
Ethane; C_2H_6 ; [74-84-0]		7.0	3.58
Propadiene; C_3H_4 ; [463-49-0]		31.5	5.47
Propyne; C_3H_4 ; [74-99-7]		30.0	5.64
Propene; C_3H_6 ; [115-07-1]		31	5.96
Propane; C_3H_8 ; [74-98-6]		40	6.20
n-Butane; C_4H_{10} ; [106-97-8]		272	—
Auxiliary Information			
Method/Apparatus/Procedure		Source and Purity of Materials:	
A McBain balance with a quartz spring was used in sorption measurement.		PVTMS synthesized in the presence of BuLi had $M_w = 608\,000$ and $M_n = 416\,000$. All the gases were chromatographically pure.	
Estimated Error:		Estimated Error:	
$\delta S/S = 10\%$.			

Components:		Original Measurements:
(1) Sulfur dioxide; SO ₂ ; [7446-09-5]	(XV)	V. V. Volkov, A. K. Bokarev, and S. G. Durgaryan, <i>Vysokomol. Soedin.</i> , Ser. A 26 , 1294 (1984).
(2) Poly(vinyltrimethyl silane); [25036-32-2]	(XV)	
Variables:		Prepared By:
T/K = 298		S. M. Shishanskii
p/MPa = 0–0.4		

Experimental Data	
TABLE 1. Sorption isotherm of sulfur dioxide in PVTMS at 298 K. Thickness of the film: 64 μm (The original data were represented graphically)	
Relative pressure	Sorption ($V_1^*(\text{STP})/V_2^*$)
0.24	12.14
0.34	15.00
0.40	17.03
0.47	19.89
0.54	22.00
0.70	27.81
0.80	31.27
Relative pressure (p/p_s) = ratio of partial pressure and its saturated vapor pressure at the temperature of the experiment.	

TABLE 2. Sorption and desorption isotherms of sulfur dioxide in PVTMS at 298 K. Thickness of the film: 160 μm (The original data were represented graphically)		
Relative pressure	Sorption ($V_1^*(\text{STP})/V_2^*$)	Desorption ($V_1^*(\text{STP})/V_2^*$)
0.18	10.04	0.14
0.24	13.16	0.18
0.27	14.25	0.20
0.33	15.34	0.25
0.38	17.96	0.33
0.40	17.96	0.40
0.51	21.49	0.46
0.60	23.94	0.55
0.72	28.40	0.68
0.83	32.45	0.75
0.96	40.63	0.85
0.98	43.16	0.90
1.00	46.62	0.94
Relative pressure (p/p_s) = ratio of partial pressure and its saturated vapor pressure at the temperature of the experiment.		

Auxiliary Information		
Method/Apparatus/Procedure	Source and Purity of Materials:	
Sorption was measured gravimetrically using a McBain balance.	PVTMS: Kuskovo Chemical Plant.	
	Estimated Error:	
	No information given.	

Components:		Original Measurements:
(1) Various hydrocarbons	(XV)	M. B. Davydova, Yu. P. Yampol'skii, N. K. Gladkova, and S. G. Durgaryan, <i>Vysokomol. Soedin.</i> , Ser. A 30 , 554 (1988);
(2) Poly(vinyltrimethyl silane); [25036-32-2]	(XV)	M. B. Davydova, Yu. P. Yampol'skii, and S. G. Durgaryan, <i>Vysokomol. Soedin.</i> , Ser. A 30 , 1430 (1988).
Variables:		Prepared By:
T/K = 295–345		Yu. P. Yampol'skii

Experimental Data		
Solubility coefficients $S/(\text{cm}^3(\text{STP})/\text{cm}^3 \text{ atm})$ at 295 K		
Gas	S	S
Ethyne; C ₂ H ₂ ; [74-86-2]	2.5	29.5
Ethylene; C ₂ H ₄ ; [74-85-1]	3.6	24
Ethane; C ₂ H ₆ ; [74-84-0]	7.2	38
1,2-Propadiene; C ₃ H ₄ ; [463-49-0]	31	

Heats of sorption, $\Delta H/(\text{kJ}/\text{mol})$, = $-Rd(\ln S)/d(1/T)$		
Gas	$-\Delta H/(\text{kJ}/\text{mol})$	$-\Delta H/(\text{kJ}/\text{mol})$
Ethyne	24.0	30.6
1,2-Propadiene	30.6	31.8
Propane	34.8	

Auxiliary Information		
Method/Apparatus/Procedure	Source and Purity of Materials:	
Inverse gas chromatographic method of measurement of solubility was described in Ref. 1. The determination was performed in the condition of infinite dilution and in the absence of diffusion limitation.	PVTMS studied had molecular mass 600 000.	
	Estimated Error:	
	$\delta(\Delta H)/\Delta H < 5.3\%$	
	References:	
	Yu. P. Yampol'skii, S. G. Durgaryan, and N. E. Kaluzhnyi, <i>J. Chrom.</i> 286 , 97 (1984).	

Components:		Original Measurements:	
(1) Xenon; Xe; [7440-63-3] Carbon dioxide; CO ₂ ; [124-38-9]		V. V. Volkov, A. K. Bokarev, S. G. Durgaryan, and N. S. Namerkin, Doklady Akad. Nauk, SSSR, 282 , 641 (1985).	
(2) Nitrous oxide; N ₂ O; [10024-97-2] Propane; C ₃ H ₈ ; [74-98-6]		N. A. Pate, A. K. Bokarev, N. E. Kaluzhnyi, E. G. Litvinova, V. S. Khotimskii, V. V. Volkov, and Yu. P. Yampol'skii, J. Membr. Sci. 60 , 13 (1991).	
Variables:		Prepared By:	
T/K=298		S. M. Shishatskii	
p/MPa=0-0.7			
Experimental Data			
Dual mode sorption parameters for PVTMS at 298 K			
Gas	$k_D \times 10^{-2} (\text{cm}^3(\text{STP})/\text{cm}^3 \text{ cm Hg})$	$C_2' / (\text{cm}^3(\text{STP})/\text{cm}^3)$	$b \times 10^2 / (\text{cm Hg})^{-1}$
Xe	1.20	18.5	0.41
CO ₂	0.46	28.7	0.11
N ₂ O	1.4	13.1	0.29
C ₃ H ₈	0.113	5.2	19.1
Auxiliary Information			
Method/Apparatus/Procedure		Source and Purity of Materials:	
Sorption was measured using a gravimetric technique described in Ref. 1.		No information given.	
Estimated Error:		No information given.	
References:		V. V. Volkov, A. K. Bokarev, and S. G. Durgaryan, Vysokomol. Soedin., Ser. A, 26 , 1295 (1984).	

Components:		Original Measurements:	
(1) Sulfur dioxide; SO ₂ ; [7446-09-5]		Yu. P. Yampol'skii, V. V. Volkov, N. E. Kaluzhnyi, and S. G. Durgaryan, Vysokomol. Soedin., Ser. A 26 , 1640 (1984).	
(2) Poly(vinyltrimethyl silane) (PVTMS); [25036-32-2] (XV)			
Variables:		Prepared By:	
T/K=298		Yu. P. Yampol'skii	
p/kPa=0-100			
Experimental Data			
Dual mode sorption parameters for SO ₂ in PVTMS at 298 K			
$k_D / \text{mol cm}^{-3}(\text{STP}) \text{ Pa}^{-1}$	$C_2' / \text{mmol cm}^{-3}$	$b / (\text{kPa})^{-1}$	
2.0109	0.45	0.01	
Sorption isotherm of sulfur dioxide in PVTMS at 298 K. (The original data were represented graphically)			
Pressure/kPa	Sorption (mmol/cm ³)		
8.68	0.06		
13.28	0.09		
19.41	0.12		
26.39	0.16		
44.28	0.24		
57.40	0.28		
58.25	0.29		
67.79	0.33		
72.90	0.35		
81.25	0.38		
91.31	0.42		

3.13. Poly(trimethylsilyl propyne)—Various Gases

Components:	Evaluator:
(1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(trimethylsilyl propyne) (PTMSP); [87842-32-8] (XVI)	Yu. P. Yampol'skii, A. V. Tophchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994

Critical Evaluation:
PTMSP is known as the most permeable among polymers, both glassy and rubbery. So its sorption drew attention of several groups of investigators.¹⁻⁵ The dual mode sorption parameters as well as the apparent solubility coefficients *S* obtained by different researchers at temperatures 298–328 K are compared below.

TABLE 1. Dual mode sorption parameters and apparent solubility coefficients

T/K	<i>p</i> /atm	<i>k</i> _D	<i>C</i> _H [*]	<i>b</i>	<i>S</i> = <i>k</i> _D + <i>C</i> _H [*] <i>p</i>	Ref.
298	0–65	3.6	47.7	0.107	8.7	2, 3
298	0–60	1.3	139	0.064	10.2	5
303	0–40	1.53	151	0.0403	6.6	4
308	0–25	1.50	113	0.058	8.0	1
328	0–25	0.98	71.9	0.059	5.2	1

Units: *k*_D and *S*/cm³(STP) cm⁻³ atm⁻¹; *C*_H^{*}/cm³(STP) cm⁻³; *b*/atm⁻¹.
A significant scatter of the values of the sorption model parameters is seen, which is related to the substantial time dependence of transport and thermodynamic properties of this polymer (for more details see Ref. 6). The scatter of the *S* values is not very large, and better agreement is observed between the data from different papers.
An essential feature of the sorption in PTMSP is the large values of Langmuir capacity parameter *C*_H^{*}, much higher than in other polymers. The minimal value reported in Refs. 2 and 3 is presumably underestimated owing to the narrow pressure range studied in these works. It is intriguing and as yet unexplained fact that Henry's law solubility coefficients *k*_D in PTMSP are significantly higher than in other polymers. This is true not only for carbon dioxide but for other gases as well.¹⁻⁵
Referring to the data given in Table 1 one can tentatively recommend the sorption parameters measured in Refs. 5 and 1 since they form a plausible temperature dependence for all three parameters and for *S*.
The enthalpy of sorption calculated from Van't Hoff plot for *S* is equal to -14.7±4.9 kJ/mol. The scatter in the temperature dependences of the *k*_D and *b* values prevents the calculation of the corresponding enthalpies of Henry's law dissolution and Langmuir adsorption.

References:
¹Y. Ichiraku, S. A. Stern, and T. Nakagawa, *J. Membr. Sci.* **34**, 5 (1987).
²A. K. Bokarev, V. V. Volkov, N. E. Kaluzhnyi, E. G. Litvinova, V. S. Khotimskii, and Yu. P. Yampol'skii, *Dokl. Akad. Nauk. SSSR* **305**, 117 (1989).
³N. A. Platé, A. K. Bokarev, N. E. Kaluzhnyi, E. G. Litvinova, V. S. Khotimskii, V. V. Volkov, and Yu. P. Yampol'skii, *J. Membr. Sci.* **60**, 13 (1991).
⁴T. Nakagawa, M. Sekiguchi, K. Nagai, and A. Higuchi, Intern. Congress on Membranes (ICOM-90), Chicago, 1990, p. 824.
⁵V. I. Bondar, Yu. M. Kukhar'skii, and V. V. Volkov, Abstracts, 5th Intern. Symp. on Solubility Phenomena, Moscow, 1992, p. 227.
⁶D. R. Paul and Yu. P. Yampol'skii, Eds., *Polymeric Gas Separating Membranes* (CRC, Boca Raton, 1994), p. 192.

Components:	Original Measurements:
(1) Nitrogen; N ₂ ; [7727-37-9] Oxygen; O ₂ ; [7782-44-7] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Poly(trimethylsilyl propyne) (PTMSP); [87842-32-8] (XVI)	Y. Ichiraku, S. A. Stern, and T. Nakagawa, <i>J. Membr. Sci.</i> 34 , 5 (1987).

Variables:	Prepared By:
T/K = 308 and 328 <i>p</i> /MPa = 0–2.7 (0–27 atm)	Yu. P. Yampol'skii

Experimental Data			
Dual mode sorption parameters for various gases in PTMSP at 308 K			
Gas	<i>k</i> _D /cm ³ (STP) cm ⁻³ atm ⁻¹	<i>C</i> _H [*] /cm ³ (STP) cm ⁻³	<i>b</i> /atm ⁻¹
CO ₂	1.497	112.9	0.058
	0.978*	71.9*	0.059*
CH ₄	0.667	87.8	0.035
N ₂	0.431	15.4	0.042
O ₂	0.656	16.8	0.036

*At 328 K.

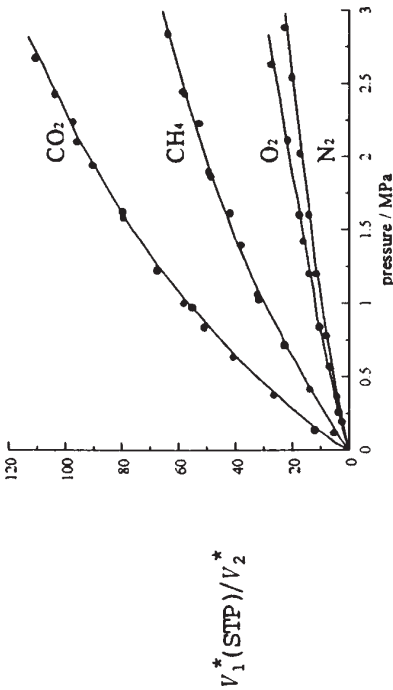


FIG. 24. Sorption isotherms of various gases in PTMSP at 308 K.

Method/Apparatus/Procedure	Auxiliary Information	Source and Purity of Materials
The solubility was measured by a volumetric method. The apparatus and the procedure are described in detail in Ref. 1.		Gases: purity >99.5%. PTMSP: Sanyo Chemical Industries, density 0.938 g/cm ³ , <i>M</i> _w = 700 000, no glass transition observed below 473 K.
		Estimated Error: Relative precision of solubilities: from ±6.6%(CO ₂) to ±5.4%(N ₂).
		References: ¹ V. M. Shah, B. J. Hardy, and S. A. Stern, <i>J. Polym. Sci., Part B: Polym. Phys.</i> 24 , 2033 (1986).

Components: (1) Xenon; Xe; [7440-63-3] Oxygen; O ₂ ; [7782-44-7] Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(trimethylsilyl propyne) (PTMSP); [87842-32-8] (XVI)		Original Measurements: S. Asakawa, Y. Saitoh, K. Waragai, and T. Nakagawa, Gas Separation Purification, 3 , 117 (1989).	
Variables: T/K = 307.8 p/kPa = 0–93		Prepared By: V. I. Bondar	
Experimental Data Linear sorption isotherms were observed for all three gases. Solubility coefficients <i>S</i>			
Gas		10 ³ S/cm ³ (STD)/cm ³ cm Hg	
Xe		19.71	
O ₂		2.4	
CO ₂		8.83	
Auxiliary Information			
Method/Apparatus/Procedure A gravimetric method of the measurement was employed (the McBain balance with a quartz spring). The correction allowing for buoyancy was made.		Source and Purity of Materials: PTMSP was prepared according to Ref. 1. It had <i>M_w</i> = 2 500 000.	
Estimated Error: No information given.		References: 1T. Masuda, E. Isobe, T. Higashimura, and K. Takada, J. Am. Chem. Soc. 105 , 74 (1983).	

Components: H. Odani, H. Shimomura, K. Nakanishi, T. Masuda, and T. Higashimura, Japan–US Polymer Symposium 1985, pp. 251–252.		Original Measurements: H. Odani, H. Shimomura, K. Nakanishi, T. Masuda, and T. Higashimura, Japan–US Polymer Symposium 1985, pp. 251–252.	
Variables: T/K = 298 p/kPa = 0–100		Prepared By: Yu. P. Yampol'skii	
Experimental Data Sorption isotherm of 2-methylpropane in PTMSP at 298 K. (The original data were represented graphically)			
Pressure/kPa		Sorption (<i>V</i> [*] _g (STD)/ <i>V</i> [*] _g)	
4.22		14.74	
9.03		20.59	
12.78		23.79	
24.40		30.22	
27.09		30.65	
41.94		35.56	
67.73		43.01	
93.33		50.19	
Auxiliary Information			
Method/Apparatus/Procedure Sorption was studied by a gravimetric method.		Source and Purity of Materials: PTMSP: synthesized according to Ref. 1 and stored in methanol until used.	
Estimated Error: No information given.		References: 1K. Takada, H. Matsuya, T. Masuda, and T. Higashimura, J. Appl. Polym. Sci. 30 , 1605 (1985).	

Auxiliary Information	
Method/Apparatus/Procedure Sorption measurements were performed using McBain balance as is described in Ref. 1	Source and Purity of Materials: PTMSP: prepared by polymerization in the presence of TaCl_5 as a catalyst; density 0.964 g/cm^3 (measured in a gradient column). $M_n = 590\,000$, $M_w = 125\,000$, glass transition temperature 503 K .
	Estimated Error: No information given.
	References: 1. V. V. Volkov, A. K. Bokarev, and S. G. Durgaryan, Vysokomol. Soedin., Ser. A 26 , 1294 (1984).
Components:	
(1) Propane; C_3H_8 ; [74-98-6]	Original Measurements: L. C. Witteby-Lakshmanan, H. B. Hopfenberg, and R. T. Chern, J. Membr. Sci. 48 , 321 (1990).
(2) Poly(trimethylsilyl propyne) (PMSP); [87842-32-8] (XVI)	
Variables: $T/\text{K} = 308$ $p/\text{kPa} = 0-120$	Prepared By: Yu. P. Yampol'skii
Experimental Data	
Dual mode sorption parameters for propane at 308 K^*	
k_D	C'_H b
$3.6 \cdot 10^{-4} \text{ mol/g atm}$	$2.16 \times 10^{-3} \text{ mol/g}$ 4.4 (atm)^{-1}
$6.3 \text{ cm}^3(\text{STP})/\text{cm}^3 \text{ atm}$	$37.7 \text{ cm}^3(\text{STP})/\text{cm}^3$ 4.4 (atm)^{-1}
*The first line gives the values as reported by the authors, the second line recalculated by the compiler.	
Auxiliary Information	
Method/Apparatus/Procedure The sorption measurements were performed with a McBain quartz spring balance following a procedure described in Ref. 1	Source and Purity of Materials: PMSP had $M_w = 600\,000$, a density 0.78 g/cm^3 . Purity of propane 99.5% .
	Estimated Error: No information given.
	References: 1. R. M. Felder, C. J. Patton, and W. J. Koros, J. Polym. Sci., Polym. Prep. 19 , 1895 (1981).

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] Propane; C ₃ H ₈ ; [74-98-6] (2) Brominated poly(1-trimethylsilyl-1-propyne)						Original Measurements: T. Nakagawa, M. Sekiguchi, K. Nagai, and A. Higuchi, Int. Congress on Membranes (ICOM-90), Chicago, 1990, pp. 824–26. T. Nakagawa, H. Nahanoo, and A. Higuchi, Membrane Symposium N1 “Control in Membrane Transport,” Kyoto, 1989, pp. 36–39.					
Variables: T/K=303 p/MPa=0–4.0						Prepared By: Yu. P. Yampol'skii					
Experimental Data Dual-mode sorption parameters						Auxiliary Information					
Gas	[Br], %	p/MPa	k _D , /cm ³ (STP)/cm ³ atm	C' _{II} , /cm ³ (STP)/cm ³	b/atm ⁻¹	Source and Purity of Materials: Poly(trimethylsilyl)propyne was synthesized according to Ref. 1. Bromination was carried out by dipping samples into bromine water. The polymer revealed a glass transition at 323 K.					
CO ₂	2.6	0–4.0	1.77	48.8	0.0701	Estimated Error: No information given.					
C ₃ H ₈	11.9	0–0.1	9.65	19.6	5.96						
Method/Apparatus/Procedure Sorption measurements were made by means of Cahn electrobalance model 2000.						References: ¹ K. Takada, H. Minuta, T. Masuda, and T. Higashimura, J. Appl. Polym. Sci. 30 , 1605 (1983).					

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] Propane; C ₃ H ₈ ; [74-98-6] (2) Poly(trimethylsilyl propyne) (PTMSP) [87842-32-8] (XVI)						Original Measurements: T. Nakagawa, M. Sekiguchi, K. Nagai, and A. Higuchi, Int. Congress on Membranes (ICOM-90) Chicago, 1990, pp. 824–26. T. Nakagawa, H. Nabano, and A. Higuchi, Membrane Symposium N1 “Control in Membrane Transport,” Kyoto, 1989, pp. 36–39.					
Variables: T/K=303 and 308 p/MPa=0–0.1 (for C ₃ H ₈) and 0–4.0 (for CO ₂)						Prepared By: Yu. P. Yampol'skii					
Experimental Data Dual-mode sorption parameters						Auxiliary Information					
Gas	T/K	k _D , /cm ³ (STP)/cm ³ atm	C' _{II} , /cm ³ (STP)/cm ³	b, atm ⁻¹		Source and Purity of Materials: PTMSP was synthesized according to Masuda <i>et al.</i> ¹ It did not reveal any glass transition up to 620 K.					
CO ₂	303	0.534	151.2	0.0403		References: ¹ K. Takada, H. Minuta, T. Masuda, and T. Higashimura, J. Appl. Polym. Sci. 30 , 1605 (1983).					
	308	1.497	112.9	0.058							
C ₃ H ₈	303	6.93	50.14	2.15							
Method/Apparatus/Procedure Sorption measurements were done by means of Cahn electrobalance, model 2000.											

3.15. Poly(2,3 Dimethylphenylene Oxide)—Carbon Dioxide, Methane

Components:		Original Measurements:	
(1) Argon; Ar; [7440-37-1] Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Poly(2,6-dimethylphenylene oxide) (PPO); [24938-67-8] (XVIII)			K. Toi, G. Morel, and D. R. Paul, J. Appl. Polym. Sci. 27 , 2997 (1982).

Variables:		Prepared By:	
7/K=308 p/MPa=0–2.5			A. K. Bokarev

Experimental Data			
Dual mode sorption parameters for various gases in PPO at 308 K			
Gas	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_H/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
Ar	0.21	9.4	0.058
CO ₂	0.95	27.5	0.250
CH ₄	0.33	18.1	0.110
N ₂	0.12	7.1	0.040

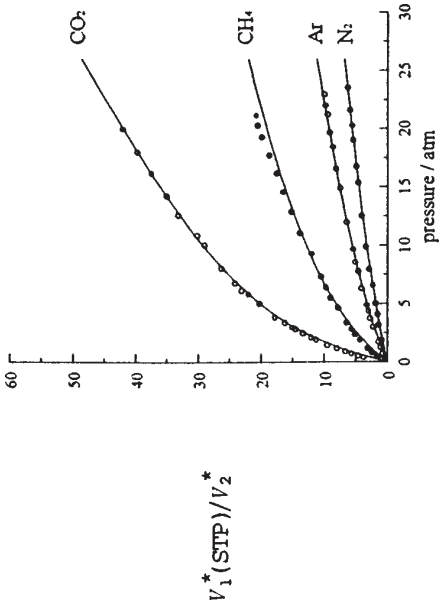


Fig. 27. Sorption isotherms of various gases in PPO at 298 K.

Auxiliary Information	
Method/Apparatus/Procedure Sorption measurements were made using facilities and procedures described previously, Ref. 1	Source and Purity of Materials: PPO: General Electric Co., $M_n = 34\,000$, $M_w = 22\,600$. Estimated Error: No information given.
References: ¹ D. R. Paul, Ber. Bunsenges Phys. Chem. 83 , 294 (1979).	

3.14. Poly(Phenylene Oxides)—Various Gases

Components:		Evaluator:	
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Poly(2,6-dimethylphenylene oxide) (PPO); [24938-67-8] (XVIII)			Yu. P. Yampol'skii, A. V. Tonchev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994

Critical Evaluation:
Four investigations are available on solubility of carbon dioxide and methane in PPO.^{1–4} PPO is a semicrystalline polymer with high glass transition temperature of amorphous phase. However, no author reported the content of amorphous and crystalline phases of polymer studied and other important characteristics like molecular mass. All this should result in predicaments in comparison of the data obtained in different papers.
Table 1 shows the dual mode sorption parameters and apparent solubility coefficients $\bar{S}$ calculated from them or from the initial slope of the experimental isotherms.

TABLE 1. Dual mode sorption parameters and apparent solubility coefficients

Gas	T/K	k_D	C'_H	b	$\bar{S}=k_D+C'_Hb$	Ref.
CO ₂	308	0.788	32.6	0.216	7.8	1
	308	0.849	25.9	0.239	7.0	3
	308	—	—	—	6*	2
CH ₄	293	—	—	—	4.7	4
	308	—	—	—	2.2*	2
	308	0.267	19.1	0.1077	2.3	3

Units: k_D and $\bar{S}/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$; $C'_H/\text{cm}^3(\text{STP})\text{cm}^{-3}$; b/atm^{-1} .
*Calculated from the plots by evaluator.
In spite of the difficulties mentioned above, the dual mode sorption parameters found by different authors agree reasonably, as well as the solubility coefficients at constant temperature.
Enthalpy of sorption of methane in PPO found from the $\bar{S}$ values measured at two different temperatures is shown to be equal to -35.6 kJ/mol .

- References:**
¹Y. Maeda and D. R. Paul, J. Polym. Sci.: Part B: Polym. Phys. **25**, 981 (1987).
²R. T. Chern, L. Jia, S. Shimoda, and H. B. Hopfenberg, J. Membr. Sci. **48**, 333 (1990).
³B. J. Story and W. J. Koros, J. Appl. Polym. Sci. **42**, 2613 (1991).
⁴O. M. Ilmichev, G. L. Semin, M. V. Chertova, and K. I. Zamaraev, J. Membr. Sci. **66**, 1 (1992).

Components: (1) Xenon, Xe, [7440-63-3] Carbon dioxide, CO ₂ [124-38-9] (2) Poly(phenylene oxide) (PPO) [24938-67-8] (XVIII)		Original Measurements: S. Asakawa, Y. Saitoh, K. Waragai, and T. Nakagawa, Gas Separation Purification 3 , 117 (1989).	
Variables: T/K = 307.8 p/kPa = 0 – 93		Prepared By: V. I. Bondar	
		Experimental Data Solubility coefficients, S	
Gas		10 ² S/cm ³ (STP)/cm ³ cm Hg	
Xe		18.81	
CO ₂		8.56	
		Auxiliary Information	
Method/Apparatus/Procedure A McBain balance with a quartz spiral was used in the solubility measurements, the correction for buoyancy was introduced.		Source and Purity of Materials: PPO was obtained by oxidative coupling method according to Ref. 1. Nothing specified on molecular mass or crystallinity.	
		Estimated Error: No information given.	
		References: 1. A. S. Hay, H. S. Blanchard, G. F. Endres, and J. W. Eustance, J. Am. Chem. Soc. 81 , 6335 (1959).	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Methane; CH ₄ ; [74-82-8] (3) Poly(2, 6-dimethylphenylene oxide) (PPO); [24938-67-8] (XVIII)		Original Measurements: B. J. Story and W. J. Koros, J. Appl. Polym. Sci. 42 , 2613 (1991).	
Variables: T/K = 308 p/MPa = 0–2.0 (0–20 atm)		Prepared By: Yu. P. Yampol'skii	
Experimental Data Dual mode sorption model parameters for pure gases in PPO at 308 K			
Gas	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_H/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
CO ₂	0.8490	25.86	0.2395
CH ₄	0.2674	19.10	0.1077

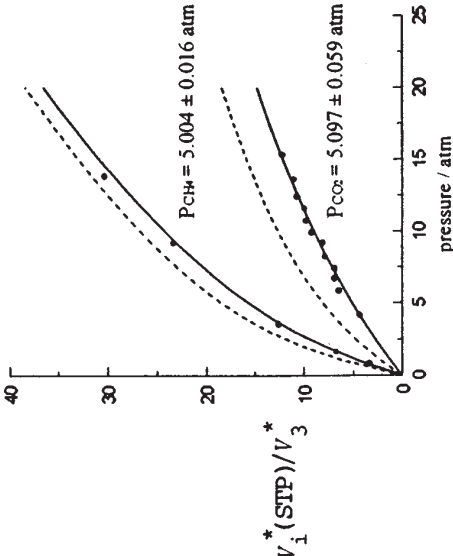


Fig. 28. Mixed gas sorption CO₂/CH₄ in poly(phenylene oxide) at 308 K. Solid lines: sorption model for mixed gas sorption $C_i = k_{D,i}p_i + C_H' b_i p_i / (1 + b_i p_i + b_j p_j)$. (Dotted lines) sorption model for pure gases.

Method/Apparatus/Procedure Standard pressure decay system (Ref. 1) was used in pure gas sorption. Mixed gas sorption experiments were performed using a special apparatus having additional chambers for preparation and chromatographic sampling of gas mixtures.		Auxiliary Information	
		Source and Purity of Materials: No information given.	
		Estimated Error: No information given.	
		References: W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).	

TABLE 3. Effect of the content of DOS (mass %) on CO₂ sorption isotherms for PPO at 308 K. (The original data were represented graphically)

Pressure/MPa	$(V_1^*/(STP)/f_{23})$	Pressure/MPa	$(V_1^*/(STP)/f_{23})$	Pressure/MPa	$(V_1^*/(STP)/f_{23})$	Pressure/MPa	$(V_1^*/(STP)/f_{23})$
DOS 0 mass %		DOS 10 mass %		DOS 20 mass %		DOS 30 mass %	
0.06	4.91	0.28	14.94	0.65	23.94	1.36	35.39
0.08	5.85	0.38	17.82	0.83	27.17	1.61	37.94
0.10	7.10	0.41	18.07	0.84	27.87	1.87	41.03
0.12	8.29	0.43	19.31	1.01	30.01	1.89	40.63
0.17	10.82	0.45	19.66	1.11	31.95	1.98	41.38
0.19	11.27	0.47	19.91	1.17	32.35	2.01	42.38
0.18	5.02	0.60	12.63	1.48	21.72	2.14	26.38
0.23	6.36	0.84	15.48	1.53	21.97	—	—
0.30	7.90	0.94	16.48	1.78	24.02	—	—
0.46	10.44	1.15	18.77	2.09	26.32	—	—
0.13	2.44	0.50	7.27	0.97	12.22	2.09	21.52
0.22	3.78	0.65	8.72	1.34	15.22	—	—
0.27	4.28	0.72	9.52	1.43	15.82	—	—
0.38	5.78	0.83	10.67	1.76	18.67	—	—
0.20	2.59	0.65	7.53	1.37	14.62	2.14	23.16
0.28	3.44	0.95	10.43	1.53	16.32	—	—
0.37	4.39	0.99	10.98	1.81	19.32	—	—
0.48	5.69	1.19	12.83	2.09	22.51	—	—

TABLE 4. Effect of the content of TCP (mass %) on CO₂ sorption isotherms for PPO at 308 K. (The original data were represented graphically)

Pressure/MPa	$(V_1^*/(STP)/f_{23})$	Pressure/MPa	$(V_1^*/(STP)/f_{23})$	Pressure/MPa	$(V_1^*/(STP)/f_{23})$	Pressure/MPa	$(V_1^*/(STP)/f_{23})$
TCP 0 mass %		TCP 10 mass %		TCP 20 mass %		TCP 30 mass %	
0.04	3.19	0.30	14.77	0.83	27.21	1.62	37.90
0.06	4.67	0.39	17.83	0.84	27.89	1.87	41.27
0.08	5.81	0.42	18.05	1.01	30.14	1.89	40.58
0.11	7.17	0.44	19.30	1.11	31.83	1.99	41.48
0.14	8.19	0.48	19.98	1.18	32.39	2.02	42.38
0.18	10.69	0.56	21.79	1.29	34.42	—	—
0.20	11.03	0.66	23.94	1.36	35.21	—	—
0.13	4.54	0.44	11.44	0.83	17.18	1.46	23.68
0.18	6.13	0.58	13.81	0.91	18.20	1.71	25.46
0.23	7.15	0.70	15.61	1.11	20.21	1.88	26.69
0.27	8.28	0.73	16.29	1.27	21.78	1.95	27.13
0.35	9.75	0.78	16.62	1.35	22.33	—	—
0.16	3.17	0.41	7.00	0.86	12.17	1.43	17.08
0.21	4.08	0.51	8.12	1.14	14.74	1.89	20.53
0.29	5.09	0.67	10.15	1.20	15.30	1.95	20.98
0.34	6.10	0.81	11.83	1.40	17.20	—	—
0.20	2.48	0.43	5.18	0.93	10.10	1.48	14.91
0.26	3.16	0.49	5.73	1.00	10.66	1.57	15.46
0.31	3.94	0.55	6.29	1.06	11.22	1.77	17.59
0.40	4.73	0.67	7.76	1.18	12.34	2.14	20.49

Components:

(1) Carbon dioxide; CO₂; [124-38-9]
 (2) Decanedioic acid, diethyl ester (diethyl sebacate, DOS); C₂₀H₄₀O₄; [2432-87-3] Phosphoric acid, trimethyl phenyl ester (trimesyl phosphate, TCP); C₃H₅O₄P; [1330-78-5]
 (3) Poly(2, 6-dimethylphenylene oxide) (PPO); [24938-67-8] (XVIII)

Original Measurements:

Y. Maeda and D. R. Paul, J. Polym. Sci., Part B: Polym. Phys. **25**, 981 (1987).

Variables:

$T/K = 308-328$
 $p/\text{MPa} = 0-2.2$ (0-22 atm)

Prepared By:

A. K. Bokarev

Experimental DataTABLE 1. Dual mode sorption parameters for CO₂ in PPO at different temperatures and its mixtures with plasticizers at 308 K

System	T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_{H_2}/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}	T_g/K
PPO	308	0.788	32.6	0.216	481.8
	318	0.586	30.0	0.164	481.8
	328	0.463	28.4	0.128	481.8
TCP (mass %)	308	0.543	21.6	0.181	427.1
10%	318	0.654	14.2	0.132	380.9
20%	328	0.821	3.8	0.251	345.0
DOS (mass %)	308	0.532	20.5	0.141	408.8
10%	318	0.763	7.3	0.172	354.1
20%	328	1.090	—	—	312.3

TABLE 2. Sorption isotherms of carbon dioxide in pure PPO (The original data were represented graphically)

Pressure/MPa	$(V_1^*/(STP)/f_3)$	Pressure/MPa	$(V_1^*/(STP)/f_3)$	Pressure/MPa	$(V_1^*/(STP)/f_3)$	Pressure/MPa	$(V_1^*/(STP)/f_3)$
$T=308\text{ K}$		$T=318\text{ K}$		$T=328\text{ K}$		$T=308\text{ K}$	
0.04	4.24	0.28	14.92	0.83	27.13	1.61	38.02
0.06	4.92	0.37	17.64	0.84	27.92	1.89	41.15
0.08	5.94	0.41	18.09	1.02	30.16	1.91	40.80
0.10	7.08	0.42	19.34	1.11	31.86	2.00	41.70
0.12	8.33	0.46	20.02	1.18	32.41	2.03	42.38
0.17	10.60	0.55	21.82	1.30	34.55	—	—
0.19	11.17	0.65	24.08	1.37	35.45	—	—
0.09	4.80	0.41	14.77	0.91	23.45	1.74	32.51
0.18	7.98	0.55	17.60	1.14	25.91	1.76	32.16
0.19	8.66	0.70	20.07	1.34	28.38	2.08	35.28
0.28	11.38	0.79	21.54	1.43	29.38	2.16	35.60
0.32	12.28	0.84	22.21	1.50	30.51	—	—
0.13	4.79	0.44	12.48	1.08	21.13	1.74	27.37
0.19	6.38	0.57	14.62	1.27	23.48	1.82	28.15
0.30	9.55	0.79	17.88	1.30	23.93	1.98	29.25
0.38	11.13	0.95	19.56	1.68	26.70	2.09	30.02

Components:			Original Measurements:		
(1) Nitrogen; N ₂ ; [7727-37-9] Methane; CH ₄ ; [74-82-8] (2) Poly(2, 6-dimethyl-1, 4-phenyleneoxide) (PPO); [24938-67-8] (XVIII) Aryl-brominated PPO (Br content 36% and 91%)			R. T. Chern, F. R. Shu, L. Jia, V. T. Stannett, and H. B. Hopfenberg, <i>J. Membr. Sci.</i> 35 , 103 (1987).		
Variables:			Prepared By:		
T/K: 308 p/MPa: 0–3.0 (1–3 atm)			A. K. Bokarev		
Experimental Data					
Dual-mode sorption parameters for gases in PPO and PPOBr at 308 K					
Polymer	Gas	$k_D/\text{cm}^{-3}(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_D/\text{cm}^3(\text{STP})\text{cm}^{-3}$	$b/(\text{atm}^{-1})$	
PPO	CO ₂	0.921	32.74	0.195	
	CH ₄	0.321	22.19	0.107	
	N ₂	0.153	9.95	0.048	
PPOBr (36%)	CO ₂	0.941	35.42	0.244	
	CH ₄	0.344	24.93	0.113	
	N ₂	0.162	11.83	0.053	
PPOBr (91%)	CO ₂	0.969	37.54	0.292	
	CH ₄	0.379	26.90	0.120	
	N ₂	0.169	15.06	0.057	
Auxiliary Information					
Method/Apparatus/Procedure		Source and Purity of Materials:			
A dual-transducer pressure-decay cell, was used for the solubility measurements. For details see Refs. 1 and 2.		PPO in powder form was obtained from General Electric Co.			
		Bromination of PPO resulted in only aryl-substituted polymer.			
		The ratio of mono- to di-substituted PPO was 2.6 for PPOBr (36%) and 8.6 for PPO (91%).			
		The purity of gases (Air Products and Chemicals) used: Coleman grade CO ₂ (99.999%), instrument grade CH ₄ (99.7%), N ₂ (≥99.99%).			
		Estimated Error: Not specified.			
		References:			
		¹ R. T. Chern, W. J. Koros, R. Yui, H. B. Hopfenberg, and V. T. Stannett, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 22 , 1061 (1984).			
		² E. S. Sanders, W. J. Koros, V. T. Stannett, and H. B. Hopfenberg, <i>J. Membr. Sci.</i> 13 , 161 (1983).			

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124:38-9] Methane; CH ₄ ; [74:82-8]		R. T. Cher. L. Jia, S. Shimoda, and H. B. Hopfenberg, J. Membr. Sci. 48 , 333 (1990).	
(2) Poly(2, 6-dimethylphenylene oxide) (PPO); [24938-67-8] (XVIII)			
Brominated PPO			
Variables:		Prepared By:	
$T/K=308$		Yu. P. Yampol'skii	
$p/\text{MPa}=0-2.5$			

TABLE 1. Properties of PPO and brominated PPO				
Characteristics	PPO	PPOBr (0.36)	PPOBr (0.91)	PPOBr (1.06)
% Repeat unit				
Mono-Br	0	20.4	73.9	60.0
Di-Br	0	7.8	8.5	24.0
Unmodified	100	71.8	17.6	16.0
Density/g cm ⁻³	1.061	1.203	1.380	1.390
T_g/K	483	506	535	542

TABLE 2. Sorption isotherms of carbon dioxide in the various polymers at 308 K (The original data were represented graphically)

PPO			PPOBr (0.36)			PPOBr (0.91)			PPOBr (1.06)		
Pressure/MPa	Sorption ($(V^*(\text{STP})/V^*)$)		Pressure/MPa	Sorption ($(V^*(\text{STP})/V^*)$)		Pressure/MPa	Sorption ($(V^*(\text{STP})/V^*)$)		Pressure/MPa	Sorption ($(V^*(\text{STP})/V^*)$)	
0.13	8.79	0.13	0.13	10.19	0.14	0.14	12.50	0.12	0.12	10.42	
0.17	9.93	0.20	0.20	13.39	0.22	0.22	17.33	0.36	0.36	22.35	
0.24	12.90	0.24	0.24	15.69	0.40	0.40	23.48	0.38	0.38	21.41	
0.30	14.95	0.32	0.32	18.43	0.45	0.45	24.85	0.24	0.24	15.93	
0.36	16.31	0.49	0.49	23.43	0.63	0.63	29.61	0.55	0.55	26.41	
0.45	18.57	0.53	0.53	24.79	0.88	0.88	35.25	0.70	0.70	32.35	
0.72	24.90	0.61	0.61	26.37	0.97	0.97	36.59	0.74	0.74	30.93	
0.81	27.17	0.76	0.76	29.52	1.08	1.08	38.60	0.96	0.96	35.20	
0.88	28.05	0.86	0.86	31.78	1.33	1.33	42.16	0.90	0.90	36.86	
1.02	30.28	0.95	0.95	33.11	1.52	1.52	44.82	1.11	1.11	40.91	
1.17	33.20	1.02	1.02	34.00	1.65	1.65	45.9	1.27	1.27	41.97	
1.37	35.16	1.28	1.28	38.47	1.73	1.73	46.77	1.41	1.41	46.29	
1.36	36.56	1.34	1.34	38.90	2.06	2.06	51.20	1.53	1.53	48.07	
1.50	36.70	1.41	1.41	40.01	2.13	2.13	51.86	1.63	1.63	48.93	
1.73	40.27	1.46	1.46	40.45	2.22	2.22	53.89	1.85	1.85	52.27	
1.76	41.18	1.75	1.75	44.20	2.32	2.32	54.52	2.06	2.06	55.85	
1.94	42.91	1.88	1.88	45.75	2.65	2.65	58.25	2.22	2.22	57.61	
2.16	45.10	1.93	1.93	46.64	—	—	—	2.53	2.53	61.35	
2.38	47.27	2.14	2.14	48.83	—	—	—	—	—	—	
2.63	51.06	2.32	2.32	51.03	—	—	—	—	—	—	
2.80	52.81	—	—	—	—	—	—	—	—	—	

Components:		Original Measurements:	
(1) Hydrocarbons C ₁ -C ₃		O. M. Ilinich, G. L. Semin, M. V. Chertova, and K. I. Zamarayev, J. Membr. Sci. 66 , 1 (1992).	
(2) Poly(phenylene oxide) (PPO); [25134-01-4]			
Variables:		Prepared By:	
$T/K=293.2$		O. M. Ilinich	
$p/\text{kPa}=0-100$			

Experimental Data					
Solubility $C/\text{cm}^3(\text{STP})\text{cm}^{-3}$ of hydrocarbons in PPO					
Gas	p/kPa	C	Gas	p/kPa	C
Methane; CH_4 ; [74-82-8]	21.3	1.0	Propane; C_3H_8 ; [74-98-6]	6.9	9.7
	34.0	1.4		13.7	12.6
	46.7	1.8		20.3	14.4
	60.0	2.3		30.0	16.1
	72.6	2.8		34.7	16.9
84.0	3.4				
Ethane; C_2H_6 ; [74-84-0]	6.0	3.3	Propylene; C_3H_6 ; [115-07-1]	4.4	6.6
	7.6	4.5		8.1	9.3
	20.0	7.0		13.6	11.6
	25.6	8.2		20.0	13.7
	34.7	9.8		26.7	15.4
			34.7	17.1	
Ethylene; C_2H_4 ; [74-85-1]	4.7	2.6			
	8.0	3.5			
	10.0	4.3			
	14.2	5.1			
	23.3	6.9			
34.3	8.6				
36.0	9.2				

Source and Purity of Materials:
PPO was prepared via oxidative polycondensation of 2,6-dimethylphenol. Major possible impurity: phenanthrene and copper. Purity >99.9%; a density 1.17 g/cm³, $T_g=482\text{ K}$. All the gases had a purity 99.9%.

Estimated Error:
 $\delta T = \pm 0.1\text{ K}$; $\delta p = \pm 0.2\text{ kPa}$.
 $\delta C/C = \pm 0.1$ (computer).

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]		B. J. Story and W. J. Koros, J. Appl. Polym. Sci. 42 , 2613 (1991).	
(2) Methane; CH ₄ ; [74-28-8]			
(3) Carboxylated poly(phenylene oxide) (CPPO)			
Variables:		Prepared By:	
T/K=308		Yu. P. Yampol'skii	
p/MPa=0-2.0 (0-20 atm)			
Experimental Data			
Dual mode sorption parameters for various gases in CPPO at 308 K			
Gas	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
CO ₂	0.7918	26.28	0.2852
CH ₄	0.2981	15.53	0.1254

TABLE 3. Sorption isotherms of methane in the various polymers at 308 K (The original data were represented graphically)					
PPO	PPOBr (0.36)		PPOBr (0.91)		PPOBr (1.06)
Pressure/MPa	Sorption ($V^*_g(\text{STP})/V^*_2$)	Pressure/MPa	Sorption ($V^*_g(\text{STP})/V^*_2$)	Pressure/MPa	Sorption ($V^*_g(\text{STP})/V^*_2$)
0.10	2.85	0.03	2.08	0.11	4.02
0.19	4.50	0.18	4.89	0.20	6.46
0.47	8.56	0.23	6.06	0.48	11.51
0.51	9.24	0.29	7.32	0.53	12.18
0.57	10.11	0.37	8.58	0.69	14.51
0.70	11.36	0.43	9.75	0.93	17.53
0.99	14.34	0.52	10.91	0.96	17.88
1.10	15.30	0.66	12.65	1.04	18.06
1.17	15.77	0.72	13.32	1.17	20.20
1.28	16.53	0.80	14.38	1.26	19.68
1.67	19.10	0.88	15.15	1.50	21.30
1.73	19.28	0.99	16.11	1.40	22.70
1.79	19.95	1.08	16.97	1.61	24.12
2.03	20.98	1.13	17.35	1.74	24.19
2.21	22.22	1.19	18.03	1.80	25.06
2.26	22.40	1.27	18.79	2.02	26.39
2.46	23.04	1.50	20.51	2.10	26.86
2.63	24.48	1.56	20.60	2.29	27.90
2.67	24.47	1.69	21.75	2.50	28.73
—	—	1.80	22.31	2.57	29.11
—	—	2.00	23.74	—	—
—	—	2.07	23.72	—	—
—	—	2.18	24.58	—	—
—	—	2.26	25.35	—	—
—	—	2.36	25.82	—	—
—	—	2.41	25.81	—	—
—	—	2.46	26.09	—	—
Auxiliary Information					
Method/Apparatus/Procedure			Source and Purity of Materials:		
Sorption isotherms were measured with a dual transducer barometric device described in Ref. 1.			Bromination was conducted at 273 K in dilute solution of PPO in chloroform (<5%). According to NMR none of the methyl groups were brominated. Aromatic rings were brominated mainly in three and five positions.		
Estimated Error:			References:		
No information given			¹ E. S. Sanders, W. J. Koros, H. B. Hopfenberg, and V. T. Stannett, J. Membr. Sci. 13 , 16 (1983).		

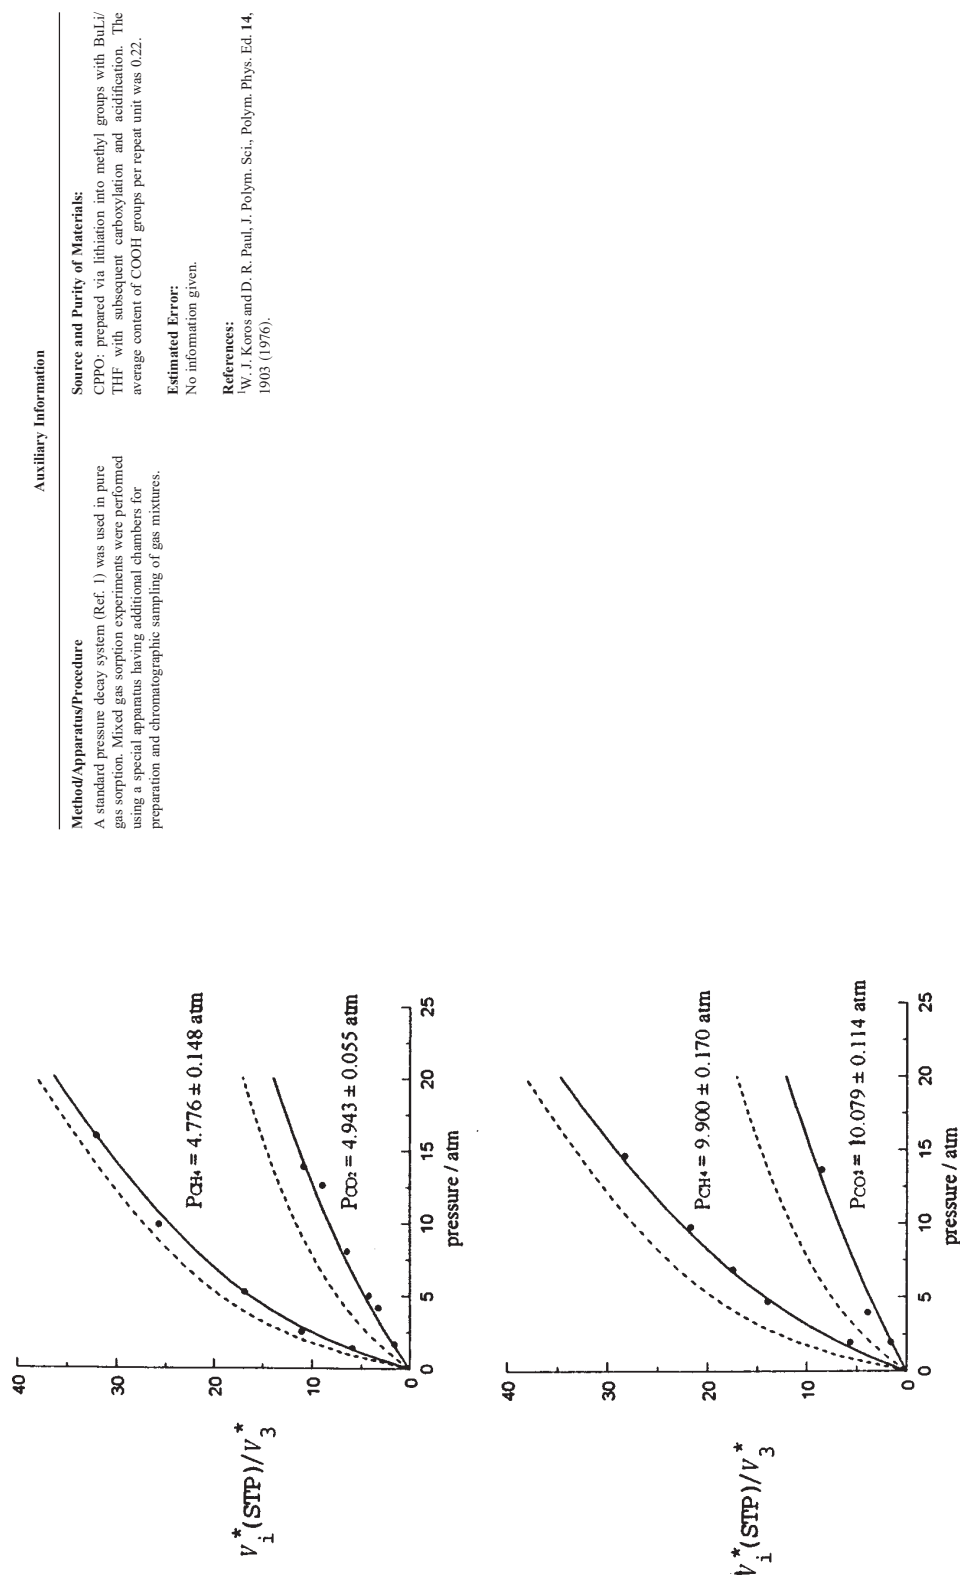


FIG. 29. Mixed gas sorption CO_2/CH_4 in CPPO at 308 K and two different pressures. (Solid lines) sorption model for mixed gas sorption $C_i = k_{Di}p_i + C_{Hi}b_i p_i / (1 + b_i p_i + b_j p_j)$. (Dotted lines) sorption model for pure gases.

Auxiliary Information	
Method/Apparatus/Procedure	A standard pressure decay system (Ref. 1) was used in pure gas sorption. Mixed gas sorption experiments were performed using a special apparatus having additional chambers for preparation and chromatographic sampling of gas mixtures.
Source and Purity of Materials	CPPO: prepared via lithiation into methyl groups with BuLi/THF with subsequent carboxylation and acidification. The average content of COOH groups per repeat unit was 0.22.
Estimated Error:	No information given.
References:	¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).

It can be seen too that the C'_H values vanish in the vicinity of T_g of PETP; in fact, one of the best documented cases of such a behavior. Table 2 presents the temperature dependence of the solubility coefficients. In spite of the substantial scatter, a decrease in the S values with temperature can be observed.

TABLE 2. Solubility coefficients S in semicrystalline samples of PETP (if not stated otherwise)

T/K	$S/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	Ref.
290	3.1	6a
298	2.7	1b,c
	3.3	2b
	3.1	5b
308	4.6	7a
	2.2	5b
	5.0	8a,c
	3.8	8a
318	1.7	4a
	1.7	5b
338	2.3	7a
	0.6	8a,c
	1.1	8a
358	0.35	5b

^aFound by evaluator from the initial slope of sorption isotherms.

^bCalculated using the dual mode sorption parameters.

^cAmorphous sample.

Further experimental studies with well characterized polymer samples are required in order to properly evaluate this system.

References:

- ¹A. S. Michaels, W. R. Vieth, and J. A. Barric, *J. Appl. Polym. Sci.*, **34**, 1 (1963).
- ²W. R. Vieth, H. H. Alcalay, and A. J. Frabetti, *J. Appl. Polym. Sci.*, **8**, 2125 (1964).
- ³K. Toti, *J. Polym. Sci., Polym. Phys. Ed.*, **11**, 1829 (1973).
- ⁴W. J. Koros, D. R. Paul, M. Fujii, and H. B. Hopfenberg, *J. Appl. Polym. Sci.*, **21**, 2899 (1977).
- ⁵W. J. Koros and D. R. Paul, *J. Polym. Sci., Polym. Phys. Ed.*, **16**, 1947 (1978).
- ⁶O. N. Tjigina, Dissertation, GIAP, Moscow, USSR, 1983.
- ⁷M. D. Sefcik, H. K. Yuen, and D. D. Chan, *Polymer*, **26**, 2043 (1985).
- ⁸Y. Kamiya, T. Hirose, Y. Naito, and K. Mizoguchi, *J. Polym. Sci., Part B: Polym. Phys.*, **26**, 159 (1988).
- ⁹T. Hirose, K. Mizoguchi, Y. Kamiya, and Y. Tanada, *J. Appl. Polym. Sci.*, **37**, 1513 (1989).

3.16. Poly(Ethylene Terephthalate)—Carbon Dioxide and Other Gases

Components:	Evaluator:
(1) Carbon dioxide; CO ₂ ; [124-38-9]	Yu. P. Yampol'skii, A. V. Topchiev, Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994
(2) Poly(ethylene terephthalate) (PETP); [25038-59-9] (XIX)	

Critical Evaluation:

This system has been studied thoroughly by a number of investigators.¹⁻⁹ However, the variation in crystallinity of polymer samples, as well as different temperature and pressure ranges studied preclude an accurate comparison of all the results.

Table 1 summarizes the dual mode sorption parameters at 298 K for the samples having different degrees of crystallinity. It is seen that other factors beside crystallinity determine the parameters of sorption isotherms. Moreover, depending on the method of crystallization, different values of model parameters can be observed for the same crystallinity.⁹ Perhaps, this is caused by the effects of quenching or swelling in high pressure gas. The same is true for the solubility coefficient.

TABLE 1. The dual mode sorption parameters and apparent solubility coefficients S at 298 K

Crystallinity/%	k_D	C'_H	b	$S=k_D+C'_Hb$	Ref.
0	0.38	5.3	0.44	2.7	1
25*	0.77	2.6	1.5	4.7	9
27**	0.73	7.0	1.3	9.8	9
43	0.21	4.2	0.45	2.1	1
46	0.37	5.7	0.52	3.3	2
59	0.36	7.9	0.35	3.1	5

*Crystallization by heating.

**Crystallization by exposing to high pressure carbon dioxide.

Units: k_D and $S/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$; $C'_H/\text{cm}^3(\text{STP})\text{cm}^{-3}$; b/atm^{-1} .

For the given samples of PETP, very good temperature dependences of the parameters of sorption isotherms have been obtained (see e.g., Refs. 5 and 9). Figure 30 shows temperature dependence of the C'_H parameter determined by different authors and for the samples with different pretreatment. It indicates that the differences in crystallization methods cause larger alterations in the C'_H values than those obtained in independent sorption studies.

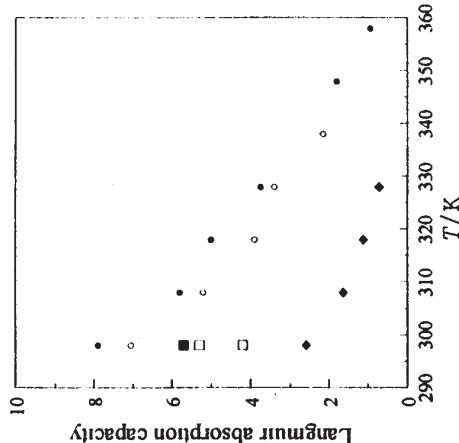


FIG. 30. Temperature dependence of Langmuir adsorption capacity $C'_H/(\text{cm}^3(\text{STP})\text{cm}^{-3})$. (○) Ref. 1; (●) Ref. 2; (◻) Ref. 5; (◼) Ref. 9 (crystallization by exposure to CO₂); (◆) Ref. 9 (crystallization by heating).

Components: (1) Argon; Ar; [7440-37-1] Nitrogen; N ₂ ; [7727-37-9] Oxygen; O ₂ ; [7782-44-7] Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(ethylene terephthalate) (PETP); [25038-59-9] (XIX)		Original Measurements: K. Toi, J. Polym. Sci., Polym. Phys. Ed. 11 , 1829 (1973).	
Variables: T/K: 288–315 p/kPa: 0–101.3		Prepared By: A. K. Bokarev	
Experimental Data			
Henry's law is obeyed by O ₂ , Ar, and N ₂ in all samples of PETP at pressure up to 1 atm. The deviations from Henry's law were observed for CO ₂ . The dual mode sorption model equation was follow $C = [1.89p/(1 + 0.45p)] + 0.38pa$, where a is volume fraction of amorphous phase, for CO ₂ /PETP systems.			
		The solubility coefficients $S/\text{cm}^3(\text{STP})\text{cm}^{-3} \text{ atm}^{-1}$ of gases in PETP-50 at 303 K	
		N ₂	0.084
		O ₂	0.092
		Ar	0.105
		CO ₂ ^a	1.353
^a PETP-75.			
Heats of sorption for CO ₂ in PETP-75 at 70 cm Hg gas pressure was equal to -5.37 kcal/mol.			
Auxiliary Information			
Method/Apparatus/Procedure Manometric method was used for the measurement of solubility. The pressure changes due to sorption were measured with a cathetometer.		Source and Purity of Materials: Four samples of commercial PETP (Daifol, Mitsubishi Plastics Ltd.) were studied: one having amorphous structure (PETP-75) and three having the degree of crystallinity of 48.0% (PETP-50, 75, and 100, where figures are the thickness of the samples). Completely amorphous PETP-75 had density 1.331 g/cc. Other samples had $\rho = 1.400$ g/cc. Commercial gases were used. CO ₂ was purified by the sublimation method by means of liquid nitrogen.	
Estimated Error: $\delta S/S = +3\%$.			

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(ethylene terephthalate) (PETP); [25038-59-9] (XIX)		Original Measurements: W. R. Vieth and K. J. Sladek, J. Colloid Sci. 20 , 1014 (1965).	
Variables: T/K = 313 p/MPa = 0–1.8		Prepared By: A. K. Bokarev	
Experimental Data			
Sorption isotherm of carbon dioxide in a PETP Mylar film at 313 K. (The original data were represented graphically)			
Pressure/MPa	Sorption (V^*_g (STP)/ V^*_s)	Pressure/MPa	Sorption (V^*_g (STP)/ V^*_s)
0.15	2.10	0.93	5.81
0.19	2.35	1.07	6.37
0.21	2.61	1.07	5.96
0.32	3.27	1.23	6.88
0.42	3.57	1.41	7.69
0.46	3.98	1.43	7.23
0.61	4.85	1.54	8.15
0.72	5.46	1.75	8.65
0.75	5.31	1.76	8.34
0.90	5.97	—	—
Auxiliary Information			
Method/Apparatus/Procedure The experimental technique used to obtain the gas solubility data was identical to that reported by Michaels <i>et al.</i> ¹ The details of the apparatus and procedure had been described in Ref. 2.		Source and Purity of Materials: PETP: commercial grade biaxially oriented Mylar film described in Ref. 2. M_w = from 15 000 to 20 000, amorphous volume fraction α = 0.54.	
		Estimated Error: No information given.	
		References: ¹ A. S. Michaels, W. R. Vieth, and J. A. Barrie, J. Appl. Phys. 31 , 1 (1963). ² W. R. Vieth, H. H. Alcalay, and A. J. Frabetti, J. Appl. Polym. Sci. 8 , 2125 (1964).	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(ethylene terephthalate); (PETP); [25038-59-9] (XIX)		Original Measurements: W. J. Koros and D. R. Paul, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 16 , 1947 (1978).	
Variables: T/K: 298–388 p/MPa: 0–2.0 (0–20 atm)		Prepared By: A. K. Bokarev	

Experimental Data			
Dual-mode sorption parameters for CO ₂ in PETP			
T/K	k_D /cm ³ (STP)cm ⁻³ atm ⁻¹	C_H /cm ³ (STP) cm ⁻³	b /atm ⁻¹
298	0.362	7.913	0.351
308	0.330	5.760	0.322
318	0.260	4.960	0.282
328	0.234	3.753	0.252
338	0.214	2.735	0.197
348	0.210	1.814	0.165
358	0.196	0.936	0.167
368	0.194		
378	0.184		
388	0.167		

Below 358 K, sorption isotherms of CO₂ in PETP show a nonlinear character typical for glassy polymers. Above 358 K, the isotherms are completely linear at pressures as high as 20 atm.

Method/Apparatus/Procedure		Auxiliary Information	
The apparatus and experimental procedure used for sorption measuring have been described elsewhere. ¹		Source and Purity of Materials: PETP (Kimmur) from Commercial Plastics Co had the weight average molecular mass of 54 000, T_g = 358 K, and the degree of crystallinity near 60%. A density of amorphous PETP was 1.331 g/cc, those of semicrystalline samples were in the range 1.4±0.003 g/cc. The CO ₂ used was >99% pure.	
		Estimated Error: No information given.	
		References: ¹ W. J. Koros, D. R. Paul, and A. A. Rocha, <i>J. Polym. Sci., Polym. Phys. Ed.</i> , 14 , 687 (1976).	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(ethylene terephthalate) (PETP); [25038-59-9] (XIX)		Original Measurements: W. J. Koros, D. R. Paul, M. Fujii, H. B. Hopfenberg, and V. Stannett, <i>J. Appl. Polym. Sci.</i> 21 , 2899 (1977).	
Variables: T/K = 308–338 p/MPa = 0–2.1		Prepared By: A. K. Bokarev	

Experimental Data				
Sorption isotherms of carbon dioxide in poly(ethylene terephthalate) at 308 and 338 K. (The original data were represented graphically)				
Pressure/MPa	Sorption (V_1^*/V_2^*)	Pressure/MPa	Sorption (V_1^*/V_2^*)	Sorption (V_1^*/V_2^*)
$T = 308$ K				
0.08	1.64	0.94	7.39	10.36
0.18	2.88	1.01	7.73	10.87
0.19	2.71	1.08	7.84	10.93
0.27	3.50	1.26	8.79	11.15
0.41	4.63	1.52	9.75	11.60
0.60	5.87	1.57	9.63	11.77
0.63	5.87	1.66	10.09	—
0.76	6.66	1.76	10.65	—
$T = 338$ K				
0.18	1.13	0.82	3.49	5.50
0.22	1.35	0.96	3.60	6.12
0.42	2.25	1.18	4.50	6.29
0.55	2.65	1.25	4.61	6.23
0.59	2.76	1.26	4.44	6.23
0.73	2.92	1.52	5.45	—

Method/Apparatus/Procedure		Auxiliary Information	
Design and operation of the sorption cell have been described in the literature. ^{1,2}		Source and Purity of Materials: PETP: commercially available transparent and highly crystalline sample. ³	
		Estimated Error: No information given.	
		References: ¹ W. J. Koros and D. R. Paul, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 14 , 1903 (1976). ² W. J. Koros, D. R. Paul, and A. A. Rocha, <i>ibid.</i> 14 , 687 (1976). ³ W. J. Koros, Ph.D. dissertation, The University of Texas at Austin, 1977.	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(ethylene terephthalate) (PETP); [25038-59-9] (XIX)		Original Measurements: M. D. Sečik, H. K. Yuen, and D. D. Chan, Polymer 26 , 2043 (1985).	
Variables: T/K = 308–328 p/kPa = 0–100 (0–1 atm)		Prepared By: Yu. P. Yampol'skii	
Experimental Data Sorption isotherms of carbon dioxide in PETP (the original data were represented graphically)			
T = 308 K		T = 318 K	
Pressure/kPa	Sorption (V [*] _g (STP)/V [*] _g)	Pressure/kPa	Sorption (V [*] _g (STP)/V [*] _g)
2.03	0.06	5.07	0.12
2.03	0.09	8.11	0.19
3.04	0.16	12.16	0.28
5.07	0.27	20.27	0.48
8.11	0.36	27.36	0.62
12.16	0.53	33.44	0.74
17.23	0.71	43.57	0.92
24.32	0.94	53.70	1.09
33.44	1.14	62.82	1.25
48.64	1.48	73.97	1.42
66.87	1.87	84.10	1.59
85.11	2.24	93.22	1.73
102.34	2.53	101.33	1.88
*Repeated after all the measurements.			
Method/Apparatus/Procedure Sorption isotherms were determined gravimetrically using a Mettler Thermoanalyzer-1.		Auxiliary Information Source and Purity of Materials: PETP: B. F. Goodrich Co., glass transition temperature 340 K, amorphous phase content 66%. A powdered sample of PETP was prepared by dissolving the polymer in a mixed solvent (67% of C ₂ H ₂ Cl ₄ and 33% of C ₂ H ₅ OH) with subsequent precipitation in excess methanol. Surface area of the powder: 7.5 m ² /g. Estimated Error: No information given.	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(ethylene terephthalate) (PETP); [25038-59-9] (XIX)		Original Measurements: O. N. Tugina, dissertation, GIAP, Moscow, USSR, 1983.			
Variables: T/T/K = 290 and 320 p/MPa = 0.4–4.0		Prepared By: S. M. Shishatskii			
Experimental Data Solubility of carbon dioxide (g/g polymer) in PETP					
T/K	p/MPa	C · 10 ²	T/K		
290	0.4	1.73	320	0.4	0.8
	0.5	2.2		0.6	1.1
	0.6	2.3		0.8	1.3
	0.8	2.9		1.0	1.5
	1.0	3.2		1.2	1.8
	1.2	3.8		1.4	1.9
	1.4	4.2		1.6	2.1
	1.6	4.5		1.8	2.2
	1.8	4.8		2.0	2.3
	2.0	5.1		2.2	2.4
	2.2	5.3		2.4	2.5
	2.4	5.5		2.6	2.6
	2.6	5.7		2.8	2.6
	2.8	5.8		3.0	2.7
	3.0	5.9		3.2	2.8
	3.2	6.0		3.4	2.8
	3.4	6.1		3.6	2.9
	3.6	6.2		3.8	2.9
	3.8	6.3			
	4.0	6.3			
Auxiliary Information Method/Apparatus/Procedure The solubility was measured by means of an apparatus of hydro-static weighing, the principle of which had been described in Ref. 1. Source and Purity of Materials: PETP (specification TU-29-02-367-71) was studied. It had a density 1.34 g/cc and a degree of crystallinity 25%. Estimated Error: δC/C = 1.5% References: 1. F. Golubev and O. A. Dobrovolskii, Gaz. Prom. N5 , 43 (1964).					

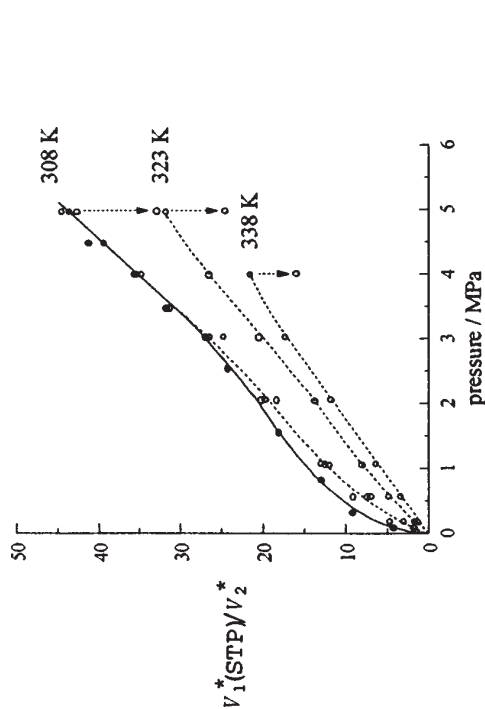


FIG. 32. Sorption isotherms of carbon dioxide in amorphous PETP. The dotted arrows show the decreases in concentration accompanying crystallization. Open and filled symbols represent sorption and desorption, respectively.

Components:		Original Measurements: Y. Kamiya, T. Hirose, Y. Naito, and K. Mizoguchi, J. Polym. Sci., Part B: Polym. Phys. 24 , 159 (1988).
(1) Carbon dioxide; CO ₂ ; [124-38-9]		
(2) Poly(ethylene terephthalate) (PETP); [25038-59-9] (XIX)		
Variables:		Prepared By: A. K. Bokarev
T/K = 308–338		
p/MPa = 0–5.0		

Experimental Data

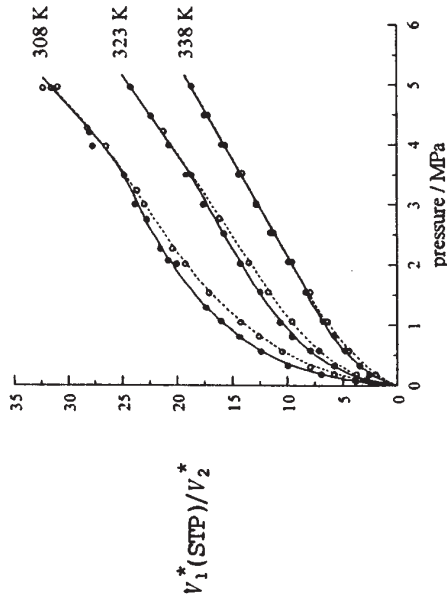
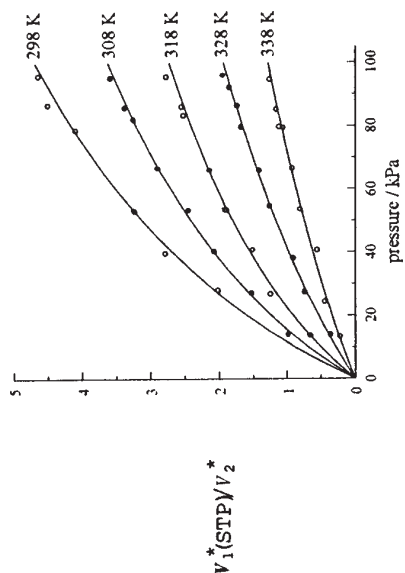
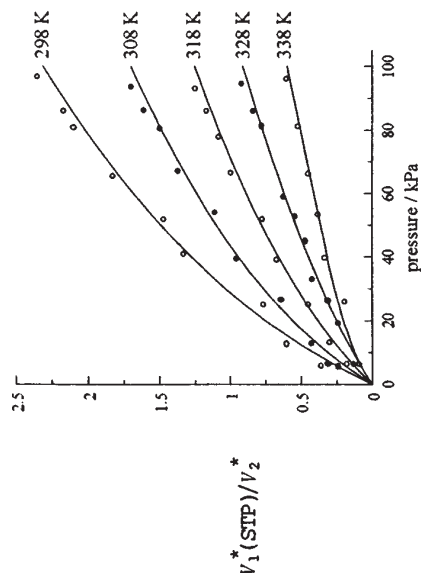


FIG. 31. Sorption isotherms of carbon dioxide in CO₂-conditioned crystalline PETP, measured after CO₂ sorption experiment at 308 K. Open and filled symbols represent sorption and desorption, respectively.

Method/Apparatus/Procedure	
The isotherms of gases in the polymer were obtained gravimetrically using a Cahn model 2000 electrobalance. Details of this apparatus were described previously. ¹	
Auxiliary Information	
Source and Purity of Materials:	
CO ₂ : purity 99.99%.	
Amorphous PETP: Diafoil Ltd., density 1.336 g/cm ³ .	
PETP after thermal crystallization for about 5 h at 393 K in an air: density 1.37–1.38 g/cm ³ .	
PETP after CO ₂ exposure crystalline film to 50 atm at 308 K for 24 h or more: density 1.367 g/cm ³ .	
Estimated Error:	
No information given.	
References:	
¹ Y. Kamiya, K. Mizoguchi, Y. Naito, and T. Hirose, J. Pol. Sci., Polym. Phys. Ed. 24 , 535 (1986).	

FIG. 33. Sorption isotherms of carbon dioxide in *c*-PETP.FIG. 34. Sorption isotherms of carbon dioxide in *h*-PETP.

Components:		Original Measurements:
(1) Carbon dioxide; CO ₂ ; [124-38-9]		T. Hirose, K. Mizoguchi, Y. Kamiya, and K. Terada, <i>J. Appl. Polym. Sci.</i> 37 , 1513 (1989).
(2) Poly(ethylene terephthalate) (PETP); [25038-59-9] (XIX)		
Variables:		Prepared By:
<i>T</i> /K = 298–338		A. K. Bokarev
<i>p</i> /kPa = 0–100 (0–1 atm)		
amorphous volume fraction α = 0.73–0.96		

Experimental Data			
TABLE 1. Dual mode sorption parameters for CO ₂ in <i>c</i> -PETP			
<i>T</i> /K	k_D /cm ³ (STP) cm ⁻³ atm ⁻¹	C_H' /cm ³ (STP) cm ⁻³	<i>b</i> /atm ⁻¹
298	0.733	7.05	1.30
308	0.633	5.22	1.36
318	0.522	3.94	1.30
328	0.485	3.45	0.739
338	0.429	2.15	0.668
308 ^a	0.633	3.19	1.50

^aAfter annealing of *c*-PETP at 338 K.

TABLE 2. Dual mode sorption parameters for CO ₂ in <i>h</i> -PETP			
<i>T</i> /K	k_D /cm ³ (STP) cm ⁻³ atm ⁻¹	C_H' /cm ³ (STP) cm ⁻³	<i>b</i> /atm ⁻¹
298	0.770	2.59	1.52
308	0.665	1.64	1.79
318	0.579	1.12	1.59
328	0.509	0.72	1.33

TABLE 3. Comparison of solubilities of CO₂ in *c*-PETP before and after thermal annealing at 338 K. (The original data were represented graphically)

Before annealing				After annealing at 338 K			
Pressure/kPa	Sorption ($V_1^*(STP)/V_2^*$)	Pressure/kPa	Sorption ($V_1^*(STP)/V_2^*$)	Pressure/kPa	Sorption ($V_1^*(STP)/V_2^*$)	Pressure/kPa	Sorption ($V_1^*(STP)/V_2^*$)
13.51	0.99	67.61	2.73	13.79	0.67	68.15	2.01
27.34	1.51	83.71	3.21	27.18	1.01	69.27	1.97
40.80	2.03	87.94	3.34	41.00	1.43	80.35	2.17
54.60	2.40	97.87	3.54	41.74	1.39	87.62	2.33
—	—	—	—	55.52	1.68	88.75	2.31
—	—	—	—	60.52	1.91	97.93	2.48

Components:		Original Measurements:							
(1) Hydrogen; H ₂ ; [1333-74-0] Nitrogen; N ₂ ; [7727-37-9]		H.-C. Draishach, D. Jeschke, and H. A. Stuart, Z.							
(2) Poly(ethylene terephthalate) (PETP); [25038-59-9] (XIX)		Naturforschung 17a, 447 (1962).							
Variables:		Prepared By:							
T/K = 293–373		Yu. P. Yampol'skii							
p/MPa = 6.65–66.5									
Experimental Data									
Solubility coefficients S 10 ² /cm ³ (STP)/cm ³ atm of hydrogen*									
Temperature/K									
Sample	293	303	313	323	333	343	353	363	373
Amorphous	2.68	2.47	2.29	2.12	2.01	2.00	2.09	2.27	2.45
Cryst., 30.6%	2.39	2.21	2.00	1.82	1.71	1.62	1.56	1.59	1.65
Cryst., 43.0%	2.21	2.00	1.83	1.68	1.62	1.56	1.50	1.53	1.53
*Smoothed values from the plot, taken by compiler.									
Enthalpies of sorption ΔH /(cal/mol of hydrogen)									
Sample	$T < T_g$				$T > T_g$				
Amorphous					1700				
Cryst., 30.6%					1900				
Cryst., 43.0%					2000				
Solubility coefficients S /cm ³ (STP)/cm ³ atm of nitrogen at 338 K									
Amorphous					Cryst., 30.6%				
0.0238					0.0231				
Cryst., 43.0%									
0.0226									
Auxiliary Information									
Method/Apparatus/Procedure				Source and Purity of Materials:					
Sorption isotherms for gases in the polymer were obtained gravimetrically using a Cahn model 2000 electrobalance. Details of this apparatus were described in Ref. 1				Three samples of commercial PETP (Terylen) were studied: one having amorphous structure and two having the degrees of crystallinity of 30.6 and 43.0%. PETP had T_g = 343 K. Nothing specified on the purity of gases.					
No information given.				Estimated Error:					
				No information given.					

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
Sorption isotherms for gases in the polymer were obtained gravimetrically using a Cahn model 2000 electrobalance. Details of this apparatus were described in Ref. 1	Amorphous PETP (<i>a</i> -PETP): Mitsubishi Diafoil Co., crystallization by exposing to CO ₂ (50 atm, 308 K) (<i>c</i> -PETP) or thermal (398 K, 5.3 h) (<i>h</i> -PETP)
	<i>a</i> -PETP: density 1.336 g/cm ³ , α = 0.96.
	<i>c</i> -PETP: density 1.362 g/cm ³ , α = 0.73.
	<i>h</i> -PETP: density 1.362 g/cm ³ , α = 0.70.
Estimated Error:	
No information given.	
References:	
1. T. Hirose, K. Mizoguchi, and Y. Kamiya, J. Appl. Polym. Sci. 34, 1657 (1987).	

TABLE 4. Sorption isotherms of carbon dioxide in PETP at 298 K (I) and 313 K (II) and at subatmospheric pressure (The original data were represented graphically)

Pressure/kPa		Sorption ($V_1^*(\text{STP})/V_2^*$)	Sorption ($V_1^*(\text{STP})/V_2^*$)		Sorption ($V_1^*(\text{STP})/V_2^*$)	
Pressure/kPa			Pressure/kPa		Pressure/kPa	
(I)						
$\alpha=0.57$						
6.73	0.16	52.14	0.91	112.39	1.61	
17.02	0.38	60.11	1.00	115.05	1.63	
21.00	0.42	69.87	1.13	131.02	1.83	
28.12	0.54	83.99	1.23	149.57	2.00	
30.35	0.58	86.62	1.23	161.07	2.11	
38.36	0.70	99.99	1.47	170.80	2.21	
41.04	0.76	103.1	1.51	—	—	
$\alpha=1.0$						
12.62	0.36	50.16	1.13	109.34	2.07	
21.14	0.57	54.63	1.23	111.56	2.11	
23.34	0.57	58.20	1.29	124.44	2.28	
35.39	0.81	72.94	1.58	137.31	2.46	
34.99	0.85	85.33	1.71	145.76	2.59	
39.44	0.92	87.14	1.77	156.39	2.71	
41.22	0.94	100.03	1.95	—	—	
(II)						
$\alpha=0.65$						
4.01	0.05	47.96	0.55	85.91	0.89	
11.47	0.15	48.38	0.60	95.27	0.99	
11.46	0.17	51.23	0.59	100.9	1.03	
17.11	0.19	53.08	0.64	101.36	1.05	
17.09	0.21	58.71	0.67	111.21	1.12	
22.21	0.29	64.81	0.72	122.00	1.20	
39.03	0.50	69.97	0.76	125.26	1.26	
42.82	0.49	71.85	0.77	132.79	1.28	
43.28	0.51	76.53	0.81	—	—	
$\alpha=1.0$						
7.23	0.15	29.60	0.48	68.88	0.93	
14.21	0.26	33.82	0.52	73.56	0.98	
16.09	0.27	38.52	0.54	82.45	1.07	
22.63	0.36	48.33	0.66	100.23	1.26	
30.10	0.45	50.65	0.71	—	—	
31.50	0.47	63.75	0.86	—	—	

Components:		Original Measurements:	
(1) Helium; He; [7440-59-7] Argon; Ar; [7440-37-1] Nitrogen; N ₂ ; [7727-37-9] Oxygen; O ₂ ; [7782-44-7] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] Ethane; C ₂ H ₆ ; [74-84-0]		A. S. Michaels, W. R. Vieth, and J. A. Barrie, J. Appl. Phys. 34 , 1 (1963).	
(2) Poly(ethylene terephthalate) (PETP); [25038-59-9] (XIX)			

Variables:		Prepared By:	
T/K = 298–338		S. M. Shishatskii	
p/MPa = 0–1.26			

Experimental Data
Henry's law is obeyed by He, O₂, Ar, N₂, and CH₄ in amorphous PETP at subatmospheric pressure. Deviations from Henry's law were observed for CO₂ and C₂H₆, even below 1 atm and at higher pressures.

TABLE 1. Solubility coefficients of various gases in amorphous PETP at 298 K						
Sorption	He	Ar	N ₂	O ₂	CO ₂	C ₂ H ₆
cm ³ (STP)/cm ³ am	0.0078	0.082	0.058	0.100	2.71	0.240
						0.99

α = amorphous volume fraction	
TABLE 2. Temperature dependence of the solubility coefficients S(cm ³ (STP)/cm ³ am)	

		Sample	
Gas		Amorphous	Crystalline ($\alpha=0.58$)
CH ₄	T/K		
	308	0.175	—
	318	0.116	—
	337	0.065	—
	308	—	0.155
CO ₂	322	—	0.100
	338	—	0.073
	298	—	2.00
	312	—	1.20
	328	—	0.64
	338	—	0.50
		348	0.34

TABLE 3. Sorption isotherms of ethane in PETP at 298 K (The original data were represented graphically)			
$\alpha=0.54$		$\alpha=1.0$	
Pressure/kPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/kPa	Sorption ($V_1^*(\text{STP})/V_2^*$)
19.09	0.13	20.54	0.20
31.29	0.24	43.08	0.38
43.39	0.33	62.01	0.51
57.63	0.41	75.77	0.60
73.57	0.49	89.41	0.67
85.53	0.55	107.63	0.76
102.61	0.64	125.24	0.84
124.64	0.72	140.59	0.92
143.81	0.78	—	—

Components: (1) Nitrogen; N ₂ ; [7727-37-9] Oxygen; O ₂ ; [7782-44-7] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Poly(ethylene terephthalate) (PETP); [25038-59-9] (XIX)		Original Measurements: W. R. Vieth, H. H. Akalay, and A. J. Frabetti, J. Appl. Polym. Sci. 8 , 2125 (1964).			
Variables: T/K = 298–328 p/MPa = 0–1.7 (17 atm)		Prepared By: A. K. Bokarev			
Experimental Data					
TABLE 1. Solubility constants for oriented poly(ethylene terephthalate), $\alpha = 0.49$					
	N ₂	O ₂	CH ₄	CH ₄	
Temperature					
T/K	298	298	298	313	
Solubility constant*				328	
S/cm ³ (STP) cm ⁻³ atm ⁻¹	0.044	0.076	0.200	0.130	
*Value found from Van't Hoff plot.					
TABLE 2. Sorption isotherms of carbon dioxide in PETP, $\alpha = 0.49$ (The original data were represented graphically)					
	T = 298 K		T = 313 K		
Pressure/kPa	Sorption ($(P^*(\text{STP})/P^*_2)$)		Pressure/kPa	Sorption ($(P^*(\text{STP})/P^*_2)$)	
5.5	0.12		9.7	0.15	
12.5	0.27		19.3	0.28	
17.3	0.38		34.9	0.43	
36.0	0.76		55.3	0.64	
52.5	0.99		75.7	0.82	
76.8	1.34		93.3	0.98	
105.1	1.67		116.4	1.16	
119.2	1.83		130.0	1.27	
TABLE 3. Sorption isotherms of carbon dioxide in oriented PETP at 298 K (The original data were represented graphically)					
Pressure/MPa	Sorption ($(P^*(\text{STP})/P^*_2)$)	Pressure/MPa	Sorption ($(P^*(\text{STP})/P^*_2)$)	Pressure/MPa	Sorption ($(P^*(\text{STP})/P^*_2)$)
0.16	3.19	0.51	6.11	1.06	8.74
0.17	3.42	0.58	6.71	1.14	9.11
0.18	3.46	0.63	6.89	1.15	9.15
0.21	3.92	0.64	6.93	1.24	9.47
0.27	4.24	0.73	7.53	1.36	9.87
0.27	4.52	0.73	7.66	1.44	10.01
0.31	4.70	0.74	7.25	1.60	10.87
0.33	4.88	0.81	7.80	1.64	10.59
0.35	4.97	0.96	8.29	1.76	11.13
0.40	5.34	0.97	8.52	—	—
0.45	5.61	0.98	8.29	—	—
0.46	5.70	1.02	8.75	—	—

TABLE 5. Sorption isotherms of carbon dioxide in PETP at elevated pressure and 298 K (The original data were represented graphically)

Pressure/MPa		Sorption ($(P^*(\text{STP})/P^*_2)$)	Pressure/MPa		Sorption ($(P^*(\text{STP})/P^*_2)$)
$\alpha = 1.0$, run I			$\alpha = 1.0$, run II		
0.17	2.89		0.14	2.71	
0.25	4.08		0.20	3.41	
0.33	4.70		0.28	3.89	
0.44	5.22		0.31	4.48	
0.48	5.55		0.36	4.70	
0.57	6.14		0.41	5.07	
0.69	6.77		0.48	5.74	
0.78	7.21		0.61	6.40	
0.85	7.31		0.73	6.95	
0.95	7.68		0.81	7.24	
1.04	8.08		0.91	7.61	
1.12	8.38		1.00	7.98	
1.19	8.60		1.07	8.27	
—	—		1.16	8.60	
—	—		1.24	9.08	
$\alpha = 0.57$, run III			$\alpha = 0.57$, run IV		
0.12	1.78		0.28	2.55	
0.15	1.89		0.41	3.66	
0.24	2.48		0.55	4.65	
0.34	3.18		—	—	
0.47	3.69		—	—	
0.55	4.25		—	—	

The isotherms fitted the equations:

$$C = C_D + C_H = k_D^* p \alpha + C_H^* p / (1 + b p)$$

where the parameters C_H^* , and b have the usual meaning, k_D^* is Henry's law dissolution constant, and α is the amorphous volume fraction. The following dual mode sorption parameters are reported for CO₂ sorption at 298 K and 0–17 atm pressure range in PETP ($\alpha = 0.54$):

$k_D / \text{cm}^3(\text{STP}) \text{ cm}^{-3} \text{ atm}^{-1}$	$C_H^* / \text{cm}^3(\text{STP}) \text{ cm}^{-3}$	b / atm^{-1}
0.37	5.7	0.52

Heats of sorption, found from Van't Hoff for S(CO₂) in PETP ($\alpha = 0.49$):

$$\Delta H (\text{CO}_2) = -7.4 \text{ kcal/mol; } -31.0 \text{ kJ/mol}$$

$$\Delta H (\text{CH}_4) = -5.4 \text{ kcal/mol; } -22.6 \text{ kJ/mol.}$$

Method/Apparatus/Procedure	Source and Purity of Materials:
The procedure for low pressure measurements was described in Ref. 1. High pressure experiments were performed in a stainless steel bomb equipped with a pressure gauge.	CO ₂ , N ₂ , O ₂ : minimum purity 99.5%. CH ₄ : purity 99%. PETP (oriented Mylar): Du Pont Co., $M_w = 15\,000$ – $20\,000$, density 1.39 g/cm^3 , amorphous volume fraction $\alpha = 0.49$ and 0.54.

Estimated Error:
Relative precision of solubility constants: $\pm 8\%$.

References:
1. A. J. Michaels and W. R. Vieth, J. Appl. Phys. **34**, 1 (1963).

Components:	Original Measurements:
(1) Carbon dioxide; CO ₂ ; [124;38;9] (2) Poly(butylene terephthalate) (PBTP) (XX)	L. Thy and J. Springer, Colloid Polym. Sci. 266 , 614 (1988).
Variables:	Prepared By:
$T/\text{K} = 298$ – 338 $p/\text{MPa} = 0.1$ – 3.0	Yu. P. Yampol'skii

Experimental Data			
Dual mode sorption parameters for carbon dioxide in PBTP			
T/K	$k_D / \text{cm}^3(\text{STP}) \text{ cm}^{-3} \text{ atm}^{-1}$	$C_H^* / \text{cm}^3(\text{STP}) \text{ cm}^{-3}$	b / atm^{-1}
298	0.48	7.70	0.18
308	0.42	5.55	0.17
318	0.37	3.70	0.16
328	0.34	1.67	0.15
338	0.29	—	—

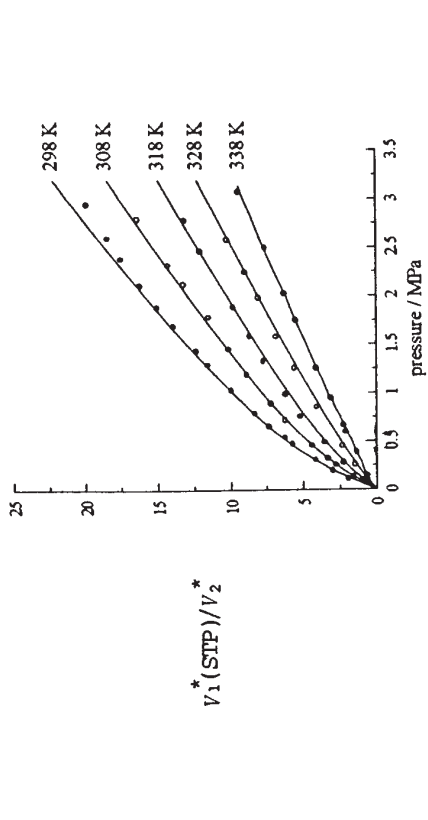


FIG. 35. Sorption isotherms of carbon dioxide in PBTP.

Auxiliary Information		
Method/Apparatus/Procedure	Source and Purity of Materials	Estimated Error:
High pressure apparatus was employed including Sartorius microbalance (model 4436).	PBTP: BASF (Ultradr B 2550). The granular degassed polymer was pressed into thin foil at 528 K and then quickly quenched in a mixture of ice, salt, and water. Density 1.283 g/cm^3 , degree of crystallinity about 19%, glass transition temperature 316 K.	No information given.

3.17. Polycarbonate—Carbon Dioxide

Components: (1) Carbon dioxide; CO ₂ ; [124:38-9] (2) Polycarbonate (PC); [24936:68-3] (XXI)		Evaluator: Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994			
Critical Evaluation: Bisphenol A polycarbonate (for brevity here and further, <i>polycarbonate</i>) is a well known and widely used industrial plastic produced by General Electric Co. under a tradename Lexan. Many authors dealt with the system PC–carbon dioxide, ^{1–11} The polymer samples studied were nearly identical in majority of the cases. The data have been obtained in the temperature range 293–373 K and at pressures up to 10 MPa. It was the system PC–CO ₂ , which was used as an example for the demonstration of the effects of annealing and conditioning on the sorption parameters, ^{4,9,11} which are generally characteristic of other glassy polymers. Exposing a polymer sample to high pressure gas, results in an increase in the concentration of dissolved gas the larger the higher is the pressure of such conditioning. ⁴ The annealing of polymer samples at sub- <i>T_g</i> temperatures leads to a decrease in the concentration of the dissolved gas. The table shows the pressure dependence of the concentration, <i>C</i> , of carbon dioxide dissolved in the polymer samples unconditioned (“as received”) and exposed to 2 MPa of carbon dioxide prior to solubility measurement. It is seen that the difference between the individual “sorption isotherms” is not dramatic. The last line presents average values of <i>C</i> at different pressures.					
Pressure dependence of the concentration <i>C</i> /(cm ³ (STP) cm ⁻³) of dissolved CO ₂ at 308 K					
Pressure/MPa					
0.5	1.0	1.5	2.0	Type of sample	Ref.
12.2	16.6	20.6	24.5	**	2
12.8	18.5	23.0	27.2	*	4
13.2	19.0	23.6	27.6	**	5
—	17	—	27	**	6
11.7	18.6	24.0	28.7	**	8
—	16	—	26	**	10
13.2	19.3	24.0	28.1	*	11
12.6	17.9	23.0	27.0	—	Av.

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124:38-9]		W. J. Koros, D. R. Paul, and A. Rocha, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 14 , 687 (1976).	
(2) Polycarbonate (PC); [2493:68-3] (XXI)			
Variables:		Prepared By:	
T/K: 308 K		A. K. Bokarev	
P/MPa: 0.1–2.5			

Experimental Data					
Solubility of carbon dioxide in PC at 308 K*					
<i>p</i> /atm		5	10	15	21
<i>C</i> */cm ³ (STP) cm ⁻³		14.2	20.5	26.7	32.0
					37.4
					42.3

*Smooth values taken from the graph by compiler.

TABLE 1. Dual mode sorption parameters for CO₂ in polycarbonate at 308 K

Method	k_D /cm ³ (STP) cm ⁻³ atm ⁻¹	C_H /cm ³ (STP) cm ⁻³	b /atm ⁻¹
Graphical	0.992	13.7	0.392
Nonlinear	0.933	15.3	0.338
Least squares			

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials
Measurements of gas solubility in polymer performed using a pressure decay method of dual-volume dual transducer type.	Bisphenol A polycarbonate (PC) (Lexan) was obtained from the General Electric Co. $M_w = 35\,800$. The CO ₂ used in experiment was >99% pure.
Estimated Error:	$\partial C_H = 0.45$ cm ³ (STP)/cm ³ (polymer).

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124:38-9]		W. R. Vieth and J. A. Eilenberg, <i>J. Appl. Polym. Sci.</i> 16 , 945 (1972).	
(2) Polycarbonate (PC); [2493:68-3] (XXI)			
Variables:		Prepared By:	
T/K=308–338		A. K. Bokarev	
<i>p</i> /MPa=0–2.2			

Experimental Data			
TABLE 1. Dual mode sorption parameters for carbon dioxide in polycarbonate			
T/K	k_D /cm ³ (STP) cm ⁻³ atm ⁻¹	C_H /cm ³ (STP) cm ⁻³	b /atm ⁻¹
308	0.765	9.53	1.50
318	0.708	7.20	1.16
338	0.346	7.09	0.94

TABLE 2. Sorption isotherms of carbon dioxide in polycarbonate (The original data were represented graphically)

T=308 K				T=318 K				T=338 K			
Pressure/MPa	Sorption ($p^*/(STP)/p_2^*$)	Pressure/MPa	Sorption ($p^*/(STP)/p_2^*$)	Pressure/MPa	Sorption ($p^*/(STP)/p_2^*$)	Pressure/MPa	Sorption ($p^*/(STP)/p_2^*$)	Pressure/MPa	Sorption ($p^*/(STP)/p_2^*$)	Pressure/MPa	Sorption ($p^*/(STP)/p_2^*$)
0.33	7.72	0.25	5.93	0.20	3.50	0.20	3.50	0.20	3.50	0.20	3.50
0.41	9.09	0.40	8.12	0.36	5.27	0.36	5.27	0.36	5.27	0.36	5.27
0.56	11.36	0.53	9.32	0.50	6.88	0.50	6.88	0.50	6.88	0.50	6.88
0.68	13.54	0.66	11.26	0.72	8.41	0.72	8.41	0.72	8.41	0.72	8.41
0.91	15.31	0.8	12.14	0.87	9.37	0.87	9.37	0.87	9.37	0.87	9.37
1.20	17.64	1.10	14.55	1.01	9.76	1.01	9.76	1.01	9.76	1.01	9.76
1.36	19.08	1.49	17.03	1.25	10.62	1.25	10.62	1.25	10.62	1.25	10.62
1.51	20.13	1.69	18.64	1.45	11.09	1.45	11.09	1.45	11.09	1.45	11.09
1.88	22.85	2.16	21.52	1.83	12.84	1.83	12.84	1.83	12.84	1.83	12.84
—	—	—	—	2.16	13.37	2.16	13.37	2.16	13.37	2.16	13.37

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials
A pressure decay method was used. Other details are given in Ref. 1.	PC; preparation described in Ref. 2. amorphous film, thickness 0.5 mm.

Estimated Error:

Relative precision: $C_H < 8.7\%$.

References

- W. R. Vieth, C. S. Frangoulis, and J. A. Rionda, *J. Colloid Interface Sci.* **22**, 454 (1966).
- P. J. Flory, thesis, B. S. Department of Chemical Eng., M.I.T., Cambridge, MA, 1968.

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]		A. H. Chan and D. R. Paul, Polym. Eng. Sci. 20 , 87 (1980).	
(2) Polycarbonate (PC); [24936-68-3] (XXI)			
Variables:		Prepared By:	
T/K = 308–348		A. K. Bokarev	
p/MPa = 0–2.0 (0–20 atm)			

TABLE 1. Temperature dependence of sorption parameters for carbon dioxide in PC. Sorption measurements were made after conditioning at 20 atm of CO₂.

T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
333	0.64	18.00	0.234
353	0.46	12.78	0.156
373	0.30	11.16	0.098
Van't Hoff parameters/(kcal/mol ⁻¹)			
	–4.0	—	–4.8

TABLE 2. Dual mode sorption parameters for carbon dioxide in annealed PC. Sorption measurements were made at 308 K after conditioning at 20 atm of CO₂.

PC sample history	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
As received	0.642	18.00	0.234
Annealed at 398 K for			
2 h	0.618	15.49	0.230
10 h	0.609	14.66	0.220
1 day	0.601	14.17	0.231
2 day	0.587	13.89	0.228
8.5 day	0.611	12.89	0.238
14 day	0.532	13.71	0.238
Annealed at 408 K for			
0.5 h	0.574	17.05	0.220
5h	0.570	15.43	0.226
10 h	0.550	15.20	0.227
2 day	0.560	14.80	0.230

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]		A. J. Wonders and D. R. Paul, J. Member. Sci. 5 , 63 (1979).	
(2) Polycarbonate (PC); [24936-68-3] (XXI)			
Variables:		Prepared By:	
T/K = 308		A. K. Bokarev	
p/MPa = 0–2.02 (0–20 atm)			

TABLE 3. Sorption isotherms of carbon dioxide in polycarbonate at 308 K. (The original data were represented graphically)

Pressure/MPa	Sorption ($V_1'(\text{STP})/V_2'$)	Pressure/MPa	Sorption ($V_1'(\text{STP})/V_2'$)
Series on initial exposure film			
0.08	3.12	0.83	15.13
0.11	3.88	1.02	17.47
0.22	5.92	1.06	17.91
0.33	7.76	1.09	18.34
0.43	9.70	1.12	18.34
0.51	10.78	1.20	19.31
0.72	13.69	1.29	20.07
0.79	14.88	1.40	21.15
Series after CO ₂ exposure at 20 atm			
0.09	4.20	0.80	16.39
0.20	7.00	0.89	17.47
0.31	9.26	1.00	18.33
0.42	11.20	1.12	19.74
0.51	12.61	1.21	20.49
0.58	13.58	1.30	21.36
0.70	15.20	1.39	22.12

Method/Apparatus/Procedure		Source and Purity of Materials:	
The sorption apparatus and procedure used in the present sorption experiments are the same as described earlier. ¹ Results labeled "initial" were obtained by beginning with "as-received" polymer and simply conducting a sorption experiment by increasing experimental pressure. "Uniform" samples were also prepared in a separate bomb using CO ₂ pressures of 20, 40, and 60 atm for 24 h.		CO ₂ : purity 99%. PC (Bisphenol A polycarbonate): Lexan, General Electric Co., $M_n = 35\,800$.	
		Estimated Error: No information given.	

References:
¹W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. **14**, 687 (1976).

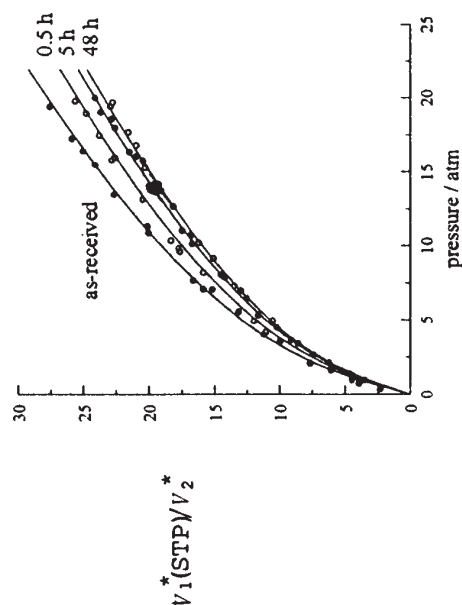


FIG. 36. Effect of temperature on carbon dioxide sorption in PC for "as-received" material conditioned at 20 atm of CO_2 .

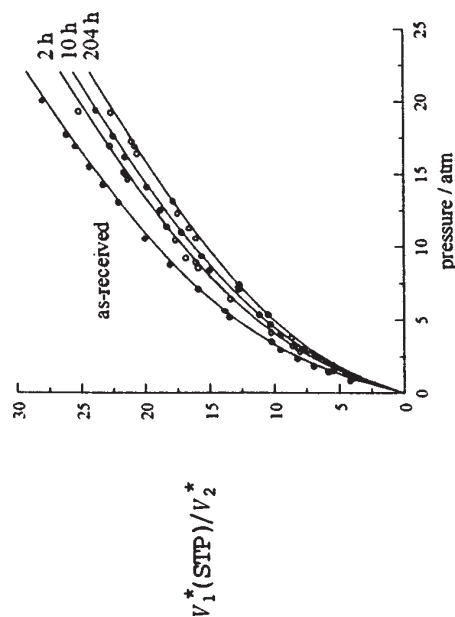


FIG. 37. Equilibrium sorption of carbon dioxide in PC samples annealed at 398 K. Sorption measurements were made at 308 K after conditioning at 20 atm of CO_2 .

FIG. 38. Same as for Fig. 37 except that the annealing temperature was equal to 408 K.

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
The equilibrium solubility of CO_2 in the polymer was measured by a pressure decay technique described earlier, Ref. 1.	PC (Lexan): General Electric Co., $M_w = 35\,800$, glass transition temperature 418 K.
	Estimated Error:
	No information given
	References:
	¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).

Components:		Original Measurements:
(1) Carbon dioxide; CO ₂ ; [124-38-9]		Y. Kamiya, T. Hirose, K. Mizoguchi, and K. Terada, J. Polym. Sci., Part B: Polym. Phys. 24 , 1525 (1986).
(2) Polycarbonate (PC); [24936-68-3] (XXI)		
Variables:		Prepared By:
T/K=308–328		A. K. Bokarev
p/MPa=0–5.0		

Experimental Data					
(For all the following tables, the original data were represented graphically)					
TABLE 1. Sorption and desorption isotherms of carbon dioxide in PC at 308 K, first series of experiments					
"As received" film			Rod specimens		
Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)
0.10	3.31	0.04	4.32	0.32	7.94
0.41	9.10	0.09	6.63	1.41	21.13
0.70	13.16	0.17	9.38	2.98	34.91
0.98	16.78	0.22	11.11	4.86	49.14
1.37	21.41	0.29	13.86	—	—
1.87	26.63	0.43	18.19	—	—
2.39	32.14	0.68	23.69	—	—
4.86	47.85	0.97	28.61	—	—
—	—	1.26	32.08	—	—
—	—	1.58	35.42	—	—
—	—	1.92	37.89	—	—
—	—	2.02	38.18	—	—
—	—	2.27	39.93	—	—
—	—	2.65	41.96	—	—
—	—	2.99	43.28	—	—
—	—	3.49	44.60	—	—
—	—	3.91	46.21	—	—

Components:		Original Measurements:
(1) Carbon dioxide; CO ₂ ; [124-38-9]		G. K. Fleming and W. J. Koros, Macromolecules 19 , 2285 (1986).
(2) Polycarbonate (PC); [24936-68-3] (XXI)		
Variables:		Prepared By:
T/K=308		A. K. Bokarev
p/MPa=0–6.2		

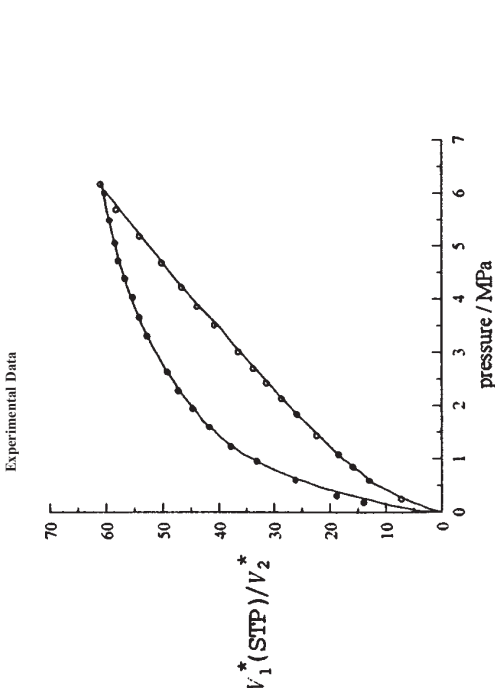


FIG. 39. Sorption and desorption isotherms of carbon dioxide in polycarbonate at 308 K. Open and filled symbols represent sorption and desorption, respectively.

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
Gas sorption measurements were made with a pressure decay cell that has been used at pressures up to 30 atm. ^{1,2} With slight modification, this design was used to make sorption measurements up to 68 atm.	CO ₂ : Linde, Inc., purity 99.99%. PC: General Electric Co. (commercial grade film), density 1.200±0.001 g/cm ³ .
Estimated Error:	References:
No information given.	¹ W. J. Koros, Ph.D. dissertation, University of Texas at Austin, Austin, TX, 1977. ² W. J. Koros and D. R. Paul, J. Membr. Sci. 5 , 63 (1978).

TABLE 4. Sorption and desorption isotherms of carbon dioxide in polycarbonate film at 318 K

First series**			Second series		Intermediate sorption***	
Pressure/MPa	Solubility (V_1^s (STP)/ V_2^s)	Pressure/MPa	Solubility (V_1^s (STP)/ V_2^s)	Pressure/MPa	Solubility (V_1^s (STP)/ V_2^s)	Solubility (V_1^s (STP)/ V_2^s)
Sorption						
0.79	11.62	0.14	4.98	0.56	15.58	
1.53	18.35	0.38	9.52	1.06	20.44	
2.95	28.96	0.57	12.83	1.61	24.93	
5.00	40.32	0.92	15.84	2.41	29.52	
		1.12	18.84	3.36	34.05	
Desorption						
0.44	13.12	1.54	22.71	4.47	37.82	
1.16	23.67	2.03	25.66	4.91	40.08	
2.20	32.10	2.98	30.49	—	—	
3.51	37.35	4.91	38.86	—	—	
Desorption						
—	—	0.09	3.99	—	—	
—	—	0.26	9.81	—	—	
—	—	0.56	15.58	—	—	
—	—	0.80	19.65	—	—	
—	—	1.71	28.99	—	—	
—	—	2.93	34.92	—	—	
—	—	4.08	38.17	—	—	

*Experiments for descending scanning isotherm.

**Series of experiments on "as received" film.

***Experiments for ascending scanning isotherm.

Method/Apparatus/Procedure		Auxiliary Information	
Sorption isotherms for gases in the polymer were obtained gravimetrically using a Cahn model 2000 electrobalance. Details of this apparatus are described in Ref. 1.		Source and Purity of Materials:	
		CO ₂ ; purity 99.99%.	
		PC (Bisphenol A polycarbonate) film (thickness 75 μ m), rod (diameter 3 mm); densities at 298 K 1.194 g/cm ³ ("as received") and 1.192 g/cm ³ (after CO ₂ exposure); glass transition temperature 417 K.	
		Estimated Error:	
		No information given.	
		References:	
		Y. Kamiya, K. Mizoguchi, Y. Naito, and T. Hirose, J. Polym. Sci., Polym. Phys. Ed. 24 , 535 (1986).	

TABLE 2. Sorption and desorption isotherms of carbon dioxide in polycarbonate film at 308 K, second and third series

Second series				Third series			
Pressure/MPa	Solubility (V_1^s (STP)/ V_2^s)	Pressure/MPa	Desorption (V_1^s (STP)/ V_2^s)	Pressure/MPa	Sorption (V_1^s (STP)/ V_2^s)	Pressure/MPa	Desorption (V_1^s (STP)/ V_2^s)
0.17	6.64	0.17	5.63	0.04	3.74	0.12	5.77
0.29	9.96	0.23	10.25	0.25	8.66	0.13	7.50
0.36	11.55	0.27	12.27	0.43	11.99	0.16	8.51
0.49	14.44	0.39	16.17	0.65	15.75	0.30	12.85
0.57	15.46	0.59	20.22	0.87	19.22	0.43	16.89
0.78	18.50	0.77	24.41	1.21	22.99	0.75	23.83
0.96	20.96	1.04	28.47	1.54	26.76	1.06	27.89
1.15	22.99	1.32	32.23	1.91	30.38	1.92	38.46
1.44	26.18	1.76	36.58	2.42	34.16	2.43	41.52
1.78	29.37	2.23	39.49	2.90	37.36	3.47	46.05
2.05	31.83	2.87	42.55	3.43	40.42	—	—
2.35	33.87	3.34	44.31	3.90	43.33	—	—
2.67	35.76	3.90	45.63	4.32	45.37	—	—
2.98	37.36	4.37	47.10	4.79	49.72	—	—
3.49	40.42	—	—	4.76	47.99	—	—
3.96	43.33	—	—	—	—	—	—
4.40	45.95	—	—	—	—	—	—
4.82	47.99	—	—	—	—	—	—

TABLE 3. Sorption and desorption isotherms of carbon dioxide in polycarbonate film at 328 K, measured after experiments at 298 K

Sorption			Desorption		Intermediate sorption*	
Pressure/MPa	Solubility (V_1^s (STP)/ V_2^s)	Pressure/MPa	Pressure/MPa	Solubility (V_1^s (STP)/ V_2^s)	Pressure/MPa	Solubility (V_1^s (STP)/ V_2^s)
0.24	4.41	0.13	0.91	16.25	—	—
0.33	6.13	0.14	1.88	23.40	—	—
0.48	7.84	0.15	3.01	28.56	—	—
0.87	12.12	0.22	4.00	31.57	—	—
1.30	15.69	0.30	—	—	—	—
1.97	21.12	0.51	—	—	—	—
2.98	26.99	0.81	—	—	—	—
3.70	30.14	1.11	—	—	—	—
4.34	32.87	1.87	—	—	—	—
4.94	35.16	2.59	—	—	—	—
—	—	3.37	—	—	—	—
—	—	4.17	—	—	—	—

Components: (1) Carbon dioxide; CO ₂ ; [124:38-9] (2) Polycarbonate (PC); [24936-68-3] (XXI)		Original Measurements: G. K. Fleming and W. J. Koros, <i>Macromolecules</i> 23 , 1353 (1990).	
Variables: <i>T</i> /K=308 <i>p</i> /MPa=0–6.3 (0–900 psia)		Prepared By: Yu. P. Yampol'skii	

Experimental Data
The effects of conditioning (pretreatment) of the polymer by exposing it prior to sorption experiments to high pressure carbon dioxide atmosphere was studied.

TABLE 1. Dual mode sorption parameters for carbon dioxide sorption in PC at 308 K (<i>p</i> : conditioning pressure)				
<i>p</i> /psia	<i>p</i> /MPa	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_D/\text{cm}^3(\text{STP})\text{cm}^{-3}$	<i>b</i> /atm ⁻¹
Pressure-based model				
300	2.07	0.681	17.30	0.261
600	4.14	0.587	29.61	0.194
900	6.21	0.542	29.21	0.167
Fugacity-based model				
300	2.07	0.844	15.16	0.303
600	4.14	0.843	19.42	0.265
900	6.21	0.868	21.24	0.257

TABLE 2. Dual mode desorption parameters for carbon dioxide in PC at 308 K (<i>p</i> : conditioning pressure)				
Fugacity-based model				
<i>p</i> /psia	<i>p</i> /MPa	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_D/\text{cm}^3(\text{STP})\text{cm}^{-3}$	<i>b</i> /atm ⁻¹
300	2.07	0.617	21.00	0.285
600	4.14	0.254	46.59	0.125
900	6.21	0.261	59.50	0.117

The differences between sorption and desorption parameters are indicative for hysteresis phenomena.

Components: (1) Carbon dioxide; CO ₂ ; [124:38-9] (2) Polycarbonate (PC); [24936-68-3] (XXI)		Original Measurements: R. G. Wissinger and M. E. Paulaitis, <i>J. Polym. Sci., Part B: Polym. Phys.</i> 25 , 2497 (1987).	
Variables: <i>T</i> /K=308.2 <i>p</i> /MPa=0–10.2		Prepared By: Yu. P. Yampol'skii	

Experimental Data
Solubility of carbon dioxide *C*

<i>p</i> /atm	<i>C</i> /cm ³ (STP)/g polymer*
9.8	13
18	21
27	27
35	34
43	40
51	47
69	59
88	63
102	65

*Taken from a graph by the compiler.

Auxiliary Information	
Method/Apparatus/Procedure The gravimetric method was used. The polymer samples were suspended from a quartz spring. The corrections for buoyancy were introduced using CO ₂ densities up to higher pressure.	Source and Purity of Materials: PC (General Electric Co) had glass transition temperature 420 K. The purity of CO ₂ (Linde Co) was 99.99%.
Estimated Error: $\delta C/C = \pm 1\text{ cm}^3(\text{STP})/\text{g polymer}$.	

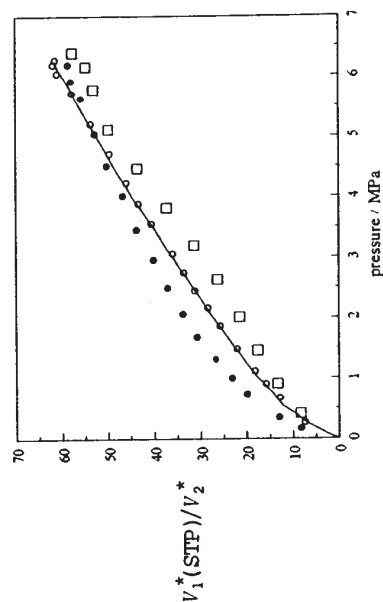


FIG. 42. Sorption isotherms of CO_2 at 308 K in CO_2 -conditioned, "as-received," and annealed PC. The annealed sample was first CO_2 -conditioned at 900 psia and then annealed at 408 K for 500 h under vacuum. (○) "as-received;" (●) 900 psia conditioned; (□) annealed.

Auxiliary Information

Method/Apparatus/Procedure

The procedures and apparatus for sorption measurements were identical with those described in Ref. 1.

Source and Purity of Materials

CO_2 : purity 99.99%
PC (Bisphenol A polycarbonate): General Electric, density 1.200 g/cm^3 .

Estimated Error:

No information given.

References:

G. K. Fleming and W. J. Koros, *Macromolecules* **19**, 2285 (1986).

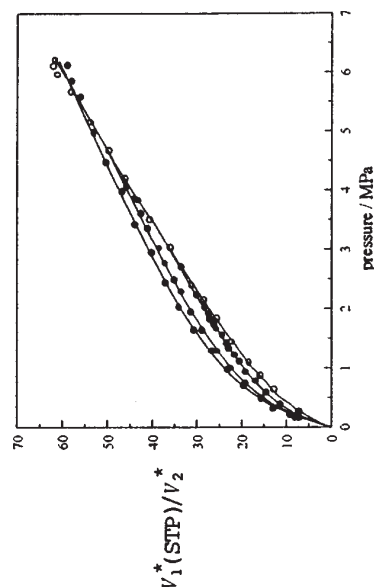


FIG. 40. Sorption isotherms of CO_2 in PC at 308 K for conditioning pressures of 300, 600, and 900 psia. (○) "as-received;" (●) CO_2 -conditioned.

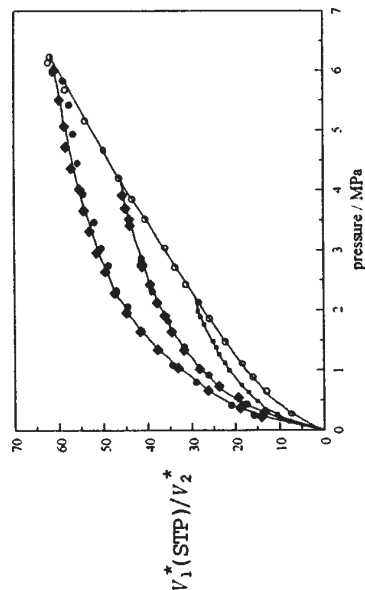


FIG. 41. Initial CO_2 sorption and desorption in PC at 308 K after conditioning pressures of 300, 600, and 900 psia. (○) "as-received;" (●) desorption.

3.18. Polycarbonate—Sulfur Dioxide

Components: (1) Sulfur dioxide; SO ₂ ; [7446-09-5] (2) Polycarbonate (PC); [24936-68-3] (XXI)		Evaluator: Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994
Critical Evaluation: The system sulfur dioxide–polycarbonate has been studied by Davis and Rooney ^{1,2} and by Frimpong <i>et al.</i> ³ In all the papers, the same commercial material Lexan (General Electric Co.) was investigated. The parameters of the dual mode sorption isotherm reported in Refs. 1 and 3 are fairly close, so the following pressure dependence of the solubility at 298 K can be recommended.		
<i>p</i> /kPa	10 30 50 101	
<i>C</i> /cm ³ (STP) cm ⁻³	11.6 ± 1.1 22.0 ± 1.6 31.2 ± 1.2 51.4 ± 2.0	
References: ¹ E. G. Davis and M. L. Rooney, <i>Kolloid Z.-Z. Polym.</i> 249 , 1043 (1971) ² E. G. Davis and M. L. Rooney, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 10 , 2325 (1972). ³ S. Frimpong, C. A. Plank, and W. L. S. Laukhaut, <i>Chem. Eng.-J.</i> 42 , 25 (1989)		

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-828] (2) Polycarbonate (PC); [24936-68-3] (XXI)		Original Measurements: E. Sada, H. Kumszawa, H. Yakushiji, Y. Bamba, K. Sakata, and S.-T. Wang, <i>Ind. Eng. Chem., Res.</i> 26 , 433 (1987).	
Variables: <i>T</i> /K = 293–313 <i>p</i> /MPa = 0.2–3.0		Prepared By: Yu. P. Yampol'skii	
Experimental Data Dual mode sorption parameters			
Gas	<i>T</i> /K	<i>k_D</i> (cm ³ (STP)/cm ³ atm)	<i>C'_{H'}</i> (cm ³ (STP)/cm ³)
CO ₂	293	0.911	23.1
	303	0.804	19.9
	313	0.702	16.0
CH ₄	293	0.335	6.40
	303	0.308	5.62
	313	0.280	4.72
Auxiliary Information			
Method/Apparatus/Procedure Equilibrium sorption was measured by the pressure decay method in the cell similar to one described in Ref. 1. The pressure changes in the cell were continuously measured by a pressure transducer.		Source and Purity of Materials: PC films were provided by Teijin Co.	
		Estimated Error: No information given.	
		References: ¹ W. J. Koros, D. R. Paul, and A. A. Rocha, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 14 , 687 (1976).	

Components: (1) Sulfur dioxide; SO ₂ ; [7446-09-5] (2) Polycarbonate; (PC); [24936-68-3] (XXI)		Original Measurements: E. G. Davis and M. L. Rooney, J. Polym. Sci., Polym. Phys. Ed. 10 , 2325 (1972).	
Variables: T/K: 298 p/kPa: 13.87; 79.46		Prepared By: A. K. Bokarev	
		Experimental Data Solubility of sulfur dioxide in polycarbonate	
p/kPa		C/cm ³ (STP) cm ⁻³	
13.87		12.8	
79.46		40.6	
Auxiliary Information			
Method/Apparatus/Procedure A modified McBain balance technique was used to measure the solubility of sulfur dioxide in the polymer.		Source and Purity of Materials: PC ("Lexan") with $\rho = 1.119$ g/cm ³ , provided by General Electric Co. (USA). $M_w = 45\ 000$; $T_g = 422$ K. Sulfur dioxide of 99.95% purity was used.	
		Estimated Error: dT/K: ± 0.5 .	

Components: (1) Sulfur dioxide; SO ₂ ; [7446-09-5] (2) Polycarbonate (PC); [24936-68-3] (XXI)		Original Measurements: E. G. Davis, M. L. Rooney, and Z.-Z. Kolloid Polym. 249 , 1043 (1971).	
Variables: T/K = 298 p/kPa = 0–100		Prepared By: A. K. Bokarev	
Experimental Data			
Dual mode sorption parameters for sulfur dioxide in polycarbonate at 298 K			
k_D /cm ³ (STP) cm ⁻³ cm Hg ⁻¹		C'_D /cm ³ (STP) cm ⁻³	b /cm Hg ⁻¹
0.522		10	0.241
Sorption isotherm of sulfur dioxide in polycarbonate at 298 K. (The original data were represented graphically)			
Pressure/kPa	Sorption ($(P_1^*/\text{STP})/P_2^*$)	Pressure/kPa	Sorption ($(P_1^*/\text{STP})/P_2^*$)
3.20	5.27	49.53	27.05
6.52	8.15	56.7	30.32
12.01	11.48	62.33	31.87
17.72	14.27	67.71	33.44
23.65	16.88	74.37	36.02
28.12	19.01	81.25	38.41
33.53	21.11	88.11	40.63
39.41	22.83	95.75	43.71
45.56	25.08	99.97	45.67
Auxiliary Information			
Method/Apparatus/Procedure A modified McBain balance technique described in Ref. 1 was used to measure the solubility of sulfur dioxide in the polymer.		Source and Purity of Materials: SO ₂ : purity 99.95%, PC: Lexan, General Electric Co., density 1.119 g/cm ³ , glass transition temperature 422 K.	
		Estimated Error: No information given.	
		References: ¹ S. Prager and A. F. Long, J. Am. Chem. Soc. 73 , 4072 (1951).	

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials
A McBain quartz spring balance was employed for sorption measurement. The apparatus is described in Ref. 2.	PC (Lexan 101): General Electric Co., glass transition temperature 421 K (DSC), melting point 496.8 K.
Estimated Error:	Estimated Error:
Relative precision in T : ± 0.1 K.	Relative precision in T : ± 0.1 K.
References:	References:
¹ C. A. Plank, W. L. S. Laukauf, and G. R. Ranade, <i>J. Appl. Polym. Sci.</i> 30 , 2695 (1985).	¹ C. A. Plank, W. L. S. Laukauf, and G. R. Ranade, <i>J. Appl. Polym. Sci.</i> 30 , 2695 (1985).
² G. R. Ranade, V. M. Nadgir, C. A. Plank, and W. L. S. Laukauf, <i>J. Appl. Polym. Sci.</i> 28 , 201 (1983).	² G. R. Ranade, V. M. Nadgir, C. A. Plank, and W. L. S. Laukauf, <i>J. Appl. Polym. Sci.</i> 28 , 201 (1983).

Original Measurements:	
(1) Sulfur dioxide; SO ₂ ; [7446-09-5]	S. Frimpong, C. A. Plank, and W. L. S. Laukauf, <i>Chem. Eng. J. (Lausanne)</i> 42 , 25 (1989).
(2) Polycarbonate (PC); [24936-68-3] (XXI)	
Variables:	Prepared By:
$T/K = 283.2\text{--}343.2$	Yu. P. Yampol'skii
$p/\text{kPa} = 0\text{--}100$	

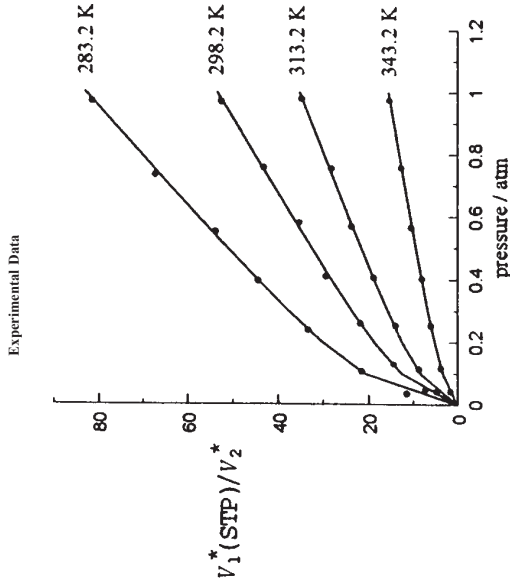


FIG. 43. Sorption isotherms of sulfur dioxide in polycarbonate.

Dual mode sorption parameters for sulfur dioxide in polycarbonate		
T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_2'/\text{cm}^3(\text{STP})\text{cm}^{-3}$
283.2	61.66	22.45
298.2	40.26	13.93
313.2	26.27	9.52
343.2	11.72	4.08

The experiment data for 298.2 and 313.2 K were correlated by the equation

$$C = 123.212 \exp[1.0772 \times 10^{-3} (RT/\text{cal mol}^{-1}) (\ln(p/\text{atm}) + (2355/(T/K) - 33)) - 10.24]$$

based on adsorption potential theory in Ref. 1.

3.19 Polycarbonate—Methane

Components:	Evaluator:
(1) Methane, CH ₄ ; [74-82-8] (2) Polycarbonate (PC); [24936-68-3] (XXI)	Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994

Critical Evaluation:

Four papers are available for the system polycarbonate—methane. Pope *et al.*¹ studied history effects on sorption isotherms (unconditioned film, the film conditioned by exposure to high pressure carbon dioxide gas and exchange-conditioned by subsequent sweeping CO₂ by methane) and showed the significant changes in the isotherm's shape caused by the pretreatment of a sample. On the other hand, the other papers²⁻³ reported the dual mode sorption parameters but did not study the effects of different pretreatment of the films on the parameters of the sorption model.
Below the solubility coefficients at 308 K are shown based on the dual mode sorption parameters¹⁻³ and by the initial slope of the isotherms.⁴

S/cm ³ (STP) cm ⁻³ atm ⁻¹	0.85	0.84	0.99	0.54	1.0
Ref.	1	2	3	4*	4**

*Unconditioned film.

**Exchange-conditioned film.

In spite of possible different film history, the solubility coefficients lie within fairly narrow limits. Accordingly, sorption isotherms are given for the samples with different pretreatment.

Solubility of methane C/(cm ³ (STP) cm ⁻³) in PC at 308 K and different pressure				
p/MPa	Ref. 1	Ref. 2	A	B
0.5	3.2	3.3	2.5	5.0
1.0	5.3	5.6	4.3	8.2
2.0	8.2	9.5	6.8	13.0
3.0	10.4	12.9	8.2	15.7

A Unconditioned film.

B Exchange-conditioned film.

These data indicate a possible range of variation of the solubility of CH₄ in polycarbonate at different pressures.

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] Nitrogen; N ₂ ; [7727-37-9] (2) Polycarbonate (PC); [24936-68-3] (XXI)		T. A. Barbari, W. J. Koros, and D. R. Paul, J. Polym. Sci., Part B: Polym. Phys. 26 , 729 (1988). W. J. Koros, Ph.D. dissertation, The University of Texas at Austin, 1977.	
Variables:		Prepared By:	
T/K: 308 p/MPa: 0–2.33		A. K. Bokarev	
Experimental Data			
Dual mode sorption parameters for polycarbonate at 308 K			
Parameter	CO ₂	CH ₄	N ₂
k_D /(cm ³ (STP)/(cm ³ atm))	0.685	0.147	0.0909
C_H /(cm ³ (STP)/(cm ³))	18.81	8.38	2.11
b /(atm ⁻¹)	0.215	0.100	0.074
Auxiliary Information			
Method/Apparatus/Procedure		Source and Purity of Materials:	
The sorption apparatus and procedures used in the present sorption experiments are the same as described earlier. ¹		Bisphenol A polycarbonate (Lexan) was obtained from the General Electric Co. M_w = 35 800. Each gas was of chromatographic quality (purity >99.99%).	
		Estimated Error: Nothing specified.	
		References: ¹ W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. 14 , 687 (1976).	

3.20. Polycarbonates—Propane and Other Gases

Components:		Original Measurements:		
(1) Propane; C ₃ H ₈ ; [74-98-6]		Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994		
(2) Polycarbonate (PC); [24936-68-3] (XXI)				
Critical Evaluation:				
Only two papers are available for this system. ^{1,2} However, they cover the same temperature (303–333 K) and pressure (0–0.1 MPa) ranges. In both cases, the polymer is probably Lexan from General Electric Co. recast from methylene dichloride. This enables a meaningful comparison of the data to be done. The parameters of sorption isotherms at 323 K reported in Refs. 1 and 2 agree within the estimated error. Hence, the following pressure dependence was calculated for propane solubility in polycarbonate.				
<i>p</i> /kPa	10	30	50	101
<i>C</i> /cm ³ (STP) cm ⁻³	0.83±0.03	1.67±0.05	2.37±0.02	4.03±0.05

References:
¹J. A. Barrie, M. J. L. Williams, and K. Munday, *Polym. Eng. Sci.* **20**, 21 (1980).
²J. A. Yavorsky and H. J. Spencer, *J. Appl. Polym. Sci.* **25**, 2109 (1980).

Components:		Original Measurements:	
(1) Methane; CH ₄ ; [74-82-8]		D. S. Pope, G. K. Fleming, and W. J. Koros, <i>Macromolecules</i> 23 , 2988 (1990).	
(2) Polycarbonate (PC); [24936-68-3] (XXI)			
Variables:		Prepared By:	
<i>T</i> /K = 308		Yu. P. Yampol'skii	
<i>p</i> /MPa = 0–6.89			

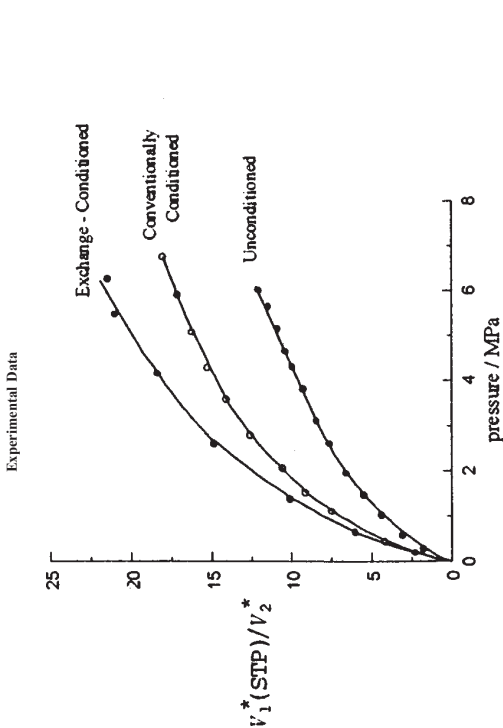


FIG. 44. Sorption isotherms of methane in polycarbonate for unconditioned, carbon dioxide conditioned and exchange conditioned samples.

Method/Apparatus/Procedure		Auxiliary Information	
Two methods of conditioning were studied. Conventionally conditioned isotherms were obtained with the samples which had been previously in contact with CO ₂ gas under pressure of 6.21 MPa for 2–3 h with consequent pumping for 2 days. Both isotherms were obtained by pressure decay method. ¹ Exchange conditioning involved exposing the samples to CO ₂ gas and then sweeping it by a CH ₄ flux with the subsequent gravimetric determination of sorption.		Source and Purity of Materials: CH ₄ : purity >99.99%. PC: General Electric Co., density 1.200 g/cm ³ , glass transition temperature 423 K.	
Estimated Error: No information given.		References: ¹ W. J. Koros and D. R. Paul, <i>J. Polym. Sci.: Polym. Phys. Ed.</i> 14 , 1903 (1976).	

Components:	
(1) Propane; C ₃ H ₈ ; [74-98-6]	
(2) Polycarbonate (PC); [24936-68-3] (XXI)	
Original Measurements:	
J. A. Barrie, M. J. L. Williams, and K. Munday, Polym. Eng. Sci. 20, 21 (1980).	
Variables:	
T/K = 303–333	
p/kPa = 0–8.0	
Prepared By:	
Yu. P. Yampol'skii	

Experimental Data				
Dual mode sorption parameters, solubility coefficients S , ($S = k_D + C_H/p$), and errors (%) for propane in polycarbonate				
T/K	$10^2 k_D/p$ cm ³ (STP) cm ⁻³ cm Hg ⁻¹	C_H/p cm ³ (STP) cm ⁻³	b /cm Hg ⁻¹	S/p cm ³ (STP) cm ⁻³ cm Hg ⁻¹
303	6.07 (±7%)	1.67 (±11%)	0.311 (±30%)	0.579 (±18%)
313	5.01 (±2%)	1.25 (±4%)	0.254 (±9%)	0.368 (±5%)
323	4.01 (±8%)	1.02 (±21%)	0.167 (±43%)	0.210 (±19%)
333	2.55 (±17%)	1.22 (±31%)	0.094 (±50%)	0.140 (±19%)

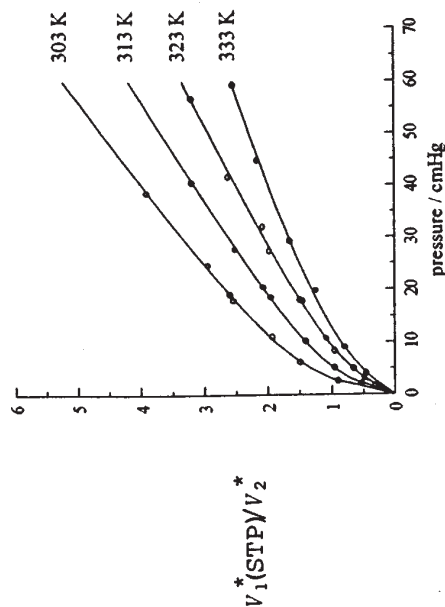


Fig. 45. Sorption isotherms for propane in PC.

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
Sorption isotherms were measured using an electronic vacuum microbalance Sartorius, model 4102 as described in Ref. 1.	PC films: cast from methylene chloride; glass transition temperature 420 K.
	Estimated Error:
	See table.
	References:
	J. A. Barrie and D. Machin, J. Makromol. Sci.-Phys. B, 3, 645 (1969).

Components:	
(1) Propane; C ₃ H ₈ ; [74-98-6]	
(2) Polycarbonate (PC); [24936-68-3] (XXI)	
Original Measurements:	
J. A. Yaworsky and H. J. Spencer, J. Appl. Polym. Sci. 25, 2109 (1980).	
Variables:	
T/K: 321.7; 323	
p/kPa: Not stated	
Prepared By:	
A. K. Bokarev	

Experimental Data	
TABLE 1. Thermal treatment of films	
Sample	Thermal treatment
PC-1	3 days in vacuum at 313–323 K
PC-A1	Treatment of PC-1 plus 49 h at 408 K in vacuum
PC-A2	Treatment of PC-A1 plus 51 h at 408 K in vacuum
PC-10	3 days in vacuum at 353 K

TABLE 2. Dual mode sorption parameters for the propane–polycarbonate system			
Sample	T/K	k_D 10 ² /cm ³ (STP) cm ⁻³ cm Hg ⁻¹	b /(cm Hg) ⁻¹
PC-1	323.0	4.5	0.23
	321.7		0.08
PC-A1	323.0	4.5	0.22
	323.0		0.22

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
The volumetric sorption procedure was used to determine the sorption equilibrium properties.	The bisphenol-A polycarbonate, Lexan, was supplied by the General Electric Co. $M_n = 12\,500$, $M_w = 35\,300$. Films were cast on mercury at about 307–309 K from 5% to 10% solutions in methylene chloride. The thermal treatment of the films is summarized in Table 1. The T_g for these films were in the range 421–428 K.
	Propane used was 99.5% pure and was subjected to freeze–pump–thaw cycles.
	Estimated Error:
	No estimates possible.

Components:	
(1) Nitrogen, N ₂ ; [7727-37-9]	
(2) Polycarbonate (PC); [24936-68-3] (XXI)	
Original Measurements:	
W. J. Koros, and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).	
Variables:	
7/K=308	
p/MPa=0.1-2.6	
Prepared By:	
A. K. Bokarev	

Experimental Data			
Sorption isotherm of nitrogen in polycarbonate at 308 K. (The original data were represented graphically)			
Pressure/MPa	Sorption ($V^*(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V^*(\text{STP})/V_2^*$)
0.08	0.18	1.37	2.14
0.11	0.21	1.44	2.21
0.14	0.27	1.63	2.47
0.19	0.42	1.82	2.72
0.30	0.58	2.03	2.96
0.40	0.69	2.25	3.18
0.60	1.03	2.29	3.24
0.75	1.34	2.49	3.50
0.90	1.58	2.60	3.57
1.14	1.85	2.59	3.63
1.29	2.01	—	—

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
Measurement of gas solubility was performed using a pressure decay method with a dual-volume dual transducers system (see also Ref. 1). In order to achieve superior precision the ratio of the two working volumes should be close to 1. It was shown that the reduction of this ratio from 9.7 to 1.45 resulted in much less scatter.	N ₂ ; purity>99% PC (Bisphenol A polycarbonate); Lexan, General Electric Co., $M_w=35\,800$.
Estimated Error:	References:
Relative precision of solubilities: $\pm 0.07\text{ cm}^3(\text{STP})/\text{cm}^3$ polymer.	¹ W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. 14 , 687 (1976).

Components:	
(1) Helium; He; [7440-59-7] Argon; Ar; [7440-37-1] Nitrogen; N ₂ ; [7727-37-9] Methane; CH ₄ ; [74-82-8]	
(2) Polycarbonate (PC); [24936-68-3] (XXI)	
Original Measurements:	
W. J. Koros, A. H. Chan, and D. R. Paul, J. Membr. Sci. 2 , 165 (1977).	
Variables:	
7/K=308	
p/MPa=0-2.53	
Prepared By:	
A. K. Bokarev	

Experimental Data		
Dual mode sorption parameters for various gases in polycarbonate at 308 K		
Gas	$k_D/\text{cm}^3(\text{STP})\text{ cm}^{-3}\text{ atm}^{-1}$	b/atm^{-1}
Ar	0.1534	0.063
He	0.0145	0.0121
CH ₄	0.1473	0.0841
N ₂	0.0909	0.0564

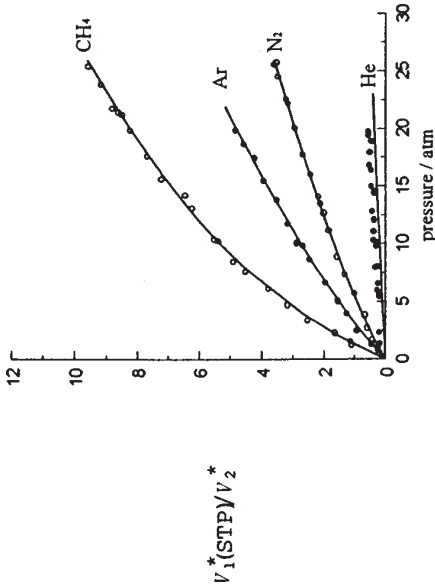


FIG. 46. Sorption isotherms of various gases in polycarbonate at 308 K.

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
The sorption apparatus and procedure used in the present sorption experiments are the same as described earlier. ¹	Gases; purity >99% PC (Bisphenol A polycarbonate, Lexan); General Electric Co., $M_w=35\,800$.
Estimated Error:	References:
No information given.	¹ W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. 14 , 687 (1976).

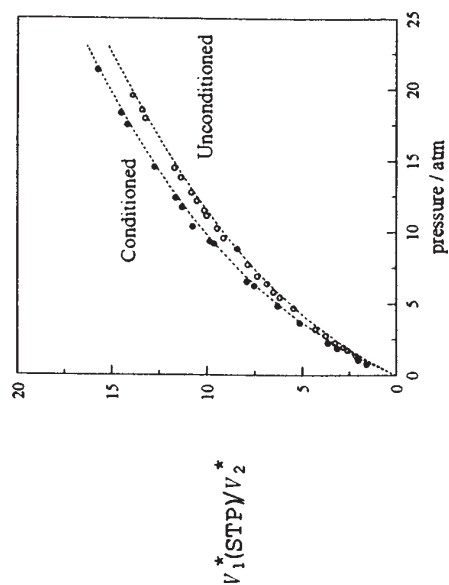


FIG. 47. Comparison of sorption isotherms of methane at 308 K in TMPC for unconditioned and conditioned films.

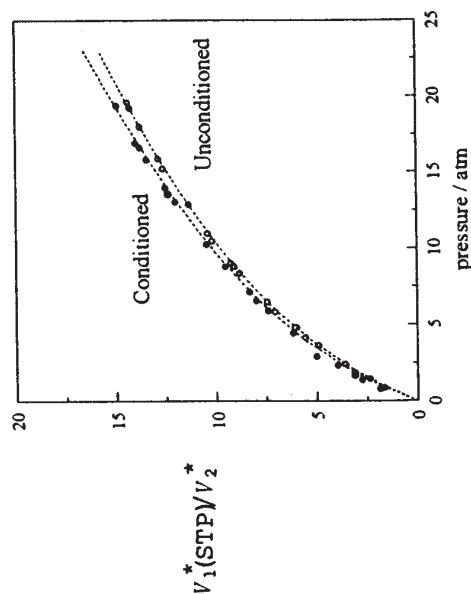


FIG. 48. Comparison of sorption isotherms of methane at 308 K in TCPC for unconditioned and conditioned films.

Components:		Original Measurements:			
(1) Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]		N. Muruganandam, W. J. Koros, and D. R. Paul, J. Polym. Sci., Part B: Polym. Phys. 25 , 1999 (1987).			
(2) Polycarbonate (PC); [24936-68-3] (XXI)					
Tetramethylpolycarbonate (TMPC); [38797-88-5] (XXII)					
Tetrachloropolycarbonate (TCPC); [26913-25-7] (XXIV)					
Tetra bromopolycarbonate (TBPC); [28774-93-8] (XXV)					
Variables:		Prepared By:			
T/K = 308–358		A. K. Bokarev			
p/MPa = 0.1–2.0 (1–20 atm)					
Experimental Data					
Dual mode sorption parameters for various gases in the polycarbonates at 308 K					
Polymer	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_D/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}	Conditions	
CO ₂	PC	0.685	18.81	0.262	Conditioned
	TMPC	1.011	27.66	0.283	Conditioned
	TCPC	0.860	26.35	0.316	Conditioned
	TBPC	0.840	24.59	0.395	Conditioned
	TBPC*	0.179	17.77	0.128	Conditioned
CH ₄	TMPC	0.281	12.29	0.106	Unconditioned
	TCPC	0.289	12.22	0.128	Unconditioned
	TBPC	0.275	12.37	0.141	Unconditioned
	PC	0.147	8.38	0.084	Conditioned
N ₂	TMPC	0.244	15.34	0.100	Conditioned
	TCPC	0.340	11.26	0.150	Conditioned
	TBPC	0.209	15.05	0.120	Conditioned
	PC	0.091	2.11	0.056	Unconditioned
TCPC	TMPC	0.102	8.43	0.032	Unconditioned
	TCPC	0.145	6.22	0.046	Unconditioned
	TBPC	0.148	4.63	0.061	Unconditioned
*At 358 K.					

* At 358 K.

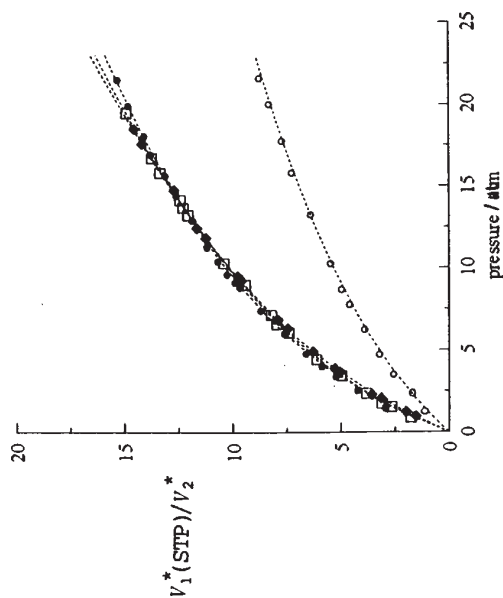


FIG. 51. Sorption isotherms of methane at 308 K in polycarbonates conditioned by prior CO_2 exposure. (○) PC; (◆) TMPC; (□) TBPC; (●) TBPC.

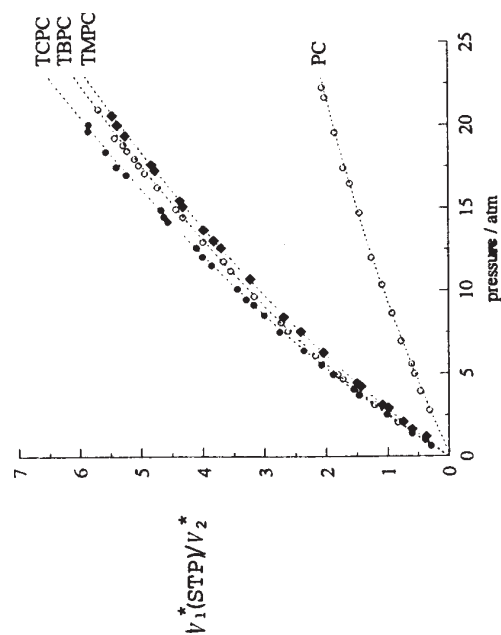


FIG. 52. Sorption isotherms of nitrogen at 308 K in polycarbonates without prior CO_2 exposure.

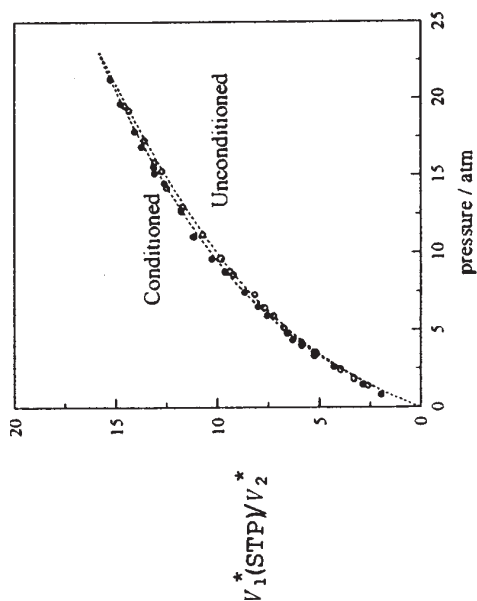


FIG. 49. Comparison of sorption isotherms of methane at 308 K in TBPC for unconditioned and conditioned films.

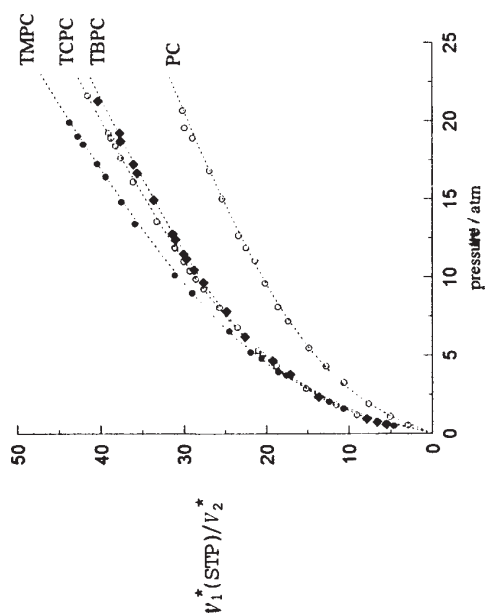


FIG. 50. Sorption isotherms of carbon dioxide at 308 K in polycarbonates conditioned by prior CO_2 exposure.

Auxiliary Information

Method/Apparatus/Procedure Sorption was measured using the method described in Ref. 1 Sorption data were collected using films never exposed to CO ₂ (unconditioned films) and films that had been exposed to CO ₂ at 20 atm for 24 h.	
Source and Purity of Materials: Gases: purity 99% PC: General Electric Co., density 1.200 g/cm ³ TMPC: Bayer AG, density 1.083 g/cm ³ TBPC: Dow Chemical Co., density 1.953 g/cm ³ Polymer <i>M_w</i> <i>h</i> /(dl/g)	
PC	35 800
TMPC	—
TCPC	0.530
TBPC	0.534
	0.417
	<i>T_g</i> /K
	423
	466
	503
	536

References: ¹ W. J. Koros, A. H. Chan, and D. R. Paul, J. Membr. Sci. 2 , 165 (1977).	
--	--

Components: (1) Methane; CH ₄ ; [74-82-8] (2) Tetramethylpolycarbonate (TMPC); [38797-88-5] (XXII)		Original Measurements: D. S. Pope, G. K. Fleming, and W. J. Koros, Macromolecules 23 , 2988 (1990).	
Variables: <i>T</i> /K=308 <i>p</i> /MPa=0–5		Prepared By: Yu. P. Yampol'skii	
Experimental Data Sorption isotherms of methane at 308 K in unconditioned, conventionally conditioned, and exchange-conditioned samples of TMPC. (The original data were represented graphically)			
Unconditioned		Conventionally conditioned	
Exchange-conditioned			
Pressure/MPa	Sorption/ (<i>p</i> ₁ [*] (STP)/ <i>p</i> ₂ [*])	Pressure/MPa	Sorption/ (<i>p</i> ₁ [*] (STP)/ <i>p</i> ₂ [*])
0.42	4.82	0.72	9.44
0.93	8.25	1.77	15.67
1.49	11.04	2.89	20.73
2.05	13.20	3.83	24.11
2.60	15.15	4.87	27.17
3.12	16.79	—	—
3.72	18.52	—	—
4.31	20.04	—	—
4.94	21.45	—	—
		0.52	9.25
		1.07	14.90
		1.77	20.21
		2.47	24.26
		3.06	26.84
		3.80	29.83
		4.48	32.29
		—	—
		—	—

Auxiliary Information	
Method/Apparatus/Procedure Two methods of conditioning were studied. Conventionally conditioned isotherms were obtained with the samples which had been previously in contact with CO ₂ gas under pressure of 6.21 MPa for 2–3 h with consequent pumping for 2 days. Exchange conditioning involves exposing samples to CO ₂ gas and then sweeping it with methane flux. For exchange conditioning runs a gravimetric technique was used, in two other types of experiments a pressure decay method was applied. ¹	
Source and Purity of Materials: CH ₄ : purity 99.99% TMPC: Dow Chemical Co., density 1.08 g/cm ³ , glass transition temperature 476 K.	
Estimated Error: No information given.	
References: ¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).	

Auxiliary Information	
Method/Apparatus/Procedure	Pressure decay sorption cell and procedure used are described in Ref. 1.
Source and Purity of Materials	CO ₂ : Linde Inc., purity 99.99% TMPC: Bayer AG, density 1.083 g/cm ³ , glass transition temperature 475 K, <i>d</i> spacing 6.0 Å (WAXD).
Estimated Error:	No information given.
References:	¹ G. K. Fleming and W. J. Koros, <i>Macromolecules</i> 19 , 2285 (1986).

Components:		Original Measurements:	
(1) Carbon dioxide, CO ₂ ; [124-38-9]		G. K. Fleming and W. J. Koros, <i>J. Polym. Sci., Part B: Polym. Phys.</i> 28 , 1137 (1990).	
(2) Tetramethylpolycarbonate (TMPC); [38797-88-5] (XXII)			
Variables:		Prepared By:	
$T/K=308$		Yu. P. Yampol'skii	
$p/\text{MPa}=0-6.2$ (0-62 atm)			
Experimental Data			
Sorption isotherm of carbon dioxide in TMPC on a fugacity basis at 308 K. (The original data were represented graphically)			
Fugacity/MPa	Sorption ($f_1^*/\text{STP}/f_2^*$)	Fugacity/MPa	Sorption ($f_1^*/\text{STP}/f_2^*$)
0.21	13.53	3.03	68.80
0.60	26.09	3.27	71.90
0.98	35.48	3.47	75.91
1.33	42.17	3.72	80.36
1.65	48.41	3.91	84.60
1.95	52.61	4.13	88.39
2.26	57.50	4.30	92.86
2.51	61.95	4.47	93.49
2.77	64.81	—	—

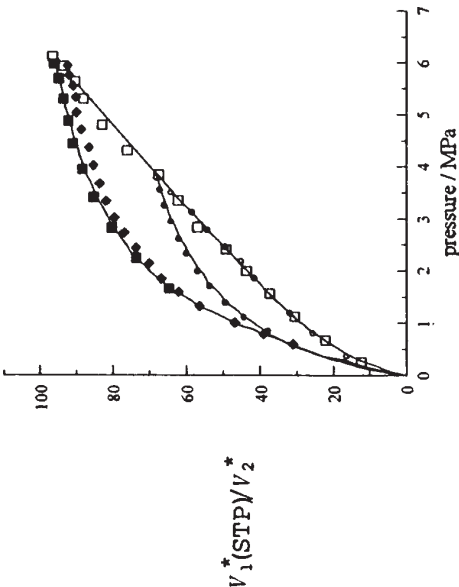


Fig. 53. Sorption (open points) and desorption (filled points) isotherms of carbon dioxide in TMPC for maximum conditioning pressures of 37.95 (○) and 62.1 (●) atm. (□) first, (■) second desorption

Components:	Original Measurements:
(1) Helium; He; [7440-59-7] Nitrogen; N; [7727-37-9] Oxygen; O ₂ ; [7782-44-7] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Tetrabromopolycarbonate (TBPC); [2874-93-8] (XXV)	M. W. Hellums, W. J. Koros, G. R. Husk, and D. R. Paul, J. Membr. Sci. 46 , 93 (1989).
Variables:	Prepared By:
$T/K = 308$ $p/\text{MPa} = 0-6.06$	Yu. P. Yampol'skii

TABLE I. Sorption and desorption isotherms of carbon dioxide in HFPC at 308 K. (The original data were represented graphically)

Solubility of gases $C/(\text{cm}^3(\text{STP})/\text{cm}^3)$ in TBPC at different pressures*					
Gas	p/atm	C	Gas	p/atm	C
He	7.2	0.40	CH ₄	3.0	4.4
	12.6	0.55		7.2	7.6
	18.4	0.80		12.0	10.6
	25.5	1.05		17.3	12.8
N ₂	3.6	1.4	CO ₂	23.0	14.7
	7.4	2.6		5.4	19
	11.7	3.6		9.5	25
	17.3	4.8		15.0	32
O ₂	20.0	5.4		20.7	37.5
	1.0	0.6			
	2.35	1.2			
	5.0	2.6			
	8.2	3.95			
	12.5	5.5			

TABLE 2. Sorption isotherms of carbon dioxide in HFPC at 308 K on fugacity basis. (The original data were represented graphically)

*Taken from the graphs by compiler.	Auxiliary Information	
	Method/Apparatus/Procedure Pressure decay apparatus was used in sorption measurement (see Ref. 1).	Source and Purity of Materials: TBPC was prepared from tetrabromo-bisphenol A using standard interfacial polymerization technique. It had the following characteristics: $\rho = 1.083 \text{ g/cc}$, $T_g = 466 \text{ K}$ Estimated Error: No information given.
	References: *W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).	

*Taken from the graphs by compiler.

J. Phys. Chem. Ref. Data, Vol. 28, No. 5, 1999

TABLE 3. Dual mode sorption parameters for carbon dioxide in HPFC at 308 K

Type	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_{H_2}/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
Pressure	1.09	28.05	0.255
Fugacity	1.33	25.48	0.275

Auxiliary Information	
Method/Apparatus/Procedure	Pressure decay sorption cell and procedure were described in Ref. 1.
Source and Purity of Materials	HPFC: Dow Chemical Co., density 1.478 g/cm ³ , glass transition temperature 445 K, d spacing 5.8 Å (WAXD method). The polymer was conditioned before measurement of sorption isotherms by exposing to CO ₂ at 33 atm.
Estimated Error:	No information given.
References:	¹ G. K. Fleming and W. J. Koros, <i>Macromolecules</i> 19 , 2285 (1986).

Components:		Original Measurements:			
(1) Methane; CH ₄ ; [74-82-8]		D. S. Pope, G. K. Fleming, and W. J. Koros, <i>Macromolecules</i> 23 , 2988 (1990).			
Tetramethylhexafluoropolycarbonate (TMHFPC); [125431-72-3] (XXIII)					
Variables:		Prepared By:			
T/K = 308		Yu. P. Yampol'skii			
p/MPa = 0–3					
Experimental Data					
Sorption isotherms of methane at 308 K in unconditioned, conventionally conditioned, and exchange-conditioned samples of TMHFPC. (The original data were represented graphically)					
Unconditioned		Conventionally conditioned		Exchange-conditioned	
Pressure/MPa	Sorption (V_1^*/V_2^*)	Pressure/MPa	Sorption (V_1^*/V_2^*)	Pressure/MPa	Sorption (V_1^*/V_2^*)
0.20	3.51	0.70	11.09	0.34	7.02
0.60	8.50	1.41	17.75	0.71	12.18
1.05	12.66	2.12	22.64	1.23	17.93
1.61	16.39	2.72	26.45	1.75	22.42
2.23	20.03	—	—	2.23	25.65
2.94	23.33	—	—	2.69	28.38
Auxiliary Information					
Method/Apparatus/Procedure			Source and Purity of Materials:		
Two methods of conditioning were studied. Conventionally conditioned isotherms were obtained with the samples which had been previously in contact with CO ₂ gas under pressure of 6.2 MPa for 2–3 h with consequent pumping for 2 days.			CH ₄ : purity >99.99% TMHFPC: synthesized, density 1.200 g/cm ³ , glass transition temperature 481 K.		
Exchange conditioning involves exposing samples to CO ₂ gas and then sweeping it with a methane flux. For exchange conditioning runs a gravimetric technique was used. In two other types of experiments a pressure decay method was applied. ¹			Estimated Error: No information given.		
			References: ¹ W. J. Koros and D. R. Paul, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 14 , 1903 (1976).		

Components:		Original Measurements:	
(1) Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Bisphenol norbornene polycarbonate (NBPC) (XXVIII)		J. S. McHattie, W. J. Koros, and D. R. Paul, J. Polym. Sci.: Part B: Polym. Phys. 29 , 731 (1991).	
Variables:		Prepared By:	
T/K = 308 p/MPa = 0–2.0 (0–20 atm)		Yu. P. Yampol'skii	
Experimental Data			
Dual mode sorption parameters at 308 K			
Gas	k_D /cm ³ (STP)/cm ³ atm	C'_f /cm ³ (STP)/cm ³	b /atm ⁻¹
N ₂	0.166	3.15	0.071
CO ₂	0.978	19.8	0.306
Method/Apparatus/Procedure		Auxiliary Information	
The measurement of sorption was carried out using a pressure decay sorption cell as described in Ref. 1. The films were cast from methylene dichloride solution.		Source and Purity of Materials: NBPC (Eastman Kodak Co) had a density 1.20 g/cc, the glass transition temperature of 308 K. The intrinsic viscosity in methylene dichloride solution was 0.55 dl/g. Purity of gases not indicated.	
		Estimated Error: No information given.	
		References: ¹ W. J. Koros, A. H. Chan, and D. R. Paul, J. Membr. Sci. 2 , 165 (1977).	

Components:		Original Measurements:		
(1) Helium; He; [7440-59-7] Nitrogen; N ₂ ; [7727-37-9] Oxygen; O ₂ ; [7782-44-7] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Tetrabromohexafluoropolycarbonate (TBHPPC); [126430-95-3] (XXVII)		M. W. Hellums, W. J. Koros, G. R. Husk, and D. R. Paul, J. Membr. Sci. 46 , 93 (1989).		
Variables:		Prepared By:		
T/K = 308 p/MPa = 0–6.0		Yu. P. Yampol'skii		
Experimental Data				
Solubility of gases C/cm ³ (STP)/cm ³ in TBPC at different pressures*				
Gas	p/atm	C	p/atm	C
He	2.4	0.2	3.0	5.3
	8.7	0.6	9.0	11.5
	15.6	1.05	13.5	14.8
	23.0	1.5	18	17.3
	35.0	2.35	22	19
N ₂			26.5	21.5
			32.5	23.5
	1.0	0.6	3.5	22
	3.0	2.0	8.0	36
	6.0	3.4	15.5	47
O ₂	9.0	4.9	22	60
	14.0	6.8	28	74
			39	100
			52	116
	0.6	0.4		
	1.6	1.3		
	2.4	1.9		
	4.1	3.1		
	6.3	4.65		

*Taken from the graphs by compiler.

Method/Apparatus/Procedure		Auxiliary Information	
Pressure decay apparatus was used in sorption measurement (see Ref. 1).		Source and Purity of Materials: TBHPPC was prepared from tetrabromohexafluorobisphenol A using standard interfacial polymerization technique. It had the following characteristics: $\rho = 1.987$ g/cc, $T_g = 528$ K.	
		Estimated Error: No information given.	
		References: ¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Bisphenol chloral polycarbonate (BCPC); [31546-39-1] (XXX)		Original Measurements: J. S. McHattie, W. J. Koros, and D. R. Paul, J. Polym. Sci., Part B: Polym. Phys. 29 , 731 (1991).	
Variables: T/K=308 p/MPa=0–2.0 (0–20 atm)		Prepared By: Yu. P. Yampol'skii	
Experimental Data Dual mode sorption parameters at 308 K			
Gas	k_D /cm ³ (STP)/cm ³ atm	C_H /cm ³ (STP)/cm ³	b /atm ^{−1}
CO ₂	0.718	14.9	0.271
CH ₄	0.130	6.64	0.088
Auxiliary Information			
Method/Apparatus/Procedure The measurement of sorption was carried out using a pressure decay apparatus (see Ref. 1). The films were cast from methylene dichloride solution.		Source and Purity of Materials: PCPC from General Electric Co had a density 1.39 g/cc and glass transition temperature of 437 K. Its intrinsic viscosity in chloroform was 0.66 dl/g. Purity of gases not indicated.	
Estimated Error: No information given.		References: ¹ W. J. Koros, A. H. Chan, and D. R. Paul, J. Membr. Sci. 2 , 165 (1977).	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Bisphenol-Z-polycarbonate (PCZ); [25135-52-8] (XXIX)		Original Measurements: J. S. McHattie, W. J. Koros, and D. R. Paul, J. Polym. Sci., Part B: Polym. Phys. 29 , 731 (1991).	
Variables: T/K=308 p/MPa=0–2.0 (0–20 atm)		Prepared By: Yu. P. Yampol'skii	
Experimental Data Dual mode sorption parameters at 308 K			
Gas	k_D /cm ³ (STP)/cm ³ atm	C_H /cm ³ (STP)/cm ³	b /atm ^{−1}
CO ₂	0.545	18.5	0.172
CH ₄	0.223	5.65	0.106
Auxiliary Information			
Method/Apparatus/Procedure The measurement of sorption was carried out using a pressure decay apparatus (see Ref. 1). The films were cast from methylene dichloride solution.		Source and Purity of Materials: PCZ (Mitsubishi Gas Chemical Co) had a density 1.20 g/cc and glass transition temperature of 458 K. Its intrinsic viscosity in chloroform was 0.49 dl/g. Purity of gases not indicated.	
Estimated Error: No information given.		References: ¹ W. J. Koros, A. H. Chan, and D. R. Paul, J. Membr. Sci. 2 , 165 (1977).	

3.21. Poly(Aryl-bis-isopropylidene Ether Ketone)—Carbon Dioxide and Methane

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]		J. M. Mohr and D. R. Paul, Polymer 32 , 2387 (1991).	
(2) Poly(aryl-bis-isopropylidene ether ketone) (PAEK-6H6F); [122165-96-2] (XXXII)			
Poly(aryl-hexafluoroisopropylidene-isopropylidene ether ketone) (PAEK-6F6H); [122165-95-1] (XXXIII)			
Variables:		Prepared By:	
T/K=308		V. I. Bondar	
p/MPa=0–2.0			
Experimental Data			
Dual mode sorption parameters for carbon dioxide in polymers at 308 K			
Polymer	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_D/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
6H6F	0.840	10.90	0.373
6F6H	0.756	12.70	0.331

Pressure (MPa)	PAEK-6H6F (V_1^*/V_2^*)	PAEK-6F6H (V_1^*/V_2^*)
0.0	0.0	0.0
0.2	4.0	4.0
0.4	7.0	7.0
0.6	9.5	9.5
0.8	11.5	11.5
1.0	13.0	13.0
1.2	14.5	14.5
1.4	16.0	16.0
1.6	17.5	17.5
1.8	19.0	19.0
2.0	20.5	20.5
2.2	22.0	22.0
2.4	23.5	23.5
2.5	24.0	24.0

Fig. 54. Sorption isotherms of carbon dioxide in PAEK-6H6F (○) and PAEK-6F6H (●).

Method/Apparatus/Procedure		Source and Purity of Materials:	
A pressure decay method was used as described in Ref. 1.		PAEK-6H6F, PAEK-6F6H: synthesized by the procedure described in Ref. 2. 6H6F: density 1.287 g/cm ³ , T_g =452 K, 6F6H: density 1.284 g/cm ³ , T_g =454 K.	
Auxiliary Information			
References:			
¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).			
² G. L. Tullios, P. E. Cassidy, and A. K. St. Clair, Proc. ACS, Div. Polym. Materials 60 , 310 (1989).			

J. Phys. Chem. Ref. Data, Vol. 28, No. 5, 1999

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ [124-38-9]		J. M. Mohr and D. R. Paul, Polymer 32, 2387 (1991).	
(2) Poly(aryl-bisopropylidene-hexafluoro-isopropylidene ether ketone) (PAEK-6H6F); [122165-96-2] (XXXXI)			
Poly(aryl-hexafluoroisopropylidene-isopropylidene ether ketone) (PAEK-6F6H); [122165-95-1] (XXXXIII)			
Variables:		Prepared By:	
T/K = 308		V. I. Bondar	
p/MPa = 0–2.0			
Experimental Data			
Dual mode sorption parameters for carbon dioxide in polymers at 308 K			
Polymer	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_D/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
6H6F	0.840	10.90	0.373
6F6H	0.756	12.70	0.331

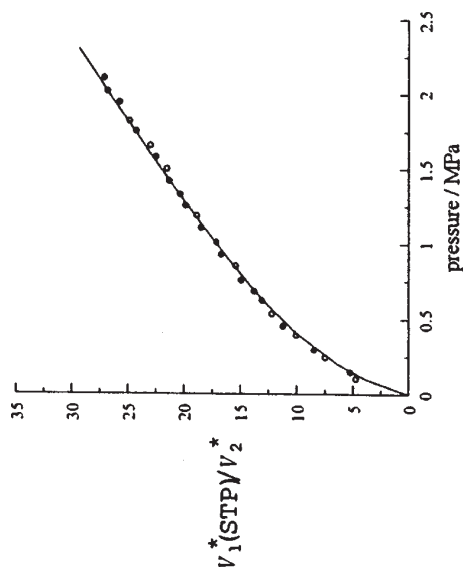


FIG. 54. Sorption isotherms of carbon dioxide in PAEK-6H6F (○) and PAEK-6F6H (●).

Method/Apparatus/Procedure		Auxiliary Information	
A pressure decay method was used as described in Ref. 1.		Source and Purity of Materials:	
		PAEK-6H6F, PAEK-6F6H: synthesized by the procedure described in Ref. 2. 6H6F: density 1.287 g/cm ³ , T_g = 452 K. 6F6H: density 1.284 g/cm ³ , T_g = 454 K.	
Estimated Error		References:	
No information given.		¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14, 1903 (1976).	
		² G. L. Tullios, P. E. Cassidy, and A. K. St. Clair, Proc. ACS, Div. Polym. Materials 60, 310 (1989).	

3.22. Polyarylate—Various Gases

Components:		Original Measurements:	
(1) Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]		T. A. Barbari, W. J. Koros, and D. R. Paul, J. Polym. Sci., Part B: Polym. Phys. 26 , 729 (1988).	
(2) Polyarylate Ardel (PA); [25639-68-3](LXX)			
Variables:		Prepared By:	
T/K=308		A. K. Bokarev	
p/MPa=0–2.33			

Experimental Data			
TABLE 1. Dual mode sorption parameters for gases in polyarylate at 308 K			
Gas	k_D /cm ³ (STP)cm ⁻³ atm ⁻¹	C'_D /cm ³ (STP)cm ⁻³	b /atm ⁻¹
CO ₂	0.631	22.69	0.215
CH ₄	0.181	6.45	0.100
N ₂	0.081	1.22	0.074

TABLE 2. Sorption isotherms of various gases in polyarylate at 308 K. (The original data were represented graphically)					
CO ₂		CH ₄		N ₂	
Pressure/MPa	Sorption ($V_1^s(STP)/V_2^s$)	Pressure/MPa	Sorption ($V_1^s(STP)/V_2^s$)	Pressure/MPa	Sorption ($V_1^s(STP)/V_2^s$)
0.21	7.30	0.26	1.65	0.19	0.30
0.27	9.17	0.32	1.98	0.23	0.37
0.31	10.11	0.36	2.22	0.30	0.44
0.35	11.14	0.42	2.53	0.33	0.54
0.60	15.81	0.62	3.39	0.40	0.54
0.65	16.74	0.70	3.82	0.44	0.63
0.73	18.33	0.78	4.09	0.59	0.78
0.97	21.03	0.85	4.44	0.68	0.89
1.04	21.96	1.04	4.97	0.70	0.98
1.13	23.27	1.13	5.40	0.85	1.13
1.38	25.49	1.21	5.66	0.92	1.20
1.46	26.52	1.29	5.95	1.03	1.30
1.58	27.72	1.48	6.38	1.11	1.39
1.84	29.38	1.56	6.71	1.19	1.52
1.91	29.94	1.65	6.97	1.29	1.61
2.30	33.08	1.74	7.23	1.40	1.70
2.33	33.36	1.92	7.66	1.49	1.74
—	—	2.02	7.92	1.57	1.87
—	—	2.12	8.16	1.64	1.98
—	—	2.18	8.31	1.75	2.04
—	—	—	—	1.82	2.15
—	—	—	—	1.94	2.19
—	—	—	—	2.04	2.26
—	—	—	—	2.22	2.46

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]		J. M. Mohr and D. R. Paul, Polymer 32 , 2387 (1991).	
(2) Poly(ary-bis(hexafluoroisopropylidene ether ketone) (PAEK-12F); [122165-97-3] (XXXIV)			
Variables:		Prepared By:	
T/K=308		V. I. Bondar	
p/MPa=0–2.0			

Experimental Data			
Dual mode sorption parameters for carbon dioxide in PAEK-12F at 308 K			
$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_D/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}	
0.970	14.32	0.381	
Sorption isotherms of carbon dioxide and methane in PAEK-12F at 308 K. (The original data were represented graphically)			
CO ₂		CH ₄	
Pressure/MPa	Sorption ($V_1^s(\text{STP})/V_2^s$)	Pressure/MPa	Sorption ($V_1^s(\text{STP})/V_2^s$)
0.14	6.00	0.16	1.81
0.31	10.48	0.23	2.55
0.47	13.37	0.34	3.19
0.63	15.47	0.50	3.93
0.77	18.01	0.65	4.70
0.93	20.20	0.84	5.40
1.09	22.30	1.01	5.95
1.27	23.68	1.18	6.63
1.41	25.70	1.33	7.23
1.58	27.35	1.49	7.63
1.76	29.36	1.67	8.12
1.90	30.93	1.83	8.47
2.05	32.32	2.00	8.82

Auxiliary Information	
Method/Apparatus/Procedure	A pressure decay method was used described in Ref. 1.
Source and Purity of Materials:	PAEK-12F synthesized (Ref. 2), density 1.401 g/cm ³ , glass transition temperature 458 K.
Estimated Error:	No information given.
References:	¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976). ² G. L. Tullios, P. E. Cassidy, and A. K. St. Clair, Proc. ACS, Div. Polym. Materials 60 , 310 (1989).

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials
The sorption apparatus and procedures used in the present sorption experiments are the same as described earlier. ¹	CO ₂ , CH ₄ , N ₂ ; purity >99.99% PA (Ardel D-100); Union Carbide Co., density 1.21 g/cm ³ , glass transition temperature 457 K.
Estimated Error:	No information given.
References:	¹ W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. 14 , 687 (1976).

Original Measurements:	
Components:	F. R. Shou, R. T. Chern, V. T. Stannett, and H. B. Hopfenberg, J. Polym. Sci., Part B: Polym. Phys. 26 , 883 (1988).
Variables:	7/K=308 p/MPa=1–2.3
Prepared By:	Yu. P. Yampol'ski

Experimental Data	
Dual mode sorption parameters	
Gas	k_D , /cm ³ (STP) cm ⁻³ atm ⁻¹ C'_D , /cm ³ (STP) cm ⁻³ b /atm ⁻¹
CO ₂	0.98 19.8 0.30
CH ₄	0.27 9.0 0.12

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials
Sorption apparatus and procedure were described in Ref. 1.	Polymer from Union Carbide had a density of 1.204 g/cm ³ and glass transition temperature 463 K.
Estimated Error:	No information given.
References:	¹ E. S. Sanders, W. J. Koros, H. B. Hopfenberger, and V. T. Stannett, J. Membr. Sci. 13 , 61 (1982)

Components:		Original Measurements:	
(1) Sulfur dioxide; SO ₂ ; [7446-09-5]		G. R. Ranaide, R. Chandler, C. A. Plank, and W. L. S. Laukhuf, Polym. Eng. Sci. 25 , 164 (1985).	
(2) Polyarylate (Ardel-D 100); [25639-68-3] (LXX)			
Variables:		Prepared By:	
T/K=298–336		S. M. Shishatskii	
p/kPa=0–90			

Experimental Data				
Dual mode sorption parameters for sulfur dioxide in polyarylate				
T/K	k_D /cm ³ (STP) cm ⁻³ atm ⁻¹	C'_D /cm ³ (STP) cm ⁻³	b /atm ⁻¹	
278	1.78	4.69	1.60	
298	32.47	16.06	16.03	
313	14.99	25.07	5.02	
328	5.01	20.01	2.77	
336	3.50	24.04	1.26	

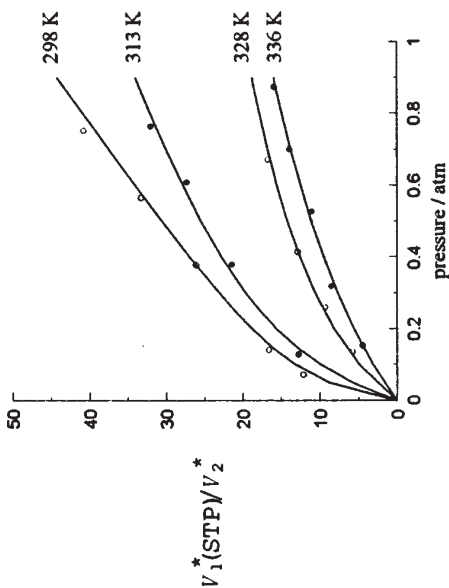


FIG. 55. Sorption isotherms of sulfur dioxide in polyarylate.

Method/Apparatus/Procedure		Auxiliary Information	
Sorption was measured using a gravimetric technique (a McBain quartz spring balance). For detailed description of the experimental procedure see Ref. 1.		Source and Purity of Materials: Polyarylate (Ardel-D 100): Union Carbide, copolyester of bisphenol A with 50/50 mixture of iso- and terephthalic acid. Density 1.21 g/cm ³ , M_n =12 300, M_w =29 800.	
Estimated Error: Precision in T: ±0.1 K		References: G. R. Ranaide, V. M. Nadgir, C. A. Plank, and W. L. S. Laukhuf, J. Appl. Polym. Sci. 28 , 201 (1983).	

Components:		Original Measurements	
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]		F. R. Shau, R. T. Chern, V. T. Stannett, and H. B. Hopfenberg, J. Pol. Sci., Part B: Polym. Phys. 26 , 883 (1988).	
(2) Polyarylate Ardel (PA); [25639-68-3] (LXX)			
Variables:		Prepared By:	
T/K=308		Yu. P. Yampol'skii	
p/MPa=0.1–2.3			

Experimental Data				
TABLE 1. Dual mode sorption parameters for gases in polyarylate at 308 K				
Gas	k_D /cm ³ (STP) cm ⁻³ atm ⁻¹	C'_D /cm ³ (STP) cm ⁻³	b /atm ⁻¹	
CO ₂	1.98	19.8	0.30	
CH ₄	0.27	9.0	0.12	

TABLE 2. Sorption isotherms of carbon dioxide and methane in polyarylate at 308 K. (The original data were represented graphically)

CO ₂				CH ₄			
Sorption ($V_1^*(STP)/V_2^*$)		Sorption ($V_1^*(STP)/V_2^*$)		Sorption ($V_1^*(STP)/V_2^*$)		Sorption ($V_1^*(STP)/V_2^*$)	
Pressure/MPa	Pressure/MPa	Pressure/MPa	Pressure/MPa	Pressure/MPa	Pressure/MPa	Pressure/MPa	Pressure/MPa
0.09	4.55	0.78	21.18	0.12	1.41	—	—
0.12	5.87	0.97	23.88	0.33	3.15	—	—
0.13	6.75	1.09	25.44	0.53	4.62	—	—
0.17	7.91	1.14	26.30	0.72	5.79	—	—
0.29	11.10	1.21	26.85	0.96	7.21	—	—
0.32	12.26	1.44	29.83	1.11	8.03	—	—
0.39	13.70	1.63	31.79	1.31	9.06	—	—
0.48	15.87	1.73	32.92	1.59	10.21	—	—
0.58	17.44	1.77	33.64	1.85	11.19	—	—
0.63	18.45	1.92	35.04	2.21	12.42	—	—
0.68	19.31	2.19	37.85	—	—	—	—

Method/Apparatus/Procedure		Auxiliary Information	
Sorption apparatus and procedure were the same as in Ref. 1.		Source and Purity of Materials: PA: Union Carbide Co., density 1.204 g/cm ³ , glass transition temperature 463 K.	
Estimated Error: No information given.		References: F. R. Shau, W. J. Koros, H. B. Hopfenberg, and V. T. Stannett, J. Membr. Sci. 13 , 61 (1983).	

3.23. Polyhydroxyether—Carbon Dioxide, Methane, Nitrogen

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Polyhydroxyether (PHE); [26402-79-9] (LXIX)	T/K: 308 p/MPa: 0-2.33	T. A. Barbari, W. J. Koros, and D. R. Paul, J. Polym. Sci., Part B: Polym. Phys. 26 , 729 (1988).	
		Prepared By: A. K. Bokarev	

Experimental Data	
Dual mode sorption parameters for PHE at 308 K	
Parameters	CO ₂ CH ₄
$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	0.289 0.051
$C'_H/\text{cm}^3(\text{STP})\text{cm}^{-3}$	10.01 2.70
b/atm^{-1}	0.184 0.067

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
The sorption apparatus and procedures used in the present sorption experiments are the same as described earlier. ¹	PHE (Union Carbide) had a tradename Phenoxo PKHH.
	Density: 1.18 g/cm ³ ; T_g = 376 K.
	Each gas was of chromatographic quality (purity > 99.99%).
References:	
	¹ W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. 14 , 687 (1976).

Components:		Original Measurements:	
(1) Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Polyhydroxyether (PHE); [26402-79-9] (LXIX)	T/K = 308 p/MPa = 0-2.5	T. A. Barbari, W. J. Koros, and D. R. Paul, J. Polym. Sci., Part B: Polym. Phys. 26 , 729 (1988).	
		Prepared By: A. K. Bokarev	

Experimental Data	
Table 1. Dual mode sorption parameters for various gases in polyhydroxyether at 308 K	
Gas	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$ $C'_H/\text{cm}^3(\text{STP})\text{cm}^{-3}$ b/atm^{-1}
CO ₂	0.289 10.01 0.184
CH ₄	0.051 2.70 0.067

Table 2. Sorption isotherms of various gases in polyhydroxyether at 308 K (The original data were represented graphically)					
CO ₂		CH ₄		N ₂	
Pressure/MPa	Sorption ($V_1^*/(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*/(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*/(\text{STP})/V_2^*$)
0.30	3.52	0.30	0.57	0.27	0.11
0.35	4.26	0.36	0.62	0.32	0.13
0.39	4.82	0.41	0.74	0.37	0.17
0.44	5.38	0.47	0.81	0.42	0.19
0.66	6.76	0.52	0.90	0.49	0.26
0.75	7.41	0.69	1.19	0.55	0.19
0.83	8.06	0.76	1.21	0.66	0.19
0.90	8.71	0.86	1.36	0.74	0.26
1.09	9.34	0.92	1.45	0.81	0.30
1.19	9.89	1.00	1.52	0.89	0.33
1.26	10.44	1.13	1.69	0.97	0.39
1.36	10.90	1.20	1.76	1.04	0.33
1.54	11.63	1.30	1.93	1.11	0.31
1.65	11.90	1.38	1.92	1.19	0.37
1.73	12.26	1.45	2.07	1.26	0.39
1.82	12.72	1.55	2.16	1.34	0.43
2.01	13.63	1.64	2.21	1.44	0.48
2.11	13.81	1.73	2.30	1.53	0.46
2.19	14.08	1.83	2.35	1.55	0.41
2.28	14.44	1.90	2.49	1.64	0.54
—	—	2.01	2.54	1.73	0.52
—	—	2.09	2.66	1.81	0.57
—	—	2.18	2.68	1.92	0.61
—	—	2.28	2.78	2.00	0.59
—	—	—	—	2.08	0.63
—	—	—	—	2.18	0.65
—	—	—	—	2.27	0.69
—	—	—	—	2.35	0.72
—	—	—	—	2.46	0.74

3.24. Poly(Phenolphthalein Phthalate)—Various Gases

Components:	(1) Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]	Original Measurements F. R. Shu and R. T. Chem, J. Polym. Sci., Part B: Polym. Phys. 27, 1121 (1989). F. R. Shu, R. T. Chem, V. Stannett, and H. B. Hopfenberg, J. Polym. Sci., Part B: Polym. Phys. 26, 883 (1988).
	(2) Poly(phenolphthalein phthalate) (PPhPh); [24938-86-1] (XXXXV)	
Variables:		Prepared By:
T/K=308.2		Yu. P. Yampol'skii
p/MPa=0–2.0		

TABLE 1. Dual mode sorption parameters for CO₂, CH₄, and N₂ in different polymers at 308.2 K

Polymer	Gas	k_D /cm ³ (STP) cm ⁻³ atm ⁻¹	C'_H /cm ³ (STP) cm ⁻³	b /atm ⁻¹
PPhPh-tere	CO ₂	1.312	36.37	0.413
	CH ₄	0.321	13.76	0.160
	N ₂	0.155	4.67	0.065
PPhPh-50:50	CO ₂	1.230	34.66	0.413
	CH ₄	0.324	13.74	0.154
	N ₂	0.151	4.39	0.077
PPhPh-iso	CO ₂	1.229	31.54	0.452
	CH ₄	0.329	13.00	0.154
	N ₂	0.157	4.12	0.067

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials:
The sorption apparatus and procedures used in the present sorption experiments are the same as described earlier. ¹	CO ₂ , CH ₄ , N ₂ : purity >99.99%.
	PHE (Phenoxy PKHH): Union Carbide, density 1.18 g/cm ³ , glass transition temperature 376 K.
Estimated Error:	No information given.
References:	¹ W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. 14, 687 (1976).

TABLE 3. Sorption isotherms of methane in poly(phenolphthalein phthalate)s at 308.2 K (The original data were represented graphically)

PPha-terc			PPha-50:50			PPha-iso		
Pressure/MPa	Sorption ($V_1^g(\text{STP})/V_2^g$)		Pressure/MPa	Sorption ($V_1^g(\text{STP})/V_2^g$)		Pressure/MPa	Sorption ($V_1^g(\text{STP})/V_2^g$)	
0.16	3.06		0.16	2.96		0.09	1.82	
			0.19	3.63		0.14	2.65	
0.27	3.94		0.29	4.77		0.23	3.94	
0.34	4.82		0.31	5.18		0.34	5.23	
0.43	5.55		0.41	6.32		0.29	4.56	
0.52	6.58		0.50	7.20		0.47	6.68	
0.62	7.67		0.57	7.87		0.49	6.89	
0.72	8.49		0.61	8.23		0.56	7.56	
0.77	9.37		0.69	9.11		0.68	8.39	
0.86	9.68		0.74	9.32		0.70	8.70	
0.98	10.61		0.83	10.09		0.84	9.78	
1.03	11.02		0.98	11.07		0.89	10.14	
1.13	11.59		1.11	11.95		0.97	10.60	
1.14	12.10		1.21	12.62		1.08	11.37	
1.24	12.26		1.32	13.23		1.12	11.63	
1.34	13.08		1.42	13.80		1.25	12.46	
1.39	13.23		1.48	13.95		1.32	12.87	
1.51	13.70		1.60	14.67		1.40	13.28	
1.61	14.31		1.74	15.07		1.51	13.69	
1.72	15.24		1.87	15.84		1.58	14.10	
1.73	15.02		1.94	16.41		1.69	14.71	
1.85	15.49		1.98	16.72		1.79	15.17	
1.86	16.16		—	—		1.90	15.63	
1.95	15.85		—	—		—	—	
1.99	16.15		—	—		—	—	
	16.88		—	—		—	—	

TABLE 2. Sorption isotherms of carbon dioxide in poly(phenolphthalein phthalate)s at 308.2 K (The original data were represented graphically)

PPha-terc			PPha-50:50			PPha-iso		
Pressure/MPa	Sorption ($V_1^g(\text{STP})/V_2^g$)		Pressure/MPa	Sorption ($V_1^g(\text{STP})/V_2^g$)		Pressure/MPa	Sorption ($V_1^g(\text{STP})/V_2^g$)	
0.07	10.09		0.07	9.22		0.20	16.71	
0.09	12.10		0.10	12.25		0.24	19.60	
0.13	15.42		0.16	15.71		0.31	22.05	
0.16	17.15		0.30	22.91		0.42	26.08	
0.25	21.47		0.38	25.07		0.51	27.67	
0.31	24.35		0.43	27.23		0.59	30.69	
0.34	25.22		0.51	29.25		0.74	32.71	
0.41	27.67		0.64	32.71		0.79	34.29	
0.44	29.54		0.80	36.17		0.90	35.88	
0.59	32.85		0.83	37.03		1.02	38.62	
0.64	34.58		0.89	38.04		1.15	40.20	
0.74	37.03		1.02	40.06		1.21	40.92	
0.78	38.04		1.25	44.24		1.34	42.94	
0.86	40.06		1.29	44.96		1.44	45.10	
0.94	40.63		1.31	44.96		1.55	46.54	
1.04	42.80		1.41	46.40		1.62	46.40	
1.21	46.11		1.64	50.29		1.76	48.41	
1.28	47.98		1.66	50.58		1.84	50.58	
1.32	47.12		1.74	51.87		1.91	51.59	
1.43	49.28		1.78	52.02		—	—	
1.57	51.73		1.93	53.46		—	—	
1.59	52.45		1.97	54.61		—	—	
1.67	54.32		—	—		—	—	
1.81	54.61		—	—		—	—	
1.85	55.04		—	—		—	—	
1.92	56.63		—	—		—	—	

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]		R. T. Chern and C. N. Provan, Macromolecules 24 , 2203 (1991).	
Methane; CH ₄ ; [74-82-8]			
Ethane; C ₂ H ₆ ; [74-84-0]			
(2) Poly(tetrabromophthalatein-terephthalate) (XXXVII)			
Variables:		Prepared By:	
T/K=308		Yu. P. Yampol'skii	
p/MPa=0–2.1			

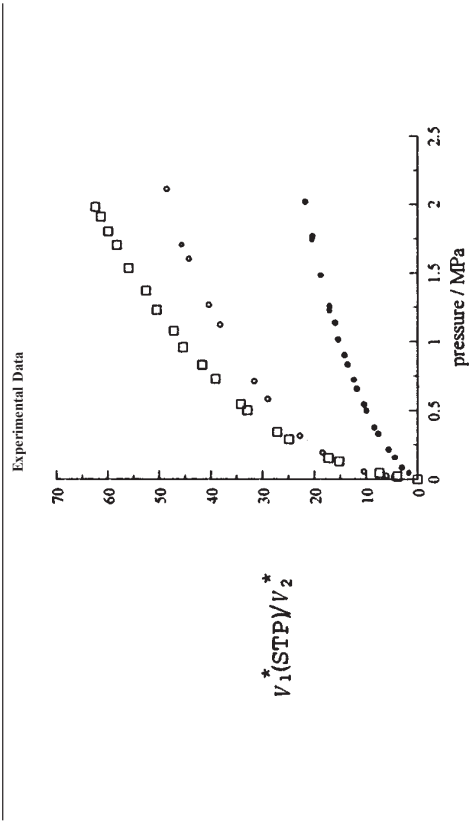


FIG. 56. Sorption isotherms of carbon dioxide (□), methane (●), and ethane (○) in the polymer at 308 K.

Method/Apparatus/Procedure		Auxiliary Information	
A pressure decay method was used.		Source and Purity of Materials: Poly(tetrabromophthalatein-terephthalate): density 1.750 g/cm ³ , $M_w = 26\,000$, $M_w/M_n = 2.0$, glass transition temp. 592 K.	
		Estimated Error: No information given.	

TABLE 4. Sorption isotherms of nitrogen in poly(phenolphthalein phthalate)s at 308.2 K (The original data were represented graphically)

PPha-tere			PPha-50:50			PPha-iso		
Pressure/MPa	Sorption ($V_1^*(STP)/V_2^*$)		Pressure/MPa	Sorption ($V_1^*(STP)/V_2^*$)		Pressure/MPa	Sorption ($V_1^*(STP)/V_2^*$)	
0.08	0.34		0.08	0.36		0.11	0.44	
0.11	0.50		0.22	0.85		0.15	0.63	
0.16	0.68		0.28	0.11		0.20	0.78	
0.21	0.87		0.35	1.40		0.28	1.06	
0.28	1.13		0.42	1.64		0.39	1.36	
0.32	1.25		0.50	1.94		0.46	1.65	
0.37	1.47		0.59	2.28		0.53	1.88	
0.42	1.60		0.65	2.43		0.61	2.07	
0.50	1.87		0.78	2.78		0.71	2.50	
0.58	2.12		0.82	2.94		0.83	2.74	
0.68	2.47		0.93	3.23		0.93	3.03	
0.72	2.70		0.98	3.40		1.02	3.24	
0.81	2.85		1.13	3.73		1.17	3.66	
0.92	3.15		1.19	3.87		1.26	3.91	
0.99	3.36		1.34	4.28		1.38	4.18	
1.11	3.65		1.56	4.74		1.46	4.27	
1.13	3.73		1.65	4.92		1.62	4.66	
1.19	3.89		1.73	5.09		1.73	4.94	
1.28	4.07		1.90	5.48		1.82	5.11	
1.32	4.21		1.95	5.58		1.89	5.21	
1.47	4.69		—	—		—	—	
1.49	4.74		—	—		—	—	
1.64	4.79		—	—		—	—	
1.67	4.95		—	—		—	—	
1.83	5.28		—	—		—	—	
1.88	5.44		—	—		—	—	
1.84	5.53		—	—		—	—	
1.93	5.52		—	—		—	—	

Method/Apparatus/Procedure		Auxiliary Information	
A pressure decay sorption cell was used in the measurements.		Source and Purity of Materials: Gas purity: CO ₂ 99.99%; CH ₄ 99.7%; N ₂ 99.999%. PPha: synthesized by interfacial polycondensation from phthaloyl chlorides and phenolphthalein. PPha-50:50: synthesized by reacting phenolphthalein with a mixture of 50:50 terephthaloyl and isophthaloyl chlorides. Iso-: $T_g = 522$ K, density 1.304 g/cm ³ . 50:50 isomers: $T_g = 552$ K, density 1.298 g/cm ³ . Tere-: $T_g = 572$ K, density 1.297 g/cm ³ .	
		Estimated Error: Precision in T: ±0.1 K.	

3.25. Polysulfone—Carbon Dioxide

Components:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]	Evaluator: Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994
(2) Polysulfone (PSF); [25135-51-7] (XXXVIII)	

Critical Evaluation:

Several investigations have been carried out for this system¹⁻⁶ In most cases PSF from Union Carbide has been studied, except the paper by Sada *et al.*⁵ where Toray Co. provided the sample and the work by McHattie *et al.*⁶ where the polymer was synthesized in the laboratory. A comparison of the dual mode sorption parameters as well as the apparent solubility coefficients $S = k_D + C'_D/b$ at different temperatures is shown in Fig. 58. A fairly good agreement between the values of k_D and C'_D can be observed. However, systematic discrepancies in the affinity parameter b can be noted between those reported by Japanese authors⁵ and found for PSF from Union Carbide. These differences are also reflected in the temperature dependence of S . Since the pressure ranges studies and the scatter of the experimental points are similar in two groups of the data, one is tempted to attribute this disagreement to some differences of the polymer sample.

Original Measurements:	
(1) Argon; Ar; [7440-37-1] Nitrogen; N ₂ ; [7727-37-9] Methane; CH ₄ ; [74-82-8]	P. Masi, D. R. Paul, and J. W. Barlow, J. Polym. Sci., Polym. Phys. Ed. 20 , 15 (1982).
(2) Copolyester (Kodur A-150)	

Variables:	
$T/K = 308$	Prepared By: A. K. Bokarev
$p/\text{MPa} = 0 - 3.5$	

Experimental Data			
Dual mode sorption parameters for various gases in copolyester at 308 K			
Gas	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'_D/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
Ar	0.117	2.09	0.050
CH ₄	0.174	2.76	0.094
N ₂	0.078	1.40	0.034

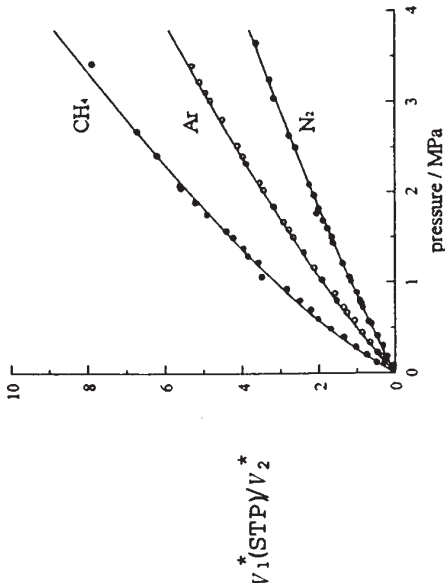


FIG. 57. Sorption isotherms of various gases in Kodur A-150 at 308 K.

Method/Apparatus/Procedure	
Sorption was measured using a pressure decay method described in Ref. 1. The specimens before measurement were exposed to CO ₂ at 20 atm for 1 day.	
Auxiliary Information	
Source and Purity of Materials: Copolyester (Kodur A-150): Eastman Chemical Products, Inc., film completely amorphous, ratio of units of isophthalic and terephthalic acids 20/80, $M_n = 22\,000$, glass transition temperature 360 K (thermal analysis).	
Estimated Error: No information given.	
References: ¹ W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. 14 , 687 (1976).	

The following dual mode sorption parameters as a function of temperature can be recommended for sorption of carbon dioxide in PSF from Union Carbide at the pressure range 0–2.0 MPa.

Critical Evaluation:

T/K	k_D	C_H	b	$S=k_D+C_H/b$	Ref.
293	0.801	26.0	0.410	11.5	3,4
308	0.705	18.9	0.325	6.8	1,3
338	0.231	17.5	0.134	2.6	3,4

Units: k_D and $S/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$; $C_H/\text{cm}^3(\text{STP})\text{cm}^{-3}$; b/atm^{-1} .

References:

¹A. J. Erb and D. R. Paul, *J. Membr. Sci.*, **8**, 11 (1981).

²J. S. Chou, Y. Maeda, and D. R. Paul, *J. Appl. Polym. Sci.*, **30**, 4019 (1985).

³J. S. Chou, Y. Maeda, and D. R. Paul, *J. Appl. Polym. Sci.*, **33**, 1823 (1987).

⁴Y. Maeda and D. R. Paul, *J. Polym. Sci., Part B: Polym. Phys.*, **25**, 957 (1987).

⁵E. Sada, H. Kumazawa, P. Xu, and M. Nishigaki, *J. Membr. Sci.*, **37**, 165 (1988).

⁶J. S. McHattie, W. J. Koros, and D. R. Paul, *Polymer*, **32**, 840 (1991).

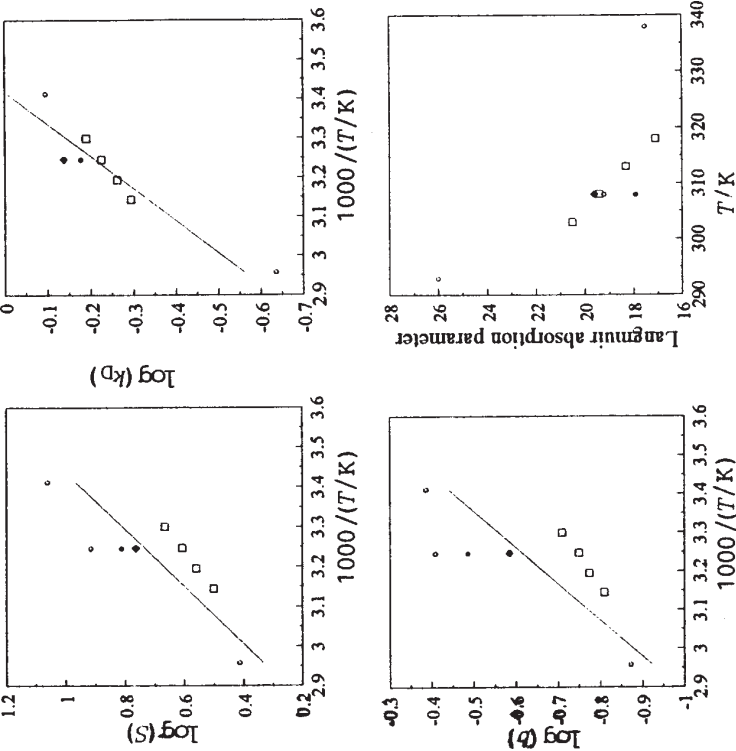


FIG. 58. (a) $\log S$ vs $1/(T/K)$; (b) $\log k_D$ vs $1/(T/K)$; (c) $\log b$ vs $1/(T/K)$; (d) C_H vs T/K .
Units: k_D and $S/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$; $C_H/\text{cm}^3(\text{STP})\text{cm}^{-3}$; b/atm^{-1} . (●) Ref. 1; (○) Ref. 4; (□) Ref. 5; (◆) Ref. 6.

3.26. Polysulfone—Methane and Other Gases

Components:		Evaluator:
(1) Methane; CH ₄ ; [74-82-8]		Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994
(2) Polysulfone (PSF); [25135-51-7] (XXXVIII)		

Critical Evaluation:

Only three papers are available for the solubility of methane in PSF at the pressure range 0–2.0 or 0–3.0 MPa.^{1–3} The polymer specimens were provided by Union Carbide Co.,¹ Toray Co.,² or synthesized in the laboratory.³ The summary of the dual mode sorption parameters and the apparent solubility coefficients *S* are presented below.

<i>T</i> /K	<i>k</i> _D	<i>C</i> _H	<i>b</i>	<i>S</i> = <i>k</i> _D – <i>C</i> _H / <i>b</i>	Ref.
303	0.441	9.26	0.116	1.5	2
308	0.161	9.86	0.0698	0.84	1
308	0.257	6.58	0.0901	0.85	3
313	0.413	7.63	0.0886	1.08	2
323	0.376	6.07	0.0748	0.83	2

Units: *k*_D and *S*/cm³(STP) cm^{–3} atm^{–1}; *C*_H/cm³(STP) cm^{–3}; *b*/atm^{–1}.

A rather poor agreement between the data of different authors is observed. One may assume that this is the result of different samples studied as it is true for the system PSE–carbon dioxide. Another possible source of errors can be caused by too narrow pressure range for methane sorption. Indeed, the affinity constants *b* reported in Ref. 1–3 are equal to 0.07–0.12 atm^{–1}. So the point of intersection of the initial slope and the high pressure (Langmuir) asymptote should be close to pressure 8.6–14.3 atm, which is not too far from the maximum pressure of the isotherms. Hence, the limiting slope of the Langmuir part of isotherms has not been probably reached. Further experimental studies of well characterized sample are required before this system can be properly evaluated, and recommended values can be advanced.

References:

- ¹A. J. Erb and D. R. Paul, *J. Membr. Sci.* **8**, 11 (1981).
²E. Sada, H. Kumazawa, P. Xu, and M. Nishigaki, *J. Membr. Sci.* **37**, 165 (1988).
³J. S. McHattie, W. J. Koros, and D. R. Paul, *Polymer* **32**, 840 (1991).

Components:	Original Measurements:
(1) Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] Ethane; C ₂ H ₆ ; [74-84-0]	Y. Kamiya, T. Hirose, K. Mizoguchi and K. Terada, <i>J. Polym. Sci., Part B: Polym. Phys.</i> 24 , 1525 (1986).
(2) Polysulfone (PSF); [25135-51-7] (XXXVIII)	

Prepared By:

A. K. Bokarev

Variables:

T/K = 308–338

p/MPa = 0–5.0

Experimental Data

TABLE 1. Sorption and desorption isotherms of carbon dioxide in polysulfone at 308 K (The original data were represented graphically)

First series ("as received" film)				Second series			
Sorption Pressure/MPa		Desorption Pressure/MPa		Sorption Pressure/MPa		Desorption Pressure/MPa	
<i>(p</i> ₁ ^o (STP)/ <i>p</i> ₂ ^o)		<i>(p</i> ₁ ^o (STP)/ <i>p</i> ₂ ^o)		<i>(p</i> ₁ ^o (STP)/ <i>p</i> ₂ ^o)		<i>(p</i> ₁ ^o (STP)/ <i>p</i> ₂ ^o)	
0.11	3.66	0.14	7.09	0.14	5.98	0.24	11.4
0.33	8.07	0.39	16.48	0.32	11.73	1.60	33.99
0.69	13.24	0.67	22.44	0.58	16.13	3.58	42.33
1.16	17.85	1.18	29.92	0.99	21.52	4.93	44.65
2.03	25.64	2.00	36.94	1.50	26.46	—	—
3.50	34.70	3.00	41.39	2.04	30.73	—	—
4.96	43.54	3.94	43.52	2.83	35.65	—	—
—	—	—	—	3.69	39.67	—	—
—	—	—	—	4.31	42.49	—	—

TABLE 4. Sorption and desorption isotherms of CH₄ and N₂ in polysulfone at 308 K, measured after CO₂ sorption experiments (The original data were represented graphically)

CH ₄				N ₂			
Pressure/MPa	Sorption ($V_T^s(\text{STP})/V_T^s$)	Pressure/MPa	Desorption ($V_T^d(\text{STP})/V_T^s$)	Pressure/MPa	Sorption ($V_T^s(\text{STP})/V_T^s$)	Pressure/MPa	Desorption ($V_T^d(\text{STP})/V_T^s$)
0.11	1.39	0.11	1.64	0.12	0.29	0.12	0.44
0.31	3.14	0.29	3.54	0.23	0.48	0.31	0.84
0.60	5.35	0.58	5.68	0.45	1.06	0.41	1.12
1.07	7.24	1.11	8.04	0.62	1.47	1.09	2.46
1.55	9.30	2.04	11.17	1.14	2.37	1.59	3.18
2.53	11.91	3.02	13.15	2.05	3.80	2.60	4.63
3.05	12.59	4.00	14.61	2.74	4.69	3.52	5.52
4.03	14.37	5.03	15.68	3.50	5.43	4.36	6.30
5.00	15.53	—	—	4.19	6.06	—	—
—	—	—	—	4.88	6.61	—	—
—	—	—	—	4.97	6.63	—	—

TABLE 5. Dual mode sorption parameters for nitrogen in polysulfone at 308 K

$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
0.043	7.5	0.031

Auxiliary Information

Method/Apparatus/Procedure
Sorption isotherms for gases in the polymer were obtained gravimetrically using a Cahn Model 2000 electrobalance. Details of this apparatus were described previously.¹

Source and Purity of Materials:
Gas purity: CO₂ 99.99%, CH₄ 99.9%, C₂H₆ 99.7%, PSF (Udel Polysulfone): Nissan Chemical Industries Ltd., densities (at 298 K) 1.240 g/cm³ ("as received") and 1.238 g/cm³ (after CO₂ exposure), glass transition temperature 455 K.

Estimated Error:
No information given.

References:
¹Y. Kamiya, K. Mizoguchi, Y. Naito, and T. Hirose, *J. Polym. Sci., Polym. Phys. Ed.* **24**, 535 (1986).

TABLE 2. Sorption and desorption isotherms of carbon dioxide in polysulfone measured after CO₂ sorption experiment at 308 K (The original data were represented graphically)

T = 318 K				T = 328 K			
Pressure/MPa	Solubility ($V_T^s(\text{STP})/V_T^s$)	Pressure/MPa	Solubility ($V_T^s(\text{STP})/V_T^s$)	Pressure/MPa	Solubility ($V_T^s(\text{STP})/V_T^s$)	Pressure/MPa	Solubility ($V_T^s(\text{STP})/V_T^s$)
Sorption							
0.34	9.93	0.33	8.00	0.10	2.81		
0.85	16.91	0.52	9.93	0.31	6.37		
1.19	20.18	0.81	13.05	0.60	9.64		
1.58	22.42	1.06	15.43	0.82	11.87		
1.87	25.09	1.54	18.71	1.15	14.70		
2.47	28.07	1.86	20.94	1.54	17.08		
3.07	30.46	2.47	23.78	1.87	19.16		
3.63	32.70	3.10	26.46	2.37	21.40		
4.33	34.80	3.57	28.26	2.91	23.35		
5.04	37.20	4.03	29.90	3.28	24.69		
—	—	4.53	31.25	3.85	26.49		
—	—	5.00	32.90	4.40	27.84		
—	—	—	—	4.92	29.49		
Desorption							
0.12	6.96	0.15	5.92	0.18	6.22		
0.37	13.78	0.39	11.56	0.40	10.52		
0.64	18.38	0.65	15.87	0.70	14.09		
1.16	24.33	1.07	20.18	0.88	16.02		
1.60	27.75	1.52	23.15	1.27	19.15		
2.06	30.43	2.03	25.99	1.59	20.93		
2.47	32.37	2.55	27.93	1.95	22.72		
3.04	34.17	3.06	29.43	2.53	24.96		
3.54	35.67	3.63	30.78	2.98	26.16		
4.14	36.57	4.32	32.13	3.49	27.66		
4.95	37.19	—	—	4.00	28.57		
—	—	—	—	4.47	29.32		
—	—	—	—	4.83	29.78		

TABLE 3. Sorption and desorption isotherms of ethane in polysulfone at 308 K, measured after CO₂ sorption experiments (The original data were represented graphically)

Sorption				Desorption			
Pressure/MPa	Solubility ($V_T^s(\text{STP})/V_T^s$)	Pressure/MPa	Solubility ($V_T^s(\text{STP})/V_T^s$)	Pressure/MPa	Solubility ($V_T^s(\text{STP})/V_T^s$)	Pressure/MPa	Solubility ($V_T^s(\text{STP})/V_T^s$)
0.12	5.65	0.10	7.39				
0.30	9.12	0.30	12.16				
0.52	11.80	0.55	15.53				
0.84	14.65	1.05	18.63				
1.09	15.50	1.97	21.27				
1.14	16.37	—	—				
2.03	19.53	—	—				
3.04	21.98	—	—				

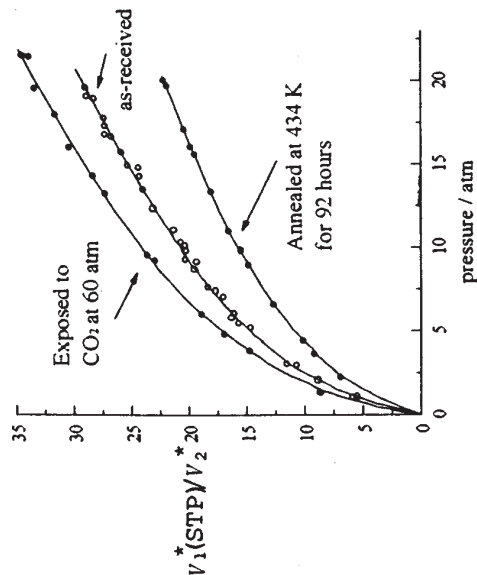


FIG. 60. Effects of history of sample treatment on sorption isotherms: CO₂ sorption at 308 K.

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials: Commercial PSF; Union Carbide Corp., studied in the form of melt extruded film; glass transition temperature 455 K (DSC).
	Estimated Error: No information given.
	References: ¹ W. J. Koros, A. H. Chan, and D. R. Paul, J. Membr. Sci. 2, 165 (1977).

Components:		Original Measurements:	
(1) Argon; Ar; [7440-37-1] Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Polysulfone (PSF); [25135-51-7] (XXXXVIII)	T/K=308 p/MPa=0–3.0	A. J. Erb and D. R. Paul, J. Membr. Sci. 8, 11 (1981). J. S. Chou, Y. Maeda, and D. R. Paul, J. Appl. Polym. Sci. 33, 1823 (1987).	
		Prepared By: Yu. P. Yampol'skii	
Experimental Data			
Dual mode sorption parameters for various gases in "as-received" polysulfone films at 308 K			
Gas	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
Ar	0.150	6.72	0.0317
N ₂	0.0753	9.98	0.0156
CO ₂	0.664	17.90	0.3260
CH ₄	0.161	9.86	0.0698

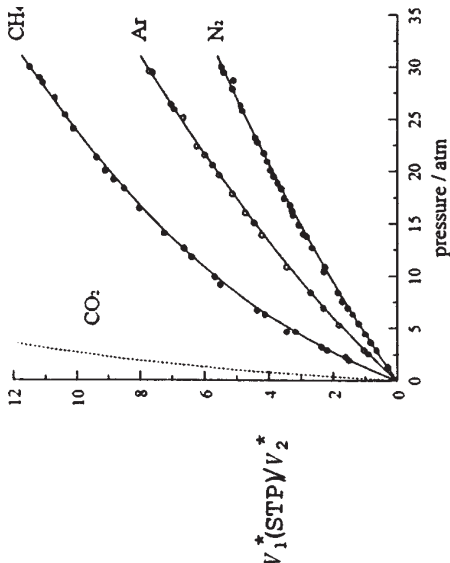


FIG. 59. Sorption isotherms of various gases in "as-received" polysulfone films.

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Polysulfone (PSF); [25135-51-7] (XXXVIII) (3) 4,4'-Dichlorodiphenyl sulfone (DDS); (C ₁₂ H ₄) ₂ C ₁₂ S; [38980-51-7] (4) <i>N</i> -phenyl-2-naphthylamine (PNA); C ₁₆ H ₁₃ N; [135-88-6] (5) Tricresyl phosphate (TCP); C ₂₁ H ₂₁ O ₄ P; [1330-78-5]		Original Measurements: Y. Maeda and D. R. Paul, <i>J. Polym. Sci., Part B: Polym. Phys.</i> , 25 , 957 (1987). J. S. Chlou, Y. Maeda, and D. R. Paul, <i>J. Appl. Polym. Sci.</i> , 33 , 1823 (1987).		
Variables: <i>T</i> /K=293–338 <i>p</i> /MPa=0–2.2 (0–22 atm)		Prepared By: Yu. P. Yampol'skii		
Experimental Data				
Dual mode sorption parameters for carbon dioxide in polysulfone at different temperatures and its mixtures with plasticizers at 308 K				
System	<i>k_D</i> /cm ³ (STP) cm ⁻³ atm ⁻¹	<i>C_f</i> /cm ³ (STP) cm ⁻³	<i>b</i> /atm ⁻¹	
PSF	293 K	0.801	26.0	0.410
	308 K	0.725	19.2	0.390
	338 K	0.231	17.5	0.134
DDS (mass %)				
	10%	0.563	13.6	0.394
	20%	0.296	10.2	0.226
30%				
	0.458	8.8	0.312	
	PNA (mass %)			
10%		0.392	13.9	0.159
20%		0.363	8.1	0.278
TCP (mass %)				
	5%	0.503	13.9	0.280
	10%	0.426	12.2	0.259
	15%	0.476	9.7	0.248
20%	0.443	7.4	0.271	

Components: (1) Carbon dioxide: CO ₂ ; [124-38-9] (2) Polysulfone (PSF); [25135-51-7] (XXXVIII)		Original Measurements: J. S. Chlou, Y. Maeda, and D. R. Paul, <i>J. Appl. Polym. Sci.</i> , 30 , 4019 (1985).	
Variables: <i>T</i> /K=308 <i>p</i> /MPa=0–2.2 (0–22 atm)		Prepared By: S. M. Shishatskii	
Experimental Data			
Sorption isotherm of carbon dioxide in polysulfone at 308 K. (The original data were represented graphically)			
Pressure/MPa	Sorption (<i>V</i> _T ⁰ (STP)/ <i>V</i> _T ⁰)	Pressure/MPa	Sorption (<i>V</i> _T ⁰ (STP)/ <i>V</i> _T ⁰)
0.12	5.95	1.10	21.58
0.17	7.97	1.20	22.68
0.28	11.07	1.39	24.11
0.32	11.49	1.46	24.70
0.45	14.10	1.61	25.54
0.61	16.37	1.79	27.14
0.68	17.29	1.83	27.14
0.81	18.89	2.02	28.41
0.85	18.97	2.07	28.66
1.04	21.08	2.12	29.17
Auxiliary Information			
Method/Apparatus/Procedure Sorption isotherm was obtained using a dual-volume dual-transducer cell design based on the pressure decay principle.		Source and Purity of Materials: PSF: conditioned at the highest CO ₂ pressure before measurement; glass transition temperature 455 K.	
Estimated Error: No information given.			

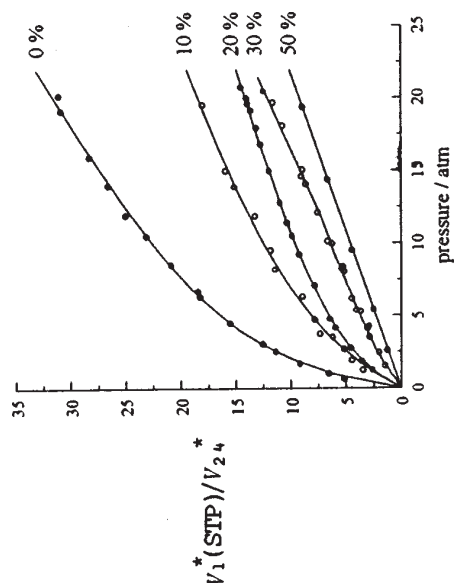


FIG. 63. Effect of the content of PNA (mass %) on CO_2 sorption isotherms for polysulfone at 308 K.

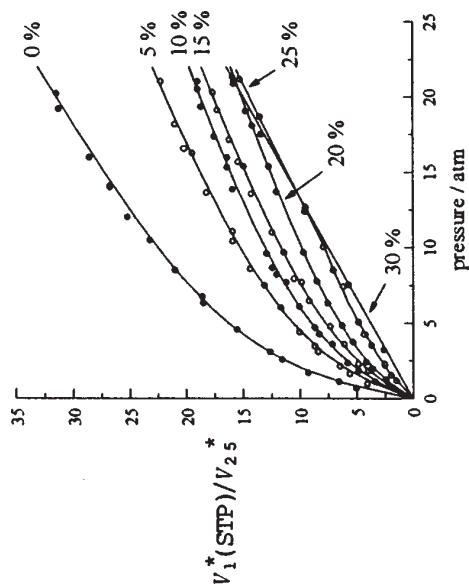


FIG. 64. Effect of the content of TCP (mass %) on CO_2 sorption isotherms for polysulfone at 308 K.

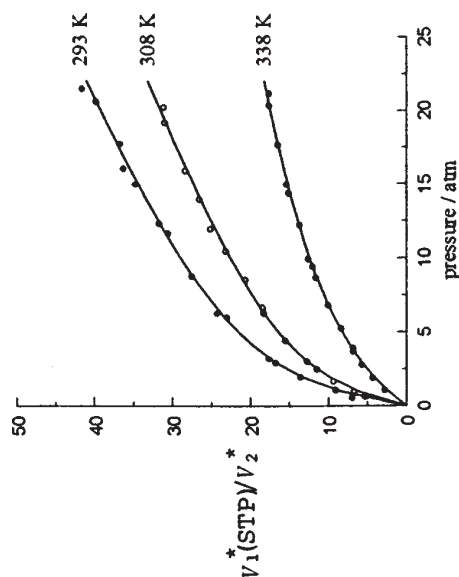


FIG. 61. Effect of temperature on CO_2 sorption isotherms in pure polysulfone.

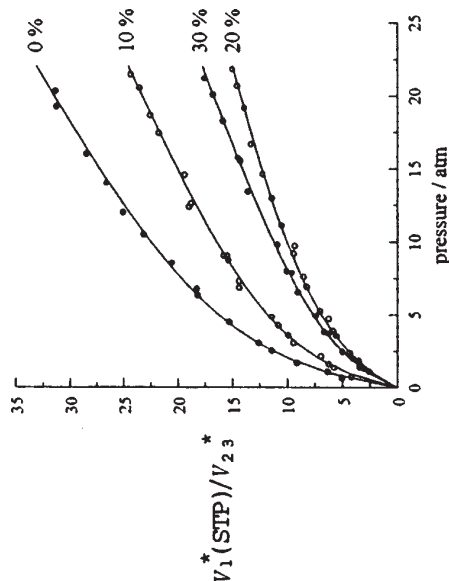


FIG. 62. Effect of the content of DDS (mass %) on CO_2 sorption isotherms for polysulfone at 308 K.

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] Nitrogen; N ₂ ; [7727-37-9]		T. A. Barbari, W. J. Koros, and D. R. Paul, J. Polym. Sci.: Part B: Polym. Phys. 26 , 729 (1988).	
(2) Polysulfone (PSF); [25135-51-7] (XXXXVIII)		A. J. Erb, M.S. thesis, The University of Texas at Austin, 1977.	
Variables:		Prepared By:	
T/K: 308		A. K. Bokarev	
p/MPa: 0–2.33			
Experimental Data			
Dual mode sorption parameters fro PSF at 308 K			
Parameters	CO ₂	CH ₄	N ₂
k_D /cm ³ (STP)/cm ³ atm	0.664	0.161	0.0753
C_H' /cm ³ (STP)/cm ³	17.91	9.86	9.98
b /(atm ⁻¹)	0.326	0.070	0.0156
Auxiliary Information			
Method/Apparatus/Procedure		Source and Purity of Materials:	
The sorption apparatus and procedures used in the present sorption experiments are the same as described earlier. ¹		PSF: no information given. Each gas was of chromatographic quality (purity >99.99%).	
		Estimated Error:	
		Nothing specified.	
		References:	
		¹ W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., polym. Phys. Ed. 14 , 687 (1976).	

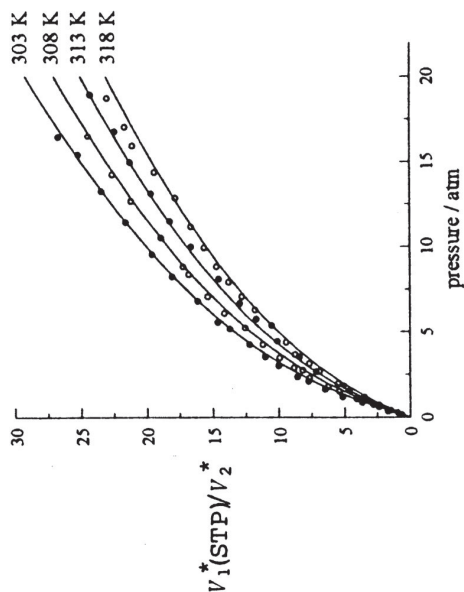


FIG. 65. Sorption isotherms of carbon dioxide in polysulfone.

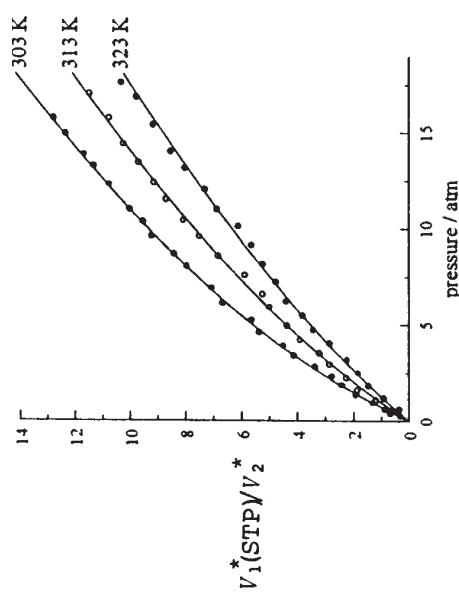


FIG. 66. Sorption isotherms of methane in polysulfone.

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]		E. Sada, H. Kumazawa, P. Xu, and M. Nishigaki, J. Membr. Sci., 37, 165 (1988).	
(2) Polysulfone (PSF); [25135-51-7] (XXXVIII)			
Variables:		Prepared By:	
T/K=303–323		Yu. P. Yampol'skii	
p/MPa=0–2.0			
Experimental Data			
Dual mode sorption parameters for carbon dioxide and methane in polysulfone			
T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_2'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
CO ₂			
Pressure			
303	0.646	20.5	0.195
308	0.595	19.4	0.178
313	0.547	18.3	0.168
318	0.508	17.1	0.155
Fugacity			
303	0.737	19.6	0.199
308	0.677	18.5	0.183
313	0.630	17.4	0.168
318	0.595	16.2	0.155
CH ₄			
Pressure			
303	0.441	9.26	0.1160
313	0.413	7.63	0.0886
323	0.376	6.07	0.0748
Fugacity			
303	0.489	8.37	0.1210
313	0.445	6.60	0.0976
323	0.415	5.12	0.0785

Auxiliary Information

Method/Apparatus/Procedure

Sorption was measured using a pressure decay method.

Source and Purity of Materials:

PSF (Toraylon-PSF): Toray Co., film samples; glass transition temperature 463 K.

Estimated Error:

No information given.

Components: (1) Nitrogen, N ₂ ; [7727-37-9] Carbon dioxide, CO ₂ ; [124-38-9] Methane, CH ₄ ; [74-82-8] (2) Polysulfone (PSF); [25135-51-7] (XXXVIII)	Original Measurements: J. S. McHattie, W. J. Koros, and D. R. Paul, <i>Polymer</i> 32 , 840 (1991).	
	Prepared By: Yu. P. Yampol'skii	
Variables: T/K=308 p/MPa=0-2.0 (0-20 atm)		

Experimental Data				
TABLE 1. Solubility of gases C/cm ³ (STP)/cm ³ in PSF*				
Pressure/atm				
Gas	5	10	15	20
N ₂	1.2	2.2	3.1	3.9
CO ₂	15.0	21.7	26.6	30.5
CH ₄	3.6	6.0	8.0	9.9

*Smoothed values taken from the plot by compiler.

TABLE 2. Dual mode sorption parameters			
Gas	k _D /cm ³ (STP)/cm ³ atm	C' _D /cm ³ (STP)/cm ³	b/atm ⁻¹
N ₂	0.166	0.957	0.104
CO ₂	0.728	19.6	0.260
CH ₄	0.257	6.58	0.0901

Auxiliary Information	
Method/Apparatus/Procedure The measurement of sorption was carried out using a pressure decay method. ¹	Source and Purity of Materials: PSF was synthesized according to Ref. 2. It had a density 1.240 g/cc and the glass transition temperature 459 K.

Estimated Error:
No information given.

References:
¹W. J. Koros and D. R. Paul, *J. Polym. Sci., Polym. Phys. Ed.* **14**, 1903 (1976).
²R. N. Johnson, A. G. Farnham, R. A. Clendinning, W. F. Hale, and C. N. Merriam, *J. Polym. Sci.: Part A-1* **5**, 2375 (1967).

Components: (1) Carbon dioxide, CO ₂ ; [124-38-9] (2) Polysulfone (PSF); [25135-51-7] (XXXVIII)	Original Measurements: E. Sada, H. Kumazawa, and P. Xu, <i>J. Polym. Sci., Part B: Polym. Phys.</i> 27 , 919 (1989).	
	Prepared By: A. K. Bokarev	
Variables: T/K=313 p/MPa=0-1.8 (0-18 atm)		

Experimental Data										
Solubility of carbon dioxide C/cm ³ (STP)/cm ³ in PSF membranes at 313 K*										
Pressure, atm										
Sample	2	4	6	8	10	12	14	16	18	20

As cast	3.0	5.7	7.9	10.2	12.1	14.0	15.9	17.7	19.5	21.2
Commercial PSF (Toraylon-PS)	5.6	9.5	12.4	14.9	16.8	18.9	20.5	22.5	23.6	25.2

*Smooth values taken from the graph by compiler.

Dual-mode sorption parameters for CO ₂ in PSF films at 313 K			
Sample	k _D /cm ³ (STP)/cm ³ atm	C' _D /cm ³ (STP)/cm ³	b/atm ⁻¹
Cast PSF	0.813	6.61	0.155
Commercial PSF (Toraylon-PS)	0.547	18.3	0.168

Auxiliary Information	
Method/Apparatus/Procedure The apparatus and procedure for measuring sorption isotherms were described in Ref. 1.	Source and Purity of Materials: The commercial polysulfone samples Toraylon-PS (Toray Co. Ltd.) and P-1700 (Union Carbide) were used. P-1700 had the glass transition temperature 459 K. A dense PSF (P-1700) membrane was prepared by casting a mixed solution of 25.5% PSF, 55.5% N,N-dimethylacetamide, and 19.0% acetone by weight. Purity of CO ₂ not specified.

Estimated Error:
No information given.

References:
¹E. Sada, H. Kumazawa, and Y. Yoshio, *J. Polym. Sci., Polym. Phys. Ed.* **26**, 1035 (1989).

Components:	
Original Measurements:	
(1) Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]	
(2) Tetramethyl bisphenol A polysulfone (TMPSF); [32034-67-6]	
Variables:	
T/K=308	
p/MPa=0-2.0 (0-20 atm)	
Prepared By:	
Yu. P. Yampol'skii	

Experimental Data			
Dual mode sorption parameters			
Gas	k_D /cm ³ (STP)/cm ³ atm	C_2 /cm ³ (STP)/cm ³	b /atm ⁻¹
N ₂	0.225	3.74	0.0461
CO ₂	0.597	26.0	0.261
CH ₄	0.460	7.26	0.233

Method/Apparatus/Procedure	
The measurement of sorption was carried out using a pressure decay method. ¹	
Source and Purity of Materials:	
TMPSF was synthesized according to Ref. 2. It had a density 1.151 g/cc and the glass transition temperature 515 K.	
Estimated Error:	
No information given.	
References:	
¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).	
² D. K. Mohanty, Y. Sachdeva, J. L. Hedrick, J. F. Wolfe, and J. E. McGrath, Polymer Preprints, ACS, Div. Polym. Chem. 25 , 2, 19 (1984).	

Components:	
Original Measurements:	
(1) Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]	
(2) Dimethyl bisphenol A polysulfone (DMPSF); [58978-16-8]	
Variables:	
T/K=308	
p/MPa=0-2.0 (0-20 atm)	
Prepared By:	
Yu. P. Yampol'skii	

Experimental Data			
TABLE 1. Solubility of gases C /cm ³ (STP)/cm ³ in DMPSF*			
Pressure/atm			
Gas	5	10	15
N ₂	1.05	1.8	2.5
CO ₂	11.8	17.2	21.3
CH ₄	3.1	5.0	6.3

* Smoothed values taken from the plot by compiler.

TABLE 2. Dual mode sorption parameters*			
Gas	k_D /cm ³ (STP)/cm ³ atm	C_2 /cm ³ (STP)/cm ³	b /atm ⁻¹
CO ₂	0.505	17.8	0.235
CH ₄	0.135	8.64	0.0564

* Fit for nitrogen did not converge.

Method/Apparatus/Procedure	
The measurement of sorption was carried out using a pressure decay method. ¹	
Source and Purity of Materials:	
DMPSF was synthesized according to Ref. 2. It had a density 1.213 g/cc and the glass transition temperature 453 K.	
Estimated Error:	
No information given.	
References:	
¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).	
² R. N. Johnson, A. G. Farnham, R. A. Clendinning, W. F. Hale, and C. N. Merriam, J. Polym. Sci.: Part A-1 5 , 2375 (1967).	

Components: (1) Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] (2) Bisphenol F polysulfone (PSF-F); [31694-05-0]		Original Measurements: J. S. McHattie, W. J. Koros, and D. R. Paul, Polymer 32 , 2618 (1991).	
Variables: T/K=308 p/MPa=0-2.0 (0-20 atm)		Prepared By: Yu. P. Yampol'skii	
Experimental Data Dual mode sorption parameters			
Gas	k_D /cm ³ (STP)/cm ³ atm	C'_D /cm ³ (STP)/cm ³	b /atm ⁻¹
CO ₂	0.505	22.6	0.162
CH ₄	0.246	8.84	0.0571
Auxiliary Information			
Method/Apparatus/Procedure The measurement of sorption was carried out using a pressure decay method. ¹		Source and Purity of Materials: PSF-F was synthesized according to Ref. 2. It had a density 1.282 g/cc and the glass transition temperature 452 K.	
Estimated Error: No information given.		References: ¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976). ² D. K. Mohanty, Y. Sachdeva, J. L. Hedrick, J. E. Wolfe, and J. E. McGrath, Polymer Preprints, ACS, Div. Polym. Chem. 25 , 2, 19 (1984).	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Hexafluorobisphenol A polysulfone (HFPSF); [31694-07-2]		Original Measurements: J. S. McHattie, W. J. Koros, and D. R. Paul, Polymer 32 , 2618 (1991).	
Variables: T/K = 308 p/MPa = 0–2.0 (0–20 atm)		Prepared By: Yu. P. Yampol'skii	
Experimental Data Dual mode sorption parameters			
Gas	k_D /cm ³ (STP)/cm ³ atm	C'_D /cm ³ (STP)/cm ³	b /atm ⁻¹
CO ₂	0.785	21.0	0.285
CH ₄	0.180	7.32	0.146
Auxiliary Information			
Method/Apparatus/Procedure The measurement of sorption was carried out using a pressure decay method. ¹		Source and Purity of Materials: HFPSF was synthesized according to Ref. 2. It had a density 1.427 g/cc and the glass transition temperature 465 K.	
Estimated Error: No information given.		References: ¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976). ² R. N. Johnson, A. G. Farnham, R. A. Glendinning, W. F. Hale, and C. N. Merriam, J. Polym. Sci.: Part A-1 5 , 2375 (1967).	

Components:		Original Measurements:	
(1) Argon; Ar; [7440-37-1] Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Polyethersulfone (PES) Vitrex 600 P; [25667-42-9] (XLIV)		E. S. Sanders, J. Membr. Sci. 37 , 63 (1988).	
Variables:		Prepared By:	
T/K=308 p/MPa=0-4.0		Yu. P. Yampol'skii	

Experimental Data			
Dual mode sorption parameters for various gases in polyethersulfone at 308 K			
Gas	k_D /cm ³ (STP)/cm ³ atm ⁻¹	C'_D /cm ³ (STP)/cm ³	b /atm ⁻¹
Ar	0.147	7.23	0.054
CO ₂	0.631	29.78	0.313
CH ₄	0.168	10.80	0.123
N ₂	0.086	5.98	0.047

Table 2. Sorption isotherms of various gases in polyethersulfone at 308 K. (The original data were represented graphically)					
Gas	Pressure/MPa	Sorption		Sorption	
		$(V_T^g(\text{STP})/V_2^g)$		$(V_T^g(\text{STP})/V_2^g)$	
Ar	Pressure/MPa	Sorption		Sorption	
		$(V_T^g(\text{STP})/V_2^g)$		$(V_T^g(\text{STP})/V_2^g)$	
Ar	0.20	1.00	1.35	5.00	2.52
	0.32	1.48	1.47	5.26	2.67
	0.51	2.32	1.83	6.32	3.06
	0.89	3.68	1.87	6.39	3.32
	1.02	4.06	2.12	6.84	—
CO ₂	0.15	11.38	0.77	25.76	2.15
	0.18	12.79	1.07	29.37	2.21
	0.27	14.60	1.21	31.58	2.23
	0.27	15.91	1.27	31.47	2.40
	0.30	15.90	1.45	34.19	2.49
CH ₄	0.40	18.02	1.74	36.89	2.61
	0.46	20.63	1.78	36.79	2.62
	0.58	23.04	1.83	37.49	2.61
	0.69	24.75	2.09	39.90	2.86
	0.32	3.81	1.72	10.39	2.66
N ₂	0.51	5.21	1.79	10.69	2.88
	0.93	7.51	1.89	10.89	2.91
	0.97	7.71	2.35	12.28	3.31
	1.18	8.61	2.37	12.17	3.65
	0.22	0.77	1.17	3.10	2.33
N ₂	0.35	1.13	1.27	3.26	2.57
	0.45	1.35	1.41	3.58	3.02
	0.49	1.52	1.47	3.68	3.24
	0.62	1.94	1.84	4.29	3.41
	0.77	2.23	1.98	4.55	3.69
N ₂	0.89	2.52	2.23	4.87	3.91
	1.03	2.81	—	—	—

Components:		Original Measurements:	
(1) Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Dimethyl bisphenol Z polysulfone (DMPSF-Z); [134140-27-5] (XLIII)		J. S. McHattie, W. J. Koros, and D. R. Paul, Polymer 32 , 840 (1991).	
Variables:		Prepared By:	
T/K=308 p/MPa=0-2.0 (0-20 atm)		Yu. P. Yampol'skii	

Experimental Data			
Dual mode sorption parameters			
Gas	k_D /cm ³ (STP)/cm ³ atm	C'_D /cm ³ (STP)/cm ³	b /atm ⁻¹
N ₂	0.153	0.694	0.196
CO ₂	0.560	18.6	0.252
CH ₄	0.330	5.21	0.0907

Method/Apparatus/Procedure		Auxiliary Information	
The measurement of sorption was carried out using a pressure decay method. ¹		Source and Purity of Materials: DMPSF-Z was synthesized according to Ref. 2. It had a density 1.227 g/cc and the glass transition temperature 470 K.	
Estimated Error: No information given.		References: ¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976). ² D. K. Mohanty, Y. Sachdeva, J. L. Hedrick, J. E. Wolfe, and J. E. McGrath, Polymer Preprints, ACS, Div. Polym. Chem. 25 , 2, 19 (1984).	

3.27. Cellulose—Sulfur Dioxide

Components: (1) Sulfur dioxide; SO ₂ : [7446-09-5] (2) Cellulose; [9004-34-6] (XLV)		Original Measurements: G. M. Eaton, dissertation: The University of Tennessee, Knoxville, 1986.
Variables: T/K=298–323	Prepared By: Yu. P. Yampol'skii	

Experimental Data
Four types of cellulosic fibers were studied: native cellulose (ethanol extracted cotton), modified cellulose (NaOH mercerized cotton and liquid ammonia treated cotton), and regenerated cellulose (viscose rayon).

Fiber type	Sorption of sulfur dioxide by cellulose fibers (mg/g fiber)			
	Dried fiber Temperature/K			Conditioned fiber*
	298	303	308	323
Extracted cotton	9.23	8.56	11.85	7.05
Mercerized cotton	26.28	16.19	15.15	13.29
Ammonia treated cotton	18.89	10.49	5.16	1.10
Viscose rayon	3.06	0.51	0.53	—
				4.19

*The tabular data for this fiber in the dissertation appear to be inconsistent with the graphical data while the graphical data appear to be consistent with those for the dried fiber. The compiler concludes that typographical errors were made in the data table and the solubility values for the conditioned fiber were therefore taken directly from the graph by digitization. These data should therefore be considered as *highly tentative*.

Auxiliary Information	
Method/Apparatus/Procedure An exposure chamber was developed which would simulate ambient conditions. Fiber samples were dried or conditioned to 69% rel. humidity and exposed to 3 ppm sulfur dioxide for 5 h at 170 °C/min. Then the samples were exposed to a stream of dry air at the same flow rate for 4 h. The concentration of gas exiting the chamber was monitored and compared with the known concentration of gas introduced into the chamber to evaluate the amount of gas sorbed.	Source and Purity of Materials: Native cotton (Starlab, Knoxville) and unfinished rayon staple (American Enka) were studied. The cotton was extracted in a Soxhlet for 4 h, with ethanol. Mercerization was carried out in 18% solution of NaOH for 15 min at ambient temperature. The duration of ammonia treatment was 30 s 3 ppm certified standard sulfur dioxide in dry air (Matheson Co) was used.
	Estimated Error: No information given.

3.29. Ethyl Cellulose—Various Gases

Components: (1) He; Ar; N ₂ ; O ₂ ; CO ₂ ; SO ₂ ; NH ₃ ; C ₂ H ₆ ; C ₃ H ₈ ; <i>n</i> -C ₄ H ₁₀ ; (2) Ethyl Cellulose (EC); [9004-57-3] (XLVII)		Original Measurements: P. Y. Hsieh, J. Appl. Polym. Sci. 7, 1743 (1963).	
Variables: T/K: 298 p/kPa: 6–8		Prepared By: A. K. Bokarev	
Experimental Data			
Solubility coefficients of gases for ethyl cellulose films at 298 K			
Gas	Solubility coefficient/cm ³ (STP) cm ⁻³ cm Hg ⁻¹ ;		Gravimetric
	Volumetric		
(2) Helium; [7440-59-7]	—		0.0024
(3) Nitrogen; [7727-37-9]	0.0021		0.0019
(4) Oxygen; [7782-44-7]	0.0024		0.0023
(5) Argon; [7440-37-1]	0.0026		0.0025
(6) Carbon dioxide; [124-38-9]	0.0207		0.0200
(7) Sulfur dioxide; [7446-09-5]	0.4978		0.3596
(8) Ammonia; [7664-41-7]	0.605		0.484
(9) Ethane; [115-07-1]	0.0748		0.0484
(10) Propane; [74-98-6]	0.1534		0.1263
(11) <i>n</i> -Butane; [106-97-8]	0.3887		0.2655
Auxiliary Information			
Method/Apparatus/Procedure			
Both gravimetric and volumetric methods were used. In gravimetric one sorption isotherms were determined with a quartz helix microbalance. The change in elongation of the quartz helix was detected by a linear variable differential transformer, Type 060 SLB and was amplified and read by means of a linear variable differential transformer indicator, Model 300B. No details on volumetric method were given.			
Source and Purity of Materials:			
EC (T50, content ethoxy groups 49.5%) was obtained from the Hercules Powder Company. The density was 1.10 g cm ⁻³ . Gases from the Matheson Co. had the minimum purity of 99.5%, except ethane for which the purity was 99%.			
Estimated Error:			
No information given.			

3.28. Nitrocellulose—Various Gases

Components: (1) He; Ar; N ₂ ; O ₂ ; CO ₂ ; SO ₂ ; NH ₃ ; C ₂ H ₆ ; n-C ₄ H ₁₀ ; (2) Nitrocellulose; (NC); [9004-70-0] (XLVI)		Original Measurements: P. Y. Hsieh, J. Appl. Polym. Sci. 7, 1743 (1963).	
Variables: T/K: 298 p/kPa: 5.3–6.9		Prepared By: A. K. Bokarev	
Experimental Data Solubility coefficients of gases for nitrocellulose films at 298 K			
Gas	Solubility coefficient; cm ³ (STP) cm ⁻³ cm Hg ⁻¹ ;		Gravimetric
	Volumetric		
(2) Helium; [7440-59-7]	—		0.0016
(3) Nitrogen; [7727-37-9]	0.0009		0.0006
(4) Oxygen; [7782-44-7]	0.0019		0.0013
(5) Argon; [7440-37-1]	0.0016		0.0014
(6) Carbon dioxide; [124-38-9]	0.0131		0.0096
(7) Sulfur dioxide; [7446-09-5]	0.2215		0.0977
(8) Ammonia; [7664-41-7]	1.2359		0.7265
(9) Ethane; [115-07-1]	0.0533		0.0483
(10) Propane; [74-98-6]	0.0534		0.0394
(11) n-Butane; [106-97-8]	0.0248		0.0147
Auxiliary Information			
Method/Apparatus/Procedure Both gravimetric and volumetric methods were used. In gravimetric one, sorption isotherms were determined with a quartz helix microbalance. The change in elongation of the transformer, Type 060 SLB and was amplified and read by means of a linear variable differential transformer indicator, Model 300B. No details on volumetric method were given.		Source and Purity of Materials: NC from the Hercules Powder Co. had a density of 1.46 g/cm ³ . Gases from the Matheson Co. had the minimum purity of 99.5%, except ethane for which the purity was 99%.	
Estimated Error: No information given.		Estimated Error: No information given.	

Components: (1) <i>n</i> -Butane; C ₄ H ₁₀ ; [106-97-8] 2-Methylpropane; C ₄ H ₁₀ ; [75-28-5] 2,2-Dimethylpropane C ₄ H ₁₀ ; [463-82-1] (2) Ethyl Cellulose (EC); [9004-57-3] (XLVII)		Original Measurements: R. M. Barrer, J. A. Barrie, and J. Slater, J. Polym. Sci. 27 , N 115, 177 (1958). A. H. Chan, W. J. Koros, and D. R. Paul, J. Membr. Sci. 3 , 117 (1978).	
Variables: <i>T</i> /K = 303.7–353 <i>p</i> /kPa = 0–24		Prepared By: Yu. P. Yampol'skii	
Experimental Data			
TABLE 1. Enthalpies of sorption of hydrocarbon gases in ethyl cellulose			
		$-\Delta H_D$	
Gas		/kcal mol ⁻¹	/kJ mol ⁻¹
<i>n</i> -Butane		4.33	18.12
2-Methylpropane		2.01	8.41
2,2-Dimethylpropane		9.10	38.07
			3.28
			2.25
			9.36
			13.72
			9.41
			39.16

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Ethyl Cellulose (EC); [9004-57-3] (XLVII)		Original Measurements: A. H. Chan, W. J. Koros, and D. R. Paul, J. Membr. Sci. 3 , 117 (1978).	
Variables: <i>T</i> /K=308 <i>p</i> /MPa=0–2.6		Prepared By: Yu. P. Yampol'skii	
Experimental Data			
Dual mode sorption parameters for carbon dioxide in ethyl cellulose at 308 K			
k_D / cm ³ (STP) cm ⁻³ atm ⁻¹	C'_{ij} / cm ³ (STP) cm ⁻³	b /atm ⁻¹	
1.189	4.847	0.365	
Sorption isotherm of carbon dioxide in ethyl cellulose at 308 K. (The original data were represented graphically)			
Pressure/MPa	Sorption V_T^* (STP)/ V_T^*		
0.15	3.44		
0.24	5.09		
0.37	7.44		
0.66	11.50		
1.32	19.76		
1.97	27.19		
2.35	32.29		
2.62	35.59		

Method/Apparatus/Procedure Sorption apparatus used was described in Ref. 1.		Auxiliary Information	
Source and Purity of Materials: EC: Dow Chemical Co., presumed ethoxy groups content 48.6%, glass transition temperature in the region 393–398 K.		Estimated Error: No information given.	
References: ¹ W. J. Koros, and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).			

TABLE 3. Dual mode sorption parameters for gases in EC calculated by Chan *et al.* by treatment of sorption isotherms (The original data were represented graphically)

<i>T</i> /K	k_D / cm ³ (STP) cm ⁻³ cm Hg ⁻¹	C'_H / cm ³ (STP) cm ⁻³	b / cm Hg ⁻¹
<i>n</i> -C ₄ H ₁₀			
303	0.1656	3.71	0.2173
313	0.1161	3.73	0.1252
323	0.1020	2.30	0.1297
333	0.1007	1.28	0.1395
343	0.0610	1.30	0.1005
<i>iso</i> -C ₄ H ₁₀			
303	0.0909	3.34	0.1810
313	0.0614	2.94	0.0087
323	0.0978	0.75	0.4587
333	0.0552	2.03	0.0688
343	0.0698	0.51	0.1362
<i>neo</i> -C ₅ H ₁₂			
323	0.1023	1.68	0.2074
338	0.0699	1.45	0.1149
348	0.0390	2.37	0.0638
353	0.0346	1.26	0.0894

Auxiliary Information

Method/Apparatus/Procedure
A glass volumetric apparatus was employed. The sorption system was immersed in a thermostat and the pressure was read by a cathetometer.

Source and Purity of Materials
EC: Standard Ethocel, density 1.13 g/cm³, $M_n = 35\ 000$.
Estimated Error:
Relative precision: $p \pm 6.6\%$.
Precision in T : ± 0.05 K.

References:
W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. **14**, 687 (1976).

TABLE 2. Sorption isotherms of various gases in ethyl cellulose measured by Barrer *et al.* (The original data were represented graphically)

<i>n</i> -C ₄ H ₁₀		<i>iso</i> -C ₄ H ₁₀		<i>neo</i> -C ₅ H ₁₂	
Pressure/cm Hg	Sorption, 10 ³ s / (mol _l cm ₂ ⁻³)	Pressure/cm Hg	Sorption, 10 ³ s / (mol _l cm ₂ ⁻³)	Pressure/cm Hg	Sorption, 10 ³ s / (mol _l cm ₂ ⁻³)
<i>T</i> = 303.7 K					
1.78	5.86	1.93	4.38	2.80	4.00
3.57	9.75	5.20	8.79	4.91	5.70
5.69	13.27	7.06	10.87	7.23	7.61
8.82	17.26	10.86	13.70	11.23	9.65
11.71	20.58	14.80	16.35	13.62	11.19
14.53	23.22	—	—	15.40	12.52
<i>T</i> = 313.5 K					
2.56	5.34	2.77	3.83	2.12	1.77
5.18	8.81	4.59	5.81	4.10	3.20
7.81	11.87	6.85	7.65	6.65	4.63
11.61	15.34	11.59	10.82	9.68	5.99
15.14	17.88	14.52	12.42	14.34	7.52
<i>T</i> = 323.3 K					
3.60	4.82	3.54	3.38	4.87	2.69
6.70	7.78	5.79	4.98	7.86	3.81
9.99	10.47	8.39	6.61	11.15	5.13
11.51	11.30	11.15	8.04	16.15	6.38
14.50	13.17	14.04	9.30	—	—
—	—	16.16	10.01	—	—
<i>T</i> = 333 K					
2.93	2.85	2.02	1.40	2.65	1.33
4.61	4.20	4.28	2.83	5.27	2.41
8.38	6.58	7.00	4.19	8.49	3.39
12.15	8.81	10.06	5.61	11.95	4.61
14.03	9.69	13.16	6.8	15.67	5.52
—	—	15.64	7.44	—	—
<i>T</i> = 343 K					
3.57	2.33	2.39	1.12	—	—
5.62	3.42	5.11	2.34	—	—
9.99	5.49	8.24	3.53	—	—
11.57	6.12	11.67	4.62	—	—
14.43	7.36	14.93	5.66	—	—

TABLE 3. Sorption isotherms of *n*-butane in ethyl cellulose

Pressure/kPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/kPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/kPa	Sorption ($V_1^*(\text{STP})/V_2^*$)
<i>T</i> = 303 K					
1.81	1.43	<i>T</i> = 313 K			
3.11	1.99	1.76	0.93	1.76	0.61
4.36	2.46	3.10	1.36	2.96	0.91
5.75	2.97	4.44	1.78	4.44	1.20
7.09	3.42	5.79	2.15	5.73	1.48
9.86	4.19	7.08	2.48	7.07	1.71
12.55	4.87	9.81	3.05	9.75	2.19
15.27	5.48	12.44	3.61	12.39	2.59
18.00	6.03	15.21	4.09	15.16	2.99
21.93	6.83	17.94	4.60	17.79	3.34
26.09	7.63	21.91	5.24	21.86	3.93
<i>T</i> = 333 K					
1.71	0.38	25.93	5.83	25.97	4.46
3.05	0.63	<i>T</i> = 343 K			
4.21	0.82	1.66	0.26		
5.59	1.03	2.96	0.42		
6.93	1.22	4.25	0.57		
9.61	1.55	5.77	0.71		
12.38	1.87	6.97	0.81		
15.20	2.19	9.70	1.09		
17.83	2.51	12.38	1.35		
21.80	2.98	15.15	1.61		
25.87	3.45	17.78	1.85		
		21.89	2.19		
		25.90	2.57		

TABLE 4. Sorption isotherms of ethane in EC at various temperatures

Pressure/kPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/kPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/kPa	Sorption ($V_1^*(\text{STP})/V_2^*$)
<i>T</i> = 303 K					
2.99	0.11	<i>T</i> = 313 K			
5.67	0.23	2.88	0.09	2.80	0.08
8.33	0.36	5.60	0.19	5.64	0.15
11.02	0.47	8.40	0.29	8.30	0.22
13.63	0.58	11.02	0.38	10.99	0.29
17.65	0.74	13.68	0.46	13.65	0.36
25.87	1.08	17.66	0.59	17.63	0.46
<i>T</i> = 333 K					
2.99	0.07	25.84	0.85	25.82	0.66
5.61	0.12	<i>T</i> = 343 K			
8.26	0.18	2.95	0.06		
10.92	0.24	5.57	0.10		
13.50	0.29	8.26	0.14		
17.56	0.38	11.03	0.20		
25.82	0.55	13.50	0.23		
		17.60	0.30		
		25.72	0.44		

Components:		Original Measurements:	
(1) Ethane: C ₂ H ₆ ; [15-07-1] Propane: C ₃ H ₈ ; [74-98-6]		E. Casur and T. G. Smith, J. Appl. Polym. Sci. 31 , 1425 (1986).	
<i>n</i> -Butane: C ₄ H ₁₀ ; [106-97-8]			
(2) Ethyl Cellulose (EC); [9004-57-3] (XLVII)			
Variables:		Prepared By:	
<i>T</i> /K = 303–343		A. K. Bokarev	
<i>p</i> /kPa = 0–26			

Experimental Data				
TABLE 1. Dual mode sorption parameters for various gases in ethyl cellulose				
Gas	<i>T</i> /K	<i>k</i> _D /cm ³ (STP) cm ³ cm Hg ^{−1}	<i>C</i> _H ⁺ /cm ³ (STP) cm ^{−3}	<i>b</i> /cm Hg ^{−1}
C ₂ H ₆	303	0.0476	0.348	0.0349
	313	0.0378	0.300	0.0307
	323	0.0295	0.299	0.0225
	333	0.0248	0.280	0.0179
	343	0.0199	0.250	0.0169
C ₃ H ₈	349	0.1181	0.4251	0.4251
	303	0.1319	0.479	0.2914
	313	0.1012	0.295	0.2601
	323	0.0769	0.217	0.2347
	333	0.0613	0.096	0.3280
C ₄ H ₁₀	343	0.0493	0.089	0.3267
	303	0.2282	3.718	0.3128
	313	0.1884	2.650	0.2684
	323	0.1635	1.577	0.2645
	333	0.1439	0.809	0.3043
	343	0.1181	0.303	0.4251

TABLE 2. Heats of sorption in ethyl cellulose/(kcal/mol). Values obtained from van't Hoff plots for <i>k</i> _D , <i>b</i> and the solubility coefficient <i>S</i> (<i>S</i> = <i>k</i> _D − <i>C</i> _H ⁺ / <i>b</i>), respectively				
Gas	Δ <i>H</i> _D	Δ <i>H</i> _H	Δ <i>H</i> _S	
Ethane	−4.46	−4.12	−4.68	
Propane	−5.10	−2.10	−7.13	
<i>n</i> -Butane	−3.27	−1.65	−8.46	

(For Tables 3, 4 and 5, the original data were represented graphically.)

3.30. Cellulose Acetate—Carbon Dioxide

Components:		Evaluator:			
(1) Carbon dioxide, CO ₂ ; [124-38-9]		Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994			
(2) Cellulose acetate (CA); [9004-35-7] (XLVIII)					
Critical Evaluation:					
Three papers are available on the system cellulose acetate-carbon dioxide. ¹⁻³ In all the cases the degree of esterification and the origin of the samples were the same: CA obtained from Eastman Kodak Co. contained 39.8% of acetyl groups. Stern and De Meringo ¹ studied sorption of CO ₂ in CA at 273-343 K and reported the dual mode sorption parameters for somewhat narrower range of temperature. In a subsequent paper ² of the same group the reported isotherm at 303 K was confirmed, but no sorption parameters were given. Sada <i>et al.</i> ³ studied the sorption in the temperature range 293-313 K. The table summarizes the sorption parameters found in Refs. 1 and 3 for this system. It can be seen that there is a reasonable agreement for Henry's law solubility coefficient k_D , but not for other two model parameters. The C'_H and b values reported in both papers monotonously decrease with temperature, but there is a significant discrepancy between two sets of values.					
Dual mode sorption parameters at different temperatures					
T/K	k_D	C'_H	b	$S = k_D + C'_H b$	Ref.
273.2	3.4	44.57	0.511	26.2	1
283.2	2.9	35.26	0.441	18.5	1
293.2	1.83	22.7	0.500	13.2	3
302.9	1.24	20.3	0.437	10.1	3
303.2	1.24	42.6	0.134	6.9	1
313.2	1.10	17.7	0.280	6.0	3
318.2	0.79	36.5	0.107	4.7	1

Units: k_D and $S/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$; $C'_H/\text{cm}^3(\text{STP})\text{cm}^{-3}$; b/atm^{-1}

The temperature dependencies of S and k_D are shown in Figs. 67 and 68.

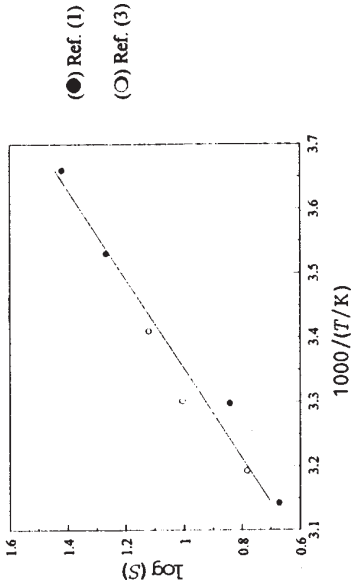


FIG. 67. Temperature dependence of apparent solubility coefficient $S'/(\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1})$.

TABLE 5. Sorption isotherms of propane in EC at various temperatures

Pressure/kPa	Sorption ($V^*_g(\text{STP})/V^*_g$)	Pressure/kPa	Sorption ($V^*_g(\text{STP})/V^*_g$)	Sorption ($V^*_g(\text{STP})/V^*_g$)
$T=303\text{ K}$				
4.40	0.60	4.37	0.44	0.42
5.77	0.81	5.62	0.57	0.60
7.10	0.99	7.07	0.72	0.78
9.80	1.31	9.81	0.92	0.97
12.51	1.61	12.43	1.20	1.20
15.17	1.92	15.14	1.39	1.44
17.83	2.17	17.80	1.60	1.68
21.94	2.56	21.84	1.92	—
25.94	2.92	25.98	2.22	—
$T=333\text{ K}$				
5.70	0.30	5.66	0.25	—
8.33	0.45	8.33	0.34	—
11.03	0.58	10.92	0.46	—
13.73	0.71	13.70	0.57	—
17.73	0.91	17.66	0.73	—
21.88	1.09	21.84	0.88	—
25.95	1.28	25.95	1.05	—

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
Sorption was determined by a gravimetric method using a Cahn microbalance (Model KG). Corrections were made for buoyancy effects.	Gases: purity 99.99%.
	EC (Ethocel 10 cp): Dow Chemical Co., contained 48%–49.5% ethoxy groups, density 1.13 g/cm ³ , glass transition temperature 396 K.
Estimated Error:	No information given.

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124:38-9]		S. A. Stern and A. H. De Meringo, J. Polym. Sci., Polym. Phys. Ed. 16, 735 (1978).	
(2) Cellulose 2,4-acetate (CA); [9004:35-7] (XLVIII)			
Variables:		Prepared By:	
T/K = 273.0–343.0		A. K. Bokarev	
p/MPa = 0–4.0			
Experimental Data			
Dual mode sorption parameters for carbon dioxide in cellulose 2,4-acetate			
T/K	k_D /cm ³ (STP) g ⁻¹ atm ⁻¹	C_H /cm ³ (STP) g ⁻¹	b /atm ⁻¹
273.0	2.50	32.77	0.511
283.0	2.13	25.93	0.441
303.0	0.911	31.31	0.134
318.0	0.580	26.81	0.107

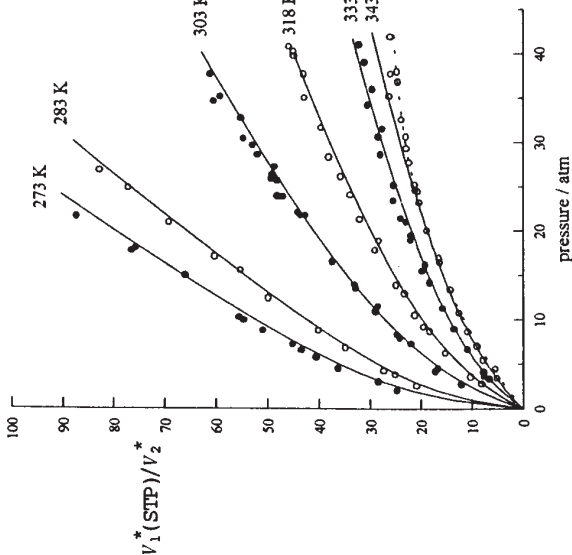


FIG. 69. Sorption isotherms of carbon dioxide. Continuous curves: Gas solubilities calculated from the dual mode sorption model. Dotted curve: Gas solubility at 343 K calculated from the empirical relation $C = 1.4p \exp(-0.02p)$.

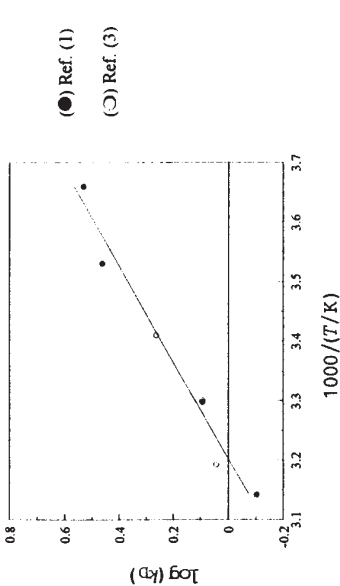


FIG. 68. Temperature dependence of Henry's law solubility coefficient k_D / (cm³(STP) cm⁻³ atm⁻¹).

From the temperature dependence of k_D and S it was found, respectively,

$$\log(S/(\text{cm}^3(\text{STP})\text{cm}^{-3} \text{ atm}^{-1})) = -3.8226 + 1438.7/(T/\text{K})$$
$$\log(k_D/(\text{cm}^3(\text{STP})\text{cm}^{-3} \text{ atm}^{-1})) = -3.9595 + 1236.3/(T/\text{K})$$
$$\Delta H_D = -23.7 \pm 1.8 \text{ kJ/mol}$$
$$\Delta H_S = -27.5 \pm 2.3 \text{ kJ/mol}$$

It is difficult to give much credit to the parameters reported in any of these works. Nevertheless, as one may tentatively suspect the effects of exposing the polymer to high pressure of CO₂ as a main reason for these differences, the data of Sida *et al.*³ should be regarded as describing the sample "as received," while those of Stern and De Meringo¹ as characterizing the polymer swollen in high pressure gas. Much larger values of the Langmuir capacity parameter C_H are typical for such samples.

References:

¹S. A. Stern and A. H. De Meringo, J. Polym. Sci., Polym. Phys. Ed. 16, 735 (1978).

²S. A. Stern and S. S. Kuikarni, J. Membr. Sci. 10, 235 (1982).

³E. Sida, H. Kumazawa, Y. Yoshio, S.-T. Wang, and P. Xu, J. Polym. Sci., Part B: Polym. Phys. 26, 1035 (1988).

Auxiliary Information

Method/Apparatus/Procedure

A volumetric method was used in measurement of the solubility. The gas pressure decay with time was followed by means of a gauge. Corrections for the equation of state of CO₂ were made according to Ref. 1.

Source and Purity of Materials:

CO₂: purity 99.9%
C/A: Eastman Kodak, Trademark Edukit; content of acetyl groups 39.8%, density 1.36 g/cm³.

Estimated Error:

Standard error of estimate of CO₂ concentration: from 5.5% at 273 K to 14% at 343 K.

References:

¹N. E. Van Huff, G. Houghton, and J. Coull, J. Chem. Eng. Data **8**, 336 (1963).

Components:

(1) Carbon dioxide; CO₂; [124-38-9] Methane; CH₄; [74-82-8]
(2) Cellulose 2,4-acetate (CA); [9004-35-7] (XLVIII)

Original Measurements:

S. A. Stern and S. S. Kulkarni, J. Membr. Sci. **10**, 235 (1982).

Variables:

T/K=263–303

Prepared By:

A. K. Bokarev

p/MPa=0–4 (0–40 atm)

Experimental Data

TABLE 1. Dual mode sorption parameters for methane in cellulose 2,4-acetate (sample I)

T/K	k_D /cm ³ (STP) cm ⁻³ atm ⁻¹	C'_H /cm ³ (STP) cm ⁻³	b /atm ⁻¹
303	0.024±0.035	10.03±2.99	0.052±0.016
293	0.067±0.018	8.32±1.21	0.076±0.013
288	0.083±0.061	8.35±3.54	0.087±0.043
283	0.099±0.019	8.22±1.14	0.109±0.022
273	0.101±0.043	10.22±2.71	0.104±0.040
263	0.119±0.028	11.48±1.61	0.117±0.024

Heats of solution of CH₄ in cellulose 2,4-acetate (sample I)

Apparent heat of ordinary dissolution: $\Delta H_D = -5.4$ kcal/mol; -22.6 kJ/mol.

Apparent heat of "hole-filling": $\Delta H_H = -2.9$ kcal/mol; -12.1 kJ/mol.

Solubility=(vol. of gas at STP/cm³)/(mass of unswollen polymer /g)

TABLE 2. Solubility isotherm of carbon dioxide in cellulose 2,4-acetate (sample II) at 303 K (The original data were represented graphically)

Time sequence	Pressure/MPa	Solubility (V_1^* (STP)/m ₂ [*])	Time sequence	Pressure/MPa	Solubility (V_1^* (STP)/m ₂ [*])
1	2.07	38.80	5	2.61	43.70
2	0.97	25.63	6	2.53	42.21
3	0.57	18.13	7	—	—
4	2.67	44.60	—	—	—

TABLE 3. Effect of CO₂ exposure on the solubility isotherm of CH₄ in cellulose 2,4-acetate at 293 K (The original data were represented graphically)

Sample I, after exposure to CO ₂			Sample III, prior to exposure to CO ₂		
Pressure/MPa	Solubility (V_1^* (STP)/m ₂ [*])	Time sequence	Pressure/MPa	Solubility (V_1^* (STP)/m ₂ [*])	Time sequence
0.47	2.56	1	1.80	3.73	1
0.68	3.41	2	2.50	4.12	2
1.03	4.39	3	0.83	2.65	3
1.51	5.45	4	0.30	1.43	4
1.68	5.84	5	2.13	4.00	5
2.15	6.59	6	0.58	2.28	6
2.48	7.04	7	2.81	4.34	7
2.83	7.56	8	1.28	3.25	8
3.12	7.93	9	1.43	3.26	9
3.59	8.43	10	3.22	4.71	10
—	—	11	3.79	4.89	11
—	—	12	2.55	4.22	12

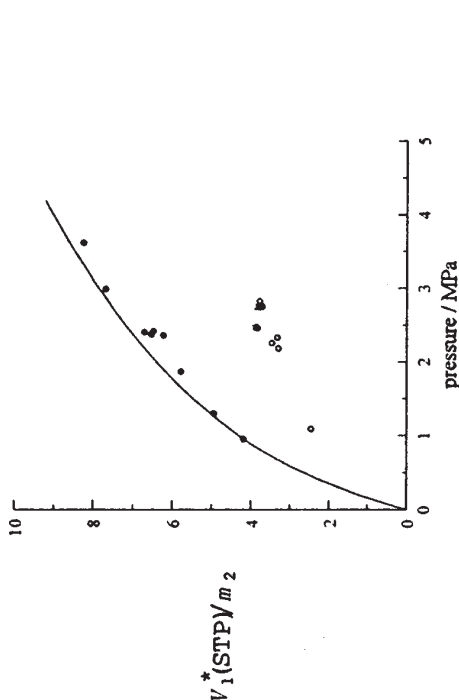


FIG. 71. Reproducibility of solubility isotherms of methane in cellulose 2,4-acetate at 293 K. Solubility = (vol. of gas at STP/cm³)/(mass of unswollen polymer/g). (Solid line) calculated from the dual mode sorption model with sample I, after exposure to CO₂. (O) measurements with sample II prior to CO₂ exposure. (●) measurements with sample II after exposure to high-pressure CO₂.

Polymer sample	k_D / cm ³ (STP) cm ⁻³ atm ⁻¹	C'_H / cm ³ (STP) cm ⁻³	b / atm ⁻¹
Sample I after CO ₂ exposure	0.067 ± 0.018	8.32 ± 1.21	0.076 ± 0.013
Sample II prior CO ₂ exposure	0.046 ± 0.033	3.09 ± 2.92	0.159 ± 0.070
Sample II after CO ₂ exposure	0.082 ± 0.019	6.23 ± 2.27	0.120 ± 0.059
Sample III prior CO ₂ exposure	0.038 ± 0.019	4.12 ± 1.62	0.151 ± 0.031

The fact that the Henry's law dissolution was found to be more exothermic than Langmuir "hole-filling" process lead the authors to test a different type of sorption isotherm—"two Langmuir sorption model", proposed by Vieth *et al.*²

$$C = C'_H(1/b(1)p/[1 + b(1)p] + C'_L(2)b(2)p/[1 + b(2)p]).$$

The parameters of this model are presented in Table 5.

TABLE 5. "Two Langmuir sorption model" parameters

T/K	$C'_H(1)$ / cm ³ (STP) g ⁻¹	$C'_L(2)$ / cm ³ (STP) cm ⁻³	$b(1)$ / atm ⁻¹	$b(2)$ / atm ⁻¹
303	12.09	2.76	0.021	0.126
293	14.14	3.18	0.020	0.146
288	15.11	3.56	0.020	0.158
283	16.26	4.39	0.018	0.165
273	17.21	5.01	0.021	0.177
263	20.61	6.03	0.018	0.220

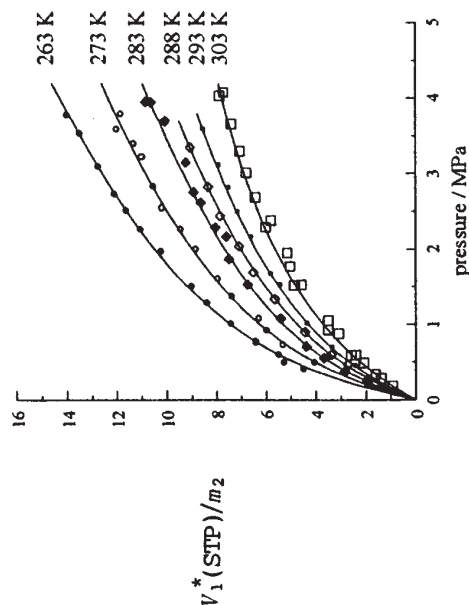


FIG. 70. Solubility isotherms of methane in cellulose 2,4-acetate (sample I). Solubility = (vol. of gas at STP/cm³)/(mass of unswollen polymer/g).

Method/Apparatus/Procedure
The solubility of CO₂ and CH₄ in cellulose 2,4-acetate was measured by a volumetric method. The apparatus and experimental procedure used have been described in Ref. 1.

Auxiliary Information

Source and Purity of Materials:

CO₂: Matheson, purity 99.99% CH₄: Matheson, purity 99.97%
CA: Eastman Kodak Co., density 1.36 g/cm³. Sample I: previously exposed to carbon dioxide in the temperature range from 273 to 343 K and at pressure up to 45 atm.

Estimated Error:

Relative precision of solubilities: CO₂ 10%, CH₄ between 16% and 20%.

References:

- S. A. Stern and A. H. De Meringo, J. Polym. Sci., Polym. Phys. Ed. **16**, 735 (1978).
- W. R. Vieth and M. A. Amiri, Ind. Eng. Chem. Fundam. **16**, 82 (1977).

3.31. Poly(γ -Methyl Glutamate)—Carbon Dioxide

Components:	
Original Measurements:	
(1) Xenon: Xe; [7440-63-3] Carbon dioxide: CO ₂ ; [124-38-9]	T. Yoshida, A. Takizawa, and Y. Tsujita, <i>J. Appl. Polym. Sci.</i> 22 , 279 (1978).
(2) Poly(γ -methyl-L-glutamate) (PMG); [25086-16-2] (XLIX)	
Variables:	
$T/K = 293-308$	Prepared By:
$p/\text{kPa} = 6.6-52.5$	Yu. P. Yampol'skii

Experimental Data

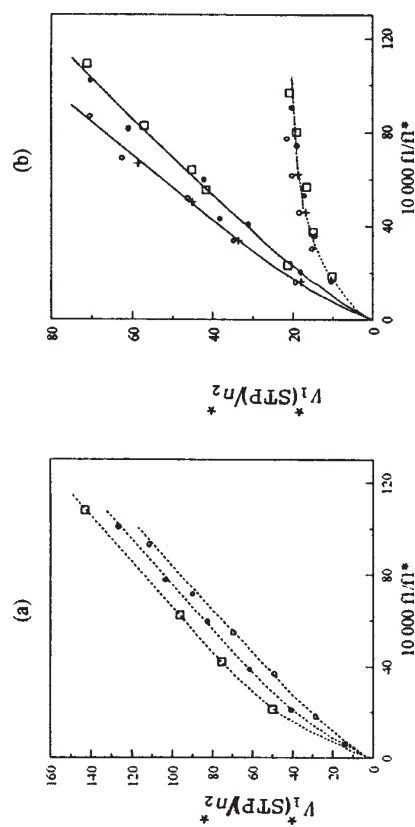


Fig. 73. Sorption isotherms of carbon dioxide (a) and xenon (b) in PMG. Sorption = (vol. of gas at STP/cm³)/mol of residue. (□) 293 K, (●) 298 K, (○) 303 K, (+) 308 K. Broken line is heat treated sample.

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials:
Cahn microbalance was used to determine sorption. Fugacity ratio was calculated by means of corresponding state principle. ^{1,2}	PMG: Kyowa Hakko K. K.; viscosity average degree of polymerization about 1150.

Estimated Error:
Weight determination accuracy: ± 10 mg for 50–100 mg samples. Precision in T : ± 0.5 K.

References:
¹T. H. Hildebrand and R. Scott, *The Solubility of Nonelectrolytes* (New York, 1964).
²T. M. Prusnitz, *J. Phys. Chem.* **66**, 640 (1962).

Components:	
Original Measurements:	
(1) Carbon dioxide: CO ₂ ; [124-38-9]	E. Sada, H. Kumazawa, Y. Yoshio, S.-T. Wang, and P. Xu, <i>J. Polym. Sci., Part B: Polym. Phys.</i> 26 , 1035 (1988).
(2) Cellulose Acetate (CA); [9004-35-7] (XLVIII)	
Variables:	
$T/K = 293-313$	Prepared By:
$p/\text{MPa} = 0-1.5$	Yu. P. Yampol'skii

Experimental Data

Dual mode sorption parameters for carbon dioxide in cellulose acetate			
T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H^*/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
293	1.83	22.7	0.500
302	1.24	20.3	0.437
313	1.10	17.7	0.280

$\Delta H_H = -22.7$ kJ/mol; $\Delta H_D = -17.8$ kJ/mol.

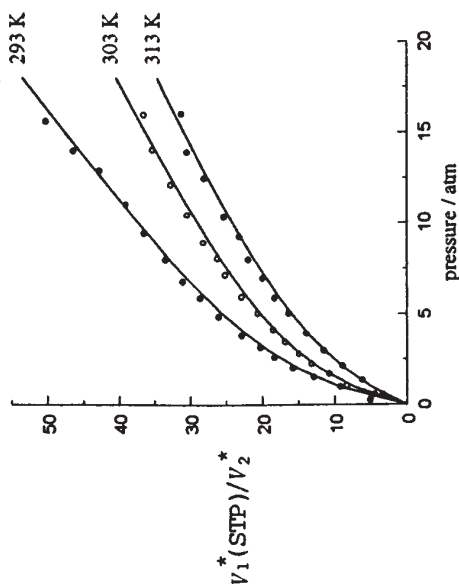


Fig. 72. Sorption isotherms of carbon dioxide in cellulose acetate.

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials:
Sorption was measured by the pressure decay method. The procedure and apparatus were similar to those described in Ref. 1.	CA: Eastman Kodak (E 398-3); content of acetyl groups 39.8%. The film cast from acetone solution was annealed in a water bath at 363 K for 10 min. The film was dried in vacuum for 24 h before measurement of sorption.

Estimated Error:
No information given.

References:
¹W. J. Koros, D. R. Paul, and A. A. Rocha, *J. Polym. Sci., Polym. Phys. Ed.* **14**, 667 (1976).

Auxiliary Information	
Method/Apparatus/Procedure	Method of sorption measurement was described in Ref. 1.
Source and Purity of Materials:	PMG: Ajimoto Co.; $M_w = 100\,000$. Films were cast from CHCl_3 , DMFA, mixture of DMFA and CH_2Cl_2 . PMG in β -form was cast from CH_2Cl_2 , then treated by 80% water solution of HCOOH and dried.
Estimated Error:	No information given.
References:	¹ H. Kodama, Y. Tsujita, and A. Takizawa, J. Macromol. Sci., Phys. 17 , 57 (1980).

Original Measurements:	
(1) Carbon dioxide; CO_2 ; [124-38-9]	Y. Tsujita, T. Sumitomo, M. Nomura, and A. Takizawa, J. Appl. Polym. Sci. 30 , 2723 (1985).
(2) Poly(γ -methyl-L-glutamate) (PMG); [25086-16-2] (XLIX)	
Prepared By:	
Yu. P. Yampol'skii	
Variables:	
$T/\text{K} = 298-308$	
$p/\text{kPa} = 0-40$	

Experimental Data	
Different forms of PMG: PMG cast from chloroform (C), dimethyl-formamide (D), mixture of methylene chloride-dimethyl-formamide (D-D), and β -form of PMG (β).	
Sorption = (vol. of gas at STP (cm^3)/mol of residue.	

TABLE 1. Parameters of Langmuir equation $p/n = 1/ab + p/b$

Sample	$a/(\text{cm Hg})^{-1}$	$b/(\text{cm}^3(\text{STP}) \text{mol}^{-1})$
C	0.036	660
D	0.022	370
D-D	0.035	480
β	0.018	371

TABLE 2. Sorption isotherms of carbon dioxide in the different forms of PMG at (a) 298 K and (b) 308 K (The original data were represented graphically)

	Fugacity ratio $10^4 f_1/f_1^s$	Sorption $(V^s(\text{STP})/n_2^s)$	Fugacity ratio $10^4 f_1/f_1^s$	Sorption $(V^s(\text{STP})/n_2^s)$	Fugacity ratio $10^4 f_1/f_1^s$	Sorption $(V^s(\text{STP})/n_2^s)$
(a)						
Form C	12.25	106.36	46.00	219.72	70.69	286.40
	21.64	145.08	54.17	242.58	84.52	319.70
	38.96	198.34	63.06	260.50	—	—
Form D-D	22.01	115.18	—	—	—	—
	39.50	165.03	—	—	—	—
	59.01	210.67	—	—	—	—
Form D	7.44	25.15	29.91	66.93	61.01	116.04
	11.64	40.93	38.41	82.59	72.12	132.77
	21.07	56.57	48.98	101.98	83.78	146.08
Form β	13.50	38.99	39.25	69.33	70.51	113.90
	23.29	52.73	51.88	89.04	83.85	129.05
	30.99	60.47	62.23	102.39	—	—
(b)						
Form C	22.53	138.62	56.05	244.8	73.47	283.50
	39.48	191.14	65.70	265.73	84.10	312.15
Form D-D	18.18	100.53	53.91	172.97	92.31	254.05
	36.17	140.91	71.55	217.15	—	—
Form D	19.94	54.33	39.92	85.58	64.36	115.19
	29.74	70.33	52.90	102.26	—	—

Components:	
(1) Xenon; Xe; [7440-63-3]	Original Measurements: T. Yoshida, A. Takizawa, and Y. Tsujita, <i>J. Appl. Polym. Sci.</i> 22 , 279 (1978).
(2) Poly(<i>n</i> -alkyl- <i>L</i> -glutamates) (LI)	
Variables:	
$T/K=293$	Prepared By: Yu. P. Yampol'skii
$p/\text{kPa}=6.6-52.5$	

Experimental Data

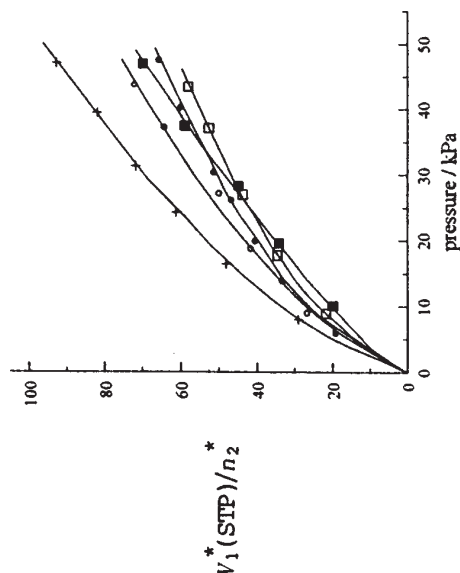


FIG. 75. Sorption isotherms of xenon in poly(*n*-alkyl-*L*-glutamates) at 298 K. Sorption = (vol. of gas at STP/cm³)/mol of residue. (■) Me, (□) Et, (●) Pr, (△) Bu, (▲) Amyl.

Method/Apparatus/Procedure	
Cahn electrobalance was used to measure sorption. Corresponding state principle was applied for calculation of fugacity ratio. ^{1,2}	
Source and Purity of Materials	
Xe: purity 99.999%. Poly(<i>n</i> -alkyl- <i>L</i> -glutamates) and alkyls C ₃ -C ₅ : prepared according to Ref. 3 by ester exchange method. Other alkyl derivatives: Kyowa Hakko K. K. and Ajimoto Co.; degree of polymerization 1150.	
Estimated Error:	
Weight determination accuracy: ±10 mg for 50–100 mg samples. Precision in T : ±0.5 K.	
References:	
¹ T. H. Hildebrand and R. Scott, <i>The Solubility of Nonelectrolytes</i> (New York, 1964).	
² T. M. Praisnitz, <i>J. Phys. Chem.</i> 66 , 640 (1962).	
³ A. Takizawa, H. Okada, S. Kadota, and H. Nonomura, <i>J. Appl. Polym. Sci.</i> 18 , 1443 (1974).	

Components:	
(1) Xenon; Xe; [7440-63-3]	Original Measurements: T. Yoshida, A. Takizawa and Y. Tsujita, <i>J. Appl. Polym. Sci.</i> 22 , 279 (1978).
(2) Poly(γ -ethyl-L-glutamate) (PELG); [25189-52-0] (LI)	
Variables:	
$T/K=293-308$	Prepared By: Yu. P. Yampol'skii
$p/\text{kPa}=6.6-52.5$	

Experimental Data

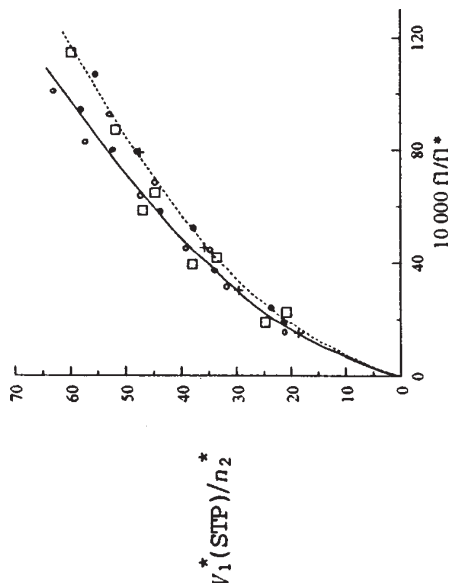


FIG. 74. Sorption isotherms of xenon in PELG. Sorption = (vol. of gas at STP/cm³)/mol of residue. (□) 293 K, (●) 298 K, (○) 303 K, (+) 308 K. Broken line is heat treated sample.

Method/Apparatus/Procedure	
Cahn electrobalance was used to measure sorption. Corresponding state principle was applied for calculation of fugacity ratio. ^{1,2}	
Source and Purity of Materials	
Xe: purity 99.999%. PELG: Ajinomoto K. K.; viscosity average degree of polymerization about 1150.	
Estimated Error:	
Weight determination accuracy: ±10 mg for 50–100 mg samples. Precision in T : ±0.5 K.	
References:	
¹ T. H. Hildebrand and R. Scott, <i>The Solubility of Nonelectrolytes</i> (New York, 1964).	
² T. M. Praisnitz, <i>J. Phys. Chem.</i> 66 , 640 (1962).	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(γ -benzyl-L-glutamate) (PBLG); [25014-27-1] (LII)		Original Measurements: Y. Ohashi, H. Hamano, T. Yoshida, Y. Tsujita, and A. Takizawa, <i>J. Appl. Polym. Sci.</i> 22 , 1469 (1978). T. Yoshida, A. Takizawa, and Y. Tsujita, <i>J. Appl. Polym. Sci.</i> 22 , 279 (1978).	
Variables: $T/K=293-308$ $p/kPa=6.6-52.5$		Prepared By: Yu. P. Yampol'skii	

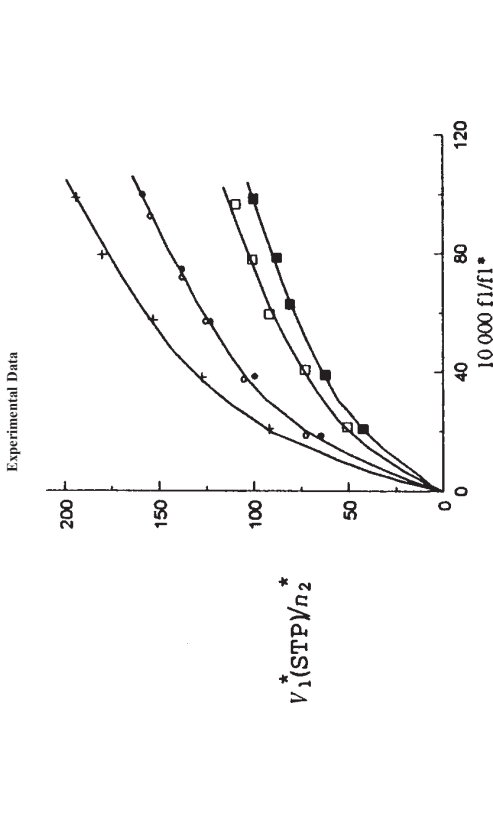


FIG. 76. Fugacity ratio calculated by corresponding state principle, Refs. 1,2. Sorption=(vol. of gas at STP/cm³)/mol of residue. Sorption isotherms of carbon dioxide in PBLG, (●) PBLG cast from benzene at 318 K, (○) same film heat treated, (■) PBLG cast from benzene at 333 K, (□) same film heat treated, (+) cast from ethylene dichloride at 298 K.

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(γ -octyl-L-glutamate)		Original Measurements: T. Yoshida, A. Takizawa, and Y. Tsujita, <i>J. Appl. Polym. Sci.</i> 22 , 279 (1978).	
Variables: $T/K=293-303$ $p/kPa=6.6-52.5$		Prepared By: Yu. P. Yampol'skii	

Experimental Data			
Sorption isotherms of carbon dioxide in poly(γ -octyl-L-glutamate) based on fugacity. (The original data were represented graphically.) Sorption=vol. of gas at STP/mol of polymer (cm ³ (STP)/n polymer)			
$T=293\text{ K}$		$T=298\text{ K}$	
Fugacity ratio $10^4 f_1/f_1^0$	Sorption (cm ³ mol ⁻¹)	Fugacity ratio $10^4 f_1/f_1^0$	Sorption (cm ³ mol ⁻¹)
15.38	89.52	13.27	78.75
32.19	119.68	27.16	114.45
52.59	153.57	44.05	131.26
73.39	181.53	60.92	150.66
—	—	78.14	173.40
—	—	—	170.74

Method/Apparatus/Procedure A. Cahn electrobalance was used to measure the sorption.		Auxiliary Information	
Source and Purity of Materials: CO ₂ : purity 99.999% Poly(γ -octyl-L-glutamate): prepared according to Ref. 1 by a ester exchange method.		Estimated Error: Weight determination accuracy: ± 10 mg for 50–100 mg sample. Relative precision in T : ± 0.5 K.	
References: 1. A. Takizawa, H. Okada, S. Kadota, and H. Nonovama, <i>J. Appl. Polym. Sci.</i> 18 , 1443 (1974).			

Method/Apparatus/Procedure Cahn electrobalance was used to measure sorption.		Auxiliary Information	
Source and Purity of Materials: PBLG: prepared by benzylolation of L-glutamic acid with subsequent polymerization. The degree of polymerization was always 1200, except the sample cast from ethylene dichloride where it was equal to 550. Heat treatment was performed at 413 K for several hours.		Estimated Error: Weight determination accuracy: ± 10 mg for 50–100 mg samples. Precision in T : ± 0.5 K.	
References: 1. T. H. Hildebrand and R. Scott, <i>The Solubility of Nonelectrolytes</i> (New York, 1964). 2. T. M. Prausnitz, <i>J. Phys. Chem.</i> 66 , 640 (1962).			

3.32. Poly(β -Benzyl-L-Aspartate)—Carbon-Dioxide

Components:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]	Original Measurements: H. Kodama, Y. Tsujita, and A. Takizawa, J. Macromol. Sci. Phys. B 17, 57 (1980).
(2) Poly(β -benzyl-L-aspartate) (PBLA) (LIII)	
Variables:	
$T/K=303-313$	Prepared By: Yu. P. Yampol'skii
$p/\text{kPa}=9.3-43.9$	

Experimental Data

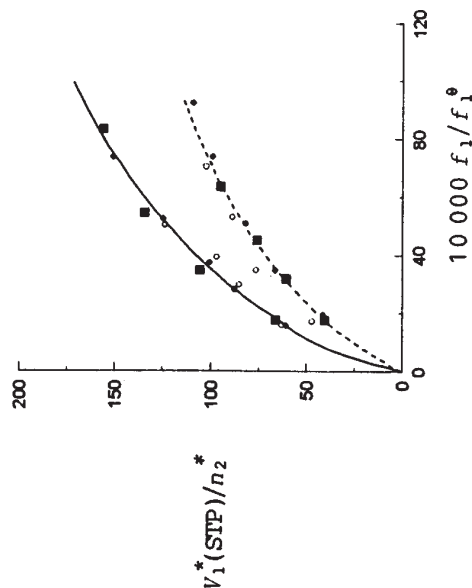


FIG. 77. Sorption isotherms of carbon dioxide in the α and ω forms of PBLA. Sorption=(vol. of gas at STP/cm³)/mol of residue. ($\bullet$) 303 K, ($\circ$) 313 K. Continuous line: α form; broken line: ω form.

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials
Sorption measurements were performed by means of electrobalance Cahn RG.	PBLA: $M_w=12\ 000$. Hexagonal or α -form: prepared by casting from 4 mass % CHCl ₄ solution. Tetragonal or ω -form: prepared by annealing of α -form films at 423 K.
Estimated Error: No information given.	

Components:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]	Original Measurements: S. Vivatbanachart, Y. Tsujita, and A. Takizawa, Makromol. Chem. 182, 1197 (1981).
(2) Poly(γ -benzyl-L-glutamate) (PBG); [25014-27-1] (LII)	
Variables:	
$T/K=283$	Prepared By: S. M. Shishatskii
$p/\text{kPa}=6.5-46$	

Experimental Data

The sorption isotherms can be presented by the Langmuir equation:

$$p/n = 1/(ab + p/b),$$

where p is pressure and n is the volume of carbon dioxide in cm³(STP)/mol of residue. The parameters have the following values:
 $b=0.065\text{ cm}^3(\text{STP})/\text{residue}$, $a=250\text{ cm Hg}^{-1}$.

Auxiliary Information

Method/Apparatus/Procedure	Source and Purity of Materials
The method of sorption determination was the same as described in Ref. I.	Racemic PBG was obtained by dissolution of equal amounts of L and D forms of the polymer. Both forms were prepared by polymerization of corresponding N-carboxyanhydrides.
Estimated Error: No information given.	
References: ¹ H. Kodama, Y. Tsujita, and A. Takizawa, J. Macromol. Sci. Phys. 17, 57 (1980).	

TABLE 3. Sorption and desorption isotherms of hydrogen chloride in nylon at 273 and 293 K

T = 273 K						T = 293 K					
Sorption			Desorption			Sorption			Desorption		
Pressure/kPa	Solubility (10 ³ m ₁ /m ₂)		Pressure/kPa	Solubility (10 ³ m ₁ /m ₂)		Pressure/kPa	Solubility 1000 m ₁ /m ₂		Pressure/kPa	Solubility (10 ³ m ₁ /m ₂)	
0	81.7		0	289.2		0	142.4		0.34	307.9	
0	183.8		7.23	400.1		0	257.2		2.93	347.1	
4.13	395.1		—	—		5.17	360.4		—	—	
12.57	445.4		—	—		14.3	392.9		—	—	
26.35	480.7		—	—		33.42	416.1		—	—	
54.09	505.0		—	—		66.83	442.6		—	—	
91.29	524.3		—	—		108.00	464.7		—	—	
111.45	530.9		—	—		—	—		—	—	

Sorption isotherms of ammonia and hydrogen chloride at lower temperature exhibit hysteresis (sorption curves are below desorption curves). It vanishes for the sorption of hydrogen chloride at 273 and 293 K.

Method/Apparatus/Procedure		Auxiliary Information	
Sorption measurements were made using a McBain type microbalance described in Ref. 1.		Source and Purity of Materials: NH ₃ : purity 99.9%, traces of water removed by melted sodium. HCl: liberated by dropping hydrochloric acid into sulfuric acid; water vapor removed by P ₂ O ₅ trap, redistilled using dry CO ₂ /acetone bath. Nylon 6,6: undrawn bright yarn contained 0.02% of TiO ₂ .	
Estimated Error: No information given.		References: 1. L. H. Ryerson and J. H. Honig, J. Amer. Chem. Soc. 75 , 3925 (1953).	

3.33. Polyamides (Nylons)—Various Gases

Components:		Original Measurements:	
(1) Hydrogen chloride; HCl; [7647-01-0] Ammonia; NH ₃ ; [7664-41-7]		L. H. Ryerson and L. E. Peterson, J. Phys. Chem. 60 , 1172 (1956).	
(2) Poly(hexamethylene adipinamide) (Nylon 66); [32131-17-2] (LIV)		Prepared By: Yu. P. Yampol'skii	
Variables: T/K = 194.3–303.6 p/kPa = 0–120			

Experimental Data
(For the following tables the original data were represented graphically.)
Relative pressure= ratio of partial pressure and its saturated vapor pressure at the temperature of the experiment.

TABLE 1. Sorption and desorption isotherms of ammonia in nylon at 241.9 and 303.6 K

T = 241.9 K						T = 303.6 K					
Sorption			Desorption			Sorption			Desorption		
Relative pressure	Solubility (10 ³ m ₁ /m ₂)		Relative pressure	Solubility (10 ³ m ₁ /m ₂)		Relative pressure	Solubility (10 ³ m ₁ /m ₂)		Relative pressure	Solubility (10 ³ m ₁ /m ₂)	
0.004	0.85		0.004	1.37		0.07	7.65		0.06	16.62	
0.010	1.36		0.047	3.82		0.22	15.58		0.55	42.34	
0.016	1.80		0.069	4.45		0.43	26.39		0.78	48.31	
0.021	2.06		0.092	5.10		0.65	37.94		0.89	52.50	
0.027	2.45		0.111	5.64		0.81	46.65		—	—	
0.034	2.74		—	—		0.89	52.50		—	—	
0.046	3.19		—	—		—	—		—	—	
0.057	3.64		—	—		—	—		—	—	
0.076	4.31		—	—		—	—		—	—	
0.089	4.96		—	—		—	—		—	—	
0.111	5.64		—	—		—	—		—	—	

TABLE 2. Sorption and desorption isotherms of hydrogen chloride in nylon at 194.3 K

Sorption				Desorption			
Pressure/kPa	Solubility (10 ³ m ₁ /m ₂)			Pressure/kPa	Solubility (10 ³ m ₁ /m ₂)		
0.13	484			0	610		
1.77	718			7.49	1022		
4.19	789			32.29	1160		
11.84	915			81.65	1376		
26.19	1072			121.75	1633		
51.66	1217			—	—		
71.08	1306			—	—		
98.89	1453			—	—		
121.75	1633			—	—		

Components:		Original Measurements:					
(1) Sulfur dioxide; SO ₂ ; [7446-09-5]		E. G. Davis and M. L. Rooney, Kolloid Z.-Z. Polym. 249 , 1043 (1991).					
(2) Polyamide (Nylon 11); [25035-04-5] (LV)							
Variables:		Prepared By:					
T/K: 298		A. K. Bokarev					
p/kPa: 0–101.3							
Experimental Data							
p/kPa	13.3	26.6	39.9	53.2	66.5	79.8	93.1
C* ^a /cm ³ (STP) cm ⁻³	6.6	9.8	12.3	14.8	17.3	20.1	22.2
*Smoothed values taken from the graph by compiler.							
Dual-mode sorption parameters for SO ₂ in PA at 298 K							
k _D /cm ³ cm ⁻³ cm Hg ⁻¹	C' _D /cm ³ (STP) cm ⁻³					b/(cm Hg) ⁻¹	
0.248	5.8					0.169	
Method/Apparatus/Procedure				Auxiliary Information			
A modified McBain balance technique described in Ref. 1 was used to measure the solubility coefficient of sulfur dioxide in Nylon 11.				Source and Purity of Materials:			
				PA (Nylon 11): density 1.030 g/cm ³ ; from Societe Organico (France). T _g = 319 K.			
				Sulfur dioxide of 99.95% purity was used.			
				Estimated Error:			
				No estimates possible.			
				References:			
				1 S. Prager and A. F. Long, J. Am. Chem. Soc. 73 , 4072 (1951).			

Components:		Original Measurements:					
(1) Neon; Ne; [7440-01-9] Argon; Ar; [7440-37-1] Hydrogen; H ₂ ; [1333-74-0] Carbon dioxide; CO ₂ ; [124-38-9] Polyundecanamide; Nylon 11; [25035-04-5] (LV)		R. Ash, R. M. Barrer, and D. G. Palmer, Polymer 11 , 421 (1970).					
Variables:		Prepared by:					
T/K = 293.2–333.2 p/kPa = 6.65–33.25		Yu. P. Yampol'skii					
Experimental Data							
Solubility isotherms obeyed Henry's law; the solubility coefficients S (cm ³ /cm ³ atm) determined from their slopes are given below, as well as the enthalpies of solution ΔH (kcal/mol)							
Gas	T/K	$S \cdot 10^2$	ΔH	T/K	Gas	$S \cdot 10^2$	ΔH
Ne	293.2	0.54	1.0	293.2	H ₂	1.45	0.5
	303.2	0.56		303.2		1.48	
	313.2	0.62		313.2		1.50	
	323.2	0.65		323.2		1.58	
	333.2	0.66		333.2		1.63	
Ar	313.2	3.91	−0.4	313.2	CO ₂	36.8	−3.2
	323.2	3.88		323.2		31.4	
	333.2	3.77		333.2		28.0	
Auxiliary Information							
Method/Apparatus/Procedure							
After the equilibrium was attained the remaining gas was swept by mercury. The measurement of the pressure of gas desorbed was performed by means of McLeod type gauge. Corrections for loss of gas by desorption during flushing process were introduced.							
Source and Purity of Materials:							
Nylon 11 was obtained from Griflex Ltd. Gases (British Oxygen Co) were spectrally pure.							
Estimated Error:							
$\delta T = \pm 0.1$ K. $\delta S/S = \pm 0.02$.							

3.34. Polyimide Kapton H—Carbon Dioxide, Methane, Sulfur Dioxide

Components:		Evaluator:
(1) Carbon dioxide; CO ₂ ; [124-38-9]		Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994
(2) Polyimide Kapton H; [25036-53-7] (LVI)		

Critical Evaluation:

Sorption of carbon dioxide in poly(4,4'-oxydiphenylene pyromellitimide) known under trademark Kapton H was studied in a number of works.¹⁻⁶ The majority of researchers dealt with commercial samples of this material. Only Okamoto *et al.*⁵ investigated the specimens of this polymer prepared in the laboratory by imidization at different temperatures. The parameters of sorption isotherms obtained for this material differ from those measured for Kapton H. The table shows the selected dual mode sorption parameters for the system Kapton H—CO₂. It is seen that smooth temperature dependence is observed for all three model parameters and for the apparent solubility coefficient *S*.

Dual mode sorption parameters for the system Kapton H—CO ₂					
<i>T</i> /K	<i>k_D</i>	<i>C'_H</i>	<i>b</i>	<i>S</i> = <i>k_D</i> − <i>C'_H</i> <i>b</i>	Ref.
308	0.594	23.5	0.300	7.6	3
323	0.630	13.3	0.394	5.9	5
323	0.650	12.8	0.42	6.0	2
353	0.436	8.5	0.239	2.5	5
353	0.40	8.9	0.23	2.4	2
383	0.28	6.1	0.16	1.3	2
383	0.292	5.7	0.153	1.2	5

Units: *k_D* and *S*/cm³(STP) cm^{−3} atm^{−1}; *C'_H*/cm³(STP) cm^{−3}; *b*/atm^{−1}.

A larger scatter is observed for the affinity parameter *b* especially at lower temperatures. The enthalpies corresponding to van't Hoff plots of *k_D*, *b*, and *S* are as follows:

$$\Delta H_D = -11.3 \text{ kJ/mol}$$
$$\Delta H_H = -11.9 \text{ kJ/mol}$$
$$\Delta H_S = -25.1 \text{ kJ/mol.}$$

The Langmuir capacity parameters decrease with temperature. It is noteworthy that temperature dependence is strongly nonlinear, so it is difficult to determine the temperature at which *C'_H* vanishes. However, it is probably lower than the glass transition temperature of this polymer for which the values higher than 600 K^{2,3} and even 780 K¹ have been reported.

References:

- ¹R. T. Chern, W. J. Koros, B. Yui, H. B. Hopfenberg, and V. T. Stannett, *J. Polym. Sci., Polym. Phys. Ed.* **22**, 1061 (1984).
- ²K. Tanaka, H. Kita, and K. Okamoto, Japan-US Polymer Symposium, 1985, p. 249.
- ³T. Uragami, H. B. Hopfenberg, W. J. Koros, D. K. Yang, V. T. Stannett, and R. T. Chern, *J. Polym. Sci., Part B: Polym. Phys.* **24**, 779 (1986).
- ⁴K. C. O'Brien, W. J. Koros, and G. R. Husk, *Polym. Eng. Sci.* **27**, 211 (1987).
- ⁵K. Okamoto, K. Tanaka, O. Yokoshi, and H. Kita, *J. Polym. Sci., Part B: Polym. Phys.* **27**, 643 (1989).
- ⁶H. Hachisuka, Y. Tsujita, A. Takizawa, and T. Kinoshita, *Polym. J.* **21**, 681 (1989).

Components:		Original Measurements: R. Y. Chern, W. J. Koros, B. Yui, H. B. Hopfenberger, and V. T. Stannett, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 22 , 1061 (1984).
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]		
(2) Polyimide Kapton H; [25036-53-7] (LVI)		
Variables:		Prepared By: Yu. P. Yampol'skii
<i>T</i> /K=333		
<i>p</i> /MPa=0–2.0 (0–20 atm)		

Experimental Data			
Dual mode sorption parameters for carbon dioxide and methane in Kapton H at 333 K			
Gas	<i>k_D</i> /cm ³ (STP) cm ^{−3} atm ^{−1}	<i>C'_H</i> /cm ³ (STP) cm ^{−3}	<i>b</i> /atm ^{−1}
Based on pressure			
CO ₂	0.380±0.054	12.280±1.48	0.296±0.023
CH ₄	0.700±0.011	2.684±0.376	0.174±0.032
Based on fugacity			
CO ₂	0.439±0.058	11.817±1.486	0.316±0.069
CH ₄	0.073±0.011	2.653±0.384	0.175±0.034

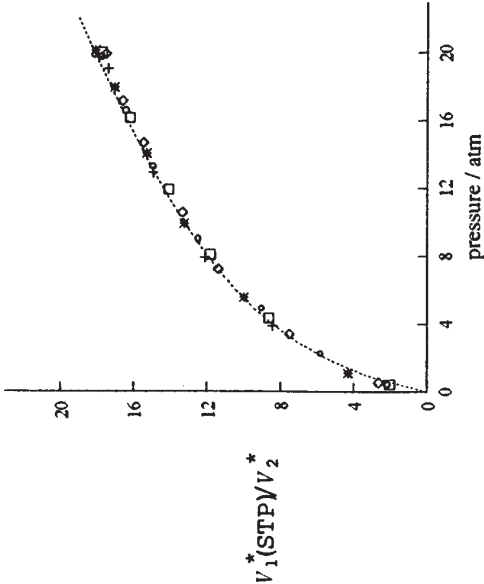


Fig. 78. Sorption isotherms of carbon dioxide in Kapton H at 333 K. Different symbols stand for different runs.

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]		K. Tanaka, H. Kita, and K. Okamoto, Japan-US Polymer Symposium, 1985, pp. 249-250.	
(2) Polyimide Kapton H; [2536-53-7] (LVI)			
Variables:		Prepared By:	
T/K = 323–383		Yu. P. Yampol'skii	
p/MPa = 0–2.0			
Experimental Data			
Dual mode sorption parameters*			
T/K	$k_D / (\text{cm}^3(\text{STP})/\text{cm}^3 \text{ atm})$	$C_H' / (\text{cm}^3(\text{STP})/\text{cm}^3)$	$b / (\text{atm}^{-1})$
323	0.65	12.8	0.42
353	0.4	8.9	0.23
383	0.28	6.1	0.16
(Sorption enthalpies: $\Delta H_D = -14.4 \text{ kJ/mol}$, $\Delta H_H = -18.9 \text{ kJ/mol}$)			
*Taken from a graph by the compiler.			
Method/Apparatus/Procedure		Auxiliary Information	
Sorption was measured by the pressure decay method. The same isotherms were obtained for "as received" samples and the specimens preliminary exposed to 50 atm of carbon dioxide at 323 K for 24 h.		Source and Purity of Materials: Polyimide Kapton H (Du Pont Co) had glass transition temperature >573 K. No other information given.	
		Estimated Error: No information given.	

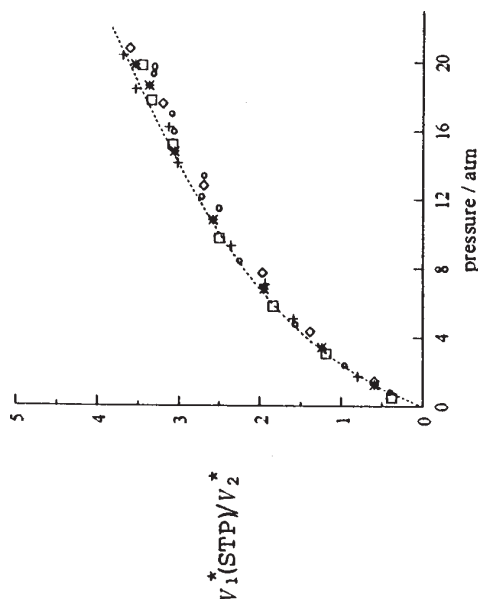


Fig. 79. Sorption isotherms of methane in Kapton H at 333 K. Different symbols stand for different runs.

Method/Apparatus/Procedure		Auxiliary Information	
A pressure decay method of sorption measurement used was described in detail in Ref 1. Each isotherm included several consecutive series of runs with stepwise pressure increase. The virgin films were degassed at 333 K for 120 h before measurement.		Source and Purity of Materials: CO ₂ : Coleman-grade 99.999%. CH ₄ : instrument-grade 99.7%. Kapton H: E. I. DuPont Co.; no glass transition temperature revealed in DSC measurement up to 777 K.	
		Estimated Error: No information given.	
		References: 1W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14, 1903 (1976).	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Polyimide Kapton H; [25036-53-7] (LVI)	Original Measurements: K. C. O'Brien, W. J. Koros, and G. R. Husk, <i>Polym. Eng. Sci.</i> , 27 , 211 (1987).	
	Prepared By: Yu. P. Yampol'skii	
Variables: <i>T</i> /K = 308 <i>p</i> /MPa = 0–1.1	Method/Apparatus/Procedure A method based on the principle of material balance for all gas introduced into the cell was employed. ^{1,2}	
	Source and Purity of Materials: Kapton H: density 1.430 g/cm ³ , <i>M_w</i> = 39 200. PMDA-ODA: density 1.402 g/cm ³ , <i>M_w</i> = 36 900; structure confirmed by IR spectroscopy.	
Estimated Error: No information given.		
References: ¹ E. S. Sanders, Ph.D. dissertation, N. C. State University, 1983. ² W. J. Koros and D. R. Paul, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 14 , 1903 (1976).		

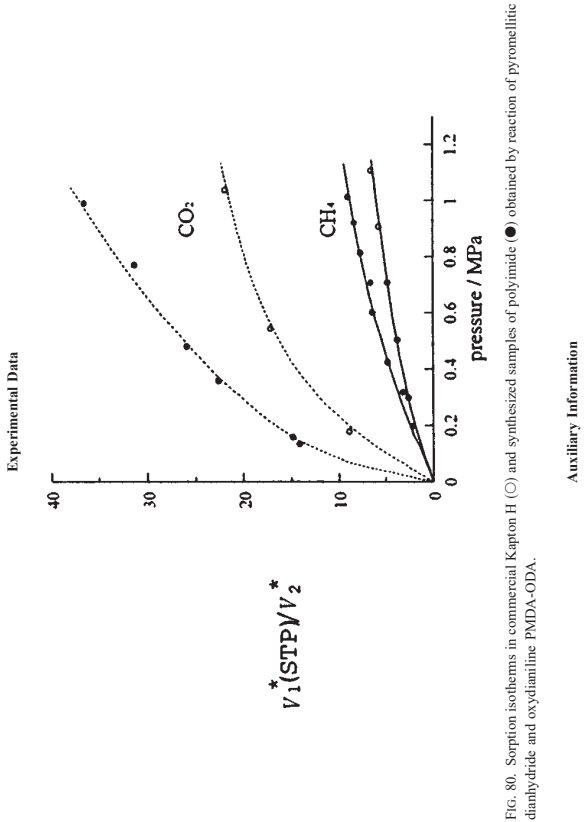


FIG. 80. Sorption isotherms in commercial Kapton H (O) and synthesized samples of polyimide (●) obtained by reaction of pyromellitic dianhydride and oxydianiline PMDA-ODA.

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Polyimide Kapton H; [25036-53-7] (LVI)	Original Measurements: T. Uragami, H. B. Hopfenberg, W. J. Koros, D. K. Yang, V. T. Stannett, and R. T. Chern, <i>J. Polym. Sci., Part B: Polym. Phys.</i> 24 , 779 (1986).	
	Prepared By: A. K. Bokarev	
Variables: <i>T</i> /K = 308–328 <i>p</i> /kPa = 0–78	Method/Apparatus/Procedure A quartz spring balance and experimental procedure similar to that reported in Ref. 1 were used to measure the sorption of CO ₂ in Kapton.	
	Source and Purity of Materials: CO ₂ : Air Products and Chemical Inc., purity 99.999%. Polyimide Kapton: E. I. du Pont de Nemours & Co., film density 1.42 g/cm ³ , glass transition temperature in the range 620–720 K. ²	
	Estimated Error: No information given.	
	References: ¹ C. H. M. Jaques and H. B. Hopfenberg, <i>Polym. Eng. Sci.</i> 14 , 441 (1974). ² W. J. Wrasidlo, <i>Macromol. Sci. Phys.</i> B6 , 559 (1972).	

TABLE 1. Dual mode sorption parameters for carbon dioxide in Kapton Film at 308 and 318 K

<i>T</i> /K	<i>k_D</i> /cm ³ (STP) cm ⁻³ atm ⁻¹	<i>C'_H</i> /cm ³ (STP) cm ⁻³	<i>b</i> /atm ⁻¹
308	0.461	18.19	0.287
318	0.389	13.29	0.275

TABLE 2. Equilibrium sorption isotherms of carbon dioxide in Kapton film (The original data were represented graphically)

$T = 308\text{ K}$			$T = 318\text{ K}$			$T = 328\text{ K}$		
Pressure/kPa	Sorption ($V_1^*(\text{STP})/V_2^*$)		Pressure/kPa	Sorption ($V_1^*(\text{STP})/V_2^*$)		Pressure/kPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	
2.61	0.20		3.18	0.17		3.53	0.12	
3.75	0.26		4.89	0.26		4.78	0.18	
5.68	0.39		7.39	0.39		6.03	0.20	
7.50	0.55		10.01	0.50		7.40	0.26	
10.01	0.70		13.53	0.72		9.44	0.34	
11.60	0.83		17.06	0.88		11.38	0.40	
13.98	0.98		21.61	1.14		14.45	0.52	
17.51	1.24		27.07	1.41		17.63	0.65	
22.28	1.58		35.15	1.78		22.87	0.83	
28.42	1.99		42.20	2.12		28.33	1.02	
35.82	2.46		47.66	2.36		35.61	1.27	
44.91	2.98		58.24	2.82		44.37	1.55	
51.62	3.34		66.65	3.14		56.20	1.94	
57.76	3.72		72.80	3.39		63.14	2.16	
64.59	4.13		77.46	3.57		70.77	2.41	
72.78	4.56		—	—		76.34	2.57	
76.98	4.75		—	—		—	—	

Auxiliary Information	Method/Apparatus/Procedure A quartz spring balance and experimental procedure similar to that reported in Ref. 1 were used to measure the sorption of CO ₂ in Kapton.	Source and Purity of Materials: CO ₂ : Air Products and Chemical Inc., purity 99.999%. Polyimide Kapton: E. I. du Pont de Nemours & Co., film density 1.42 g/cm ³ , glass transition temperature in the range 620–720 K. ²
	Estimated Error: No information given.	
	References: ¹ C. H. M. Jaques and H. B. Hopfenberg, <i>Polym. Eng. Sci.</i> 14 , 441 (1974). ² W. J. Wrasidlo, <i>Macromol. Sci. Phys.</i> B6 , 559 (1972).	

Components:		Original Measurements:		
(1) Carbon dioxide; CO ₂ ; [124-38-9]		K. Okamoto, K. Tanaka, O. Yokoshi, and H. Kita, J. Polym. Sci., Part B: Polym. Phys. 27, 643 (1989).		
(2) Polyimide (PMDA-ODA) (Kapton H); [25036-53-7] (LVI)				
Variables:		Prepared By:		
T/K = 323–383		S. M. Shishatskii		
p/MPa = 0–2.7				
Experimental Data				
Dual mode sorption parameters for carbon dioxide in polyimide films				
Sample	T/K	k_D /cm ³ (STP) cm ^{−3} atm ^{−1}	C_H' /cm ³ (STP) cm ^{−3}	b /atm ^{−1}
Imidization at 473 K	323	0.900	24.2	0.375
	353	0.599	17.7	0.206
	383	0.424	12.0	0.133
Imidization at 673 K	353	0.444	10.6	0.226
Kapton-H	323	0.630	13.3	0.394
	353	0.436	8.5	0.239
	383	0.292	5.7	0.153

Method/Apparatus/Procedure		Source and Purity of Materials	
Pressure decay method was used for sorption measurements. The cell employed was similar to the one described in Ref. 1.		Polyimide was obtained by condensation of pyromellitic acid dianhydride and oxydiphenylenediamine with subsequent thermal imidization at 473 and 673 K. These samples and commercial polyimide Kapton H (Tonay-DuPont Inc.) had the following densities: 1.405, 1.429, and 1.431 g/cm ³ , respectively. No information given on carbon dioxide purity.	
		Estimated Error: No information given.	
		References: 1W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed., 14 , 1903 (1976).	

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]		K. C. O'Brien, W. J. Koros, and G. R. Husk, J. Membr. Sci. 35 , 217 (1988).	
(2) Copoly(pyromellitic dianhydride-oxydianiline); PMDA-ODA (polyimide Kapton H); [25036-53-7] (LVI)			
Variables:		Prepared By:	
T/K = 308		Yu. P. Yampol'skii	
p/MPa = 0.1 – 1.4			
Experimental Data			
Sorption isotherms of carbon dioxide and methane in PMDA-ODA at 308 K. (The original data were represented graphically)			
CO ₂		CH ₄	
Pressure/MPa	Sorption (V^*/V^*_2)	Pressure/MPa	Sorption (V^*/V^*_2)
0.16	14.36	0.21	3.21
0.36	22.17	0.31	4.46
0.52	26.96	0.47	5.84
0.76	32.12	0.71	7.36
0.98	36.22	0.91	8.61
1.37	42.11	1.00	9.07
—	—	1.12	9.80

Method/Apparatus/Procedure		Source and Purity of Materials	
Sorption measurements were carried out using a single transducer apparatus described in Ref. 1.		PMDA-ODA: polymerization performed in dimethylacetamide at 288–293 K to form polyamic acid precursor according to standard procedure. ² The polyamic acid solution was wet cast on a glass substrate heated for 1 h at 353 K under Ar to remove the solvent and then imidized by a two-step cure under vacuum (24 h at 483 K and 4 h at 553 K). The polymer studied did not reveal a glass transition temperature at temperatures up to 750 K. Density was 1.402 g/cm ³ .	
		Estimated Error: Relative precision of solubilities: 5%.	
		References: 1S. E. Sanders, Ph.D. dissertation, NC State University, 1983. 2C. E. Sroog, A. L. Endrey, S. V. Abravio, C. E. Berro, W. M. Edwards, and K. L. Olivier, J. Pol. Sci., Part A 3 , 1373 (1965).	

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials
Sorption measurement was carried out by Cahn 2000 electronic-micro-balance.	CO ₂ ; purity 99.9% Polyimide: prepared by imidization of the polyamide produced by the reaction of pyromellitic acid dianhydride with 4,4'-diaminodiphenyl ether in <i>N</i> -methylpyrrolidone solution. Imidization was carried out at 423 K for 50–400 h <i>in vacuo</i> . An additional sample with 100% imide content was also studied. For the thermally treated samples, the imide content lay in the range 35%–58%. <i>T_g</i> of unimidized polymer and polyimide were equal to 428 and 683 K, respectively.
	Estimated Error: No information given.

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]		H. Hachisuka, Y. Tsujita, A. Takizawa, and T. Kinoshita, Polymer J. 21 , 681 (1989).	
(2) Copoly(pyromellitic dianhydride-oxydianiline)			
PMDA-ODA (polyimide Kapton H), [25086-53-7] (LVI)			
Variables:			
<i>T</i> /K = 298		Prepared By:	
<i>p</i> /kPa = 0–1.200		Yu. P. Yampol'skii	

TABLE 1. Dual mode sorption parameters as a function of imide content (%) for CO₂ in polyimide films. (The original data were represented graphically).

%	<i>k_D</i> /cm ³ (STP) cm ³ cm Hg ^{−1}	<i>C_H</i> ⁰ /cm ³ (STP) cm ^{−3}	<i>b</i> /cm Hg ^{−1}
3.62	0.0596	2.14	0.0047
34.76	0.0810	72.84	0.0061
40.61	0.0872	273.54	0.0072
51.28	0.0956	211.76	0.0073
57.93	0.0922	175.26	0.0075
100	0.0720	34.44	0.0084

TABLE 2. Sorption isotherms of CO₂ in the films imidized for various periods at 423 K (The original data were represented graphically).

Pressure/kPa	Sorption (<i>V₁⁰</i> /(STP)/ <i>V₂⁰</i>)	Pressure/kPa	Sorption (<i>V₁⁰</i> /(STP)/ <i>V₂⁰</i>)	Pressure/kPa	Sorption (<i>V₁⁰</i> /(STP)/ <i>V₂⁰</i>)
Film not imidized					
49	3.08	400	15.97	800	25.54
97	5.32	501	18.67	900	27.33
199	9.37	596	20.97	—	—
301	12.67	696	23.17	—	—
Film imidized for 50 h					
68	6.47	534	21.43	1052	30.45
135	9.91	665	24.03	1191	32.60
268	14.91	799	26.50	—	—
398	18.20	906	28.36	—	—
Film imidized for 100 h					
134	12.62	533	25.97	910	34.09
295	19.18	665	29.01	1056	36.68
399	22.55	782	31.74	1174	38.47
Film imidized for 200 h					
64	9.94	553	27.85	1044	37.44
135	13.88	667	30.46	1178	39.54
264	19.82	800	33.25	—	—
400	23.87	924	35.41	—	—
Film imidized for 400 h					
132	14.89	519	28.62	936	37.48
266	20.83	660	31.72	1048	39.46
395	24.94	791	34.89	—	—

Components:		Original Measurements:	
(1) Sulfur dioxide; SO ₂ ; [7446-09-5]		R. M. Felder, C. J. Patton, and W. J. Koros, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 19 , 1895 (1981).	
(2) Polyimide Kapton H; [25036-53-7] (LVI)			
Variables:		Prepared By:	
<i>T</i> /K = 298–308		Yu. P. Yampol'skii	
<i>p</i> /kPa = 0–80			

Experimental Data			
Dual mode sorption parameters for sulfur dioxide in polyimide Kapton H			
<i>T</i> /K	k_D /cm ³ (STP) cm ³ atm ⁻¹	C_H' /cm ³ (STP) cm ⁻³	<i>b</i> /atm ⁻¹
298	32.51	21.29	20.40
308	28.48	16.78	18.06
318	21.94	14.22	16.31
328	18.71	11.11	16.02

The following parameters of temperature dependence of k_D and b are reported:

$$k_D = k_{D_0} \exp[3.7(\text{kcal mol}^{-1})/RT]$$

$$b = b_0 \exp[1.6(\text{kcal mol}^{-1})/RT]$$

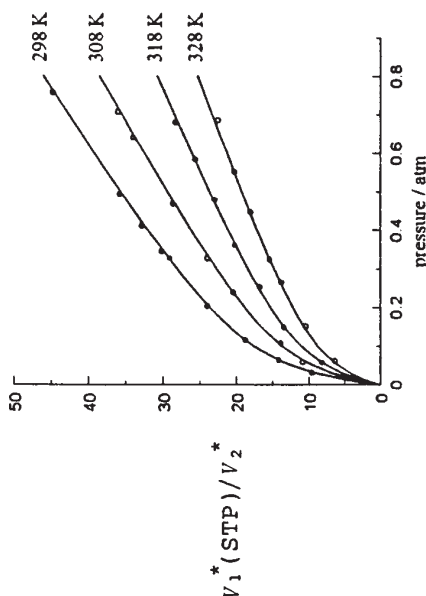


FIG. 81. Sorption isotherms of sulfur dioxide in polyimide Kapton H.

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
A quartz spring balance was used to measure the sorption.	Kapton H; DuPont Co, density 1.42 g/cm ³ .
	Estimated Error:
	No information given.

Components:		Original Measurements:	
(1) Sulfur dioxide; SH ₂ ; [7446-09-5]		W. J. Koros, C. J. Patton, R. M. Felder, and S. J. Fincher, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 18 , 1485 (1980).	
(2) Polyimide Kapton; [25036-53-7] (LVI)			
Variables:		Prepared By:	
<i>T</i> /K: 298		A. K. Bokarev	
<i>p</i> /kPa: 0–75			

Experimental Data					
Solubility of SO ₂ in Kapton at 298 K*					
<i>p</i> /atm	0.1	0.2	0.3	0.4	0.5
<i>C</i> /cm ³ (STP) cm ⁻³	18.1	24.2	28.1	32.3	35.6
					39.3
					42.8
					46.0

* Smooth values taken from the graph by compiler.

Dual mode sorption parameters of SO ₂ sorption in Kapton film at 298 K		
k_D /cm ³ (STP) cm ⁻³ atm ⁻¹	C_H' /cm ³ (STP) cm ⁻³	<i>b</i> /atm ⁻¹
0.389	13.29	0.275

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
The sorption apparatus and procedures used in the present sorption experiments was described earlier.	The polyimide Kapton (E.I. du Pont de Nemours Co.) had density 1.42 g/cm ³ , and the glass transition temperature 600 K. The SO ₂ was obtained from Air Products and Chemical, Inc., at purity of 99.9%.
Estimated Error:	No information given.
References:	References:
	[C. H. M. Jaques and H. B. Hopfenberg, <i>Polym. Eng. Sci.</i> 14 , 441 (1974).

3.35. Polimide Uplex R—Carbon Dioxide

Components:		Evaluator:
(1) Carbon dioxide; CO ₂ ; [124-38-9]		Yu. P. Yampol'skii, A. V. Topchiev Institute of Petrochemical Synthesis, Russian Academy of Sciences, April, 1994
(2) Polyimide Uplex R; [26615-45-2] (LVII)		

Critical Evaluation:

Three investigations are available on sorption of CO₂ in the polyimide obtained from 3,3', 4,4'-biphenyltetracarboxy dianhydride and 4,4'-oxydianiline known under the tradename Uplex R.¹⁻³ The authors studied commercial samples of Uplex R, but in one case specimens synthesized and pretreated under different conditions were investigated as well.³ For the temperature range 308–383 K and at pressures up to 3 MPa, the sorption isotherms can be described by parameters shown in the table which are based on data reported in two papers^{1,3} by the same group. The results of Sada *et al.*² are somewhat different, particularly at lower temperatures.

Selected dual mode sorption parameters for the system Uplex R–CO₂

T/K	<i>k_D</i>	<i>C'_H</i>	<i>b</i>	<i>S</i> = <i>k_D</i> + <i>C'_Hb</i>	Ref.
308	0.596	12.0	0.478	6.3	3
323	0.50	8.6	0.44	4.3	1
323	0.456	10.3	0.348	4.0	3
353	0.335	5.9	0.252	1.8	3
353	0.35	5.0	0.30	1.8	1
383	0.254	3.4	0.162	0.8	3
383	0.25	3.0	0.19	0.8	1

Units: *k_D* and *S*/cm³(STP) cm⁻³ atm⁻¹; *C'_H*/cm³(STP) cm⁻³; *b*/atm⁻¹.

Figures 82–84 show the temperature dependences of *S*, *b*, and *k_D*, respectively.

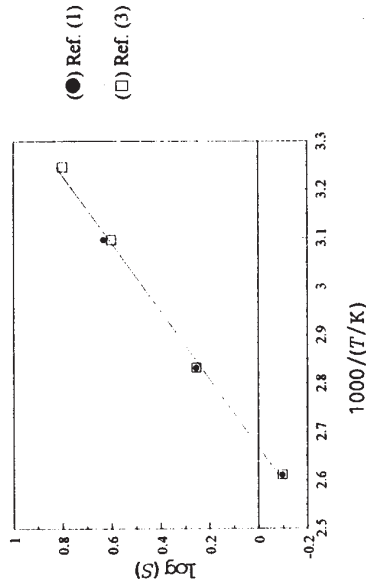


Fig. 82. Temperature dependence of apparent solubility coefficient *S*/cm³(STP) cm⁻³ atm⁻¹.

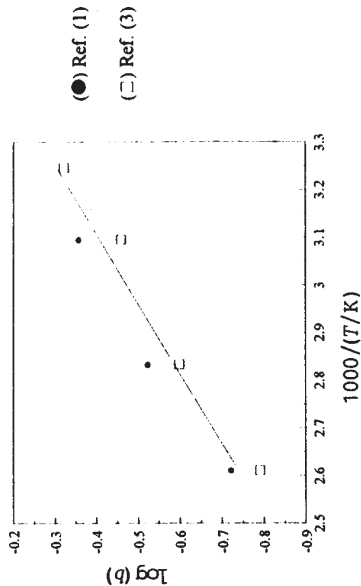


Fig. 83. Temperature dependence of the affinity parameter *b*/atm⁻¹.

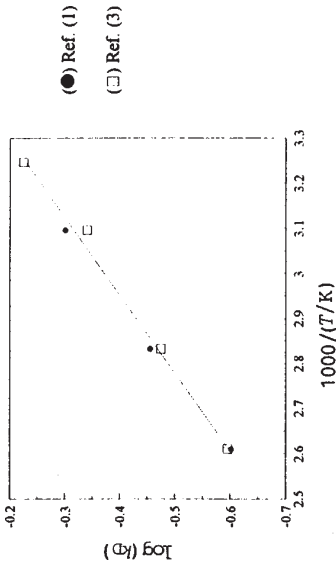


Fig. 84. Temperature dependence of Henry's law solubility coefficient *k_D*/cm³(STP) cm⁻³ atm⁻¹.

A least squares treatment of the temperature dependence of *k_D*, *b*, and *S* resulted in the following values of enthalpies:

$$\begin{aligned}\Delta H_D &= -11.10 \text{ kJ/mol} \\ \Delta H_H &= -13.13 \text{ kJ/mol} \\ \Delta H_S &= -27.35 \text{ kJ/mol}\end{aligned}$$

The temperature dependence of Langmuir capacity adsorption parameter *C'_H* shows that it vanishes in the vicinity of 450 K or at temperatures much lower than the glass transition temperature of this polymer. The dual mode sorption parameters can be found based on fugacity instead of pressure.² The values calculated in two cases do not differ greater than by 10%, although the enthalpies ΔH_D and ΔH_H are greater when the parameters are found via fugacity.

A study of the effects of pretreatment of the films indicated³ that the presence of the solvent led to the increase in the apparent solubility coefficient, while the annealing resulted in the opposite effect.

References:

- ¹K. Tanaka, H. Kita, and K. Okamoto, Japan-US Polymer Symposium, 1985, p. 249.
- ²E. Sada, H. Kumazawa, and P. Xu, J. Appl. Polym. Sci. **35**, 1497 (1988).
- ³K. Okamoto, K. Tanaka, H. Kita, A. Nakamura, and Y. Kusuki, J. Polym. Sci., Part B: Polym. Phys. **27**, 1221 (1989).

Components:				Original Measurements:			
(1) Carbon dioxide; CO ₂ ; [124-38-9]				E. Sada, H. Kumazawa, and P. Xu, J. Appl. Polym. Sci. 35 , 1497 (1988).			
(2) Polyimide Upilex R; [26615-45-2] (LVII)							
Variables:				Prepared By:			
T/K=303–333				Yu. P. Yampol'skii			
p/MPa=0–1.7							
Experimental Data							
Dual sorption parameters for carbon dioxide in Upilex polyimide							
T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}				
Based on pressure							
303	1.24	7.39	1.70				
313	1.04	5.67	1.23				
323	0.817	4.27	0.865				
333	0.692	3.34	0.635				
Based on fugacity							
303	1.35	6.93	1.91				
313	1.12	5.28	1.35				
323	0.875	3.95	0.954				
333	0.736	3.09	0.683				
Van't Hoff parameters ΔH_D from $k_D(T)$ and ΔH_H from $b(T)$ plots							
Parameter		Pressure		Fugacity			
$\Delta H_D/\text{kJ}\cdot\text{mol}^{-1}$		–16.6		–15.9			
$\Delta H_H/\text{kJ}\cdot\text{mol}^{-1}$		–27.9		–29.0			

Components:				Original Measurements:			
(1) Carbon dioxide; CO ₂ ; [124-38-9]				K. Tanaka, H. Kita, and K. Okamoto, Japan-US Polymer Symposium, 1985, pp. 249–250.			
(2) Polyimide Upilex R; [26615-45-2] (LVII)							
Variables:				Prepared By:			
T/K=323–383				Yu. P. Yampol'skii			
p/MPa=0–2.0							
Experimental Data							
Dual mode sorption parameters*							
T/K	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}				
323	0.50	8.6	0.44				
353	0.35	5.0	0.30				
383	0.25	3.0	0.19				
*Read by the compiler from the plot.							
Sorption enthalpies: $\Delta H_D = -12.3\text{ kJ/mol}$, $\Delta H_H = -15.7\text{ kJ/mol}$.							
Auxiliary Information							
Source and Purity of Materials:							
Polyimide Upilex R (Ube Industries) had the glass transition temperature 558 K.							
Estimated Error:							
No information given.							
Method/Apparatus/Procedure							
Sorption was measured by the pressure decay method. The same isotherms were obtained for “as received” samples and the specimens preliminary exposed to 50 atm of carbon dioxide at 323 K for 24 h.							

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Polyimide Upilex R; [26615-45-2] (LVII)				Original Measurements: K. Tanaka, H. Kita, and K. Okamoto, Japan-US Polymer Symposium, 1985, pp. 249-250.			
Variables: T/K = 323-383 p/MPa = 0-2.0				Prepared By: Yu. P. Yampol'skii			
Experimental Data Dual mode sorption parameters*							
T/K		$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$		$C'_{II}/\text{cm}^3(\text{STP})\text{cm}^{-3}$		b/atm^{-1}	
323		0.50		8.6		0.44	
353		0.35		5.0		0.30	
383		0.25		3.0		0.19	
*Read by the compiler from the plot.							
Sorption enthalpies: $\Delta H_D = -12.3\text{ kJ/mol}$, $\Delta H_{II} = -15.7\text{ kJ/mol}$.							
Auxiliary Information							
Method/Apparatus/Procedure Sorption was measured by the pressure decay method. The same isotherms were obtained for "as received" samples and the specimens preliminary exposed to 50 atm of carbon dioxide at 323 K for 24 h.				Source and Purity of Materials: Polyimide Upilex R (Ube Industries) had the glass transition temperature 558 K.			
Estimated Error: No information given.							

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Polyimide from 3,3', 4,4'-Biphenyltetracarboxylic dianhydride (BPDA) and 4,4'-Oxydianiline (ODA) (Upilex-R); [26615-45-2] (LVII)		Original Measurements: K. Okamoto, K. Tanaka, H. Kim, A. Nakamura, and Y. Kusuki, J. Poly. Sci.: Part B: Polym. Phys. 27, 1221 (1989). K. Okamoto, K. Tanaka, K. Yokoshi, K. Hidetoshi, and A. Nakamura.		
Variables: T/K=308–383 p/MPa=0–3.0		Prepared By: Yu. P. Yampol'skii		
Experimental Data Dual mode sorption parameters for CO ₂ in commercial and laboratory samples of BPDA-ODA polyimides				
Sample	T/K	$k_D/\text{cm}^3(\text{STP})/\text{cm}^3\text{ atm}$	$C'_{if}/\text{cm}^3(\text{STP})/\text{cm}^3$	b/atm^{-1}
Upilex-R	308	0.596	12.0	0.478
	323	0.456	10.3	0.348
	353	0.335	5.9	0.252
	383	0.254	3.4	0.162
1	323	0.609	17.9	0.392
	353	0.449	10.6	0.236
	353	0.316	11.0	0.167
	383	0.327	7.0	0.140
2	353	0.267	4.7	0.216
Method/Apparatus/Procedure Apparatus and procedure of sorption measurement was similar to one described in Ref. 1		Auxiliary Information Source and Purity of Materials: Films of the polymer prepared from BPDA and ODA in <i>p</i> -chlorophenol were cast from the same solvent, dried (373 K, 3 h), immersed in ethanol, dried once more at 443 K for 20 h (sample 1). Sample 2 was prepared by annealing it at 543 K, 3 h. Commercial Upilex-R (Ube Industries) had $T_g=558\text{ K}$, $\rho=1.402\text{ g/cc}$. Sample 1 had the same T_g .		
		Estimated Error: No information given.		
		References: ¹ W. J. Koros, and D. R. Paul J. Polym. Phys., Polym. Phys. Ed. 14, 1903 (1976).		

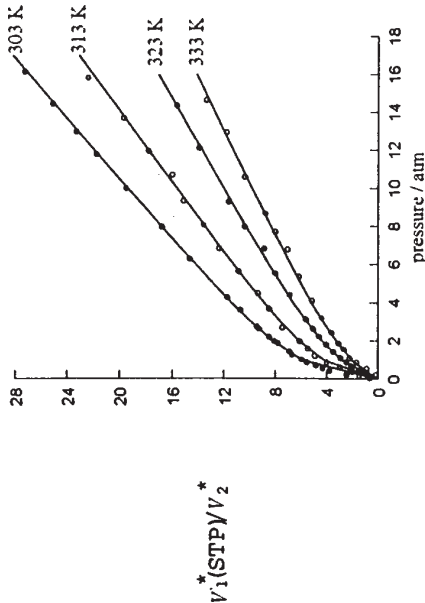


FIG. 85. Sorption isotherms of carbon dioxide in polyimide Upilex R.

Method/Apparatus/Procedure Sorption was measured by pressure decay method. The apparatus was similar to that described in Ref. 1.	Auxiliary Information Source and Purity of Materials: Polyimide Upilex R: Ube Industries; glass transition temperature 558 K. Estimated Error: No information given. References: ¹ W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. 14, 687 (1976).
---	--

3.36. Other Polyamides—Various Gases

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Copoly(pyromellitic dianhydride-isopropylidene diamline); PMDA-IPDA (LIX)		Original Measurements: K. C. O'Brien, W. J. Koros, and G. R. Husk, <i>J. Membr. Sci.</i> , 35 , 217 (1988).			
Variables: <i>T</i> /K=308 <i>p</i> /MPa=0.1–1.7		Prepared By: Yu. P. Yampol'skii			
Experimental Data					
Sorption isotherms of carbon dioxide and methane in PMDA-IPDA at 308 K. (The original data were represented graphically)					
CO ₂		CH ₄			
Pressure/MPa	Sorption (<i>V</i> ₁ ^g (STP)/ <i>V</i> ₂ ^g)	Pressure/MPa	Sorption (<i>V</i> ₁ ^g (STP)/ <i>V</i> ₂ ^g)		
0.15	14.35	0.22	3.86		
0.46	35.63	0.59	9.90		
0.88	47.54	1.03	13.46		
1.31	55.91	1.50	16.26		
1.63	63.02	—	—		
Auxiliary Information					
Method/Apparatus/Procedure Sorption measurements were carried out using a single transducer apparatus described in Ref. 1.		Source and Purity of Materials: PMDA-IPDA: polymerization performed in dimethylacetamide at 288–293 K to form polyamic acid precursor according to standard procedure. ² The polyamic acid solution was wet cast on a glass substrate heated for 1 h at 353 K under Ar to remove the solvent and then imidized by a two-step cure under vacuum (24 h at 483 K and 4 h at 553 K). <i>T</i> _g was not reached even through the polymer was heated to 750 K. Density was 1.285 g/cm ³ .			
Estimated Error: Relative precision of solubilities: ±5%.		References: ¹ S. E. Sanders, Ph.D. dissertation, NC State University, 1983. ² C. E. Sroog, A. L. Endrey, S. V. Abravio, C. E. Berro, W. M. Edwards, and K. L. Olivier, <i>J. Pol. Sci., Part A</i> , 3 , 1373 (1965).			

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Copoly(pyromellitic dianhydride-methylene diamline); PMDA-MDA (LVIII)		Original Measurements: K. C. O'Brien, W. J. Koros, and G. R. Husk, <i>J. Membr. Sci.</i> , 35 , 217 (1988).			
Variables: <i>T</i> /K=308 <i>p</i> /MPa=0.2–1.3		Prepared By: Yu. P. Yampol'skii			
Experimental Data					
Sorption of carbon dioxide and methane in PMDA-MDA at 308 K. (The original data were represented graphically)					
CO ₂		CH ₄			
Pressure/MPa	Sorption (<i>V</i> ₁ ^g (STP)/ <i>V</i> ₂ ^g)	Pressure/MPa	Sorption (<i>V</i> ₁ ^g (STP)/ <i>V</i> ₂ ^g)		
0.20	16.66	0.22	3.48		
0.27	19.32	0.49	5.84		
0.57	28.03	0.80	8.24		
0.85	32.67	1.12	10.08		
0.99	34.27	—	—		
1.31	38.56	—	—		
Auxiliary Information					
Method/Apparatus/Procedure Sorption measurements were carried out using a single transducer apparatus described in Ref. 1.		Source and Purity of Materials: PMDA-MDA: polymerization performed in dimethylacetamide at 288–293 K to form polyamic acid precursor according to standard procedure. ² The polyamic acid solution was wet cast on a glass substrate heated for 1 h at 353 K under Ar to remove the solvent and then imidized by a two-step cure under vacuum (24 h at 483 K and 4 h at 553 K). <i>T</i> _g was not reached even though the polymer was heated to 750 K. Density was 1.352 g/cm ³ .			
Estimated Error: Relative precision of solubilities: ±5%.		References: ¹ S. E. Sanders, Ph.D. dissertation, NC State University, 1983. ² C. E. Sroog, A. L. Endrey, S. V. Abravio, C. E. Berro, W. M. Edwards, and K. L. Olivier, <i>J. Pol. Sci., Part A</i> , 3 , 1373 (1965).			

Components: (1) Nitrogen; N ₂ ; [7727-37-9] Oxygen; O ₂ ; [7782-44-7] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Polyimides derived from hexafluoroisopropylidene dianhydrides and diamines (see formulas)	Original Measurements: M. R. Coleman and W. J. Koros, <i>J. Membr. Sci.</i> 50 , 285 (1990).			
Variables: <i>T</i> /K = 308 <i>p</i> /MPa = 1.013 (10 atm)	Prepared By: Yu. P. Yampol'skii			
Experimental Data				
Solubility coefficients <i>S</i> /cm ³ (STP)/cm ³ atm of gases in polyimides				
Gases				
Polymer	O ₂	N ₂	CO ₂	CH ₄
6FDA-ODA	1.03	0.54	4.89	1.32
6FDA-MDA	0.82	0.46	3.96	1.18
6FDA-IPDA	0.90	0.50	4.24	1.20
6FDA-6FpDA	0.99	0.67	4.72	1.44
6FDA-6FmDA	0.61	0.35	2.89	0.81
Auxiliary Information				
Method/Apparatus/Procedure				
Sorption measurements were made with a pressure decay cell described in Ref. 1				
Source and Purity of Materials:				
Polyimides from Hoechst-Celanese Co. had the following characteristics:				
Polymer	<i>T_g</i> K		ρ, g/cc	
6FDA-ODA	577		1.432	
6FDA-MDA	577		1.400	
6FDA-IPDA	583		1.352	
6FDA-6FpDA	593		1.466	
6FDA-6FmDA	527		1.493	
The gases had purity >99.97%.				
Estimated Error:				
No information given.				
References:				
¹ W. J. Koros and D. R. Paul, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 14 , 1903 (1976).				

Components: (1) Nitrogen; N ₂ ; [7727-37-9] Methane; CH ₄ ; [74-82-8] (2) Copoly(pyromellitic dianhydride-isopropylidene dianiline); PMDA-IPDA (LIX)		Original Measurements: T. H. Kim, W. J. Koros, G. R. Husk, and K. C. O'Brien, J. Appl. Polym. Sci. 34 , 1767 (1987).	
Variables: <i>T</i> /K=308 <i>p</i> /MPa=0–2.1		Prepared By: Yu. P. Yampol'skii	
Experimental Data Sorption isotherms of methane and nitrogen in PMDA-IPDA at 308 K. (The original data were represented graphically)			
CH ₄		N ₂	
Pressure/MPa	Sorption (<i>V</i> [*] ₁ (STP)/ <i>V</i> [*] ₂)	Pressure/MPa	Sorption (<i>V</i> [*] ₁ (STP)/ <i>V</i> [*] ₂)
0.60	10.01	0.29	1.55
1.05	13.62	0.47	2.29
1.53	16.44	0.55	2.54
2.02	18.47	0.76	3.36
—	—	0.83	3.70
—	—	1.17	4.84
—	—	1.51	5.99
—	—	1.81	6.84
—	—	2.09	7.51
Auxiliary Information			
Method/Apparatus/Procedure The pressure decay method of measurement of sorption was described in Ref. 1.		Source and Purity of Materials: PMDA-IPDA; prepared by reaction of pyromellitic dianhydride with isopropylidene diamine. No details on synthesis or properties of the polymer are given.	
		Estimated Error: No information given.	
References: ¹ W. J. Koros and D. R. Paul, J. Polym. Sci., Polym. Phys. Ed. 14 , 1903 (1976).			

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Polyimide; product of biphthalotetracarboxylic dianhydride and sulfonodiamine; (BPDA-SDA)		Original Measurements: K. Okamoto, K. Tanaka, O. Yokoshi, K. Hidetoshi, and A. Nakamura, Intern. Congress on Membranes ICOM-87, 1987, 9-P15, pp. 542-543.	
Variables: <i>T</i> /K: 353 <i>p</i> /MPa: 0–2.5		Prepared By: Yu. P. Yampol'skii	
Experimental Data Dual-mode sorption parameters for carbon dioxide			
k_D , /cm ⁻³ (STP) cm ⁻³ atm ⁻¹	0.647	C'_{II} , /cm ³ (STP) cm ⁻³	b /atm ⁻¹ 0.279
Auxiliary Information			
Method/Apparatus/Procedure Equilibrium sorption was measured by the pressure decay method using a dual-volume sorption cell.		Source and Purity of Materials: Polyimide BS-1 had the following characteristics: density 1.417 g/cm ³ , glass transition temperature 623 K.	
Estimated Error: No information given.		Estimated Error: No information given.	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Polyimide Utem; [61128-24-3] (LXVIII)		Original Measurements: K. Okamoto, K. Tanaka, O. Yokoshi, K. Hidetoshi, and A. Nakamura, Intern. Congress on Membranes ICOM-87 1987, 9-P15, pp. 542-543.	
Variables: <i>T</i> /K: 353 <i>p</i> /MPa: 0–3.0		Prepared By: Yu.P. Yampol'skii	
Experimental Data Dual-mode sorption parameters for carbon dioxide			
k_D , /cm ³ (STP)cm ⁻³ atm ⁻¹	0.527	C'_{II} , /cm ³ (STP) cm ⁻³	b /atm ⁻¹ 0.286
Auxiliary Information			
Method/Apparatus/Procedure Equilibrium sorption was measured by the pressure decay method using a dual-volume sorption cell.		Source and Purity of Materials: Commercial sample of Utem-1000 (General Electric Co) had a density 1.289 g/cm ³ , glass transition temperature 488 K, and had an amorphous structure.	
Estimated Error: No information given.		Estimated Error: No information given.	

Components: (1) Carbon dioxide; CO ₂ ; [124-38-9] (2) Polyimide Ultem; [61128-24-3] (LXVIII)		Original Measurements: K. Okamoto, K. Tanaka, O. Yokoshi, K. Hidetoshi, and A. Nakamura, Intern. Congress on Membranes ICOM-87, 1987, 9-P15, pp. 542-543.	
Variables: <i>T</i> /K: 353 <i>p</i> /MPa: 0-3.0		Prepared By: Yu. P. Yampol'skii	
Experimental Data Dual-mode sorption parameters for carbon dioxide			
k_D , /cm ³ (STP)cm ⁻³ atm ⁻¹	0.527	C'_{II} , /cm ³ (STP) cm ⁻³	b /atm ⁻¹
		6.1	0.286
Auxiliary Information			
Method/Apparatus/Procedure Equilibrium sorption was measured by the pressure decay method using a dual-volume sorption cell.		Source and Purity of Materials: Commercial sample of Ultem-1000 (General Electric Co) had a density 1.289 g/cm ³ , glass transition temperature 488 K, and had an amorphous structure.	
Estimated Error: No information given.		Estimated Error: No information given.	

Components: (1) Helium; He; [7440-59-7] Nitrogen; N ₂ ; [7727-37-9] Oxygen; O ₂ ; [7782-44-7] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Poly(amide aminoacid) 6FDA-TADPO; [132634-94-7] (LXVII)		Original Measurements: D. R. B. Walker and W. J. Koros, <i>J. Membr. Sci.</i> 55 , 99 (1991).	
Variables: T/K= 308 p/MPa=0.3–1.0		Prepared By: Yu. P. Yampol'skii	
Experimental Data Solubility coefficient $S/(\text{cm}^3(\text{STP})/\text{cm}^3 \text{ atm})$			
He	N ₂	O ₂	CH ₄
0.058	0.33	0.56	3.05
			0.8
Auxiliary Information			
Method/Apparatus/Procedure Pressure decay method and apparatus was used.		Source and Purity of Materials: The polymer was synthesized according to Ref. 1. It had a density 1.413 g/cc. All the gases were Linde UHP (purity more than 99.97%).	
		Estimated Error: No information given.	
		References: ¹ R. T. Foster and C. S. Marvel, <i>J. Polym. Sci., A</i> 3 , 417 (1965).	

Components: (1) Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Polyetherimide (PEI); [61128-24-3] (LXXI)		Original Measurements: T. A. Barbari, W. J. Koros, and D. R. Paul, <i>J. Polym. Sci., Part B: Polym. Phys.</i> 26 , 729 (1988).	
Variables: T/K=308 p/MPa=0–2.3		Prepared By: A. K. Bokarev	

Experimental Data TABLE 1. Dual-mode sorption parameters for various gases in polyetherimide at 308 K			
Gas	$k_D/(\text{cm}^3(\text{STP}) \text{ cm}^{-3} \text{ atm}^{-1})$	$C'_D/(\text{cm}^3(\text{STP}) \text{ cm}^{-3})$	b/atm^{-1}
CO ₂	0.758	25.02	0.366
CH ₄	0.207	7.31	0.136
N ₂	0.063	4.15	0.045

TABLE 2. Sorption isotherms of various gases in polyetherimide at 308 K (The original data were represented graphically)					
CO ₂		CH ₄		N ₂	
Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)	Pressure/MPa	Sorption ($V_1^*(\text{STP})/V_2^*$)
0.19	10.88	0.12	1.12	0.27	0.65
0.24	12.85	0.24	2.10	0.34	0.81
0.27	14.26	0.29	2.51	0.40	0.83
0.33	15.38	0.37	3.08	0.45	0.98
0.56	20.05	0.45	3.59	0.71	1.44
0.64	21.83	0.67	4.78	0.77	1.59
0.70	23.23	0.81	5.35	0.88	1.65
0.78	23.79	0.90	5.81	0.94	1.78
0.98	26.96	1.07	6.55	1.14	2.11
1.08	28.17	1.14	6.59	1.25	2.24
1.16	29.10	1.25	7.29	1.34	2.26
1.25	29.75	1.29	7.17	1.42	2.35
1.45	32.17	1.48	7.98	1.59	2.70
1.55	33.10	1.57	8.15	1.75	2.93
1.64	33.93	1.66	8.53	1.79	2.85
1.72	34.39	1.79	8.69	1.89	2.94
1.93	36.43	1.89	9.15	2.26	3.39
2.02	37.36	2.06	9.60	2.35	3.52
2.20	38.37	—	—	—	—

Method/Apparatus/Procedure The sorption apparatus and procedures used in the present sorption experiments are the same as described earlier. ¹		Auxiliary Information	
Source and Purity of Materials: Gas: purity >99.99% (chromatographic quality). PEI (Uitem): General Electric Co., density 1.28 g/cm ³ , glass transition temperature 488 K.		Estimated Error: No information given.	
References: 1W. J. Koros, D. R. Paul, and A. A. Rocha, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 14 , 687 (1976).			

3.38. Block Copolymers and Polymer Blends—Various Gases

Components: (1) Nitrogen; N ₂ ; [7727-37-9] Oxygen; O ₂ ; [7782-44-7] Carbon dioxide; CO ₂ ; [124-38-9] (2) Poly(4-vinylpyridine-co-acrylonitrile); [25232-41-1]		Original Measurements: M. Yoshikawa, T. Ezaki, K. Sami, and N. Ogata, J. Appl. Polym. Sci. 35 , 145 (1988).	
Variables: T/K=303 p/kPa=0–80 (0–0.8 atm)		Prepared By: S. M. Shishatskii	

Experimental Data
The solubility of gases in two statistical copolymers having a mole fraction of 4-vinylpyridine equal to 0.038 (copolymers I) and 0.098 (copolymer II) was studied.

TABLE 1. Dual mode sorption parameters and solubility coefficient, S, for various gases in the copolymers (I) and (II) at 303 K				
Gas	S/cm ³ (STP) cm ⁻³ atm ⁻¹	k _D /cm ³ (STP) cm ⁻³ atm ⁻¹	C _H /cm ³ (STP) cm ⁻³	b/atm ⁻¹
N ₂	(I) 6.92	—	—	—
	(II) 8.54	—	—	—
O ₂	(I) 16.8	—	—	—
	(II) 18.2	—	—	—
CO ₂	(I) —	46.5	10.2	25.3
	(II) —	52.6	7.5	44.9

TABLE 2. Sorption isotherms of various gases in the copolymers (I) and (II) at 303 K. (The original data were represented graphically)

CO ₂				N ₂				O ₂					
Pressure/kPa		Sorption ($V_1^*(\text{STP})/V_2^*$)		Pressure/kPa		Sorption ($V_1^*(\text{STP})/V_2^*$)		Pressure/kPa		Sorption ($V_1^*(\text{STP})/V_2^*$)			
(I)	3.89	6.91		(I)	30.10	2.18		(I)	40.84	6.68			
	12.31	13.66			58.23	4.69			61.26	9.79			
	27.18	21.47			73.74	5.31			75.66	12.79			
	40.13	27.81			—	—			—	—			
	57.57	35.79			—	—			—	—			
(II)	4.26	7.31		(II)	24.98	2.17		(II)	35.71	6.55			
	11.63	11.77			40.52	3.12			53.18	9.95			
	26.37	21.16			63.97	5.27			65.95	11.94			
	40.85	28.74			—	—			—	—			
	57.11	38.52			—	—			—	—			

3.37. Polypyrrolone—Various Gases

Components: (1) Helium; He; [7440-59-7] Nitrogen; N ₂ ; [7727-37-9] Oxygen; O ₂ ; [7782-44-7] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8] (2) Polypyrrolone; [12634-94-7]		Original Measurements: D. R. B. Walken and W. J. Koros, J. Membr. Sci. 55 , 99 (1991).	
Variables: T/K=308 p/MPa=0.3–1.0		Prepared By: Yu. P. Yampol'skii	

Experimental Data			
Solubility coefficient S/cm ³ (STP) cm ³ atm			
He	N ₂	O ₂	CH ₄
0.091	0.72 ± 0.08	1.04	4.41
			1.7

Auxiliary Information

Method/Apparatus/Procedure
Pressure decay method and apparatus was used.

Source and Purity of Materials:
The polymer was synthesized according to Ref. 1. It had a density 1.405 g/cc.
All the gases were Linde UHP (purity more than 99.97%).

Estimated Error:
No information given.

References:
1R. T. Foster and C.S. Marvel, J. Polym. Sci., A, **3**, 417 (1965).

Components:				
(1) Nitrogen; N ₂ ; [7727-37-9] Oxygen; O ₂ ; [7782-44-7] (2) Copoly(vinylidene cyanide-vinyl acetate) (CVC-VA); [9003-24-1]				
Variables:		Original Measurements:		
T/K = 298 p/MPa = 0.13–1.3		H. Hachisuka, H. Kito, Y. Tsujita, A. Takizawa, and T. Kinoshita, <i>J. Appl. Polym. Sci.</i> 35 , 1333 (1988).		
Prepared By:		Prepared By:		
Y. P. Yampol'skii		Y. P. Yampol'skii		
Experimental Data				
Dual mode sorption parameters for nitrogen and oxygen in CVC-VA membranes at 298 K for different times of annealing at 433 K				
Time of annealing		$10^4 k_D / \text{cm}^2 (\text{STP}) \text{ cm}^{-3} \text{ cm Hg}^{-1}$	$C_H' / \text{cm}^3 (\text{STP}) \text{ cm}^{-3}$	$10^3 b / \text{cm Hg}^{-1}$
N ₂	"as cast"	2.0	1.74	0.8
	5 h	2.0	1.70	0.8
	15 h	2.0	1.66	0.8
O ₂	"as cast"	2.6	2.18	1.1
	5 h	2.6	2.12	1.1
	15 h	2.6	2.06	1.1

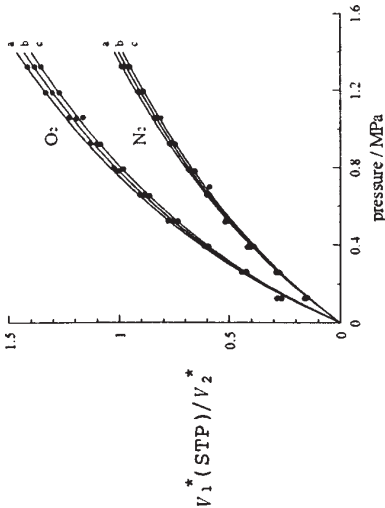


FIG. 86. Sorption isotherms of nitrogen and oxygen in CVC-VA at 298 K for different times of annealing at 433 K: (a) as cast; (b) 5 h annealing; (c) 15 h annealing.

Auxiliary Information	
Method/Apparatus/Procedure Sorption measurements were carried out by means of Cahn Electrobalance 2000 instrument. A correction for a buoyancy contribution was introduced. The films were cast from DMF.	Source and Purity of Materials: Gases: purity >99.9%. Alternating copolymer of VC and VA: Mitsubishi Petrochemical Co., amorphous polymer, glass transition temp. 449 K, density of as cast film, and ones annealed for 5 and 15 h equal to 1.212, 1.217, and 1.220 g/cm ³ , respectively (at 433 K).
Estimated Error: No information given.	

Components:	
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]	Original Measurements: P. C. Raymond and D. R. Paul, J. Polym. Sci.: Part B: Polym. Phys. 28 , 2079 (1990).
(2) Random copolymers styrene/methyl methacrylate (SMMA)	
Variables:	
<i>T</i> /K=308	Prepared By: Yu. P. Yampol'skii
<i>p</i> /MPa=0–2.5 (0–2.5 atm)	
Weight % MMA=20.5–88.0	

Experimental Data				
Dual mode sorption parameters in SMMA copolymers				
<i>N</i>	Weight % MMA	k_D / cm ³ (STP)/cm ³ atm	C'_D / cm ³ (STP)/cm ³	<i>b</i> / atm ⁻¹
1	20.5	Methane*	3.06	0.085
2	58.5	0.132	2.03	0.156
3	88.0	0.145	1.72	0.152
		0.181		
1	20.5	Carbon dioxide**	10.7	0.182
2	58.5	0.539	10.5	0.249
3	88.0	0.812	13.8	0.193
		1.07		

*Unconditioned film never exposed to CO₂.

**The isotherms obtained after exposing to CO₂ at 25 atm for 24 h.

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials: For the copolymers 1, 2, and 3 the glass transition temperatures were 371, 375, and 378 K, respectively, and the densities 1.075, 1.132, and 1.168 g/cc.
The equipment and procedure for sorption measurement were the same as in Ref. 1.	Estimated Error: No information given.
	References: ¹ Y. Maeda and D. R. Paul, Polymer 26 , 2055 (1985).

Components:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]	Original Measurements: H. Hachisuka, Y. Tsujita, A. Takizawa, and T. Kinoshita, Polymer 29 , 2050 (1988).
(2) Copoly(vinylidene cyanide-vinyl acetate) (CVC-VA); [9003-24-1]	
Variables:	
<i>T</i> /K=298	Prepared By: Yu. P. Yampol'skii
<i>p</i> /MPa= 0–1.33	

Experimental Data			
The effects of annealing time at 433 K on dual mode sorption parameters for carbon dioxide in CVC-VA at 298 K (taken from the plot by compiler)			
Time of annealing/h	$10^2 k_D$ / cm ³ (STP) cm ⁻³ cm Hg ⁻¹	C'_D / cm ³ (STP) cm ⁻³	$10^3 b$ / cm Hg ⁻¹
0	1.65	17.3	3.65
1	1.50	16.4	3.65
5	1.50	15.0	3.65
10	1.48	14.3	3.65
15	1.48	14.2	3.65

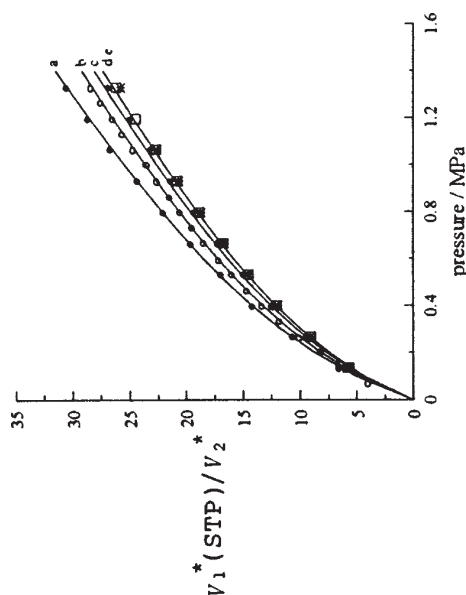


FIG. 87. Sorption isotherms of carbon dioxide in CVC-VA at 298 K for different times of annealing at 433 K: (a) as cast; (b) 1 h; (c) 5 h; (d) 10 h; (e) 15 h.

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials: Alternating copolymer VC-VA: amorphous polymer, intrinsic viscosity 4.9 dl/g, glass transition temperature of the films "as cast" 449 K.
Sorption was determined using gravimetric apparatus with Cahn Electrobalance 2000 instrument. A buoyancy correction was made.	Estimated Error: No information given.

Components: (1) Hydrocarbons C ₁ -C ₃ (2) Statistical copolymer of 2,6-dimethyl-1,4-phenylene oxide (97.5 mol %) and 2,6-diphenyl-1,4-phenylene oxide (2.5 mol %)			Original Measurements: O. M. Ilinitch, G. L. Semin, M. V. Chertova, and K. I. Zamarayev, J. Membr. Sci. 66 , 1 (1992).		
Variables: T/K=293.2 p/MPa=0-100			Prepared By: O. M. Ilinitch		
Experimental Data Solubility C/(cm ³ (STP) cm ⁻³ of hydrocarbons in the copolymer					
Gas	p/kPa	C	Gas	p/kPa	C
Methane CH ₄ [74-82-8]	28.0	0.6	Ethane C ₂ H ₆ [74-84-0]	2.7	0.9
	34.7	0.4		5.3	1.6
	50.0	0.7		8.0	2.2
	66.6	1.2		10.7	2.6
Propane C ₃ H ₈ [74-98-6]	86.6	1.4	Propene C ₃ H ₆ [115-07-1]	13.3	2.9
	96.0	1.5		17.3	3.4
	3.3	2.8		21.3	3.8
	6.3	3.6		25.3	4.4
Catalyst [74-98-6]	9.6	4.3	The copolymer and PPHP were synthesized in the presence of a catalyst described in Ref. 1.	1.6	2.0
	13.3	5.1		4.0	2.9
	18.7	5.8		6.7	4.0
	24.0	6.6		10.6	4.9
Polymer	29.3	7.3	Sorption measurements were done by means of Cahn electrobalance, model 2000.	14.0	5.6
	29.3	4.9		20.0	6.8
	33.3	5.5		26.7	7.6
	34.4	7.9		33.3	9.0
Compolymer	40.0	8.4	Sorption isotherms for three propyne polymers were reported. Their parameters are given below	38.7	9.6
	46.7	9.4		53.3	11.5
	53.3	10.2			
	61.3	11.2			

Method/Apparatus/Procedure The conventional McBain sorption spring balance was used.		Auxiliary Information	
Source and Purity of Materials: The copolymer was prepared via oxidative copolycondensation of two monomers. The purity of product 99.9%, it had density 1.10 g/cm ³ and T _g = 754 K. All the gases had a purity >99.9%.		Estimated Error: δT = ± 0.1 K; δp = ± 0.2 kPa. δC / C = 0.1 (complier).	

Components: (1) Propane; C ₃ H ₈ ; [74-98-6] (2) Copoly(trimethylsilylpropyne-phenylpropyne) Poly(trimethylsilylpropyne) (PTMSP); [87842-32-8] Poly(1-phenyl-1-propyne) (PPHP)		Original Measurements: T. Nakagawa, M. Sekiguchi, K. Nagai, and A. Higuchi, Int. Congress on Membranes (ICOM-90), Chicago, 1990, pp. 824-826.	
Variables: T/K=303 p/kPa=0-100 Copolymer composition: [TMSP]=90%; [PHP]=10%		Prepared By: Yu. P. Yampol'skii	
Experimental Data Sorption isotherms for three propyne polymers were reported. Their parameters are given below			
Polymer	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_D/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
PTMSP	6.93	50.14	2.15
Compolymer	8.35	43.59	2.77
PPHP	5.84	12.47	5.48
Auxiliary Information			
Method/Apparatus/Procedure Sorption measurements were done by means of Cahn electrobalance, model 2000.		Source and Purity of Materials: The copolymer and PPHP were synthesized in the presence of a catalyst TaCl ₅ -Ph ₃ Bi-H ₂ O. The synthesis of PTMSP was described in Ref. 1.	
References: J.K. Takada, H. Minuta, T. Masuda, and T. Higashimura, J. Appl. Polym. Sci. 30 , 1605 (1983).			

Components:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]	
(2) Copolyimide	
Original Measurements:	
K. Okamoto, K. Tanaka, O. Yokoshi, K. Hidetoshi, and A. Nakamura, Intern. Congress on Membranes ICOM-87, 9-115, pp. 542-543.	
Variables:	
<i>T</i> /K=353	
<i>p</i> /MPa=0-2.5	
Prepared By:	
Yu. P. Yampol'skii	

Experimental Data			
Dual-mode sorption parameters for carbon dioxide			
Sample	<i>k_D</i> /(cm ³ (STP)/cm ³ atm)	<i>C_H</i> /(cm ³ (STP)/cm ³)	<i>b</i> /atm ⁻¹
Cast	0.588	20.9	0.281
Annealed	0.573	18.5	0.249

Auxiliary Information	
Method/Apparatus/Procedure	Equilibrium sorption was measured by the pressure decay method using a dual-volume sorption cell.
Source and Purity of Materials	The polymers films (both cast and annealed at 603 K for 5 h) had the following characteristics: density 1.357 g/cm ³ , glass transition temperature 623 K. Cast and annealed films had amorphous structure.
Estimated Error:	No information given.

Components:	
(1) Hydrocarbons C ₁ -C ₃	
(2) Statistical copolymer of 2,6-dimethyl-1,4-phenylene oxide (75 mol %) and 2,6-diphenyl-1,4-phenylene oxide (25 mol %)	
Original Measurements:	
O. M. Ilinitch, G. L. Semin, M. V. Chertova, and K. I. Zamarayev, J. Membr. Sci. 66 , 1 (1992).	
Variables:	
<i>T</i> /K=293.2	
<i>p</i> /MPa=0-100	
Prepared By:	
O. M. Ilinitch	

Experimental Data					
Solubility $C/(\text{cm}^3(\text{STP})\text{cm}^{-3})$ of hydrocarbons in the copolymer					
Gas	p/kPa	C	Gas	p/kPa	C
Methane CH_4 [74-82-8]	34.0	0.4	Propane	5.1	3.1
	53.3	0.8	C_3H_8	10.0	4.4
	66.7	1.2	[74-98-6]	14.0	5.1
	82.6	1.5		20.0	5.9
Ethane C_2H_6 [74-84-0]	7.3	1.1		24.0	6.6
	14.0	1.4		29.3	7.2
	21.3	2.1		34.4	7.8
	26.9	2.5		40.0	8.4
Ethylene C_2H_4 [74-85-1]	34.4	3.6		46.6	9.4
				53.3	10.2
				61.3	11.2
Propylene C_3H_6 [115-07-1]	8.0	1.0	Propylene	1.6	2.0
	12.0	1.3		4.0	2.9
	14.3	1.6		6.7	4.0
	18.7	1.8		10.6	4.9
	22.0	2.1		14.0	5.6
	26.0	2.6		20.0	6.8
	34.7	3.2		26.7	7.6
				33.3	9.0
			38.7	9.6	
			53.3	11.5	

Auxiliary Information	
Method/Apparatus/Procedure	The conventional McBain sorption spring balance was used.
Source and Purity of Materials:	The copolymer was prepared via oxidative copolycondensation of two monomers. The purity of product 99.9%, it had density 1.10 g/cm ³ and <i>T_g</i> =483 K. All the gases had a purity >99.9%.
Estimated Error:	$\delta T = \pm 0.1$ K; $\delta p = \pm 0.2$ kPa. $\delta C/C = 0.1$ (computer).

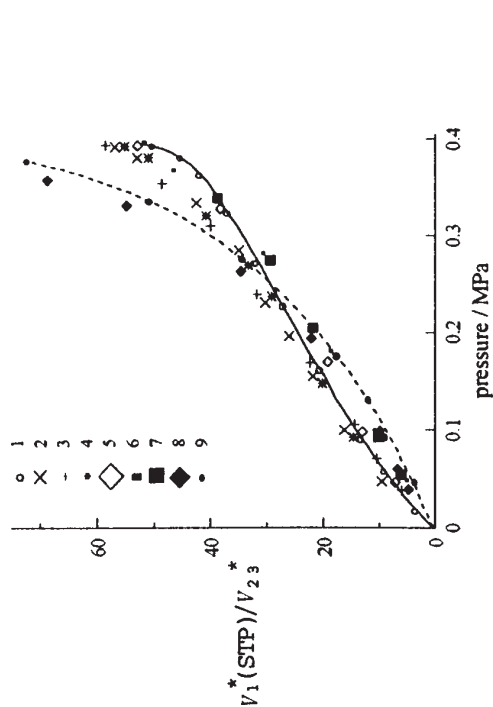


FIG. 89. Sorption isotherms of sulfur dioxide in silane-siloxane copolymers with mass % siloxane content of: 0% (1), 4% (2), 13% (3), 22% (4), 34% (5), 38% (6), 42% (7), 62% (8), 100% (9).

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials
Sorption was measured by means of a McBain balance using the technique described in Ref. 1.	PVTMS: $M_n = 200\,000$. PDMS: $M_n = 150\,000$. Silane-siloxane block-copolymers of the A-B type: prepared by anionic polymerization; M_n (silane block) = 200 000, weight contents of siloxane block indicated in Fig. 89.
Estimated Error:	
No information given.	
References:	
1. V. V. Volkov, A. K. Bokarev, and S. G. Durgaryan, Vysokomol. Soedin., Ser. A 26, 1294 (1984).	

Components:		Original Measurements: V. V. Volkov, A. K. Bokarev, and S. G. Durgaryan, Vysokomol. Soedin, Ser. B 26, 107 (1985).
(1) Sulfur dioxide; SO ₂ ; [7446-09-5]		
(2) Poly(dimethylsiloxane) (PDMS); [9016-00-6]		
(3) Poly(vinyltrimethyl silane) (PVTMS); [25036-32-2] (XV)		
Variables:		Prepared By: S. M. Shishatskii
T/K = 298		
p/MPa = 0-0.4		

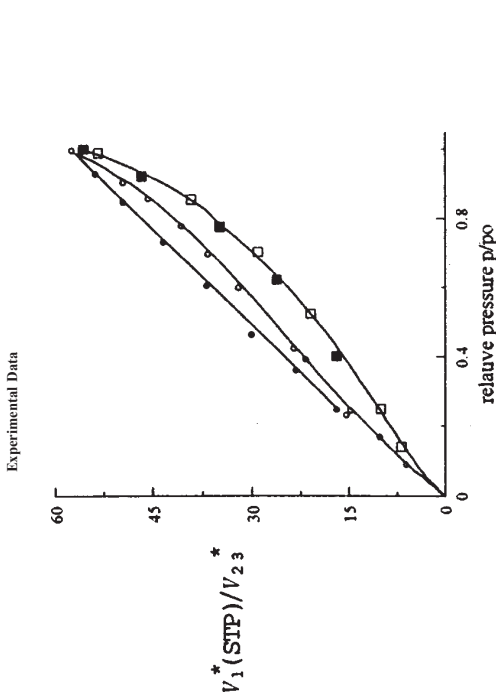


FIG. 88. Sorption (open symbols) and desorption (closed symbols) isotherms of sulfur dioxide in block-copolymers with mass % siloxane content of 13% (circles) and 42% (squares).

Components:		Original Measurements:			
(1) Helium; He; [7440-59-7] Argon; Ar; [7440-37-1] Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]		J. S. Chou, J. W. Barlow, and D. R. Paul, <i>J. Appl. Polym. Sci.</i> 30 , 1137 (1985).			
(2) Poly(methyl acrylate) (PMA); [9003-21-8] (V)					
(3) Poly(epichlorohydrin) (PECH); [24969-06-0]					
Variables:		Prepared By:			
T/K: 308		A. K. Bokarev			
p/MPa: 0–2.0					
Experimental Data					
At 308 K sorption isotherms of simple gases in PMA/PECH blends are completely linear at pressures as high as 2 MPa, and sorption can be described by Henry's law.					
Solubility coefficients $k_D \cdot 10^4$ (cm ³ (STP)/cm ³ cm Hg)					
Gases	PMA	75 PMA/25 PECH	50 PMA/50 PECH	25 PMA/75 PECH	PECH
He	1.35	1.26	1.14	—	0.990
Ar	9.96	9.19	8.73	8.33	7.73
N ₂	4.86	4.34	4.17	3.98	3.66
CH ₄	19.4	17.6	16.6	16.4	15.6
CO ₂	261.0	225.0	181.0	152.0	124.0
Auxiliary Information					
Method/Apparatus/Procedure		Source and Purity of Materials:			
The apparatus and experimental procedure used for sorption measuring have been described elsewhere. ¹		The PMA (from Celanese Chemical Co.) had $M_w = 576\,000$; $T_g = 291$ K; $\rho = 1.21$ g/cm ³ . The PECH (Hydrin 100) was obtained from B. F. Goodrich Co. $T_g = 251$ K; $\rho = 1.37$ g/cm ³ . Gases: no information.			

References:
¹W. J. Koros, D. R. Paul, and A. A. Rocha, *J. Polym. Sci., Polym. Phys. Ed.* **14**, 687 (1976).

Components:		Original Measurements:		
(1) Carbon dioxide; CO ₂ ; [124-38-9]		J. A. Barrie and W. D. Webb, <i>Polymer</i> 30 , 327 (1989).		
(2) Copolymer of ethylene-vinyl acetate (CEVA); [24937-78-8]				
(3) Chlorosulphonated polyethylene Hypalon-48 (CPE)				
Variables:		Prepared By:		
T/K=303–323 p/kPa=0–33.25		Yu. P. Yampol'skii		
CEVA conc. in blends, wt. %: 0–100				
Experimental Data				
Solubility in miscible blends of CEVA and CPE obeys Henry's law.				
Solubility coefficients $S \cdot 10^2$ (cm ³ (STP)/cm ³ cm Hg) of CO ₂ in the blends				
Temperature K				
CEVA, wt %	303	313	323	T_g /K
100	2.00	1.73	1.48	257
90	1.87	1.59	1.38	
80	1.81	1.57	1.37	
70	1.71	1.44	1.26	
60	1.56	1.35	1.18	
50	1.52	1.32	1.17	
40	1.42	1.22	1.08	
30	1.33	1.15	1.00	
20	1.27	1.10	0.98	
0	1.10	0.96	0.85	
				293
				127

Estimated Error:
 No information given.

Components:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]	Original Measurements: J. S. Chioi, Y. Maeda, and D. R. Paul, J. Appl. Polym. Sci. 30 , 4019 (1985).
(2) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)	
(3) Poly(vinylidene fluoride) (PVF ₂); [24937-79-9]	
Variables:	
T/K = 308	Prepared By: Yu. P. Yampol'skii
p/MPa = 0–2.53 (0–25 atm)	

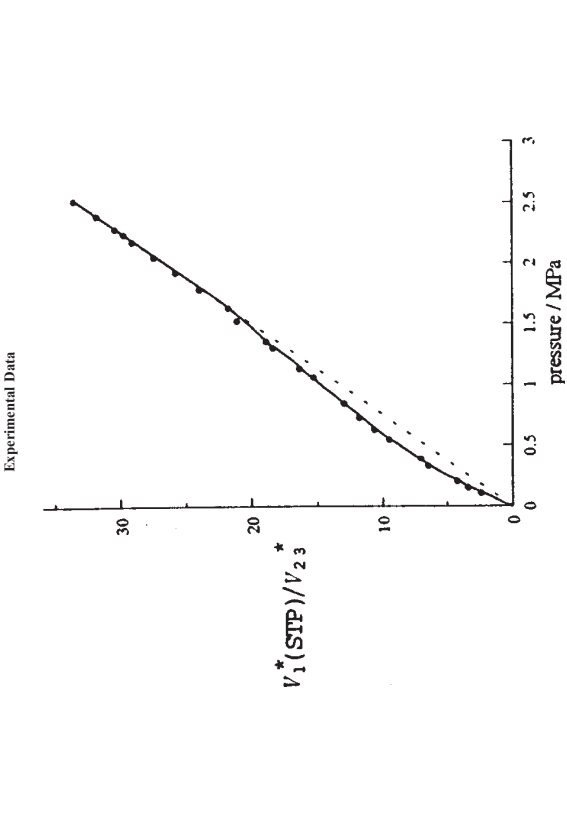


FIG. 91. Sorption isotherm of carbon dioxide in an amorphous blend containing 65% PMMA and 35% PVF₂ at 308 K.

Method/Apparatus/Procedure	
Sorption isotherm was obtained using the dual-transducer cell design based on the pressure decay principle.	
Auxiliary Information	
Source and Purity of Materials: Polymers: conditioned at highest pressure of carbon dioxide before measurement, completely amorphous and miscible blend, glass transition temperature 335 K.	
Estimated Error: No information given.	

Components:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]	Original Measurements: J. S. Chioi and D. R. Paul, J. Appl. Polym. Sci. 34 , 1037 (1987).
(2) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)	
(3) Styrene/acrylonitrile copolymer (CPSAN)	
Variables:	
T/K = 308	Prepared By: S. M. Shishatskii
p/MPa = 0.2–2.6 (2–26 atm)	

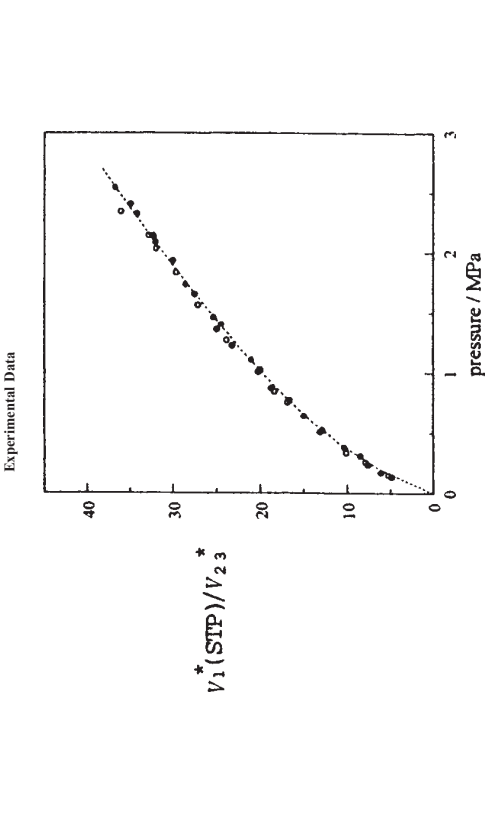


FIG. 90. Sorption of carbon dioxide was studied in homogeneous and phase separated blends PMMA/CPSAN (50/50 by mass). The composition of CPSAN is 28 mass % of acrylonitrile. The parameters of dual mode sorption isotherm for carbon dioxide in the blends at 308 K are $k_D = 0.89 \text{ cm}^3(\text{STP})/\text{cm}^3 \text{ atm}$; $C'_D = 16.6 \text{ cm}^3(\text{STP})/\text{cm}^3$; $b = 0.183 \text{ atm}^{-1}$. Sorption isotherm of carbon dioxide in homogeneous (●) and phase-separated (○) PMMA/CPSAN blends.

Method/Apparatus/Procedure	
A pressure decay method was used but no details are given. The films cast from tetrahydrofuran had a morphology of homogeneous blends. Subsequent heating at 488 K resulted in phase separated blends.	
Auxiliary Information	
Source and Purity of Materials: PMMA: Rohm and Haas Plexiglas V(811). $M_w = 105\,400$, $M_n = 52\,400$, density 1.188 g/cm^3 , glass transition temperature 379 K. CPSAN: Union Carbide RMD-4511. $M_w = 223\,000$, $M_n = 88\,600$, density 1.080 g/cm^3 , glass transition temperature 377 K.	
Estimated Error: No information given.	

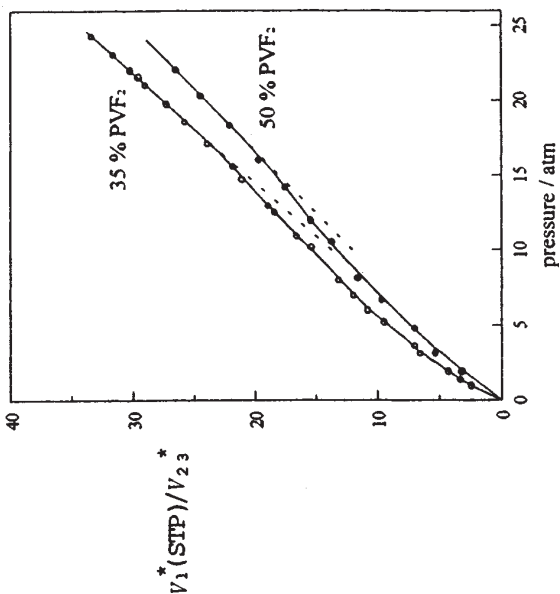


FIG. 93. Sorption isotherms of carbon dioxide in PMMA/PVF₂ blends at 308 K for 35 and 50 mass % of PVF₂.

Auxiliary Information

Method/Apparatus/Procedure
No details of the experimental procedure are given. Apparently, sorption is measured by pressure decay method.¹

Source and Purity of Materials:
PMMA Rohm and Haas Co. (Plexiglas V(811)), fully amorphous, glass transition temp. 378 K.
PVF₂ Penwalt Co. (Kynar 460 N), crystallinity 60%, melting point 433 K.
Blends: prepared as described in Ref. 2. Miscible blends were studied.

Estimated Error:
No information given.

References:
¹W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. **14**, 687 (1976)
²J. S. Chou, J. W. Barlow, and D. R. Paul, J. Appl. Polym. Sci. **30**, 2633 (1985).

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]		J. S. Chou and D. R. Paul, J. Appl. Polym. Sci. 32 , 2897 (1986).	
(2) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)			
(3) Poly(vinylidene fluoride) (PVF ₂); [24937-79-9]			
Variables:		Prepared By:	
T/K = 308		Yu. P. Yampol'skii	
p/MPa = 0–2.5 (0–25 atm)			
mass % PVF = 0–100			

Experimental Data

The sorption isotherms for some blends (PVF₂ content in the range 35–60 mass %) showed an unusual form and could not be described by dual mode sorption model. A modified DMS model was proposed where for the Langmuir capacity parameter C'_{H_2} from the DMS model an equation was suggested:

$$C'_{H_2} = C'_{H_2}(T_g - T)/(T_g - T_g^0)$$

where C'_{H_2} is initial Langmuir capacity parameter prior to any reduction in T_g due to CO₂ plastisization, T_g^0 is the glass transition temperature for the pure polymer. T_g is the glass transition temperature in the presence of sorbed gas, and T is the temperature of measurement, i.e., 308 K.

Sorption parameters for carbon dioxide in PMMA/PVF₂ blends *

PVF ₂ mass %	Volume fraction of amorph phase α	From isotherm slope		From regression analysis	
		k_D	k_D/α	k_D	C'_{H_2}/α
100	0.426	0.664	1.559	—	—
80	0.621	0.865	1.394	—	—
60	0.812	1.105	1.362	1.494	7.26
50	0.886	1.215	1.371	—	—
40	0.953	1.283	1.346	1.403	8.15
35	0.971	1.319	1.358	1.417	10.9
20	1.0	—	—	1.352	16.3
0	1.0	—	—	1.409	25.6
					0.0993

Units: α , dimensionless; k_D , cm³(STP)/cm³ atm; C'_{H_2} , cm³(STP)/cm³; b , atm⁻¹.

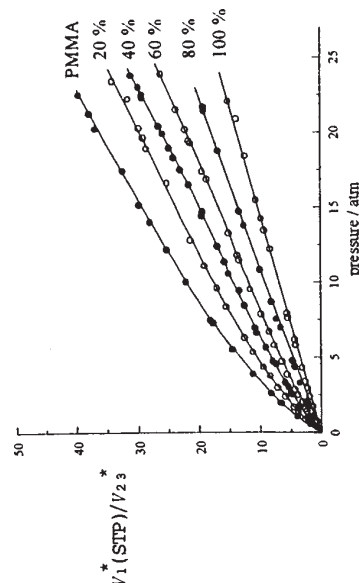
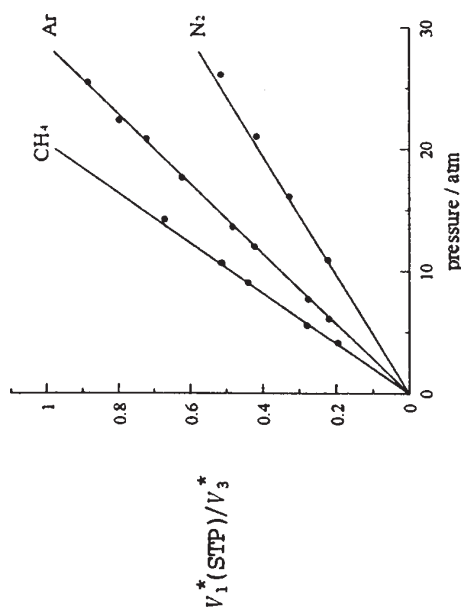
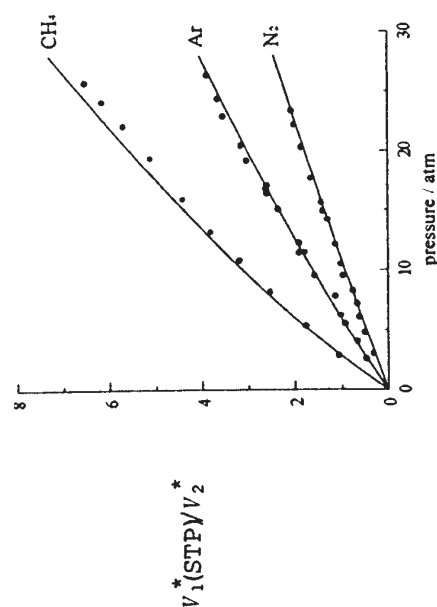


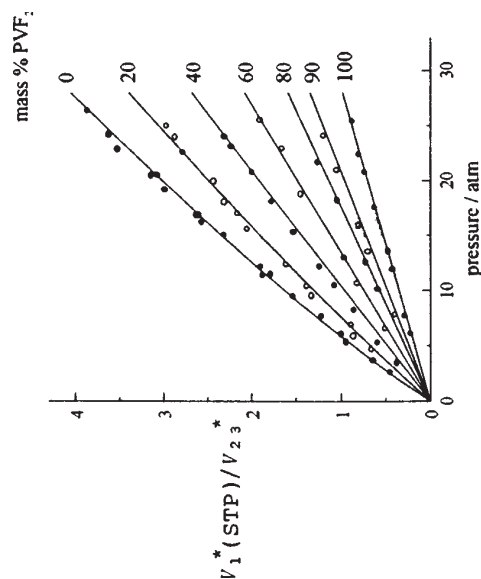
FIG. 92. Sorption isotherms of carbon dioxide in PMMA/PVF₂ blends at 308 K (mass % PVF₂).

FIG. 94. Sorption isotherms of Ar, CH₄, and N₂ in PVF₂ at 308 K.FIG. 95. Sorption isotherms of Ar, CH₄, and N₂ in PMMA at 308 K.

Components:		Original Measurements:		
(1) Argon; Ar; [7440-37-1] Nitrogen; N ₂ ; [7727-37-9] Carbon dioxide; CO ₂ ; [124-38-9] Methane CH ₄ ; [74-82-8]		J. S. Chioi and D. R. Paul, J. Appl. Polym. Sci. 32 , 4793 (1986).		
(2) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)				
(3) Poly(vinylidene fluoride) (PVF ₂); [24937-79-9]				
Variables:		Prepared By:		
T/b/MPa=0–2.7 (0–27 atm)		Yu. P. Yampol'skii		
mass % PVF=0–100				
Experimental Data				
TABLE 1. Solubility coefficients of various gases in PVF ₂ at 308 K				
Gas	Ar	N ₂	CH ₄	
S'/cm ³ (STP) cm ⁻³ atm ⁻¹	0.0350	0.0206	0.0488	
TABLE 2. Dual mode sorption parameters for various gases in PMMA at 308 K				
Gas	k _D /cm ³ (STP) cm ⁻³ atm ⁻¹	C' _D /cm ³ (STP) cm ⁻³	b/atm ⁻¹	
Ar	0.1150	1.450	0.0480	
N ₂	0.0737	0.814	0.0301	
CH ₄	0.1820	3.620	0.0560	
TABLE 3. Dual mode sorption parameters for argon in extruded PMMA/PVF ₂ blends at 308 K.				
PVF ₂ mass %	k _D /cm ³ (STP) cm ⁻³ atm ⁻¹	C' _D /cm ³ (STP) cm ⁻³	b/atm ⁻¹	(k _D /α)/cm ³ (STP) cm ⁻³ atm ⁻¹
100	0.0350	—	—	0.0779
90	0.0480	—	—	0.0857
80	0.0568	—	—	0.0849
60	0.0742	—	—	0.0817
40	0.0893	—	—	0.0893
20	0.1040	0.982	0.0345	0.1040
0	0.1150	1.450	0.0480	0.1150

is the crystallinity of PVF₂ in the blend.

α is the crystallinity of PVF₂ in the blend.

FIG. 96. Sorption isotherms of argon in PMMA/PVF₂ blends at 308 K.

Auxiliary Information

Method/Apparatus/Procedure

The apparatus and procedure were the same as described in Ref. 1.

Source and Purity of Materials:

PMMA: Rohm and Haas (Plexiglas V(811)), glass transition temp. 378 K, completely amorphous.

PVF₂: Penwalt (Kynar 460N), crystallinity 60%, melting point 433 K.

Blends: films prepared by extrusion. Miscible blends were studied.

Estimated Error

No information given.

References:

¹W. J. Koros, D. R. Paul, and A. A. Rocha, *J. Polym. Sci., Polym. Phys. Ed.* **30**, 2633 (1985).

Components:	Original Measurements:
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]	P. C. Raymond and D. R. Paul, <i>J. Polym. Sci.: Part B: Polym. Phys.</i> 28 , 2103 (1990).
(2) Poly(methyl methacrylate) (PMMA); [9011-14-7] (VI)	
(3) Bisphenol chloral polycarbonate (BCPC); [31546-39-1] (XXX)	

Variables:

$T/K = 308$

$p/\text{MPa} = 0 - 2.5$

Prepared By:

V. I. Bondar

Experimental Data

Dual mode sorption parameters for carbon dioxide and methane in polymers at 308 K

PMMA Vol. %	$k_D / \text{cm}^3(\text{STP}) \text{cm}^{-3} \text{atm}^{-1}$	$C_H / \text{cm}^3(\text{STP}) \text{cm}^{-3}$	b / atm^{-1}
Carbon dioxide (in conditioned polymers)			
0	0.718	14.9	0.271
28.0	0.736	14.8	0.240
53.9	0.778	15.7	0.190
77.8	1.03	11.9	0.245
100	1.20	15.6	0.172
Methane (in unconditioned polymers)			
0	0.130	6.64	0.088
28.0	0.116	6.92	0.069
53.9	0.144	4.58	0.077
77.8	0.133	4.60	0.061
100	0.199	1.53	0.153

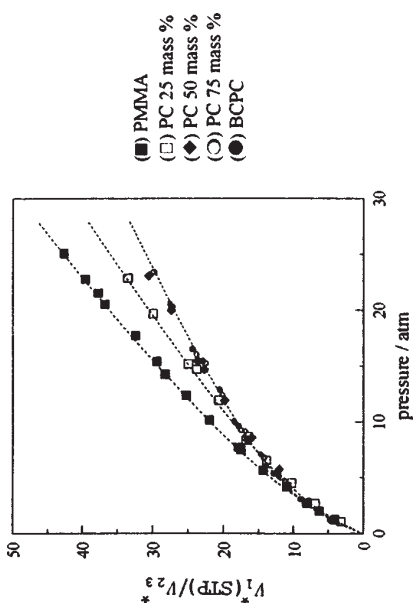


FIG. 97. Sorption isotherms of carbon dioxide in conditioned blends and homopolymers at 308 K.

Components:		Original Measurements:	
(1) Propane; C ₃ H ₈ ; [74-98-6]		H. G. Spencer and J. A. Yavorsky, J. Appl. Polym. Sci. 28 , 2937 (1983).	
(2) Polystyrene (PS); [9003-53-62] (IX)			
(3) Poly(vinylmethyl ether) (PVME); [9003-09-2]			
Variables:		Prepared By:	
T/K = 312–370		A. K. Bokarev	
p/kPa = 0–40			
PS mass content/% = 25–75			
Experimental Data			
In the pressure range indicated above solubility obeys Henry's law. Temperature dependence for the solubility coefficient S of propane in PS/PVME blends is given by the equation:			
$S = S_0 \exp(-\Delta H/RT)$			
TABLE 1. Mass content dependence for the solubility coefficient S of propane in PS/PVME blends at 353 K			
PS content mass %	–ΔH/(kJ/mol)	ln(S ₀ /(cm ³ (STP)/cm ³ cm Hg))	ln(S/(cm ³ (STP)/cm ³ cm Hg))
25	10	–7.49	–3.99
50	7	–6.61	–4.36
75	5	–6.15	–4.54
TABLE 2. Temperature dependence of the solubility coefficient S of propane in PS/PVME blends			
T/K	ln(S/(cm ³ (STP)/cm ³ cm Hg))		
PS 25 mass %			
328.3	–3.82		
333.7	–3.73		
346.4	–3.79		
350.4	–4.08		
358.7	–4.17		
364	–4.06		
PS 50 mass %			
324.9	–4.19		
337.2	–4.29		
361.3	–4.48		
370.9	–4.46		
PS 75 mass %			
313.6	–4.35		
323.8	–4.49		
333.2	–4.35		
353.5	–4.59		

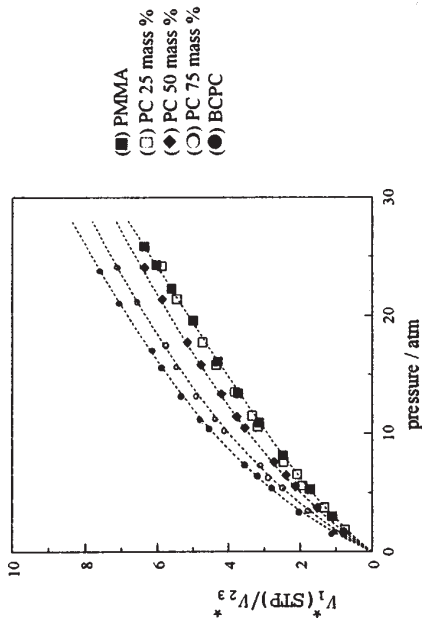


FIG. 98. Sorption isotherms of methane in unconditioned blends and homopolymers at 308 K.

Auxiliary Information		
Method/Apparatus/Procedure	Source and Purity of Materials:	
A pressure decay method was used. Methane sorption was measured on samples that had not previously been exposed to CO ₂ . For CO ₂ these measurements were preceded by conditioning the films at 25 atm of CO ₂ for 24 h.	BCPC: General Electric Co.	
	PMMA: Rohm and Haas Co.	
	PMMA mass %	
	0	T _g / K 437 density/g cm ^{–3} 1.392
	25	413 1.336
	50	401 1.285
	75	386 1.235
	100	379 1.188
Estimated Error:		
No information given.		

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials
Sorption measurements were carried out in a low pressure, constant-volume cell previously described. ¹	C ₃ H ₈ : Matheson, purity 99.99%.
	PS, PVME: Polysciences, Inc.
	PS: $M_{w,0} = 23\ 000$; PVME: $M_w = 34\ 000$.
PS/%	T_g / K
25	253
50	275
75	303
$\rho / g, cm^{-3}$	
—	
1.052	
1.060	

Estimated Error:
No information given.

References:
¹J. A. Yavorsky and H. G. Spencer, J. Appl. Polym. Sci. **25**, 2109 (1980).

Components:		Original Measurements:	
(1) Propane: C ₃ H ₈ : [74-98-6]		J. A. Yavorsky, Ph.D. dissertation, 1984.	
(2) Polystyrene (PS): [9003-53-62] (X)			
(3) Poly(vinylmethyl ether) (PVME): [9003-09-2]			
Variables:		Prepared By:	
$T / K = 278 - 374$		A. K. Bokarev	
$p / kPa = 0 - 798$			

Experimental Data
The PS/PVME blends studied contained 90.0% and 75.0% by weight PS. $M_s = 0.90$ and $M_s = 0.75$, respectively.

TABLE 1. Sorption isotherms of propane below 350 K in the copolymer blend for which $M_s = 0.90$ (The original data were represented graphically)

$T = 283\ K$				$T = 303.5\ K$				$T = 322\ K$			
Pressure/kPa	Sorption ($V_1^*(STP)/V_2^*$)	Pressure/kPa	Sorption ($V_1^*(STP)/V_2^*$)	Pressure/kPa	Sorption ($V_1^*(STP)/V_2^*$)	Pressure/kPa	Sorption ($V_1^*(STP)/V_2^*$)	Pressure/kPa	Sorption ($V_1^*(STP)/V_2^*$)	Pressure/kPa	Sorption ($V_1^*(STP)/V_2^*$)
28.83	0.80	31.97	0.47	32.66	0.28	70.22	1.30	75.92	0.98	78.92	0.50
79.17	2.81	185.78	2.75	172.72	1.44	167.26	3.06	353.37	5.19	172.07	1.67
239.05	6.22	378.07	7.15	306.54	2.28	299.18	5.68	710.15	11.39	368.64	4.08
—	—	791.00	12.15	745.61	5.89	—	—	—	—	—	—

Sorption isotherms above 350 K show a linear relationship, and the solubility coefficient is independent of pressure.

TABLE 2. Dual mode sorption parameters and solubility coefficient, S, for propane in the copolymer blend for which $M_s = 0.90$ (pressure range 0–798 kPa)

T / K	k_D	$10^3 / cm^3(STP) cm^{-3} cm Hg^{-1}$	$C_H / cm^3(STP) cm^{-3}$	$b / cm Hg^{-1}$	$S / cm^3(STP) cm^{-3} cm Hg^{-1}$
283	2.29% ± 9%	10.9% ± 15%	0.50% ± 35%	2.84% ± 10%	2.84% ± 10%
303.5	1.15% ± 19%	10.8% ± 35%	1.30% ± 53%	2.55% ± 9%	2.55% ± 9%
322	0.86% ± 12%	11.4% ± 22%	0.70% ± 44%	1.66% ± 12%	1.66% ± 12%
353	0.90% ± 6%	4.5% ± 50%	0.15% ± 100%	0.97% ± 10%	0.97% ± 10%
364	0.82% ± 12%	—	—	0.82% ± 12%	0.82% ± 12%
369	1.11% ± 9%	—	—	1.11% ± 9%	1.11% ± 9%

TABLE 3. Sorption isotherms of propane below 323 K in the co-polymer blend for which $M_s = 0.75$ (The original data were represented graphically)

$T = 278\text{ K}$			$T = 293\text{ K}$			$T = 308\text{ K}$		
Pressure/kPa	Sorption ($V^*_g(\text{STP})/V_{23}$)		Pressure/kPa	Sorption ($V^*_g(\text{STP})/V_{23}$)		Pressure/kPa	Sorption ($V^*_g(\text{STP})/V_{23}$)	
14.2	1.07		6.45	0.38		6.04	0.13	
31.83	2.24		10.30	0.58		6.86	0.24	
62.01	5.20		22.19	1.16		10.47	0.42	
—	—		26.45	1.06		13.37	0.41	
—	—		46.51	2.46		15.44	0.29	
—	—		57.04	2.64		16.86	0.50	
—	—		—	—		18.81	0.59	
—	—		—	—		22.72	0.94	
—	—		—	—		31.42	1.06	
—	—		—	—		55.68	2.21	

Sorption isotherms above 323 K are linear in the pressure range studied, and the solubility coefficients are independent of pressure.

TABLE 4. Dual mode sorption parameters and solubility coefficient, S , for propane in the copolymer blend for which $M_s = 0.75$ (pressure range 0–66 kPa)

T/K	$k_D \cdot 10^2/\text{cm}^3(\text{STP}) \text{ cm}^{-3} \text{ Hg}^{-1}$	$C'_H/\text{cm}^3(\text{STP}) \text{ cm}^{-3}$	$b/\text{cm Hg}^{-1}$	$S'/\text{cm}^3(\text{STP}) \text{ cm}^{-3} \text{ cm Hg}^{-1}$
278	$6.40\% \pm 11\%$	$3.2\% \pm 20\%$	$2.15\% \pm 50\%$	$13.29\% \pm 16\%$
293	$4.00\% \pm 12\%$	$2.2\% \pm 22\%$	$1.80\% \pm 44\%$	$7.99\% \pm 44\%$
308	$3.50\% \pm 11\%$	$2.1\% \pm 19\%$	$0.55\% \pm 40\%$	$6.79\% \pm 12\%$
323	$2.40\% \pm 12\%$	$1.4\% \pm 32\%$	$0.35\% \pm 55\%$	$4.33\% \pm 51\%$
323	$2.40\% \pm 12\%$	$1.4\% \pm 32\%$	$0.35\% \pm 55\%$	$4.33\% \pm 51\%$
333	$3.06\% \pm 4\%$	—	—	$3.06\% \pm 4\%$
343	$2.49\% \pm 4\%$	—	—	$2.49\% \pm 4\%$
353	$1.99\% \pm 4\%$	—	—	$1.99\% \pm 4\%$
364	$1.89\% \pm 4\%$	—	—	$1.89\% \pm 4\%$
374	$1.65\% \pm 4\%$	—	—	$1.65\% \pm 4\%$

The isotherms when $M_s = 0.75$ Q and $M_s = 0.75$ QA were linear.

TABLE 5. Solubility coefficient when $M_s = 0.75$ Q

T/K	$k_D \cdot 10^2/\text{cm}^3(\text{STP}) \text{ cm}^{-3} \text{ cm Hg}^{-1}$
323	$3.19\% \pm 8\%$
328	$3.67\% \pm 4\%$
333	$2.96\% \pm 4\%$
343	$2.21\% \pm 4\%$
358	$1.99\% \pm 4\%$

TABLE 6. Solubility coefficient when $M_s = 0.75$ QA

T/K	$k_D \cdot 10^2/\text{cm}^3(\text{STP}) \text{ cm}^{-3} \text{ cm Hg}^{-1}$
323	$2.45\% \pm 4\%$
327	$3.14\% \pm 4\%$
338	$2.71\% \pm 4\%$
358	$2.00\% \pm 4\%$

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]	(2) Polystyrene (PS); [9003-53-6] (3) Poly(vinylmethyl ether) (PVME); [9003-09-2] (polymer blends)	H. Hachisaka, T. Sato, Y. Tsujita, A. Takizawa, and T. Kinoshita, Polym. J. 21 , 417 (1989).	
(2) Polystyrene (PS); [9003-53-6]			
(3) Poly(vinylmethyl ether) (PVME); [9003-09-2]			
Variables:		Prepared By:	
T/K=298	p/MPa=0–1.33	Yu. P. Yampol'skii	

Experimental Data					
Dual mode sorption parameters for CO ₂ in PS/PVME blends					
Composition total	PS/PVME phase	k_D 10 ² /cm ³ (STP)/cm ³ cm Hg	C'_D /cm ³ (STP)/cm ³	b 10 ² /(cm Hg) ⁻¹	
100/0	—	1.12	4.1	2.36	
75/25	—	1.41	1.5	1.45	
50/50	—	2.01	—	—	
20/80	—	2.62	—	—	
75/25	(83/17)/(1/79)	1.49	2.4	2.76	
50/50	(73/27)/(31/69)	2.05	0.4	4.73	
20/80	(74/26)/(19/81)	2.93	1.1	3.95	
0/100	—	4.00	—	—	

Auxiliary Information			
Method/Apparatus/Procedure		Source and Purity of Materials:	
Sorption measurement was carried out using electromicrobalance Cahn 2000. The correction for buoyancy was introduced.		Type	T_g , K
		Single phase	315.0
		same	262.9
		same	248.6
		Phase separated (75/25)	321.2
		Phase separated (50/50)	249.2
		Phase separated (20/80)	301.2
		Phase separated (20/80)	253.2
		Phase separated (20/80)	308.6
		Phase separated (20/80)	248.0

CO₂ purity >99.99%

Estimated Error:
No information given.

Components:		Original Measurements:	
(1) Propane; C ₃ H ₈ ; [74-98-6] Miscible blend (75/25% w/w) of (2) Polystyrene (PS); [9003-53-6] and (3) Poly (vinylmethyl ether) (PVME); [9003-09-2]		J. A. Yavorsky and H. J. Spencer, J. Appl. Polym. Sci. 31 , 501 (1986).	
Variables:		Prepared By:	
T/K: 308–374 p/kPa: 0–80		A. K. Bokarev	

Experimental Data				
Sorption parameters for the 75/25% (w/w) PS/PVME blends				
Series	T/K/ cm ³ (STP) cm ⁻³ cm Hg ⁻¹	10 ² k_D /cm ³ (STP) cm ⁻³	10 ² b /cm ³ (STP) cm ⁻³ cm Hg ⁻¹	k^*
C-1	308	3.5(±11%)	2.1(±19%)	6.79(±12%)
	293	4.0(±12%)	1.8(±44%)	7.99(±13%)
	278	6.4(±11%)	2.2(±22%)	13.3(±16%)
	323	2.4(±12%) ^a	3.2(±20%)	4.33(±51%) ^b
	333		1.4(±32%)	3.06(±4%)
	343			2.49(±4%)
	353			1.99(±4%)
	364			1.89(±4%)
	374			1.65(±4%)
	323			3.19(±8%)
Q	328			3.67(±4%)
	333			2.96(±4%)
	343			2.21(±4%)
	358			1.99(±4%)
SC-2	323			2.45(±4%) ^c
	327			3.14(±4%)
	338			2.71(±4%)
	356			2.00(±4%)

$k^*=k_D+C'_D b$
 α_k^* , after extended annealing in vacuum at 323 K.
 $\alpha_{k^*}^*$, initial sorption isotherm.
 α_k^* , after annealing.

Auxiliary Information	
Method/Apparatus/Procedure A dual volume–single transducer manometric system similar to that previously described ¹ was used.	
Source and Purity of Materials: PS and PVME (Poly Sciences, Inc.) had M_n 190 000 and 34 000, respectively. Two 75/25% PS/PVME blends were prepared and three thermal histories developed. Sample SC-1 was cooled slowly, a rate of 0.75 K/min, from 358 K to room temperature. Q was rapidly quenched from 358 K to room temperature. After investigating sample Q up to 358 K, it was very slowly cooled, a rate of 0.05 K/min, to 333 K. This sample is designated SC-2. Propane (Matheson Co) 99.98% purity.	
References: ¹ H. J. Spencer and J. A. Yavorsky, J. Appl. Polym. Sci. 28 , 2937 (1983).	

Components:	Original Measurements:
(1) Carbon dioxide; CO ₂ ; [124-38-9] Methane; CH ₄ ; [74-82-8]	N. Mungamandam and D. R. Paul, J. Polym. Sci., Part B: Polym. Phys. 25 , 2315 (1987).
(2) Polystyrene (PS); [9003-53-6] (IX)	
(3) Tetramethyl bisphenol A Polycarbonate (TMPC)	
Variables:	Prepared By:
T/K=308	Yu. P. Yampol'skii
p/MPa=0-2.0	

Experimental Data				
TABLE 1. Dual mode sorption parameters for carbon dioxide in TMPC/PS blends at 308 K				
TMPC mass %	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	$C_H''/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
0	0.550	9.44		0.177
20	0.604	11.53		0.198
40	0.579	15.37		0.186
60	0.667	19.05		0.207
81	0.879	20.49		0.275
100	1.011	27.66		0.283

TABLE 2. Dual mode sorption parameters for methane in TMPC/PS blends at 308 K				
TMPC mass %	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	$C_H''/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
0	0.109	6.99		0.068
20	0.252	3.85		0.126
40	0.192	6.80		0.094
60	0.230	8.90		0.090
81	0.237	12.72		0.086
100	0.244	15.34		0.100

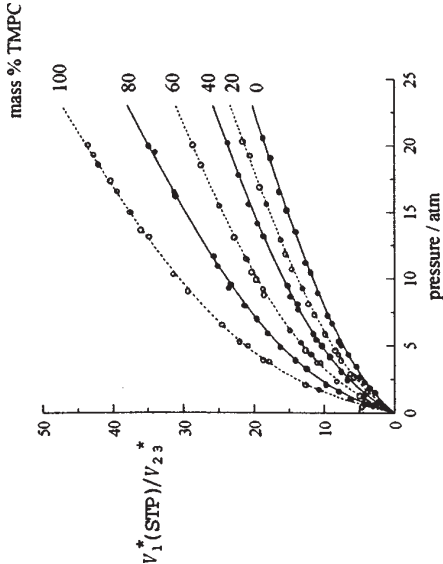


FIG. 99. Sorption isotherms of carbon dioxide in TMPC/PS blends at 308 K.

Components:	Original Measurements:
(1) Carbon dioxide; CO ₂ ; [124-38-9]	G. Morel and D. R. Paul, J. Membr. Sci. 10 , 273 (1982).
(2) Poly(phenylene oxide) (PPO); [25134-01-4] and miscible blends	
(3) Polystyrene (PS); [9003-34-6] (IX)	
Variables:	Prepared By:
T/K: 308	A. K. Bokarev
p/MPa: 0-2.3	

Experimental Data				
Dual mode sorption parameters for CO ₂ in miscible blends PPO and PS*				
% PPO in blends	$k_D/\text{cm}^3(\text{STP})\text{cm}^{-3}\text{atm}^{-1}$	$C_H'/\text{cm}^3(\text{STP})\text{cm}^{-3}$	$C_H''/\text{cm}^3(\text{STP})\text{cm}^{-3}$	b/atm^{-1}
0	0.550	9.28		0.133
10	0.488	12.22		0.126
25	0.482	14.72		0.124
50	0.494	20.56		0.155
75	0.589	22.78		0.165
90	0.683	25.00		0.175
100	0.754	29.00		0.198

*Taken from the plot by compiler.

Auxiliary Information	
Method/Apparatus/Procedure	Source and Purity of Materials:
The experimental equipment and procedures for sorption measurements have been described previously. ¹	The PPO used was supplied by General Electric Co.; $M_n = 22\,600$; $M_w = 34\,000$.
	The PS used was a commercial product Costen Polystyrene 550.
	Films containing different proportions of these polymers were cast from 10% trichloroethylene solutions on mercury surface.
References:	¹ W. J. Koros, A. H. Chan, and D. R. Paul, J. Membr. Sci. 2 , 165 (1977).

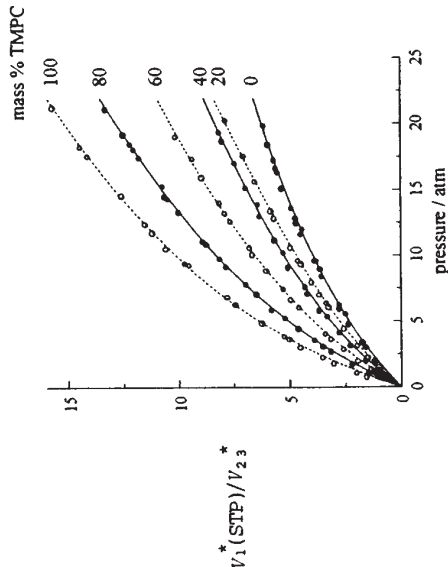


FIG. 100. Sorption isotherms of methane in TMPC/PS blends at 308 K.

Components:		Original Measurements:	
(1) Carbon dioxide; CO ₂ ; [124-38-9]		P. Masi, D. R. Paul, and J. W. Barlow, <i>J. Polym. Sci., Polym. Phys. Ed.</i> 20 , 15 (1982).	
(2) Polycarbonate (PC); [24936-68-3] (XXI)			
(3) Copolyester (Kodar A-150)			
Variables:		Prepared By:	
T/K = 308		A. K. Bokarev	
p/MPa = 0–2.1			

Experimental Data			
TABLE 1. Dual mode sorption parameters for CO ₂ in polycarbonate–copolyester blends at 308 K (taken from the plot by the compiler)			
PC mass %	k_D /cm ³ (STP) cm ^{−3} atm ^{−1}	C_2 /cm ³ (STP) cm ^{−3}	b /atm ^{−1}
0	0.644	9.4	0.29
25	0.613	13.1	0.23
50	0.613	13.8	0.28
75	0.655	18.0	0.23
100	0.686	19.2	0.26

Auxiliary Information		
Method/Apparatus/Procedure	Source and Purity of Materials:	
The apparatus and procedure are described in Ref. 1. The films previously had been exposed to carbon dioxide at 20 atm for 24 h.	PS: Cosden Oil and Chemical Co., $M_w = 100\,000$, $M_v = 350\,000$, glass transition temp. 375 K. TMPC: Bayer AG, glass transition temp. 466 K. Blends: glass transition temperatures varied monotonously in the range of the values characteristic for pure components.	
	Estimated Error:	No information given.
	References:	¹ W. J. Koros, A. H. Chan, and D. R. Paul, <i>J. Membr. Sci.</i> 2 , 165 (1977).

TABLE 2. Sorption isotherms of carbon dioxide in polycarbonate-copolyester blends at 308 K

Pressure/MPa	Sorption ($V_1^g(\text{STP})/V_{23}$)	Pressure/MPa	Sorption ($V_1^g(\text{STP})/V_{23}$)	Pressure/MPa	Sorption ($V_1^g(\text{STP})/V_{23}$)
PC 0 mass %					
0.09	2.57	0.71	10.75	1.47	17.39
0.13	3.34	0.92	12.86	1.67	18.47
0.17	4.05	0.94	12.49	1.74	19.29
0.21	4.88	1.05	13.78	1.75	18.68
0.31	6.18	1.25	15.28	1.86	19.67
0.43	8.01	1.28	15.76	2.08	21.11
0.59	9.71	1.35	16.16	—	—
PC 25 mass %					
0.42	8.50	1.11	16.42	1.58	19.46
0.51	9.73	1.21	17.29	1.66	20.40
0.56	10.99	1.36	17.66	1.79	21.75
0.60	11.03	1.34	18.09	1.90	22.13
0.73	12.68	1.48	19.01	1.96	22.35
1.01	15.61	1.51	19.73	—	—
PC 50 mass %					
0.32	8.53	1.07	16.97	1.58	20.97
0.42	10.06	1.17	17.79	1.72	22.01
0.49	11.13	1.26	18.66	1.79	22.29
0.73	13.94	1.43	19.93	1.91	23.10
0.84	14.94	1.46	19.99	2.02	24.15
PC 75 mass %					
0.29	9.26	1.23	20.97	1.76	25.68
0.40	11.22	1.24	21.45	1.80	26.09
0.53	13.23	1.29	21.73	1.83	26.14
0.72	15.52	1.31	21.96	1.90	26.72
0.84	16.99	1.41	22.60	2.03	27.28
1.02	19.10	1.47	23.54	2.06	28.36
1.08	19.87	1.57	24.36	2.12	28.76
PC 100 mass %					
0.11	5.22	0.97	20.33	1.71	27.21
0.18	7.49	1.12	21.61	1.84	28.19
0.44	12.89	1.21	22.66	1.93	29.61
0.54	14.97	1.29	23.42	2.00	29.10
0.74	17.38	1.49	24.68	2.09	30.16
0.80	18.69	1.52	25.40	—	—

Auxiliary Information

Method/Apparatus/Procedure

Sorption was measured using a pressure decay method described in Ref. 1. The specimens were exposed to CO₂ at 20 atm for 1 day.

Source and Purity of Materials:

Copolyester (Kodak A-150): Products, Inc. contained the units of isophthalic and terephthalic acid in a ratio 20/80; $M_n = 22\,000$, glass transition temperature 360 K.
PC (Bisphenol A Polycarbonate): Lexan 131-111 General Electric Co., $M_n = 13\,300$, $M_w = 34\,200$, glass transition temperature 421 K. The blends were produced by extrusion at 293 K (above T_m of the copolyester).

Estimated Error:


No information given.

References:


¹W. J. Koros, D. R. Paul, and A. A. Rocha, J. Polym. Sci., Polym. Phys. Ed. **14**, 687 (1976).

4. Structure Formulas of Polymers


I Poly(4-methylpentene-1)




II Poly(vinyl chloride) (PVC)




III Poly(vinyl acetate) (PVA)




IV Polyacrylonitrile




V Poly(methyl acrylate) (PMA)




VI Poly(methyl methacrylate) (PMMA)




VII Poly(ethyl methacrylate) (PEMA)




VIII Poly(butyl methacrylate)




IX Polystyrene (PS)




X Poly(p-methoxystyrene)




XI Poly(p-acetoxystyrene)




XII Poly(vinyl cyclohexanecarboxylate)




XIII Poly(vinyl benzoate) (PVB)




XIV Poly(vinyl butyral) (PVBu)

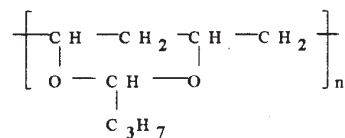


XV Poly(vinyltrimethyl silane) (PVTMS)




XVI Poly(trimethylsilyl propyne) (OTMSP)




XVII Poly(phenyl propyne)




XVIII Poly(2,6-dimethylphenylene oxide)




XIX Poly(ethylene terephthalate) (PETP)




XX Poly(butylene terephthalate) (PBTP)




XXI Polycarbonate (PC)




XXII Tetramethylpolycarbonate (TMPC)

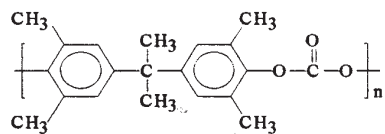

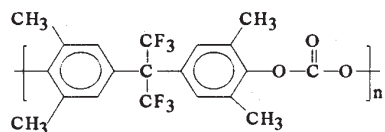
XXIII Tetramethylhexafluoropolycarbonate




XXIV Tetrachloropolycarbonate (TCPC)

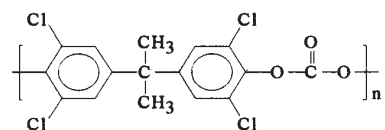


XXV Tetrabromopolycarbonate (TBPC)

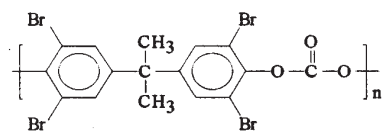


XXVI Hexafluoropolycarbonate




XXVII Tetrabromohexafluoropolycarbonate

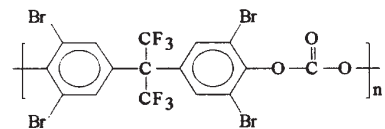


XXVIII Bisphenol norbornene polycarbonate




XXIX Bisphenol Z polycarbonate




XXX Bisphenol chloral polycarbonate




XXXI Poly(aryl-bis-isopropylidene etherketone)




XXXII Poly(aryl-isopropylidene-hexafluoroisopropylidene etherketone) (PAEK-6H6F)




XXXIII Poly(aryl-hexafluoroisopropylidene-isopropylidene etherketone) (PAEK-6F6H)




XXXIV Poly(aryl-bis hexafluoroisopropylidene etherketone)




XXXV Polyarylate




XXXVI Poly(phenolphthaleine phthalate)

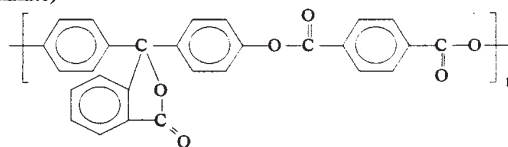

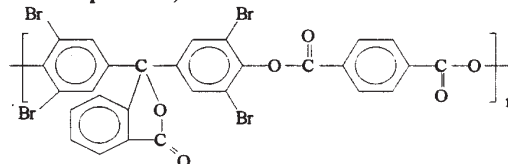
XXXVII Tetrabromo poly(phenol phthaleine phthalate)




XXXVIII Polysulfone (PSF)




XXXIX Dimethyl polysulfone




XL Tetramethyl polysulfone

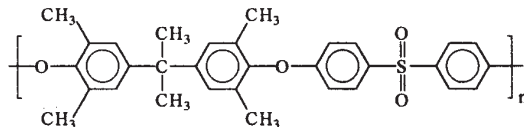


XLI Hexafluoro polysulfone




XLII Polysulfone-F




XLIII Dimethyl bisphenol Z polysulfone




XLIV Polyethersulfone




XLV Cellulose

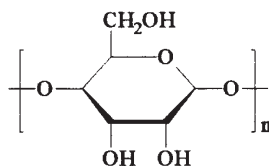


XLVI Nitrocellulose






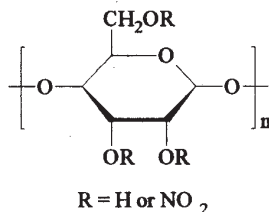


XLVII Ethyl Cellulose (EC)

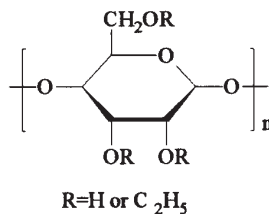


XLVIII Cellulose Acetate (CA)

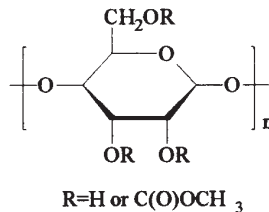


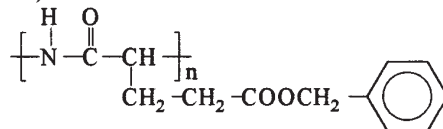XLIX Poly(γ -methyl glutamate) (PMG)L Poly(γ -ethyl glutamate)LI Poly(γ -alkyl-*L*-glutamates)LII Poly(γ -benzyl-*L*-glutamate) (PBLG)LIII Poly(β -benzyl-*L*-aspartate) (PBLA)


LIV Poly(hexamethylene adipinamide) (Nylon 6.6)




LV Nylon 11




LVI Polyimide Kapton H (PMDA-ODA)

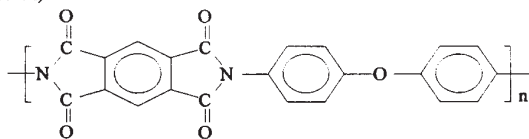


LVII Polyimide Upilex R

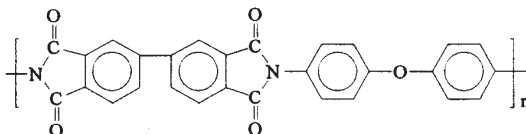

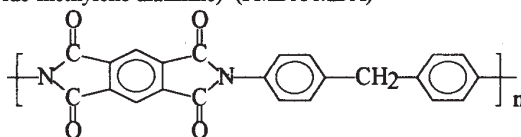
LVIII Copoly(pyromellitic dianhydride-methylene dianiline) (PMDA-MDA)



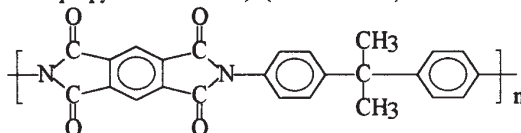
LIX Copoly(pyromellitic dianhydride - isopropylidene diamine) (PMDA-IPDA)




LX 6FDA-ODA

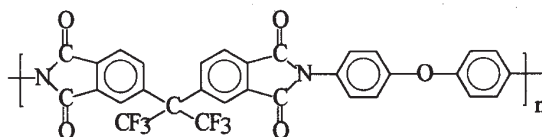


LXI 6FDA-MDA

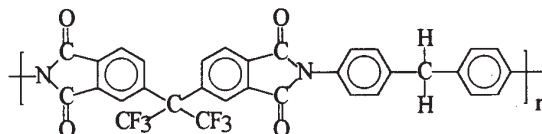


LXII 6FDA-IPDA

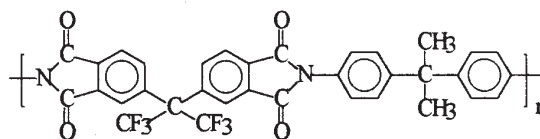


LXIII 6FDA-6FpDA

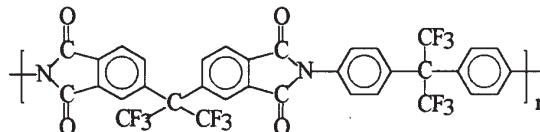


LXIV 6FDA-6FmDA

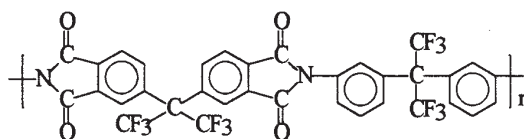


LXV Polyimide BS-1

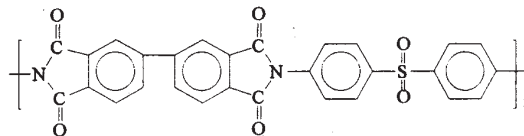


LXVI Polypyrrolone

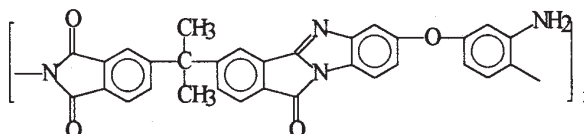


LXVII 6FDA-TADPO Poly(amide amino acid)

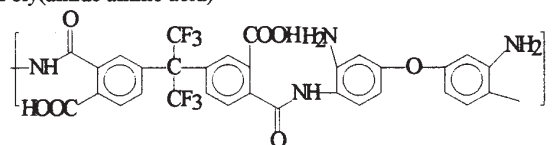


LXVIII Ultem 1000

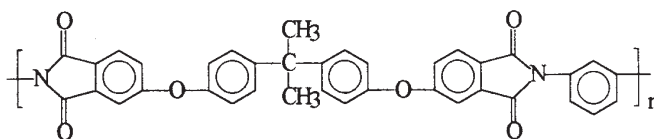


LXIX Polyhydroxyether



LXX Polyarylate (Ardel)



LXXI Polyetherimide (Ultem)

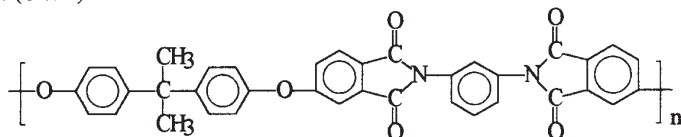

5. Polymer Index

Page numbers preceded by E refer to evaluation texts whereas those not preceded by E refer to compiled tables.

Bisphenol F polysulfone	1382
Bisphenol chloral polycarbonate	1362, 1423–1424
Bisphenol norbornene polycarbonate	1361, 1362
Bisphenol Z polycarbonate	1362
Cellulose	1384
Cellulose acetate	E1389–E1390, 1390–1392, 1393
Copoly(dimethylphenylene oxide-diphenylphenylene oxide)	1416, 1417
Copolyester Kodar	1371, 1429–1430
Copoly(ethylene vinylacetate)	1419
Copolyimide	1417
Copoly(styrene-acrylonitrile)	1420
Copoly(styrene-methyl methacrylate)	1415
Copoly(trimethylsilyl propyne-phenylpropyne)	1416
Copoly(vinylidene cyanide-vinyl acetate)	1414, 1415
Copoly(vinyltrimethylsilane-dimethylsiloxane)	1418
Copoly(4-vinylpyridine acrylonitrile)	1413–1414
Dimethyl bisphenol A polysulfone	1381
Dimethyl bisphenol Z polysulfone	1383
Ethyl Cellulose	1385–1389
6FDA polyimides	1410, 1412
Hexafluoropolycarbonate	1359–1360
Hexafluoropolysulfone	1382
Nitrocellulose	1385
Poly(<i>p</i> -acetoxystyrene)	1307
Polyacrylonitrile	1273
Polyamide Nylon 11	1399
Polyamide Nylon 66	1398
Poly(alkyl glutamate)s	1395
Polyarylate Ardel	1364–1366

Poly(aryl- <i>bis</i> -hexafluoroisopropylidene etherketone)	1364
Poly(aryl- <i>bis</i> -isopropylidene etherketone)	1363
Poly(aryl-isopropylidenehexafluoro etherketone)	1363
Poly(benzyl aspartate)	1397
Poly(benzyl glutamate)	1396, 1397
Poly(butylene terephthalate)	1339
Poly(<i>n</i> -butyl methacrylate)	1289
Polycarbonate	E1340, 1340–1348, E1348, 1349–1350, E1351, 1351–1352, 1353–1357, 1429–1430
Polyepichlorhydrine	1419
Polyetherimide	1412
Polyethersulfone	1383–1384
Polyethylene, sulfochlorinated	1419
Polyethylene terephthalate	E1330, 1331–1339
Poly(dimethylsiloxane)	1418
Poly(ethyl glutamate)	1395
Poly(ethyl methacrylate)	E1283–E1284, 1284–1289
Polyhydroxyether	1367–1368
Polyimide aminoacid 6FDA-TADPO	1412
Polyimide BPDA-SDA	1411
Polyimide PMDA-IPDA	1409–1410
Polyimide PMDA-MDA	1409
Polyimide Kapton (PMDA-ODA)	E1400, 1400–1405
Polyimide Upilex	E1406, 1407–1408
Polyimide Ultem	1411
Poly(<i>p</i> -methoxystyrene)	1306
Poly(methyl acrylate)	1419
Poly(γ -methyl- <i>L</i> -glutamate)	1393–1394
Poly(methyl methacrylate)	E1274, 1274–1283, 1421–1424
Poly(4-methylpentene-1)	E1265, 1265–1267
Poly(octyl glutamate)	1396
Poly(phenolphthaleine phthalate)	1368–1370
Poly(phenylene oxide)	E1323, 1323–1329, 1428
Poly(phenylene oxide) brominated	1326, 1327
Poly(phenylene oxide) carboxylated	1328–1329
Poly(phenyl propyne)	1416
Polypyrrolone	1413
Polystyrene	E1290, E1291, E1292, E1293, E1294, 1294–1306, 1423–1430
Poly(tetrabromophenolphthalein terephthalate)	1370
Polysulfone	E1371–E1372, E1373, 1373–1381
Poly(trimethylsilyl propyne)	E1318, 1318–1322, 1416
Poly(trimethylsilyl propyne) brominated	1322
Poly(vinyl acetate)	1271–1273
Poly(vinyl benzoate)	1309–1311
Poly(vinyl butyral)	1312
Poly(vinyl chloride)	E1267, 1268–1271
Poly(vinyl cyclohexanecarboxylate)	1307–1308
Poly(vinylidene fluoride)	1420–1423
Poly(vinylmethyl ether)	1313, 1424–1427
Poly(vinyltrimethyl silane)	E1313–E1314, 1314–1317, 1418
Tetrabromohexafluoro polycarbonate	1361
Tetrabromo polycarbonate	1355–1357, 1359
Tetrachloro polycarbonate	1355–1357
Tetramethyl bisphenol A polysulfone	1381
Tetramethyl bisphenol A polycarbonate	1428–1429
Tetramethylhexafluoro polycarbonate	1360
Tetramethyl polycarbonate	1355–1358
Plasticizers and additives	
4,4'-Dichlorodiphenyl sulfone	1376–1378
Diocetyl sebacate	1325–1326
Mineral oil	1299
<i>N</i> -phenyl-2-naphthylamine	1376–1378
Tricresyl phosphate	1270, 1299, 1325–1326, 1376–1378

6. Gas Index

Page numbers preceded by E refer to evaluation texts whereas those not preceded by E refer to compilation tables.

Ammonia	1385, 1398
Argon	1269, 1275, 1285–1286, 1288–1289, E1290, 1295–1296, 1309, 1314, 1320–1321, 1323, 1331, 1337–1338, 1354, 1371, 1375, 1383–1384, 1385, 1399, 1419, 1422–1423
<i>n</i> -Butane	1268, 1289, 1304, E1313–E1314, 1315, 1385, 1386–1389
Carbon dioxide	E1265, 1265–1266, 1266, E1267, 1268, 1269, 1270, 1272, 1273, E1274, 1274–1277, 1278–1279, 1280–1282, 1282, 1283, E1283, 1284, 1285–1286, 1286–1287, 1273, E1291, 1294–1296, 1297–1298, 1299, 1300–1301, 1302, 1306–1308, 1309, 1310–1311, 1312, 1314, 1317, E1318, 1318, 1319, 1320, 1320–1321, 1322, E1323, 1323–1324, 1327–1328, E1330, 1331–1334, 1335–1336, 1337–1338, 1338–1339, E1340, 1340, 1341, 1342–1344, 1344–1345, 1346, 1346–1347, 1351, 1355–1357, 1358, 1359, 1359–1360, 1361–1363, 1364–1365, 1366, 1367–1368, 1368–1370, E1371–E1372, 1373–1374, 1375, 1376–1378, 1380–1384, 1385–1386, E1389, 1390–1391, 1391–1392, 1393, 1396–1397, E1400, 1400–1401, 1402–1404, E1406, 1407–1408, 1408–1409, 1410–1412, 1413–1414, 1415, 1417, 1419–1421, 1422–1423, 1423–1424, 1427–1430
Chlorine	1271
Chlorodifluoro methane	1305–1306, E1294, 1304
Chlorofluoromethane	1304
Dichlorodifluoromethane	1304
Chloromethane	1273, 1304
2, 2-Dimethylpropane (Neopentane)	1386–1387
Ethane	1273, 1289, E1313–E1314, 1315–1316, 1320, 1327, 1337–1338, 1370, 1373–1374, 1385, 1388–1389, 1416–1417
Ethene (Ethylene)	1273, 1277–1282, E1313–E1314, 1315–1316, 1327, 1417
Ethyne (Acetylene)	1294, E1313–E1314, 1315, 1316
Helium	1265–1266, 1271, 1275, 1295, 1296, 1314, 1337–1338, 1354, 1359, 1361, 1385, 1412–1413, 1419
Hydrogen	1265–1266, 1270, 1271, 1272, 1294, 1314, 1336, 1339
Hydrogen chloride	1398
Krypton	1275, 1296, 1320–1321
Methane	E1265, 1265–1267, E1267, 1269, 1270, E1292, 1295–1296, 1301–1302, 1305–1306, E1313, 1314, 1318, 1320–1321, E1323, 1323–1324, 1327–1328, 1337–1338, 1338–1339, 1348, E1351, 1351–1352, 1354, 1355–1357, 1359, 1360–1363, 1364–1365, 1366, 1367–1368, 1370, 1371, E1373, 1373–1374, 1375, 1378, 1380, 1381–1382, 1383, 1391–1392, 1400–1401, 1402, 1403, 1409–1410, 1412, 1419, 1422–1423, 1423–1424, 1428
2-Methylpropane (Isobutane)	E1293, 1304, 1319, 1386–1387
Neon	1270, 1271, 1275, 1399
Nitrogen	1265–1266, E1267, 1268, 1269, 1275, 1285–1286, 1290, 1294–1296, 1309, 1314, 1318, 1320, 1323, 1331, 1337–1338, 1338–1339, 1351, 1354–1357, 1359, 1361, 1364–1365, 1367–1368, 1371, 1375, 1378, 1380, 1381, 1382–1384, 1385, 1410, 1412–1414, 1419, 1422–1423
Nitrous oxide	1280–1282, 1317, 1320–1321
Oxygen	1314, 1318, 1319, 1331, 1337–1339, 1359, 1361, 1385, 1410, 1412–1414
Propadiene (Allene)	E1313–E1314, 1315, 1316
Propane	1288, E1293, 1302–1306, 1313, E1313–E1314, 1315–1316, 1317, 1321, 1322, 1327, E1352, 1353, 1385, 1388–1389, 1416–1417, 1424–1427
Propene (Propylene)	E1313–E1314, 1315–1316, 1327, 1416–1417
Propyne (Methylacetylene)	E1313–E1314, 1315, 1316
Sulfur dioxide	1273, 1316–1317, E1348, 1349–1350, 1366, 1384–1385, 1399, 1405
Trichlorofluoromethane	1304
Xenon	1296, 1315, 1317, 1319, 1320–1321, 1324, 1393, 1395

7. Registry Number Index

Page numbers preceded by E refer to evaluation text whereas those not preceded by E refer to compiled tables.

74-82-8	Methane	E1265, 1265–1267, E1267, 1269, 1270, E1292, 1295–1296, 1301–1302, 1305–1306, E1313, 1314, 1318, 1320–1321, E1323, 1323–1324, 1327–1328, 1337–1338, 1338–1339, 1348, E1351, 1351–1352, 1354, 1355–1357, 1359, 1360–1363, 1364–1365, 1366, 1367–1368, 1370, 1371, E1373, 1373–1374, 1375, 1378, 1380, 1381–1382, 1383, 1391–1392, 1400–1401, 1402, 1403, 1409–1410, 1412, 1419, 1422–1423, 1423–1424, 1428
74-84-0	Ethane	1273, 1289, E1313–E1314, 1315–1316, 1320, 1327, 1337–1338, 1370, 1373–1374, 1385, 1388–1389, 1416–1417
74-85-1	Ethene (Ethylene)	1273, 1277–1282, E1313–E1314, 1315–1316, 1327, 1417
74-86-2	Ethyne (Acetylene)	1294, E1313–E1314, 1315, 1316
74-87-3	Chloromethane	1273, 1304
74-98-6	Propane	1288, E1293, 1302–1306, 1313, E1313–E1314, 1315–1316, 1317, 1321, 1322, 1327, E1352, 1353, 1385, 1388–1389, 1416–1417, 1424–1427
74-99-7	Propyne (Methylacetylene)	E1313–E1314, 1315, 1316
75-28-5	2-Methylpropane (Isobutane)	E1293, 1304, 1319, 1386–1387

75-45-6	Chlorodifluoromethane	1305-1306, E1294, 1294, 1304
75-69-4	Trichlorofluoromethane	1304
75-71-8	Dichlorodifluoromethane	1304
106-97-8	<i>n</i> -Butane	1268, 1289, 1304, E1313-E1314, 1315, 1385, 1386-1389
115-07-1	Propene (Propylene)	E1313-E1314, 1315-1316, 1327, 1416-1417
124-38-9	Carbon dioxide	E1265, 1265-1266, E1267, 1268, 1269, 1270, 1272, 1273, E1274, 1274-1277, 1278-1279, 1280-1282, 1283, E1283, 1284, 1285-1286, 1286-1287, 1273, E1291, 1294-1296, 1297-1298, 1299, 1300-1301, 1301, 1302, 1306-1308, 1309, 1310-1311, 1312, 1314, 1317, E1318, 1318, 1319, 1320, 1320-1321, 1322, E1323, 1323-1324, 1327-1328, E1330, 1331-1334, 1335-1336, 1337-1338, 1338-1339, E1340, 1340, 1341, 1342-1344, 1344-1345, 1346-1347, 1351, 1355-1357, 1358, 1359-1360, 1361-1363, 1364-1365, 1366, 1367-1368, 1368-1370, E1371-E1372, 1373-1374, 1375, 1376-1378, 1380-1384, 1385-1386, E1389, 1390-1391, 1391-1392, 1393, 1396-1397, E1400, 1400-1401, 1402-1404, E1406, 1407-1408, 1408-1409, 1410-1412, 1413-1414, 1415, 1417, 1419-1421, 1422-1423, 1423-1424, 1427-1430
135-88-6	<i>N</i> -phenyl-2-naphthylamine	1376-1378
463-49-0	Propadiene (Allene)	E1313-E1314, 1315, 1316
463-82-1	2,2-Dimethylpropane (Neopentane)	1386-1387
593-70-4	Chlorofluoromethane	1304
1330-78-5	Tricresyl phosphate	1270, 1299, 1325-1326, 1376-1378
1333-74-0	Hydrogen	1265-1266, 1270, 1271, 1272, 1294, 1314, 1336, 1399
2432-87-3	Dioctyl sebacate	1325-1326
7439-90-9	Krypton	1275, 1296, 1320-1321
7440-01-9	Neon	1270, 1271, 1274, 1399
7440-37-1	Argon	1269, 1275, 1285-1286, 1288-1289, E1290, 1295-1296, 1309, 1314, 1320-1321, 1323, 1331, 1337-1338, 1354, 1371, 1375, 1383-1384, 1385, 1399, 1419, 1422-1423
7440-59-7	Helium	1265-1266, 1271, 1275, 1295, 1296, 1314, 1337-1338, 1354, 1359, 1361, 1385, 1412-1413, 1419
7440-63-3	Xenon	1296, 1315, 1317, 1319, 1320-1321, 1324, 1393, 1395
7446-09-5	Sulfur dioxide	1273, 1316-1317, E1348, 1349-1350, 1366, 1384-1385, 1399, 1405
7647-01-0	Hydrogen chloride	1398
7664-41-7	Ammonia	1385, 1398
7727-37-9	Nitrogen	1265-1266, E1267, 1268, 1269, 1275, 1285-1286, 1290, 1294-1296, 1309, 1314, 1318, 1320, 1323, 1331, 1337-1338, 1338-1339, 1351, 1354-1357, 1359, 1361, 1364-1365, 1367-1368, 1368-1370, 1371, 1375, 1378, 1380, 1381, 1382-1384, 1385, 1410, 1412-1414, 1419, 1422-1423
7782-44-7	Oxygen	1314, 1318, 1319, 1331, 1337-1339, 1359, 1361, 1385, 1410, 1412-1414
7782-50-5	Chlorine	1271
9002-86-2	Poly(vinyl chloride)	E1267, 1268-1271
9003-09-2	Poly(vinylmethyl ether)	1313, 1424-1427
9003-20-7	Poly(vinyl acetate)	1271-1273
9003-21-8	Poly(methyl acrylate)	1419
9003-24-1	Copoly(vinylidene cyanide-vinyl acetate)	1414, 1415
9003-42-3	Poly(ethyl methacrylate)	E1283-E1284, 1284-1289
9003-53-6	Polystyrene	E1290, E1291, E1292, E1293, E1294, 1294-1306, 1424-1430
9003-63-8	Poly(<i>n</i> -butyl methacrylate)	1289
9004-34-6	Cellulose	1384
9004-35-7	Cellulose acetate	E1389-E1390, 1390-1392, 1393
9004-57-3	Ethyl cellulose	1385-1389
9004-70-0	Nitrocellulose	1385
9011-14-7	Poly(methyl methacrylate)	E1274, 1274-1283, 1421-1424
9016-00-6	Poly(dimethylsiloxane)	1418
10024-97-2	Nitrous oxide	1280-1282, 1317, 1320-1321
12634-94-7	Polypyrrolone	1413
24936-44-5	Poly(<i>p</i> -methoxystyrene)	1306
24936-68-3	Polycarbonate	E1340, 1340-1348, E1348, 1349-1350, E1351, 1351-1352, E1352, 1353-1357, 1429-1430
24937-78-8	Copoly(ethylene vinylacetate)	1419
24937-79-9	Poly(vinylidene fluoride)	1420-1423
24938-86-1	Poly(phenolphthalein phthalate)	1368-1370
24969-06-0	Poly(epichlorohydrin)	1419
24979-78-0	Poly(<i>p</i> -acetoxystyrene)	1307
24991-32-0	Poly(vinyl benzoate)	1309-1311
25014-27-1	Poly(benzyl glutamate)	1396-1397
25014-41-9	Polyacrylonitrile	1273

25036-32-2	Poly(vinyltrimethyl silane)	E1313–E1314, 1314–1317, 1418
25036-53-7	Polyimide Kapton H(PMDA-ODA)	E1400, 1400–1405
25038-59-9	Polyethylene terephthalate	E1330, 1331–1339
25068-26-2	Poly(4-methylpentene-1)	E1265, 1265–1267
25135-51-7	Polysulfone	E1371–E1372, E1373, 1373–1381
25135-52-8	Bisphenol Z polycarbonate	1362
25232-41-1	Copoly(4-vinylpyridine acrylonitrile)	1413–1414
25639-68-3	Polyarylate	1364–1366
25667-42-9	Polyethersulfone	1383–1384
26402-79-9	Polyhydroxyether	1367–1368
26615-45-2	Polyimide Upilex	E1406, 1407–1408
26913-25-7	Tetrachloropolycarbonate	1355–1357
28774-93-8	Tetrabromopolycarbonate	1355–1357, 1359
29316-32-3	Poly(vinyl cyclohexane carboxylate)	1307–1308
31546-39-1	Bisphenol chloral polycarbonate	1362, 1423–1424
31694-05-0	Bisphenol F polysulfone	1382
31694-07-2	Hexafluoropolysulfone	1382
32034-67-7	Tetramethyl bisphenol A polysulfone	1381
32131-17-2	Polyamide Nylon 66	1398
32291-26-2	Hexafluoropolycarbonate	1359–1360
38797-88-5	Tetramethylpolycarbonate	1355–1358
38980-51-7	4,4'-Dichlorodiphenyl sulfone	1376–1378
58978-16-8	Dimethyl bisphenol A polysulfone	1381
61128-24-3	Polyimide Ultem	1411
61128-24-3	Polyetherimide	1412
87842-32-8	Poly(trimethylsilyl propyne)	E1318, 1318–1322, 1416
122165-94-0	Poly(aryl-bis-isopropylidene ether ketone)	1363
122165-95-1	Poly(aryl-isopropylidenehexafluoro ether ketone)	1363
122165-97-3	Poly(aryl-bis-hexafluoroisopropylidene ether ketone)	1364
125431-72-3	Tetramethylhexafluoropolycarbonate	1360
126430-95-3	Tetrabromohexafluoropolycarbonate	1361
132634-94-7	Polyimide aminoacid 6FDA-TADPO	1412
134140-27-5	Dimethyl bisphenol Z polysulfone	1383

The following have no CA Registry number

Bisphenol norborene polycarbonate	1361, 1362
Copoly(dimethyphenylene oxide-diphenylphenylene oxide)	1416, 1417
Copolyester Kodar	1371, 1429–1430
Copolyimide	1417
Copoly(styrene-acrylonitrile)	1420
Copoly(styrene-methyl methacrylate)	1415
Copoly(trimethylsilyl propyne-phenylpropyne)	1416
Copoly(vinyltrimethylsilane-dimethylsiloxane)	1418
6FDA polyimides	1410, 1412
Polyamide Nylon 11	1399
Poly(alkyl glutamate)s	1395
Poly(benzyl aspartate)	1397
Poly(butylene terephthalate)	1339
Polyethylene, sulfochlorinated	1419
Poly(ethyl glutamate)	1395
Polyimide BPDA-SDA	1411
Polyimide PMDA-IPDA	1409–1410
Polyimide PMDA-MDA	1409
Poly(gamma-methyl-L-glutamate)	1393–1394
Poly(octyl glutamate)	1396
Poly(phenylene oxide)	E1323, 1323–1329, 1428
Poly(phenylene oxide) brominated	1326, 1327
Poly(phenylene oxide) carboxylated	1328–1329
Poly(phenyl propyne)	1416
Poly(tetrabromophenolphthalein terephthalate)	1370
Poly(trimethylsilyl propyne) brominated	1322
Poly(vinyl butyral)	1312
Tetramethyl bisphenol A polycarbonate	1428–1429
Mineral oil	1299

8. AUTHOR INDEX

Page numbers preceded by E refer to evaluation texts whereas those not preceded by E refer to compiled tables.

Alcalay H.H.	E1330, 1338–1339
Arai Y.	E1293, 1304
Asakawa S.	1319, 1324, E1323
Ash R.	1399
Bamba Y.	E1291, E1292, 1301, E1340, 1348, E1351
Ballard R.L.	E1267, 1270
Barbari T.A.	E1351, 1351, 1367–1368, 1378, 1412
Barlow J.	1371, 1419, 1429–1430
Barrer R.M.	1270, 1386–1387, 1399
Barrie J.A.	E1292, E1293, E1294, 1305–1306, E1330, 1337–1338, E1352, 1353, 1386–1387, 1419
Berens A.R.	E1267, 1268
Bokarev A.K.	E1313, 1316, E1318, 1320–1321, 1418
Bondar V.I.	E1318, 1320
Bourban D.	1288–1289
Campanile G.	E1291, 1300–1301
Carfagna C.	E1291, 1300–1301
Cassidy P.E.	1363, 1364
Casur E.	1388–1389
Chan A.H.	E1340, 1342–1344, E1351, 1354, 1386
Chan D.D.	E1330, 1333
Chandler R.	1366
Chern R.T.	E1323, 1321, 1326, 1327–1328, 1366, 1368–1370, 1371, E1400, 1400–1401, 1402
Chertova M.V.	E1323, 1327, 1416, 1417
Chiou J.S.	E1283, 1285–1286, E1291, 1299, 1376, 1419–1421
Coleman M.R.	1410
Davies E.G.	E1348, 1349, 1349, 1399
Davydova M.B.	E1313, 1316
De Meringo A.H.	E1389, 1390–1391
Draisbach H.-C.	1336
Durgaryan S.G.	E1313, 1314–1315, 1316, 1317, 1418
Durrill P.L.	E1274, 1274, E1290, E1291, E1294, 1295
Eaton G.M.	1384
Eilenberg J.A.	E1340, 1341
El-Hibri M.J.	E1267, 1269
Erb A.J.	E1371–E1372, E1373, 1375
Ezaki T.	1413–1414
Fechter J.M.H.	E1283, 1275
Felder R.M.	1405
Fincher S.J.	1405
Fleming G.K.	E1340, 1344, 1346–1347, E1351, 1352, 1357, 1358, 1360
Frabetti A.J.	E1330, 1338–1339
Frangoulis C.S.	E1292
Fried J.R.	E1267, 1270
Frimpong S.	E1348, 1350
Fujii M.	E1330, 1332
Gerrens H.	E1290
Gladkova N.K.	E1313, 1316
Goradia U.B.	1288
Grieskey R.G.	E1274, 1274, E1294, 1295
Hachisuka H.	E1300, 1404, 1414, 1418
Hamano H.	1396
Harnish D.F.	E1293, E1259, 1304
Hellums M.W.	1359, 1360
Hidetoshi K.	1411, 1417
Higashimura T.	1319
Higuchi A.	E1318, 1322
Hirose T.	E1283, 1286–1287, 1397–1308, 1309, 1310, 1310–1311, 1312, E1330, 1334, 1335–1336, 1344–1345, 1373–1374
Hopfenberg H.B.	E1274, 1273, 1275, 1277, 1278–1279, E1293, 1303, 1321, E1323, 1326, 1327–1328, E1330, 1332, 1366, E1400, 1400–1401, 1402

Hsieh P.Y.	1385
Huvarad G.S.	1273
Husk G.R.	1359, 1361, E1400, 1402, 1403, 1410
Huyett M.J.	E1292, 1297
Ichiraku Y.	E1318, 1318
Ilinitch O.M.	E1323, 1327, 1416, 1417
Iwai Y.	E1293, 1304
Jeschke D.	1336
Jia L.	E1323, 1326, 1327–1328
Kaliuzhnyi N.E.	E1313, 1315, 1317, E1318, 1320–1321
Kamiya Y.	E1283, 1286–1287, 1288–1289, 1307–1308, 1309, 1310–1311, 1312, E1330, 1334, 1335–1336, 1344–1345, 1373–1374
Khotimskii V.S.	E1318, 1320–1321
Kim T.H.	1410
Kinoshita T.	E1400, 1404, 1414, 1415, 1427
Kita H.	E1400, 1401, 1403, E1406, 1407, 1408, 1414
Kodama H.	1397
Koros W.J.	1273, E1274, 1275–1277, 1278–1279, 1280–1282, E1283, 1284, 1293, 1303, E1323, 1324, 1329, E1330, 1331–1332, E1340, 1341, 1344, 1346–1347, E1351, 1351, 1352, 1354–1357, 1359–1360, 1360–1362, 1364–1365, 1367–1368, E1371–1372, E1373, 1378, 1380–1383, 1386, E1400, 1400–1401, 1402, 1403, 1405, 1409–1410, 1412, 1413
Krukoniis V.J.	1282
Kukharskii Yu.M.	E1318, 1320
Kulkarni S.S.	E1389, 1391–1392
Kumazawa H.	E1291, E1292, 1301, E1340, 1348, E1351, E1371–E1372, E1373, 1379, 1380, E1389, 1393, E1406, 1407–1408
Kurata M.	1296, 1319
Kusuki Y.	E1406, 1408
Laukhauf W.L.S.	E1348, 1350, 1366
Liau I.S.	E1274, 1282
Litvinova E.G.	1317, E1318, 1320–1321
Liu D.D.	1273
Lundberg J.L.	E1292, 1297
Maeda Y.	E1291, 1299, 1325–1326, E1371–E1372, 1375, 1376–1378, 1420, 1421
Mallinder	1270
Masi P.	1371, 1429–1430
Masuda T.	1319
Masuoka H.	1272
Mauze G.R.	1289
McCoy N.R.	E1293, 1303
McHattie J.S.	1361–1362, E1371–E1372, E1373, 1380–1383
McHugh M.A.	E1274, 1282
Meares P.	1271
Michaels A.S.	E1290, E1291, E1292, 1295–1296, E1330, 1337–1338
Mizoguchi K.	E1283, 1286–1287, 1288–1289, 1307–1308, 1309, 1310–1311, 1312, E1330, 1334, 1335–1336, 1373–1374
Mohr J.M.	1363, 1364
Mooney E.J.	E1292
Morel G.	1323, 1428
Morikawa H.	1271
Munday K.	E1292, E1293, E1294, 1305–1306, E1352, 1353
Muruganandham N.	1306, 1307, E1340, 1355–1356, 1429–1430
Nagai K.	E1313, 1322
Naito Y.	E1283, 1286–1287, 1288–1289, 1309, 1310–1311, 1330, 1334
Nakagawa T.	E1318, 1318, 1319, 1322, E1323, 1324, 1416
Nakamura A.	1272, 1408, 1411, 1417
Nakamura K.	1272, E1406
Nakanishi K.	1319
Nametkin N.S.	E1313, 1314–1315, 1317
Nemoto N.	1296
Newitt D.M.	E1290, E1291, 1294
Nicodemo L.	E1291, 1300–1301
Nicolais L.	E1291, 1300–1301
Nishigaki M.	E1371–E1372, E1373, 1379
Norton F.J.	1340

Novitskii E.G.	E1313, 1314, 1315
O'Brien K.C.	E1400, 1402–1403, 1409–1410
Odani H.	1296, 1319
Ogata N.	1413–1414
Ohzono M.	E1293, 1304
Okamoto K.	E1400, 1401, 1403, E1406, 1407, 1408, 1411, 1417
Okonishnikov G.B.	E1274, 1275
Oohachi Y.	1396
Parker B.E.	E1267, 1270
Patton C.J.	1405
Paul D.R.	E1265, 1266, E1267, 1269, E1279, E1283, 1285–1286, E1291, E1202, 1297–1298, 1299, 1302, 1306, 1307, E1323, 1323, 1325–1326, E1330, 1331–1332, E1340, 1341, 1342, E1351, 1351, 1354–1357, 1359, 1361–1363, 1364–1365, 1367–1368, 1371, E1371–E1372, E1373, 1375, 1376–1378, 1380–1383, 1386, 1412, 1415, 1419–1421, 1422, 1423–1424, 1427–1430
Paulaitis M.E.	E1274, 1283, E1291, 1299, E1340, 1346
Peterson L.E.	1398
Plank C.A.	E1348, 1350, 1366
Plate N.A.	E1313, 1317, E1317
Pope D.S.	E1351, 1352, 1358, 1360
Prausnitz J.M.	1273
Provan C.N.	1370
Puleo A.C.	E1265, 1266, 1306, 1307
Radosz M.	1282
Ranade G.R.	1366
Raymond P.C.	E1283, E1291, E1292, 1302, 1415, 1423–1424
Reyerson L.H.	1398
Rionda J.A.	E1292
Rocha A.	1341
Rogers C.E.	E1292
Rooney M.L.	E1348, 1349, 1399
Sada E.	E1291, E1292, 1301, E1340, 1348, E1351, E1371–E1372, E1373, 1379, 1380, E1389, E1406, 1406, 1407–1408
Saitoh Y.	1319, E1323, 1324
Sakata K.	E1291, E1292, E1340, E1348, E1351
Sanders E.S.	E1274, 1277, 1278–1279, 1280–1282, 1383–1384
Sasaki M.	1272
Sato T.	1427
Schulz G.V.	E1290
Sefcik M.D.	E1330, 1333
Sekiguchi M.	E1318, 1322
Semin G.L.	E1323, 1327, 1416, 1417
Sheu F.P.	1326, 1366, 1368–1370
Shimoda S.	E1323, 1327–1328
Shimomura H.	1319
Skripov V.P.	E1274, 1275
Sladek K.J.	1331
Slater J.	1386–1387
Smith G.N.	E1274, 1276, E1283, 1284
Smith T.G.	1388–1389
Spencer H.G.	1288, 1302, 1313, E1352, 1353, 1427
Springer J.	1339
Stannett V.T.	1273, E1274, 1276, 1277, E1283, 1284, 1326, 1332, 1366, E1400, 1400–1401, 1402
Stern S.A.	1272, 1289, E1318, 1318, E1389, 1390–1391, 1391–1392
Stewart M.E.	E1293, 1303
Stiel I.	E1293, E1294, 1304
Story B.J.	E1323, 1324, 1329
Stuart H.A.	1336
Sumimoto T.	1394
Taira K.	1296
Takishima S.	1272, E1400
Takizawa A.	1393, 1394, 1395–1397, 1414, 1415, 1427
Tam P.M.	E1290, E1291, E1292, 1295–1296
Tanaka K.	E1400, 1401, 1403, E1406, 1407, 1408, 1411, 1417
Terada K.	1310, 1312, E1330, E1330, 1335–1336, 1373–1374
Thuy L.	1339

Tigina O.N.	E1265, 1265–1266, E1330, 1333
Toi K.	E1291, 1323, E1330, 1331
Tsujita Y.	1393, 1394, 1395–1397, E1400, 1404, 1414, 1415, 1427
Tullos G.L.	1363, 1364
Uragami T.	E1400, 1402
Vakil U.M.	1289
Vieth W.R.	E1290–E1292, 1295–1296, E1330, 1337–1339, E1340, 1341
Vivatpanachart S.	1397
Volkov V.V.	E1313–E1314, 1314–1315, 1316–1317, E1318, 1320–1321, 1418
Wachi S.	1271
Walker D.R.B.	1412, 1413
Wang S.-T.	E1291, E1292, 1301, 1348, E1351, E1389, 1393
Waragai K.	1319, E1323, 1324
Weale K.E.	E1290, E1291, 1294
Webb W.D.	1419
Wilk B.M.	E1292, 1297
Williams M.J.L.	E1292, E1293, E1294, 1305–1306, E1352, 1353
Wissinger R.G.	E1274, 1283, E1291, 1299, E1340, 1346
Witchey-Lakshmanan L.C.	1321
Wonders A.J.	E1340, 1342
Wong P.K.	1266, E1323
Wong P.S.-L.	1270
Xu P.	E1371–E1372, E1373, 1379, 1380, E1389–E1390, 1393, E1406, 1407–1408
Yakushiji H.	E1291, E1292, 1301, E1340, 1348, E1351
Yampolskii Yu. P.	E1313, 1315, 1316, 1317, E1318, 1320–1321
Yang D.K.	E1400, 1402
Yavorsky J.A.	E1293, 1302, 1303, 1313, E1352, 1353, 1424–1427
Yokoshi O.	E1400, 1403, 1411, 1417
Yoshida T.	1393, 1395, 1395–1396
Yoshikawa M.	1413–1414
Yoshio Y.	E1389, 1393
Yuen H.K.	E1330, 1333
Yui B.	E1400, 1400–1401
Zamaraev K.I.	E1323, 1327, 1416, 1417
Zhou S.	1272

9. Solubility Data Series*

Volume 1	H.L. Clever, <i>Helium and Neon</i> (1979)
Volume 2	H.L. Clever, <i>Krypton, Xenon and Radon</i> (1979)
Volume 3	M. Salomon, <i>Silver Azide, Cyanide, Cyanamides, Cyanate, Selenocyanate and Thiocyanate</i> (1979)
Volume 4	H.L. Clever, <i>Argon</i> (1980)
Volume 5/6	C.L. Young, <i>Hydrogen and Deuterium</i> (1981)
Volume 7	R. Battino, <i>Oxygen and Ozone</i> (1981)
Volume 8	C.L. Young, <i>Oxides of Nitrogen</i> (1981)
Volume 9	W. Hayduk, <i>Ethane</i> (1982)
Volume 10	R. Battino, <i>Nitrogen and Air</i> (1982)
Volume 11	B. Scrosati and C.A. Vincent, <i>Alkali Metal, Alkaline Earth Metal and Ammonium Halides, Amide Solvents</i> (1980)
Volume 12	C.L. Young, <i>Sulfur Dioxide, Chlorine, Fluorine and Chlorine Oxides</i> (1983)
Volume 13	S. Siekierski, T. Mioduski, and M. Salomon, <i>Scandium, Yttrium, Lanthanum and Lanthanide Nitrates</i> (1983)
Volume 14	H. Miyamoto, M. Salomon, and H.L. Clever, <i>Alkaline Earth Metal Halates</i> (1983)
Volume 15	A.F.M. Barton, <i>Alcohols with Water</i> (1984)
Volume 16/17	E. Tomlinson and A. Regosch, <i>Antibiotics: I, β-Lactam Antibiotics</i> (1985)
Volume 18	O. Popovych, <i>Tetraphenylborates</i> (1981)
Volume 19	C.L. Young, <i>Cumulative Index: Volumes 1–18</i> (1985)
Volume 20	A.L. Horvath and F.W. Getzen, <i>Halogenated Benzenes, Toluenes and Phenols with Water</i> (1985)
Volume 21	C.L. Young and P.G.T. Fogg, <i>Ammonia, Amines, Phosphine, Arsine, Stibine, Silane, Germane and Stannane in Organic Solvents</i> (1985)
Volume 22	T. Mioduski and M. Salomon, <i>Scandium, Yttrium, Lanthanum and Lanthanide Halides in Non-aqueous Solvents</i> (1985)
Volume 23	T.P. Dirkse, <i>Copper, Silver, Gold and Zinc, Cadmium, Mercury Oxides and Hydroxides</i> (1986)
Volume 24	W. Hadyuk, <i>Propane, Butane and 2-Methylpropane</i> (1986)
Volume 25	C. Hirayama, Z. Galus, and C. Guminski, <i>Metals in Mercury</i> (1986)
Volume 26	M.R. Masson, H.D. Lutz, and B. Engelen, <i>Sulfites, Selenites and Tellurites</i> (1986)
Volume 27/28	H.L. Clever and C.L. Young, <i>Methane</i> (1987)

- Volume 29 H.L. Clever, *Mercury in Liquids, Compressed Gases, Molten Salts and Other Elements* (1987)
- Volume 30 H. Miyamoto and M. Salomon, *Alkali Metal Halates, Ammonium Iodate and Iodic Acid* (1987)
- Volume 31 J. Eysseltova and T.P. Dirkse, *Alkali Metal Orthophosphates* (1988)
- Volume 32 P.G.T. Fogg and C.L. Young, *Hydrogen Sulfide, Deuterium Sulfide and Hydrogen Selenite* (1988)
- Volume 33 P. Franzosini, *Molten Alkali Metal Alkanoates* (1988)
- Volume 34 A.N. Paruta and R. Piekos, *4-Aminobenzenesulfonamides. Part I: Non-cyclic Substituents* (1988)
- Volume 35 A.N. Paruta and R. Piekos, *4-Aminobenzenesulfonamides. Part II: 5-membered Heterocyclic Substituents* (1988)
- Volume 36 A.N. Paruta and R. Piekos, *4-Aminobenzenesulfonamides. Part III: 6-membered Heterocyclic Substituents and Miscellaneous Systems* (1988)
- Volume 37 D.G. Shaw, *Hydrocarbons with Water and Seawater. Part I: Hydrocarbons C5 to C7* (1989)
- Volume 38 D.G. Shaw, *Hydrocarbons with Water and Seawater. Part II: Hydrocarbons C8 to C36* (1989)
- Volume 39 C.L. Young, *Cumulative Index: Volumes 20–38* (1989)
- Volume 40 J. Hala, *Halides, Oxyhalides and Salts of Halogen Complexes of Titanium, Zirconium, Hafnium, Vanadium, Niobium and Tantalum* (1989)
- Volume 41 C.-Y. Chan, I.N. Lepeshkov, and K.H. Khoo, *Alkaline Earth Metal Perchlorates* (1989)
- Volume 42 P.G.T. Fogg and W. Gerrard, *Hydrogen Halides in Non-aqueous Solvents* (1990)
- Volume 43 R.W. Cargill, *Carbon Monoxide* (1990)
- Volume 44 H. Miyamoto, E.M. Woolley, and M. Salomon, *Copper and Silver Halates* (1990)
- Volume 45/46 R.P.T. Tomkins and N.P. Bansal, *Gases in Molten Salts* (1991)
- Volume 47 R. Cohen-Adad and J.W. Lorimer, *Alkali Metal and Ammonium Halides in Water and Heavy Water (Binary Systems)* (1991)
- Volume 48 F. Getzen, G. Hefter, and A. Maczynski, *Esters with Water. Part I. Esters 2-C to 6-C* (1992)
- Volume 49 F. Getzen, G. Hefter, and A. Maczynski, *Esters with Water: Part II: Esters 7-C to 32-C* (1992)
- Volume 50 P.G.T. Fogg, *Carbon Dioxide in Non-aqueous Solvents at Pressures Less Than 200 kPa* (1992)
- Volume 51 J.G. Osteryoung, M.M. Schneider, C. Guminski, and Z. Galus, *Intermetallic Compounds in Mercury* (1992)
- Volume 52 I. Lambert and H.L. Clever, *Alkaline Earth Hydroxides in Water and Aqueous Solutions* (1992)
- Volume 53 C.L. Young, *Cumulative Index: Volumes 40–52* (1993)
- Volume 54 W.E. Acree, Jr., *Polycyclic Aromatic Hydrocarbons in Pure and Binary Solvents* (1994)
- Volume 55 S. Siekierski and S.L. Phillips, *Actinide Nitrates* (1994)
- Volume 56 D. Shaw, A. Skrzecz, J.W. Lorimer, and A. Maczynski, *Alcohols with Hydrocarbons* (1994)
- Volume 57 W. Hadyuk, *Ethene* (1994)
- Volume 58 W.E. Acree, Jr., *Polycyclic Aromatic Hydrocarbons: Binary Non-aqueous Systems, Part I: Solvents A–E* (1995)
- Volume 59 W.E. Acree, Jr., *Polycyclic Aromatic Hydrocarbons: Binary Non-aqueous Systems, Part II: Solvents F–Z* (1995)
- Volume 60 A.L. Horvath and F.W. Getzen, *Halogenated Methanes with Water* (1995)
- Volume 61 C.-Y. Chan, K.H. Khoo, E.S. Gryzlova, and M.-T. Saugier-Cohen Adad, *Alkali Metal and Ammonium Perchlorates, Part I: Lithium and Sodium Perchlorates* (1996)
- Volume 62 P. Scharlin, *Carbon Dioxide in Water and Aqueous Electrolyte Solutions* (1996)
- Volume 63 H.U. Borgstedt and C. Guminski, *Metals in Liquid Alkali Metals, Part I: Be to Os* (1996)
- Volume 64 H.U. Borgstedt and C. Guminski, *Metals in Liquid Alkali Metals, Part II: Co to Bi* (1996)
- Volume 65 J.J. Fritz and E. Königsberger, *Copper(I) Halides and Psuedohalides* (1996)
- Volume 66 J. Eysseltova and T. P. Dirkse, *Ammonium Phosphates* (1998)
- Volume 67 A. L. Horvath, F. W. Getzen, and Z. Maczynska, *Halogenated Ethanes and Ethenes With Water* (1999)
- Volume 68 A. L. Horvath and F. W. Getzen, *Halogenated Aliphatic Compounds C₃–C₁₄ With Water* (1999)
- Volume 69 A. Skrzecz, D. Shaw, and A. Maczynski, *Ternary Alcohol–Hydrocarbon–Water Systems* (1999)
- Volume 70 R. Paterson, Y. Yampol'skii, P. G. T. Fogg, A. Bokarev, V. Bondar, O. Ilinich, and S. Shishatskii, *Solubility of Gases in Glassy Polymers* (1999)

*Updated information on new volumes and on obtaining reprints of previously published volumes are available at the web site (<http://www.unileoben.ac.at/~eschedor/welcome.html>)